


# Peculiarities of hydrogen interaction with Ni powders and melt spun $\text{Nd}_{90}\text{Fe}_{10}$ alloy

Vladimir Dubinko<sup>1,2</sup>, Oleksii Dmytrenko<sup>1,2</sup>, Valeriy Borysenko<sup>1,2</sup>,  
Klee Irwin<sup>2</sup>, Russ Gries<sup>2</sup>

<sup>1</sup>NSC Kharkov Institute of Physics & Technology, Ukraine

<sup>2</sup>Quantum gravity research, Los Angeles, USA



# Coauthors


**Oleksii Dmytrenko**



**Valeriy Borysenko**



**Klee Irwin**



**Russ Gries**



## MOTIVATION



Hydrogen interaction with Ni powders has provoked a lot of excitement and controversy due to the works of Rossi, Parkhomov and others, who claimed to produce excess heat in their experiments that could not be explained by conventional chemical reactions. Yet, there is no reliable 100% evidence of the effect up to date, and some of subsequent experiments produced less or *zero* effect as their measuring accuracy increased. Unfortunately, the claimed evidence often depends on indirect calorimetry methods and as such it does not produce an ultimate proof. We present an experimental setup that allows accurate measuring of the main parameters controlling the reaction: **hydrogen pressure, temperature inside the fuel and at the heater**, the difference between which can provide direct evidence of the excess heat.

Our program pursues two goals: (i) verify the previous results and (ii) test our facility in a wide range of parameters to be used in experiments with novel types of fuel that we plan to create in future.

# PREHISTORY



# SUCCESSFUL replication of LENR performed by Nick Oseyko (2015)

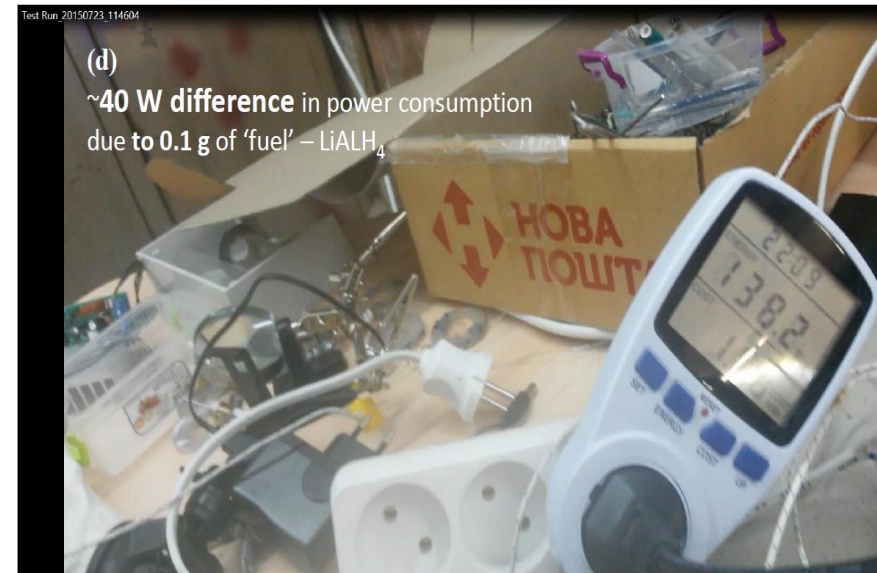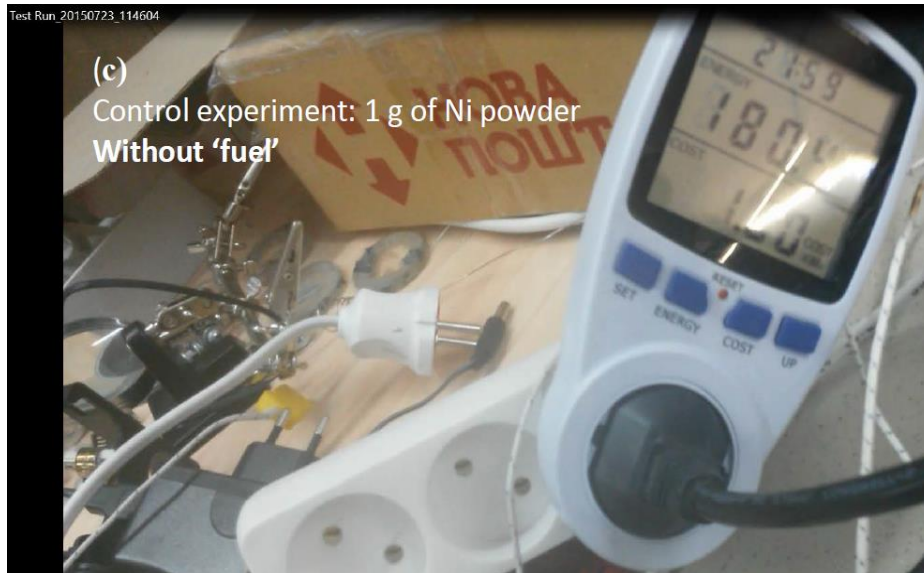


# UNSUCCESSFUL replication of LENR performed by Nick Oseyko (2016)




# Outline of the present experiments

- Interaction of Ni with H and  $\text{LiAlH}_4$  under heating and gamma irradiation
- Interaction of melt spun amorphous alloy  $\text{Nd}_{90}\text{Fe}_{10}$  with H/D under heating and gamma irradiation

## Schematic picture of the reactor system

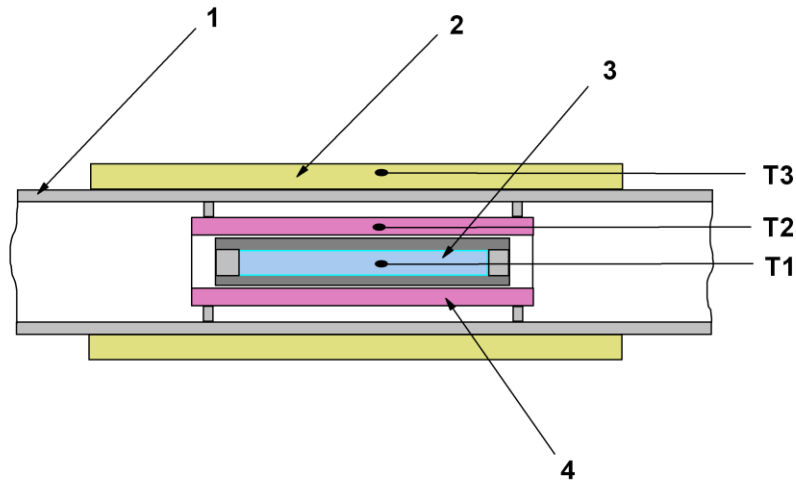

Ceramic tube (1); heat-insulation (2); experimental 'fuel' (3); ceramic tube with a heater (4).

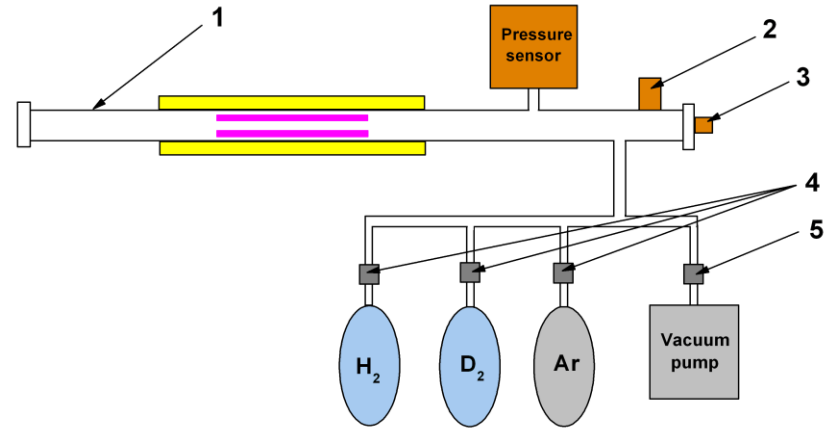

Ceramic tube (1); with electric current inputs for the heater (2); flange for entering the thermocouples T1 and T2 (3) gas valves (4); vacuum valve (5)






**Photo of the reactor system**



# Electron accelerator ELIAS at the NCS KIPT





# $\gamma$ -irradiation of the sample

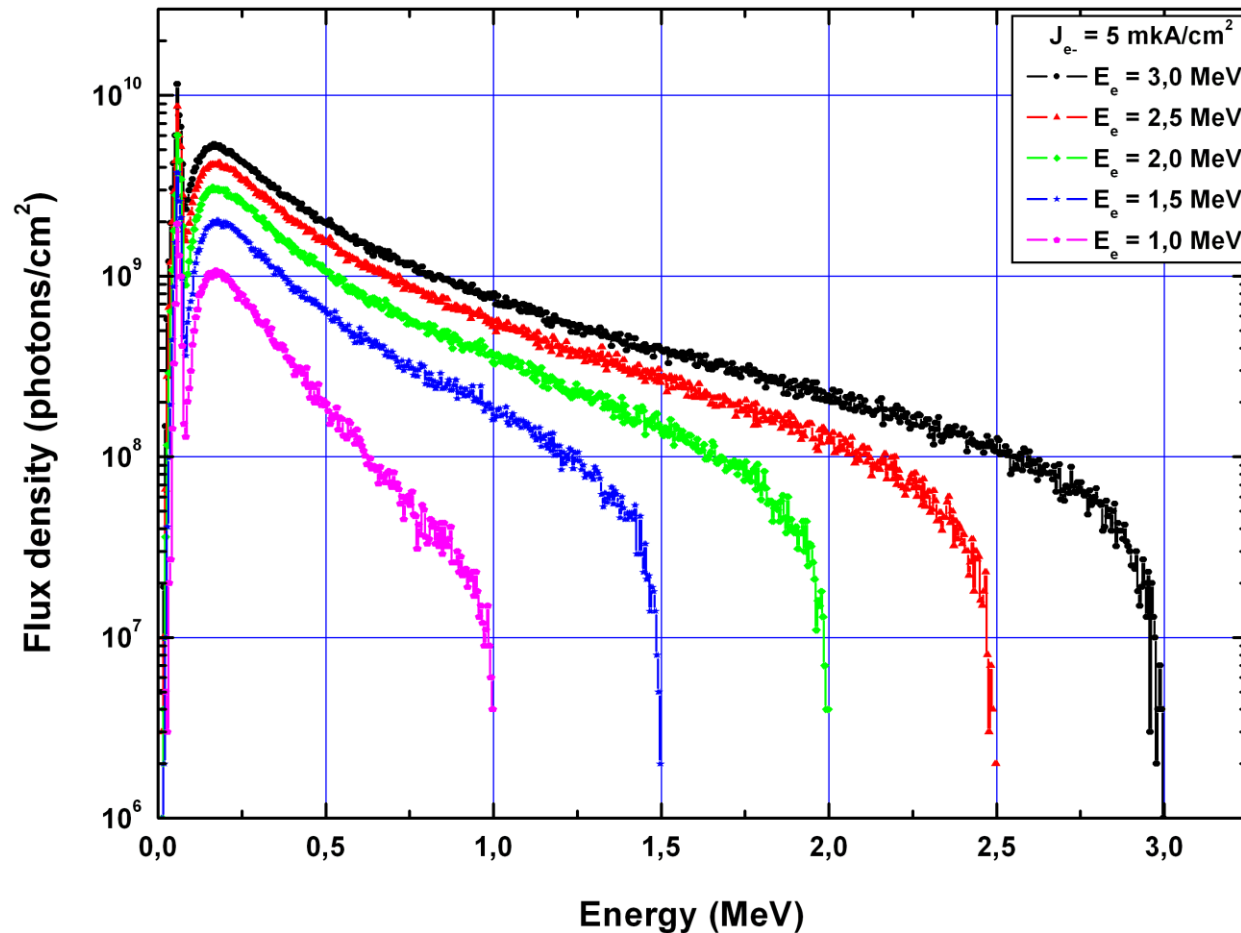



The spectra of bremsstrahlung  $\gamma$ -quanta after the tantalum convertor under its irradiation by electron beams of different energies




## SEM of the Nickel\_Oseyko, Kiev

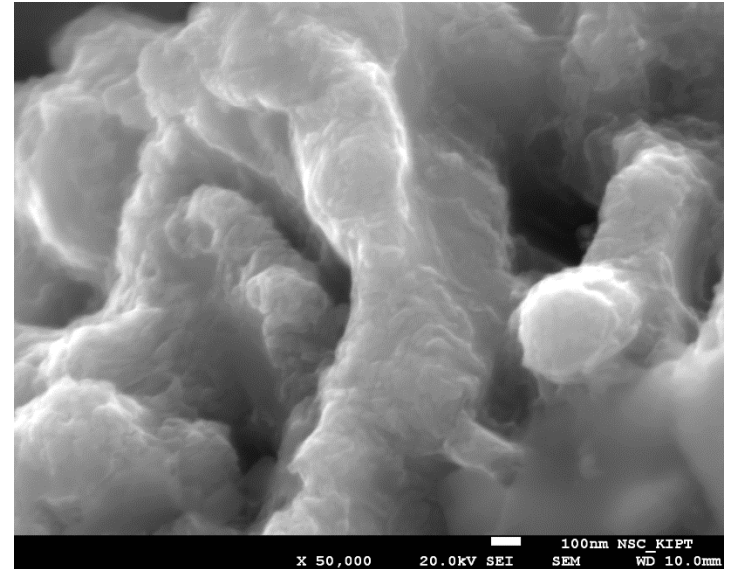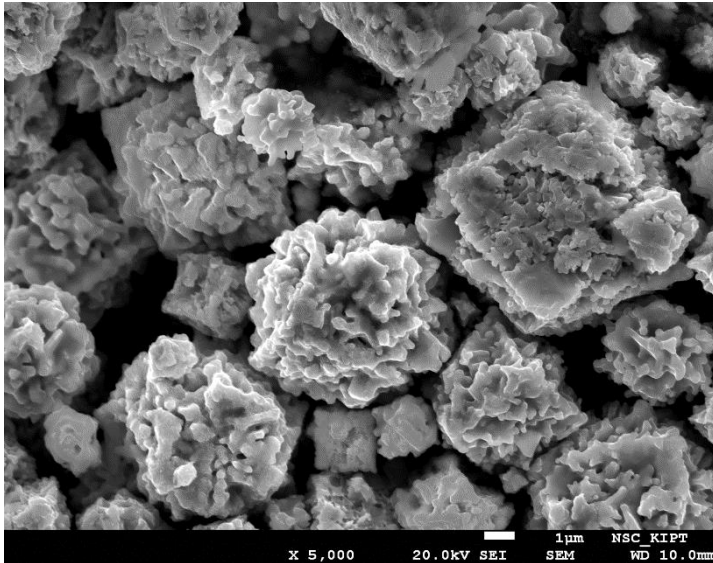

## SEM of the Nickel\_Archer, UK

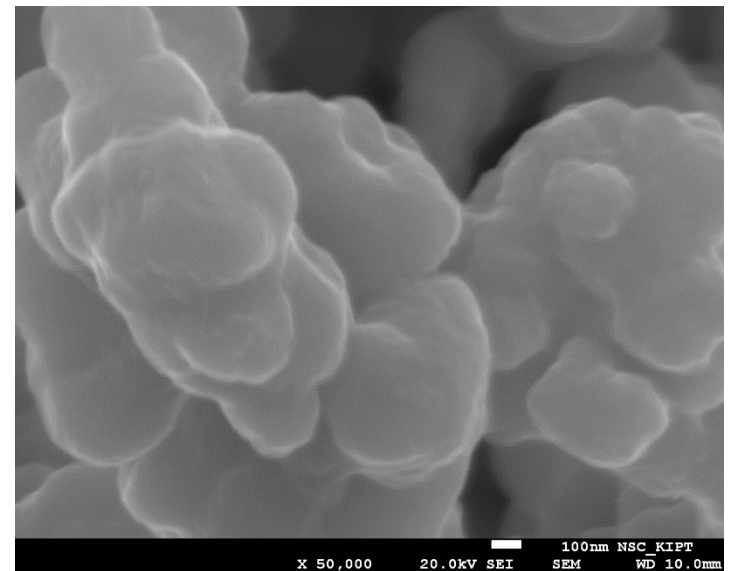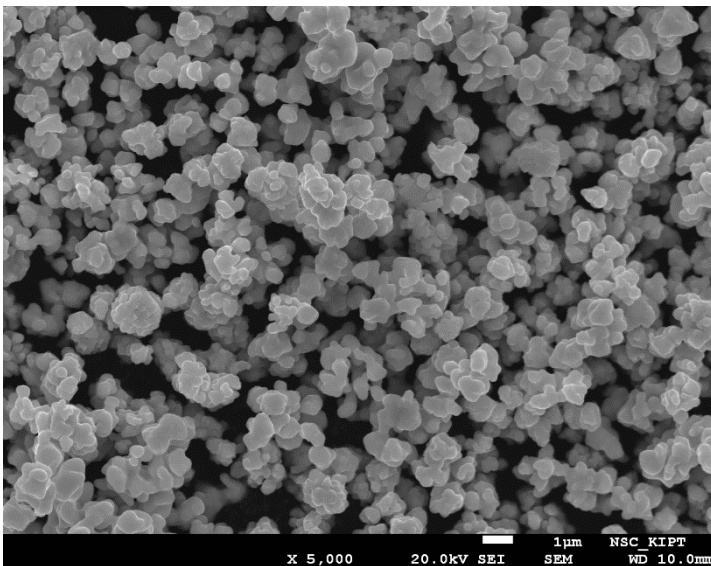


## Interaction of Ni\_Oseyko with H

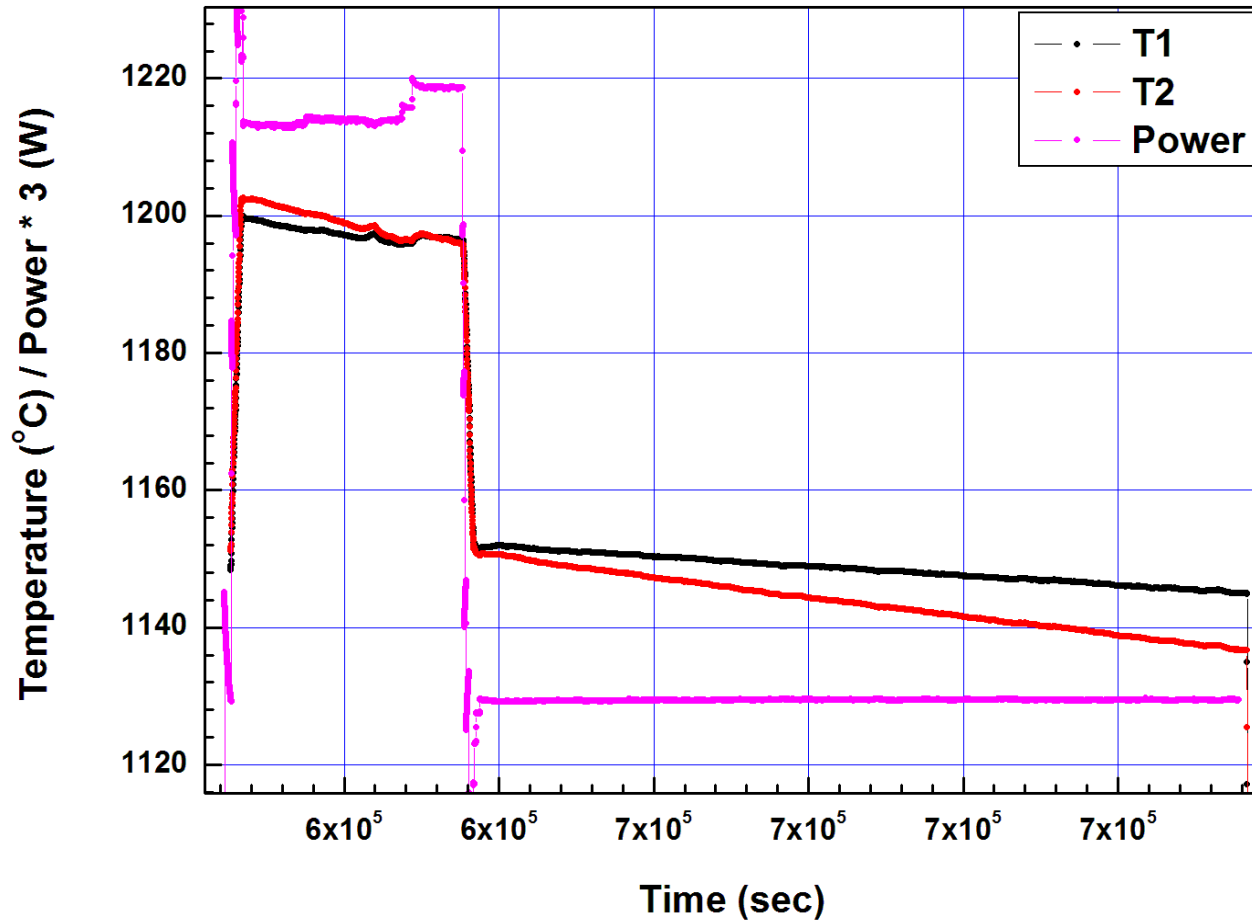

The time dependence of the temperatures of the sample (T1) and the heater (T2) as well as the input power to the heater (the seventh day of the experiment)


Irradiation of the bremsstrahlung  $\gamma$ -quantum flux with a continuous energy spectrum, received on a tantalum convertor using an electron beam with the current of 160  $\mu\text{A}$  and the energy of 2.5 MeV

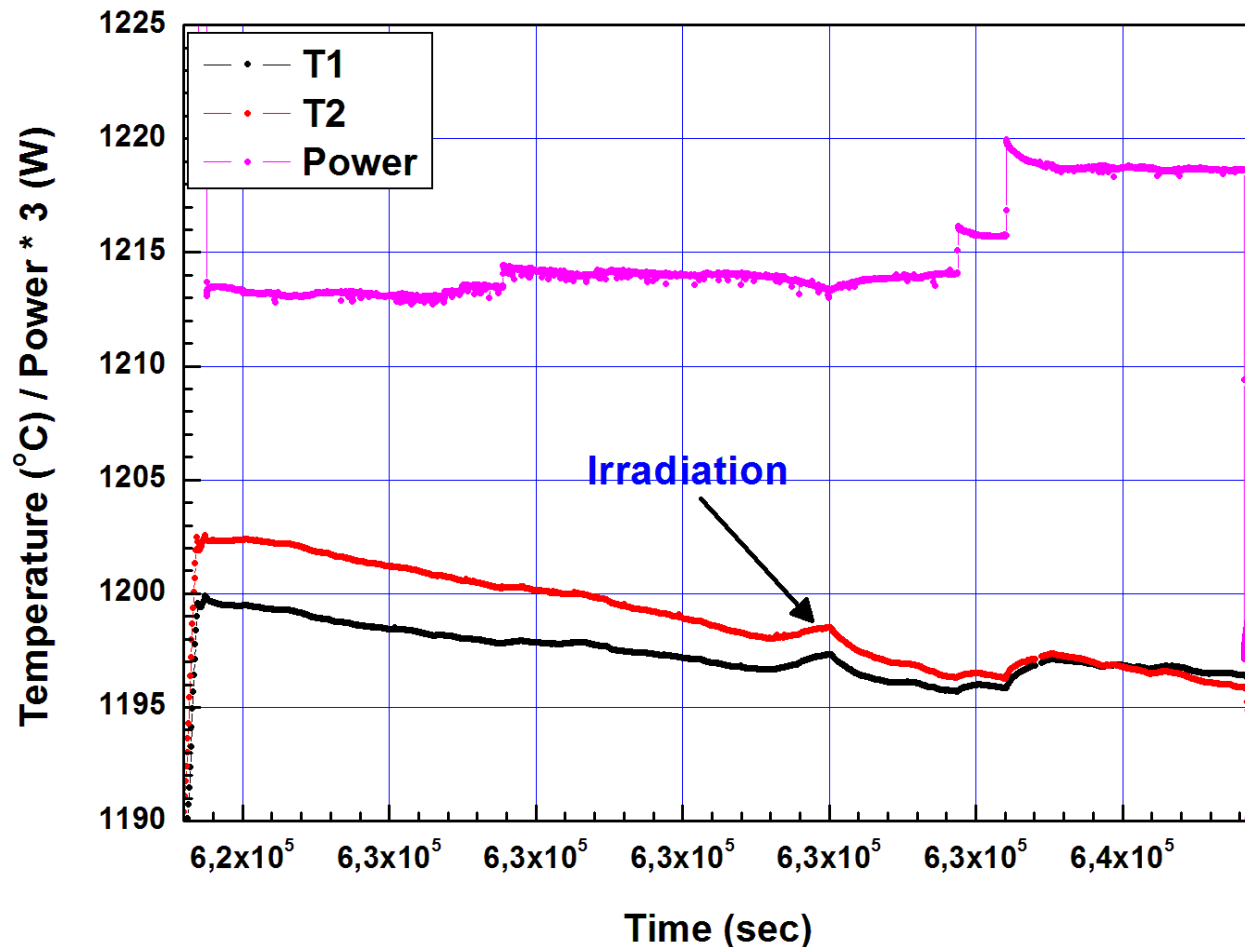




# The first experiment with Nickel\_Oseyko and $\text{LiAlH}_4$ . (02-05-2017)

**Excess heat ~1 MJ ???**

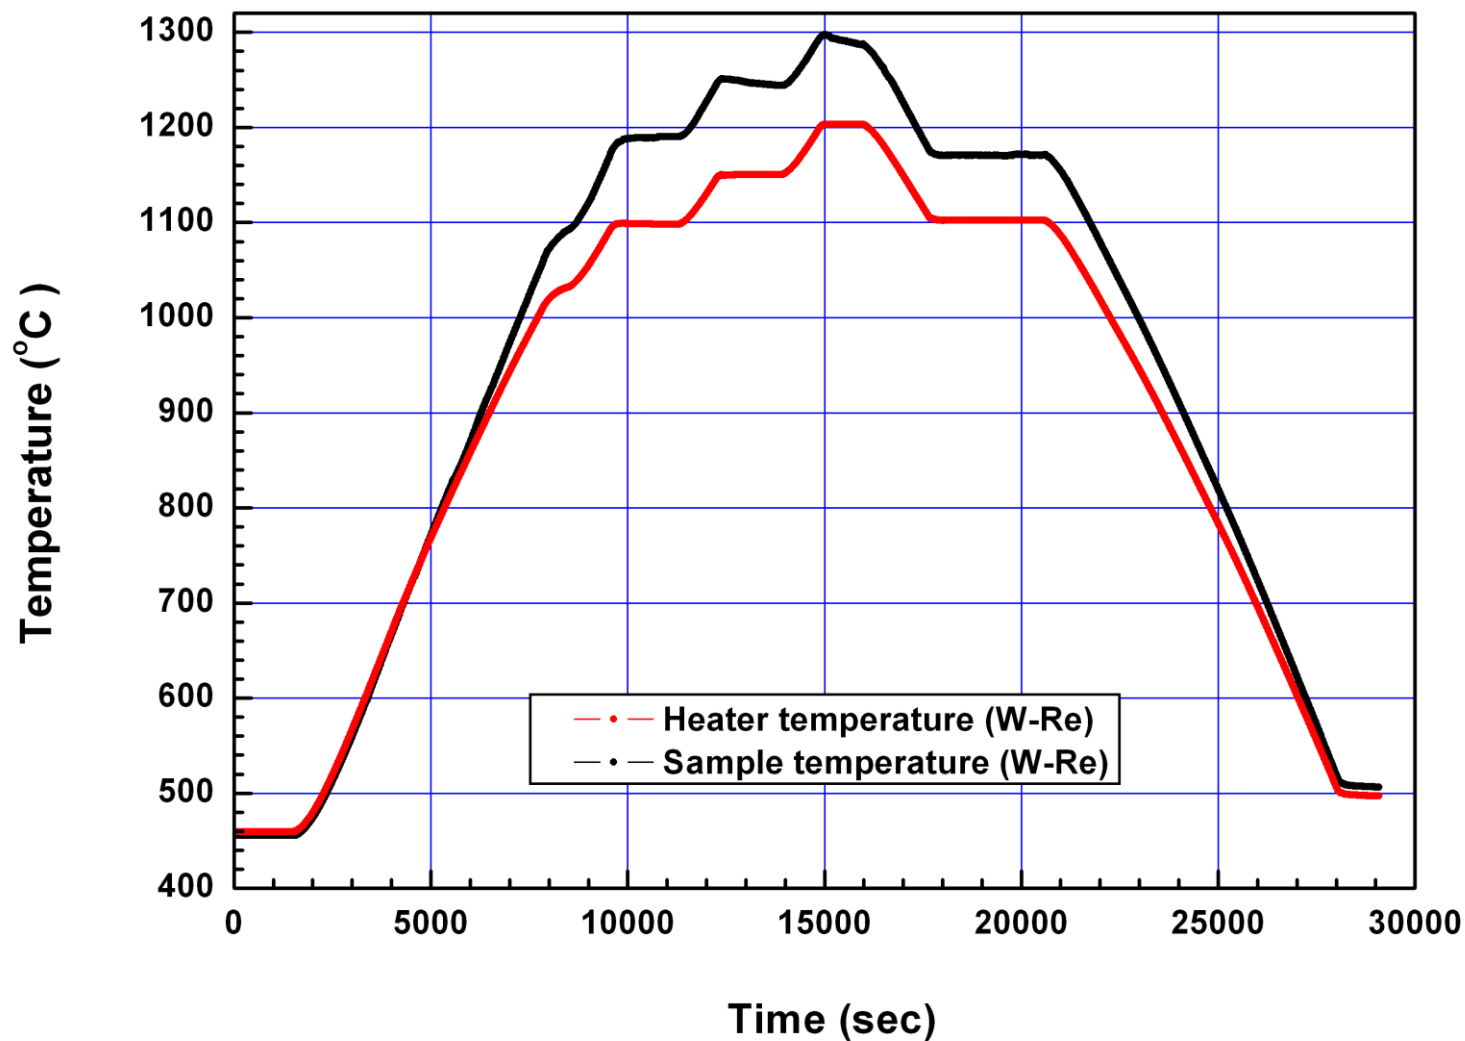

# The second experiment with Nickel\_Oseyko and $\text{LiAlH}_4$ . (19-05-2017)

Artefact due to the W-Re thermocouple degradation ???

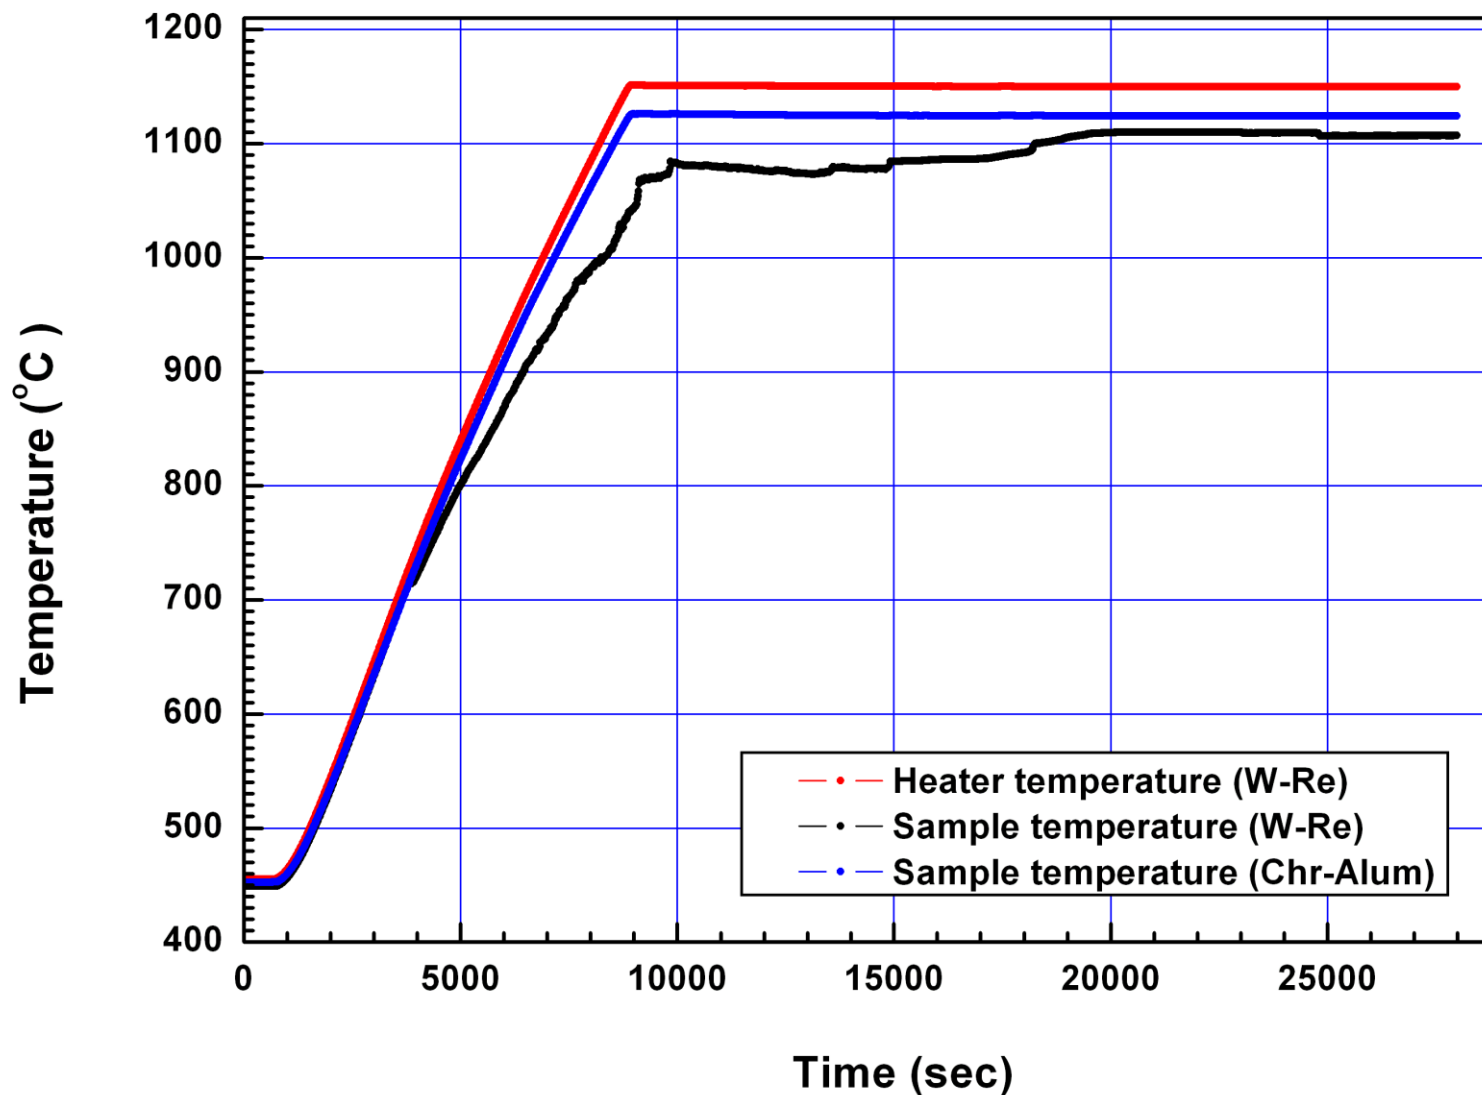

## DISCUSSION

It looks like the interaction of W-Re thermocouple with  $\text{LiAlH}_4$  resulted in a degradation of the thermocouple, which started showing either **higher** or **lower** temperatures than the real T, with unpredictable outcome. Why it responds differently to the same environment, is unclear at the moment.


In his abstract for the conference, Daniel Szumski claims that

“both endo-thermal and exo-thermal nuclear reactions occur, and that it is the predominance of one over the other that produces excess heat or no excess heat. It is only the sign of the heat change that is random.”

**However, in our case the second thermocouple did not show any response to the reaction, indicating an artefact**

# Interaction of melt spun $\text{Nd}_{90}\text{Fe}_{10}$ with $\text{H}_2$ and $\text{D}_2$


Motivation

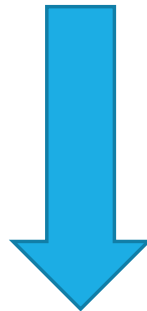



# Chemical and Nuclear catalysis

## the role of disorder in the LAV creation

“Cracks and small particles are the Yin and Yang of the cold fusion environment” E. Storms

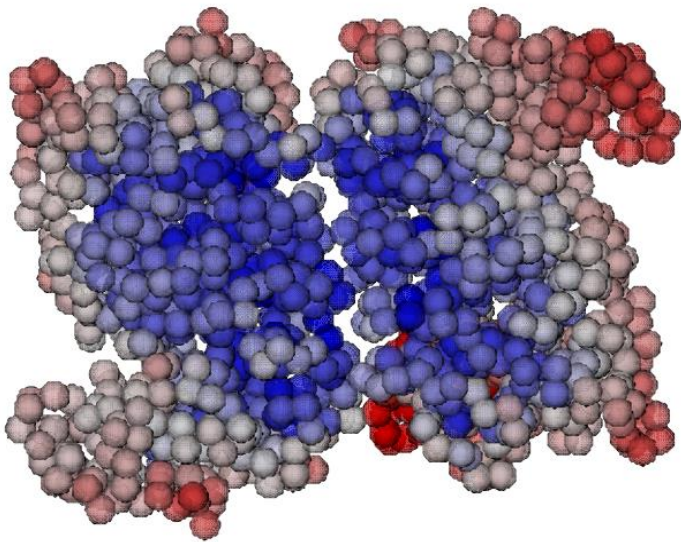

Structure of dimeric citrate synthase (PDB code 1IXE). Only  $\alpha$ -carbons are shown, as spheres in a color scale corresponding to the crystallographic B-factors, from smaller (blue) to larger (red) fluctuations [Dubinko, Piazza, 2014]

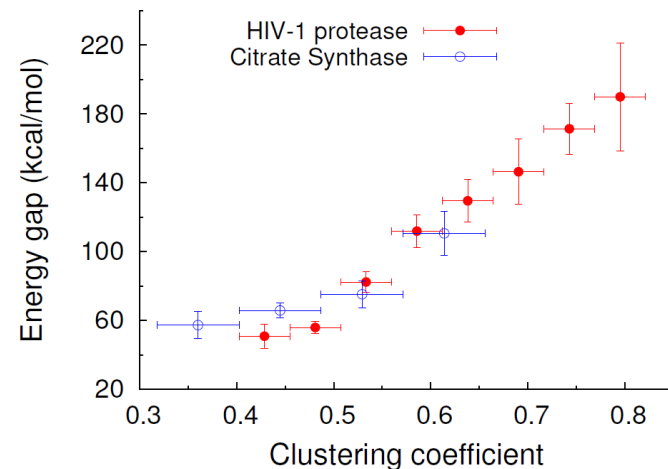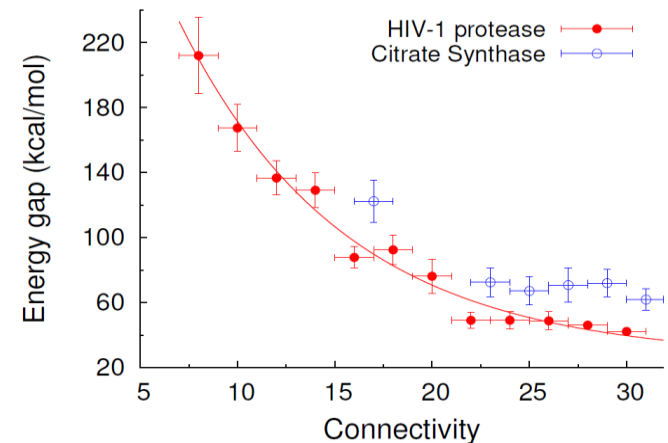


# Creation of nonequilibrium structures


*by fast cooling (up to  $10^6$  K/s)*



**a**

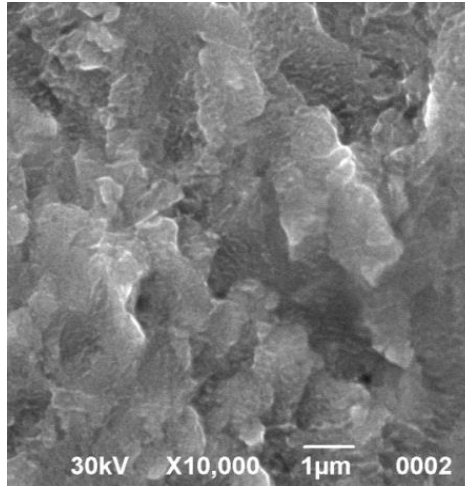

**b**

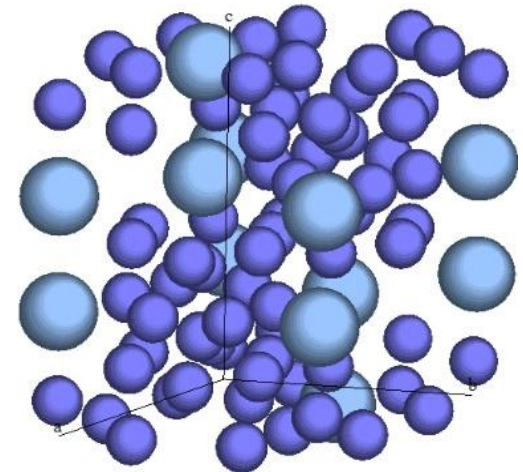


**c**

The appearance (a) and surface morphology (b) of the melt spun Nd<sub>90</sub>Fe<sub>10</sub> films. (c) The unit cell of amorphous phase Nd<sub>2</sub>Fe<sub>17</sub> entering the initial microstructure of Nd<sub>90</sub>Fe<sub>10</sub>.




# X ray diffraction study (Igor Kolodij)

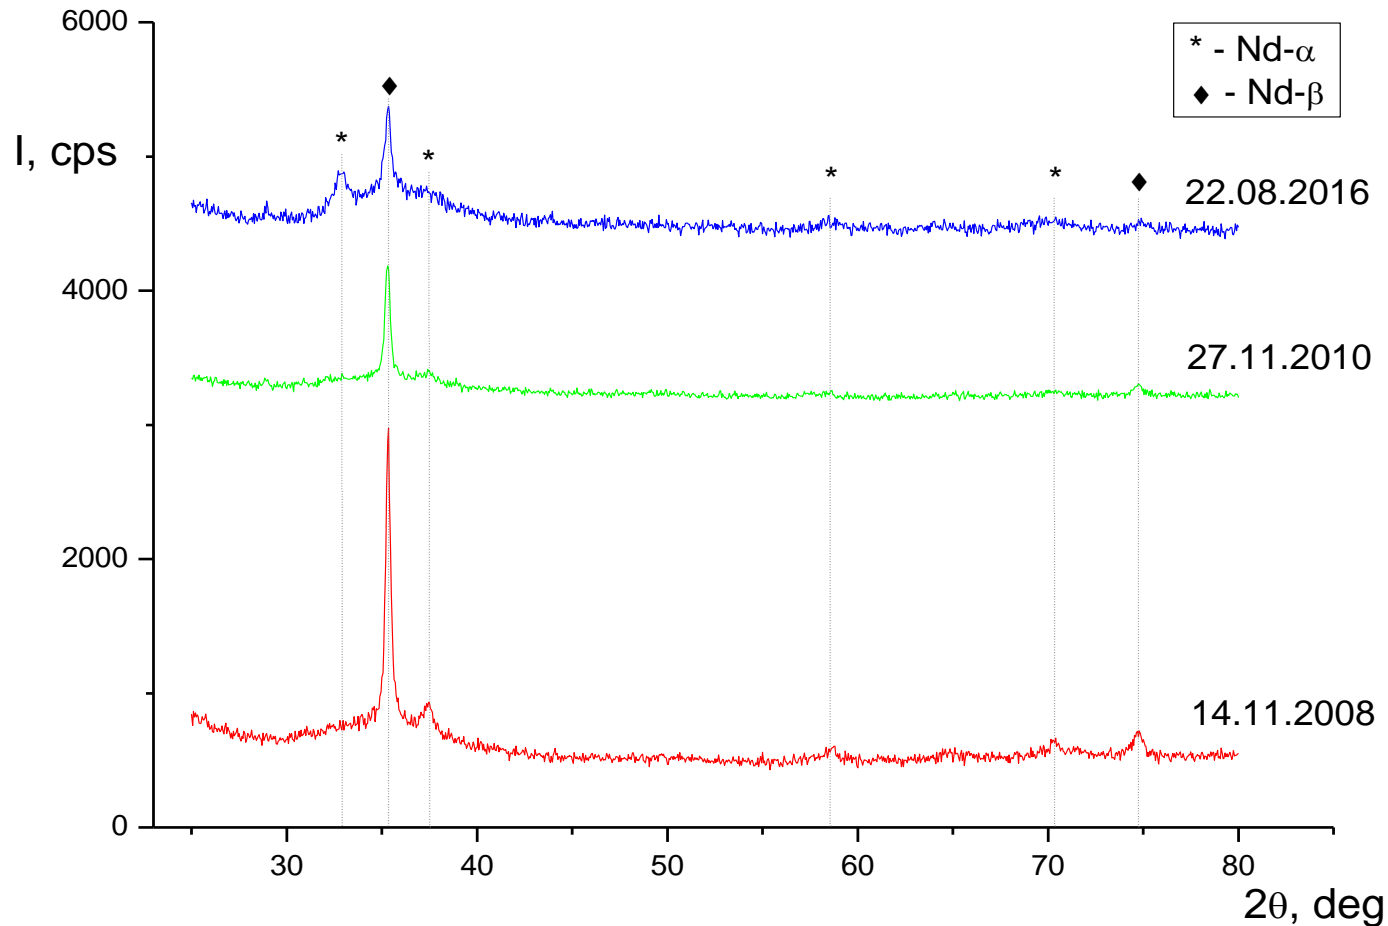

Diffractograms of three different films, where the height of the diffraction peak corresponds to the crystalline fraction in a sample  $X_c = 10\%$  (blue curve);  $20\%$  (green curve) and  $45\%$  (red curve)

# Hydrogenation of $\text{Nd}_{10}\text{Fe}_{10}$ under DC heating

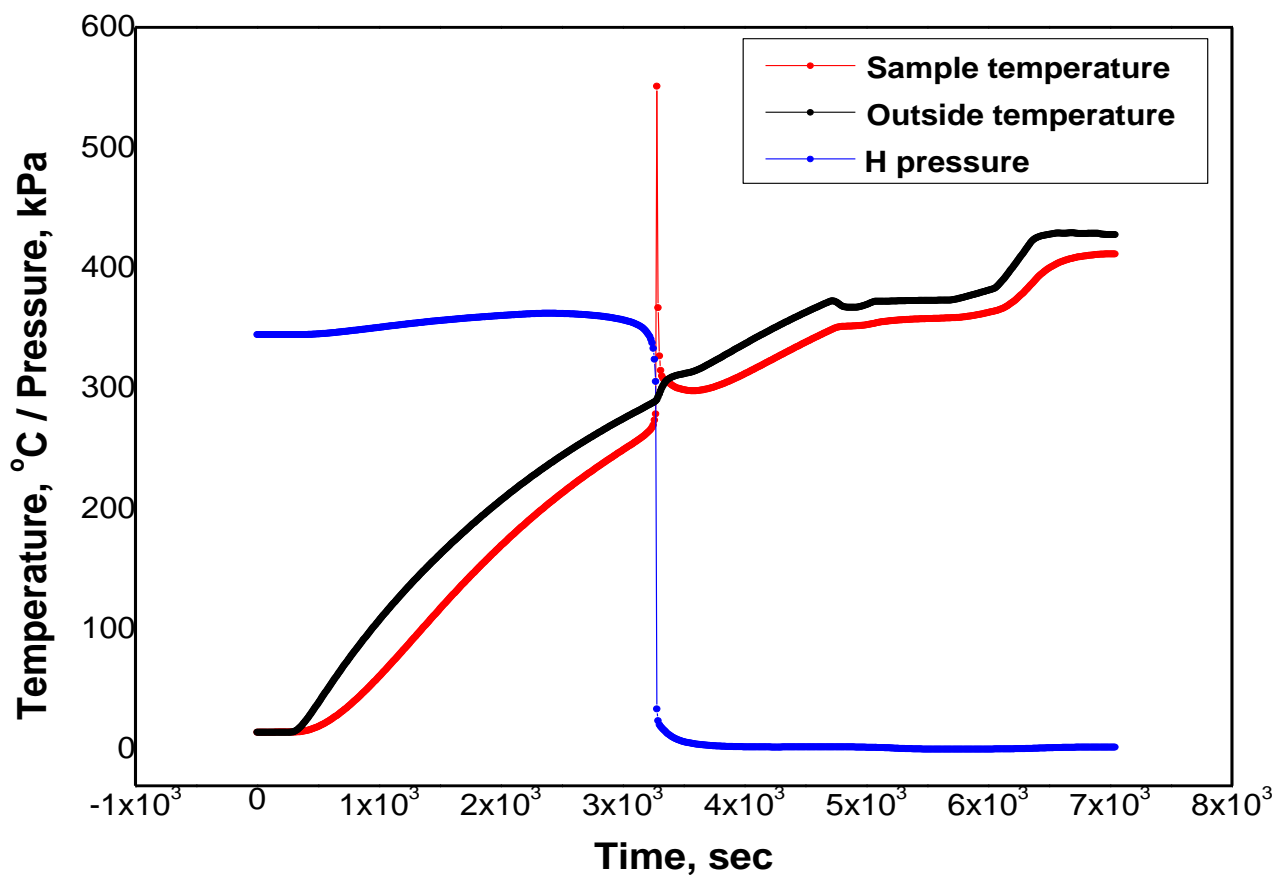

$\text{Nd}_{90}\text{Fe}_{10}$  films with  $X_c = 11\%$  of a mass 2.3713 g wrapped in a Cu foil of a mass 1.6225 gram. The loading ratio measured by the H pressure drop after hydrogenation was  $\sim 1.6$  H per metal atom ( $\sim 1.36$  wt% H). ‘Outside temperature’ is measured at 2 mm distance from the external ceramic wall of the reactor.

Before the reaction





After the reaction




$\text{Nd}_{90}\text{Fe}_{10}$  films with  $X_c = 11\%$  of a mass 2.3713 g wrapped in a Cu foil of a mass 1.6225 gram before and after hydrogenation

After the reaction

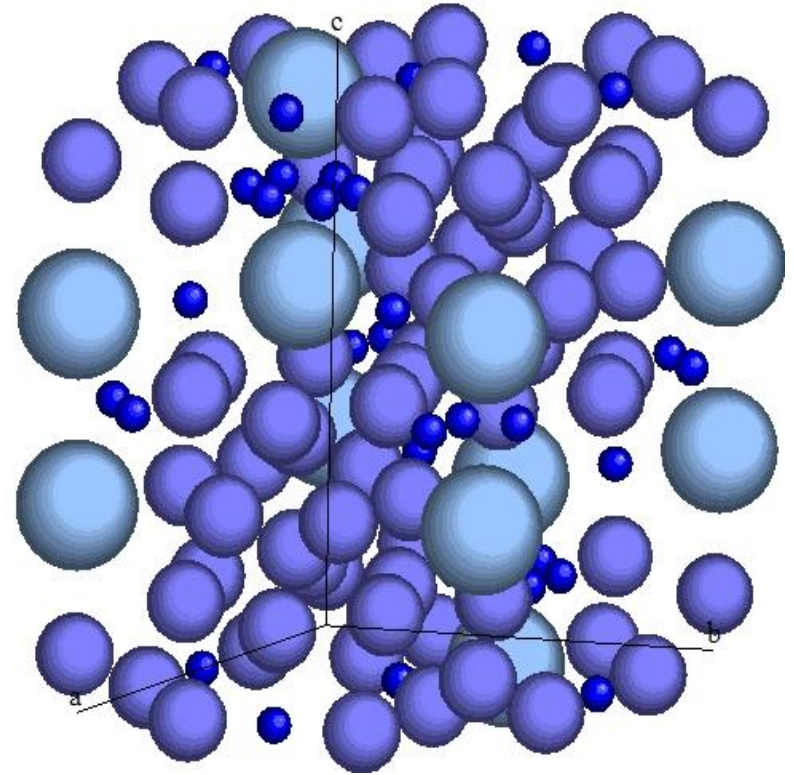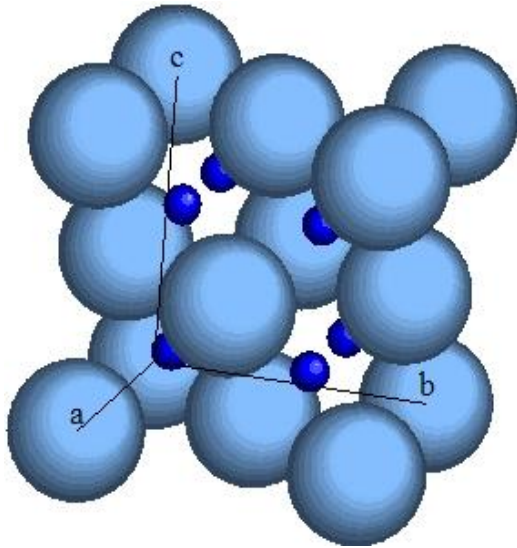

Unit cells of fcc  $\text{NdH}_2$  (left) and hcp  $\text{Nd}_2\text{Fe}_{17}\text{H}_{4.6}$  (right) phases.  $\text{NdH}_2$  is a dominating phase containing a majority of absorbed hydrogen

# Differential Scanning Calorimetry (DSC)

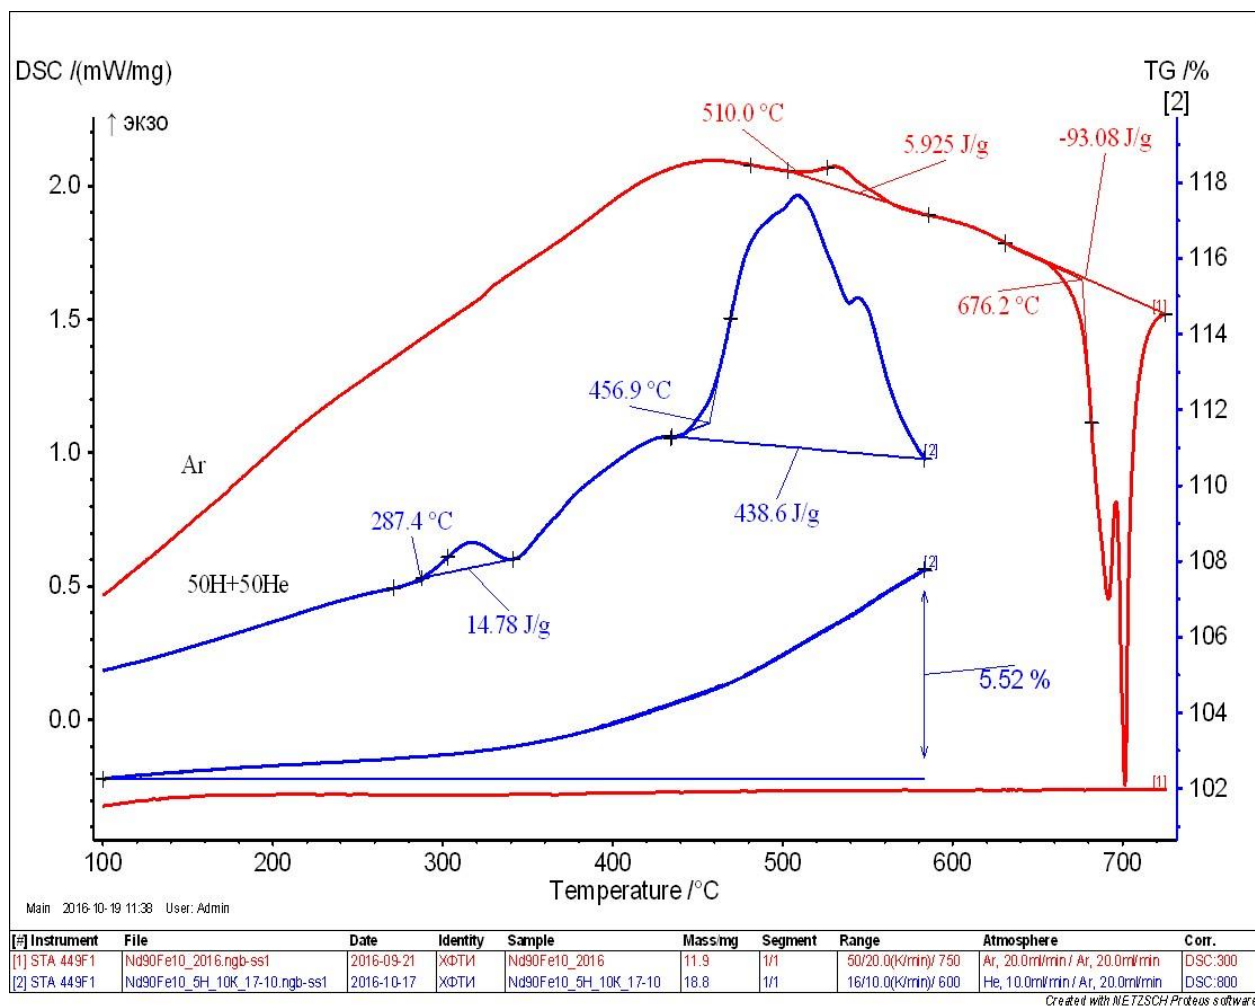

**DSC of  $\text{Nd}_{90}\text{Fe}_{10}$  samples in the Ar (11.9 mg; heating rate 20 K/min - red curves) and H/He atmosphere (18.8 mg; heating rate 10 K/min - blue curves)**

## DISCUSSION

The amount of heat produced by the observed reaction (*without account of the heat dissipation*) can be estimated as **2585 J** given by the sum

$$\Delta Q_{tot} = \Delta Q_{NdFe+Cu} (830 \text{ K}) + \Delta Q_{Al_2O_3} (13 \text{ K}) = 1263 \text{ J} + 1322 \text{ J} = 2585 \text{ J}$$

Dividing this heat by the amount of absorbed hydrogen that caused the reaction, 0.031 g, one obtains a specific heat of hydrogen absorption as

$$Q_H = 2585 \text{ J} / 0.032 \text{ g} = 80170 \text{ J} / \text{g}$$

Specific heat of hydrogen absorption in a DCS experiment is given by **11300 J/g**, which is almost an order of magnitude less than **80170 J/g** estimated in our hydrogenation experiments. It means that the underlying reactions taking place in our experiments should be different from those taking place in a DSC installation.




# What is happening ?

Hydrogenation of the **amorphous**  $\text{Nd}_{90}\text{Fe}_{10}$  structure excites LAVs  $\Rightarrow$  LAVs catalyze H absorption and LENR  $\Rightarrow$  LENR produces heat  $\Rightarrow$  heat melts the structure, which kills LAVs and stops LENR  $\Rightarrow$  the samples cool down in the form of hydride crystals:  $\text{NdH}_2$  (fcc),  $\text{Nd}_2\text{Fe}_{17}\text{H}_{4.8}$  (hcp) and  $\text{Nd}(\text{OH})_3$  (hcp)  $\Rightarrow$  shown by X ray analysis

## What is to be done ?

To slow down the reaction by regulating H supply or taking away produced heat ?

# Deuterium absorption by $\text{Nd}_{90}\text{Fe}_{10}$ mixed with Cu powder

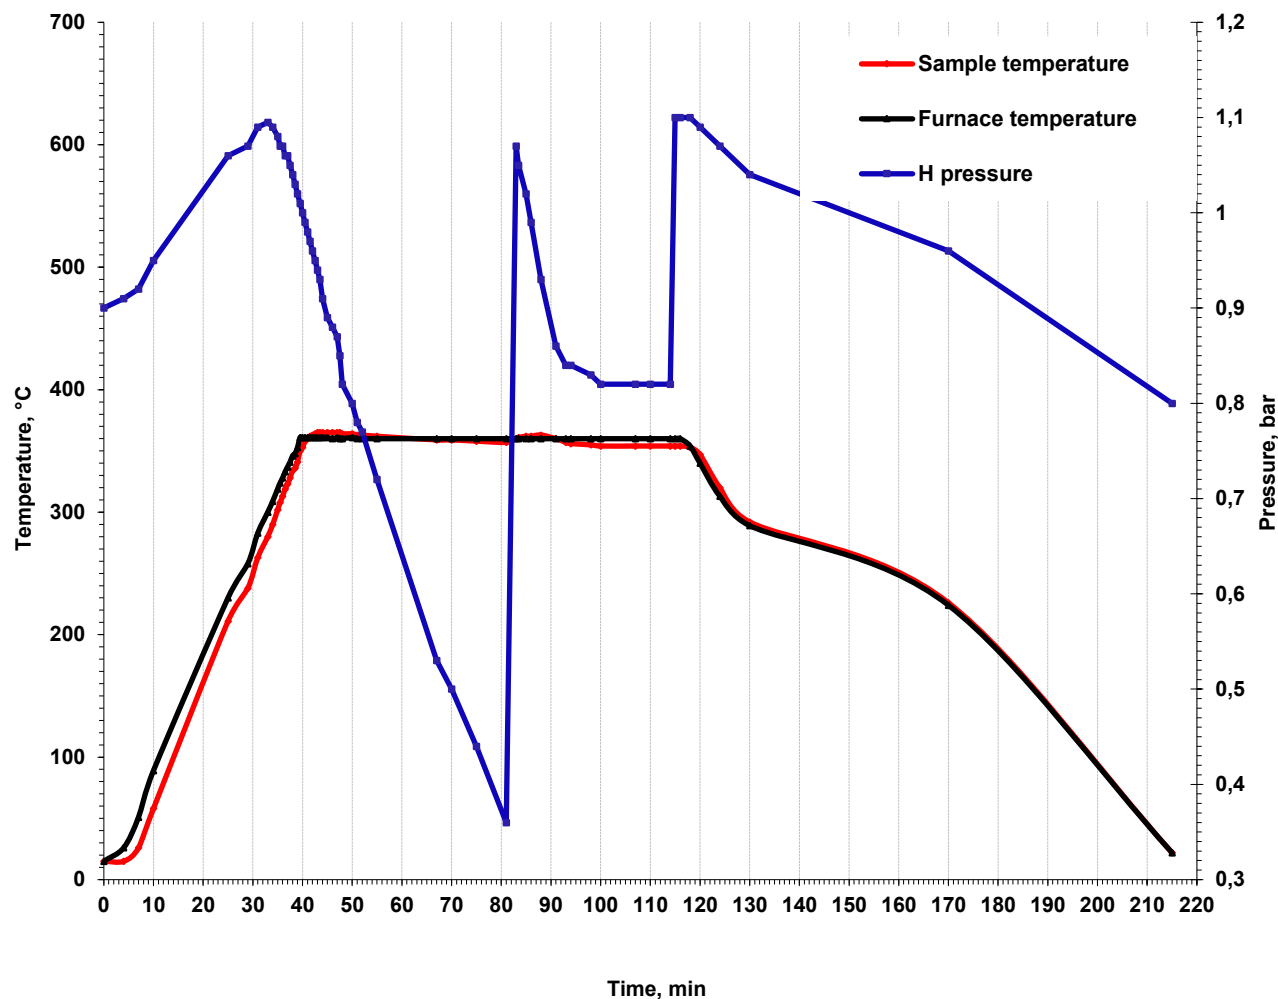

$\text{Nd}_{90}\text{Fe}_{10}$  powder with  $X_c = 11\%$  of a mass 1.7222 g mixed with Cu powder of a mass 2.2526 g, wrapped in a Cu foil of a mass 0.43955 g and packed in a Cu tube of a mass 9.565 g.

## **CONCLUSIONS on Nd<sub>90</sub>Fe<sub>10</sub> experiment:**


Quantitative analysis have shown that the amount of heat produced in Nd<sub>90</sub>Fe<sub>10</sub> samples in our experiments cannot be explained by DSC data on the heat produced in small samples.

One of the possible explanations of this discrepancy is based LENR taking place *at the initial stage of hydride formation*, when 80÷90% of amorphous phase in the films support the LAV formation, which triggered LENR. Subsequently, the amorphous phase transforms to crystalline hydrides where the LAVs do not form, which stops the LENR. Upon cooling, various hydride phases are observed by X ray analysis: NdH<sub>2</sub> (fcc) and Nd<sub>2</sub>Fe<sub>17</sub>H<sub>4.8</sub> (hcp).

# Conclusions and outlook

- We presented an experimental setup that allows accurate measuring of the main parameters controlling the reaction: hydrogen pressure, temperature inside the fuel and at the heater, the difference between which can provide direct evidence of the excess heat.
  - Our installation combines the **heating** with **electromagnetic** and **radiation-induced** driving, provides the temperature and gas pressure automatic control, gamma detectors etc.
  - First tests of the interaction of Ni with H and  $\text{LiAlH}_4$  under heating and gamma irradiation revealed important artefacts, which should be taken into account in further experimental setups.
- Specially designed new material*, based on amorphous **Nd<sub>90</sub>Fe<sub>10</sub>** composition shows **abnormal heat production** under hydrogenation, the physical origin of which requires further investigations.

Future plans: Ti-Zr-Ni alloys etc.

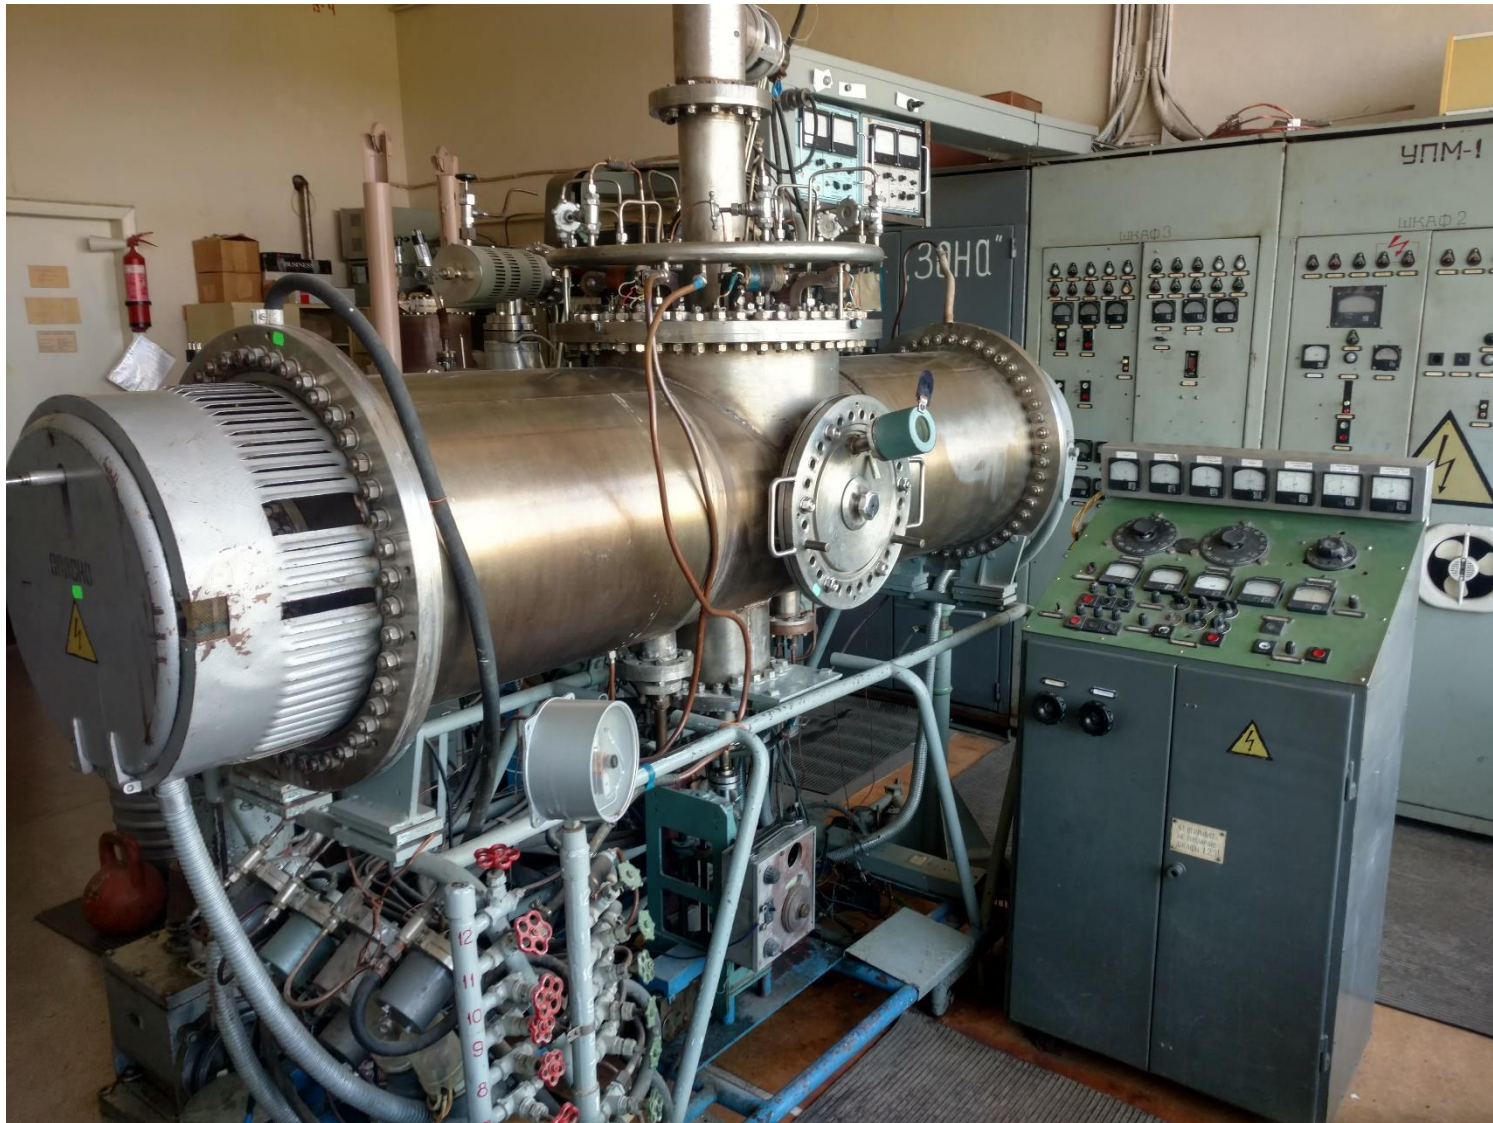

High-vacuum electron-beam melting unit for metals **EBM-1**.

# Publications

I

1. V.I. Dubinko, P.A. Selyshchev and F.R. Archilla, *Reaction-rate theory with account of the crystal anharmonicity*, **Phys. Rev. E** 83 (2011),041124-1-13
2. V.I. Dubinko, F. Piazza, *On the role of disorder in catalysis driven by discrete breathers*, **Letters on Materials** 4 (2014) 273-278.
3. V.I. Dubinko, *Low-energy Nuclear Reactions Driven by Discrete Breathers*, **J. Condensed Matter Nucl. Sci.**, 14, (2014) 87-107.
4. V.I. Dubinko, *Quantum tunneling in gap discrete breathers*, **Letters on Materials**, 5 (2015) 97-104.
5. V.I. Dubinko, *Quantum Tunneling in Breather 'Nano-colliders'*, **J. Condensed Matter Nucl. Sci.**, 19, (2016) 1-12.
6. V. I. Dubinko, D. V. Laptev, *Chemical and nuclear catalysis driven by localized anharmonic vibrations*, **Letters on Materials** 6 (2016) 16–21.
7. V. I. Dubinko, *Radiation-induced catalysis of low energy nuclear reactions in solids*, **J. Micromechanics and Molecular Physics**, 1 (2016) 165006 -1-12.
8. V.I. Dubinko, O.M. Bovda, O.E. Dmitrenko, V.M. Borysenko, I.V. Kolodiy, *Peculiarities of hydrogen absorption by melt spun amorphous alloys Nd<sub>90</sub>Fe<sub>10</sub>*, *Vestnik KhNU* (2016).
9. V. Dubinko, D. Laptev, K. Irwin, *Catalytic mechanism of LENR in quasicrystals based on localized anharmonic vibrations and phasons*, ICCF20, <https://arxiv.org/abs/1609.06625>.





## **Acknowledgments:**

financial support from Quantum Gravity Research is gratefully acknowledged.

**THANK YOU  
FOR YOUR ATTENTION!**