


# 9<sup>th</sup> European Conference on Wood Modification ECWM9

September 17 and 18, 2018, Arnhem, The Netherlands

## PROCEEDINGS

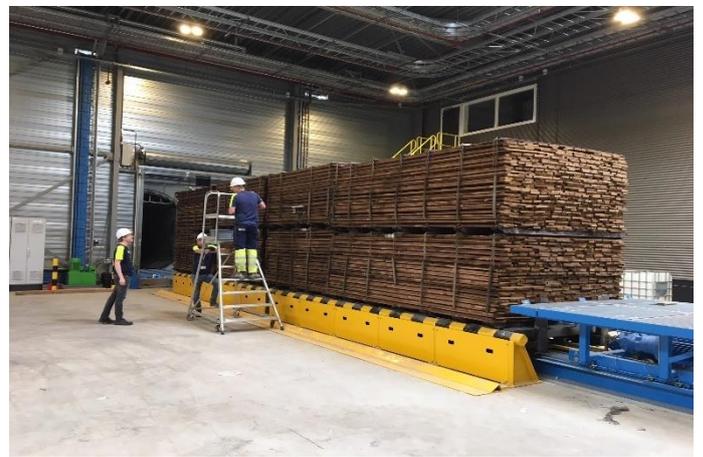

ECWM<sup>9</sup>  
The 9th European Conference on **Wood** Modification  
The Netherlands • Arnhem • September 17-18, 2018

# **PROCEEDINGS**

## **9<sup>th</sup> European Conference on Wood Modification**

Burgers' Zoo  
Arnhem, The Netherlands  
17-18 September 2018

In association with:  
COST FP1407 ModWoodLife

Edited by:  
Jos Creemers, Thomas Houben, Bôke Tjeerdsma, Holger Militz, Brigitte Junge  
and Jos Gootjes

Secretariat:  
SHR B.V.  
Nieuwe Kanaal 9b  
6709 PA Wageningen  
[www.ecwm9.shr.nl](http://www.ecwm9.shr.nl)



## Legal Notice

Although all reasonable efforts were made by the editorial team to ensure the scientific quality of the contents of these conference proceedings, the final responsibility for the contents of individual articles therein remains with the respective authors. The editors accept no responsibility for the information contained herein. The inclusion of information in this publication does not constitute any form of endorsement by the editors. The editorial team is not responsible for the contents of external websites referred to in this publication.

No permission is required to reproduce or utilise the contents of these abstracts other than in the case of diagrams, images, or other material from other copyright holders. In such cases the permission of the original copyright holder must be obtained. The proceedings may be sited as *Proceedings of the 9<sup>th</sup> European Conference on Wood Modification 2018, Arnhem, The Netherlands*.

Copyright © SHR B.V.

Nieuwe Kanaal 9<sup>b</sup>, 6709 PA Wageningen, The Netherlands

[www.shr.nl](http://www.shr.nl)

ISBN: 978-90-829466-1-1

## Preface

SHR was one of the first research institutes in Europe, who already in the 1990's did substantial research work to develop wood modification processes. It appeared, that this research area was very complex, and that for a successful application of potential processes different expertise's was needed. A good network between research partners and industry was needed and the "European Network on Wood Modification" was created. 15 years ago, in 2003, the first European Conference on Wood Modification "ECWM" was held to present the outcomes of this EU financed network. Since than, ECWM's were held each 2-3 years at different places around Europe, and now we can celebrate the 9<sup>th</sup> ECWM in the Netherlands, organized by SHR where it all began.

As already before, ECWM 9 is linked up to the European COST organisation. Thanks to the COST Action FP 1407 ModWoodLife to join and strengthen our network!

The participation of researchers of all around the world make it obvious that the name "European conference" is much too small...so: a warm welcome to researchers from industry and academia from Europe and abroad! This success has led, once again, to a large number of abstracts submitted to the organizers. In general, these abstracts were of a high quality and the members of the Scientific Committee had a hard time to select 44 full presentations and 50 poster presentations out of the many applications. We hope we have found the right balance between scientific and applied presentations to reach the key goal of ECWM: to attract researchers from academia and industry to join their expertises in this very exciting research area "wood modification".

The local conference organizers from SHR have done a great job this past year to make us feel welcome in The Netherlands and to let the conference be a success. Thank you very much to Bôke and team!



Prof. Dr. Holger Militz  
Chairman of Scientific Committee  
Georg-August-University Göttingen, Germany

### **Scientific Committee**

Dr. Julia Milne e Carmo,	Carmo Group, Portugal
Prof. Dr. Callum Hill,	JCH Industrial Ecology Ltd., United Kingdom
Dr. Dennis Jones,	Timber Consultancy (UK) / LTU, Sweden
Prof. Dr. Holger Militz,	Göttingen Uni., Germany (Chairman of Scientific Committee)
Mr. Jos Creemers,	SHR, The Netherlands
Mr. Bôke Tjeerdsma,	SHR, The Netherlands
Prof. Dr. Joris Van Acker,	Ghent Uni., Belgium
Dr. Andreja Kutnar,	University of Primorska, Slovenia (FP 1407)

### **Local Organising Committee**

Mr. Bôke Tjeerdsma,	SHR; The Netherlands (Chairman of Organizing Committee)
Mrs. Marina van der Zee,	SHR; The Netherlands
Mr. Jos Creemers, SHR	SHR; The Netherlands
Dr. René Klaassen,SHR	SHR; The Netherlands
Mr. Bas Holleboom, SKH	SKH; The Netherlands
Mrs. Mariena Mooi, SHR	SHR; The Netherlands
Mrs. Jos Gootjes, SHR	SHR; The Netherlands

## Wood modification in practice

The European Conference on Wood Modification takes place on the 17<sup>th</sup> and 18<sup>th</sup> of September 2018 in Arnhem, The Netherlands and is organised by SHR. At this conference researchers and people from industry from all over the world will come together to share their knowledge and experiences with the latest developments on wood modification methods, applications and products. The conference was given the subtitle “Wood modification comes home”, which refers to the role The Netherlands and SHR have played – and still play – in the development and industrial application of modified wood.

Techniques and methods designed for improving wood properties are almost as old as mankind itself. However the scientific and industrial rise of wood modification became significant under the influence of a number of social and economic developments in the eighties and nineties of the previous century. A strong need was felt to find alternatives for the use of tropical hardwoods and preservative treated wood, which were both under pressure for a variety of reasons. The discussions regarding a clean environment, sustainable forest management, wood use and the increasing wood demands from emerging markets in Asia also had a big impact. Wood modification was recognized to have the ability to offer a more, better and sustainable way of making use of wood as a durable material in a broad range of applications. Besides that, it was found to be a supreme method for upgrading the properties of lesser used timber species and to provide technical solutions to overcome some of the natural deficiencies of wood as water uptake, decay and dimensional changes.

Over the last decades an enormous amount of scientific work has been performed and published. We have seen many innovative modification ideas, methods and techniques passing by during the previous eight ECWM's. To make a real impact, ideas need to be developed further and put into practice. We are proud that in The Netherlands we have created a setting with a high level of knowledge, innovative thinking combined with entrepreneurship, which lead to a variety of flourishing companies involved in industrial production of modified wood. Not only producing companies, but also the wood processing industry has adopted modified wood as a highly appreciated durable material. We can declare that modified wood has become a lasting factor in the wood processing industry.

For these reasons SHR and we as the organising team, are excited to welcome you all here in The Netherlands for the 9<sup>th</sup> European Conference on Wood Modification. We hope you will enjoy your stay here in Arnhem and become inspired by all attendees, presenters and new insights this conference has to offer.

Welcome!

The organising team

## **COST 1407 - Foreword**

It is our pleasure that COST Action FP1407 “Understanding wood modification through an integrated scientific and environmental impact approach” (ModWoodLife) in part of 9th European Conference of Wood Modification. The conference brings together researchers from across Europe and beyond that jointly are addressing the mounting pressure on renewable resources (as a material source, for recreational, ecological, and other uses). By maximising the efficiency of materials derived from them, the wood modification community plays an important role. The efficiency can only be achieved if new methods to improve the functionality, durability, properties, and environmental impacts will be developed. Wood modification addresses these requirements directly, allowing wood to be used in more applications, including increased use of under-utilised species. Wood modification also addresses undesirable characteristics of wood such as fungal resistance, UV-stability, and moisture sensitivity. The COST Action FP1407 has been successful in addressing these needs in the past 3 years. We are in the last year of the Action and therefore it is even more important for us to be at ECWM9. Only sustainable collaboration and joint efforts will deliver the impacts. That objective of the Action FP1407, to characterise the relationship between wood modification processing, product properties, and the associated environmental impacts in order to maximise sustainability and minimize environmental impacts, has great value for the forest sector, for researchers, and society at large.

Wishing you a successful and memorable conference full of fruitful discussions.

Andreja Kutnar  
Chair, COST FP1407

Denis Jones  
Vice-Chair, COST FP1407

## Table of Contents

<b>Preface</b>	<b>3</b>
<b>Table of contents</b>	<b>7</b>
<b>Session One: Wood Modification World-wide - keynote presentations</b>	
<b>Modified wood in circular economy – a critical review</b>	<b>16</b>
<i>Henrik Heräjärvi, Janni Kunttu, Elias Hurmekoski, Teppo Hujala</i>	
<b>A review of wood modification across Europe as part of COST FP1407</b>	<b>24</b>
<i>Dennis Jones, Dick Sandberg, Andreja Kutnar</i>	
<b>What is wrong with Wood Modification in the U.S.?</b>	<b>32</b>
<i>Jeffrey Morrell</i>	
<b>Session Two: Commercial and Market Opportunities for Modified Wood</b>	
<b>New Standards for Approval of Modified Wood within the Nordic Wood Preservation Council (NWPC)</b>	<b>40</b>
<i>Niels Morsing, Søren Bang-Achton, Emil Englund Thybring, Morten Klamer</i>	
<b>Kebony Clear – Produced in Belgium</b>	<b>48</b>
<i>Per Brynildsen, Omar Roels, Bruno Van den Branden</i>	
<b>Improved dimensional stability of polypyrrole enriched spruce as an indication for chemical change</b>	<b>56</b>
<i>Andries van Eckeveld, Rabi Malki, Michael Sailer, Jacco Eversdijk</i>	
<b>Practical experience of acetylated wood fibre panel products in Dutch door manufacturing</b>	<b>64</b>
<i>Jeroen Lücker</i>	
<b>Wood Modification with DMDHEU (1.3-dimethylol-4.5-dihydroxy-ethyleneurea) – Status quo and latest research activities</b>	<b>74</b>
<i>Lukas Emmerich, Holger Militz</i>	
<b>Architects perception of modified wood: a parallel study in selected countries of Europe</b>	<b>82</b>
<i>Manja Kitek Kuzman, Eva Haviarova, Dick Sandberg</i>	
<b>Enhancing the Properties of ThermoWood® with Phenolic Resin Treatment</b>	<b>91</b>
<i>Reeta Stöd, Janne Pynnönen, Duncan Mayes, Bodo Caspar Kielmann</i>	

## Session Three: Poster Session 1

<b>Effect of Thermo-Mechanical Treatment on Properties of Parica Laminated Veneer Lumber (<i>Schizolobium amazonicum</i> Huber ex Ducke)</b>	<b>98</b>
<i>Mírian de Almeida Costa, Cláudio Henrique Soares Del Menezzi</i>	
<b>TanWood®: The Brazilian Process of Thermal Modification of Wood</b>	<b>104</b>
<i>Leonardo Puppi Bernardi, Djeison Cesar Batista</i>	
<b>Examining the coating performance of finishes on acetylated hornbeam wood (<i>Carpinus betulus</i> L.)</b>	<b>112</b>
<i>Fanni Fodor, Róbert Németh</i>	
<b>Colour response of heat treated spruce and pine with different surface coatings in outdoor exposure</b>	<b>119</b>
<i>Niclas Björngrim, Marie Hartwig, Olle Hagman, Tom Morén</i>	
<b>New substrates for wood modification. Characterising pore size distributions in variously dried softwood</b>	<b>123</b>
<i>Warren Grigsby, Elizabeth Dunningham, Hank Kroese</i>	
<b>Determination of resistance of thermally treated wood to weather conditions in different countries (HTW) - Preliminary results</b>	<b>126</b>
<i>Idalina Domingos, José Ferreira, Luisa Cruz-Lopes, Júlia Carmo, Jorge Martins, René Herrera, Lina Nunes, Bruno Esteves</i>	
<b>Investigation of <i>Abies alba</i> wood thermal stability according to its radial position</b>	<b>131</b>
<i>Joël Hamada, Anélie Pétrissans, Julien RuellE, Frédéric Mothe., Francis Colin, Mathieu Pétrissan, Philippe Gérardin</i>	
<b>Properties improvement of bamboo materials through furfurylation</b>	<b>137</b>
<i>Li Wanju, Wang Hankun, Liu Minghui, Yu Yan</i>	
<b>Veneer modification with fire retardant chemicals</b>	<b>143</b>
<i>Saara Hautamäki, Michael Altgen, Tuomas Hänninen, Lauri Rautkari</i>	
<b>Natural Weathering and Photostability of Wood Modified by Fatty Acid esters</b>	<b>149</b>
<i>Mohamed Jebrane, Nasko Terziev, Ivo Heinemaa</i>	
<b>Effects of thermal modification on bending properties and chemical structure of Iroko and Padauk</b>	<b>155</b>
<i>Michal Kroupa, Milan Gaff, Olov Karlsson, Olena Myronycheva, Dick Sandberg</i>	
<b>Modified wood in actual use and its weathering performance after outdoor exposure</b>	<b>162</b>
<i>Ville Lahtela, Tim Kärki</i>	
<b>Performance of thermal modified radiata pine in real cases of facades and deckings in North Spain</b>	<b>167</b>
<i>David Lorenzo, Alfonso Lozano, Juan Fernández-Golfin, Manuel Touza, René Herrera</i>	

## Table of Contents

<b>Water free PEG impregnation of hardwood veneer using a roll press</b> <i>Tillmann Meints, Axel Rindler, Niklas Bugelnig, Christian Hansmann</i>	<b>173</b>
<b>The impact of cerium dioxide nanoparticles on thermally modified wood-coating system during weathering</b> <i>Josip Miklečić, Vlatka Jirouš-Rajković</i>	<b>177</b>
<b>Application of time-temperature-humidity superposition to the hygrothermally accelerated ageing of spruce wood</b> <i>Eiichi Obataya, Nanami Zeniya, Kaoru Endo, Miyuki Matsuo-Ueda</i>	<b>181</b>
<b>Preliminary studies on the effect of acetylation and subsequent weathering on tensile strength and stiffness of Rubber wood (<i>Hevea brasiliensis</i>)</b> <i>Samuel Olaniran, E. Cabane, M. Rüggeberg</i>	<b>187</b>
<b>Mild torrefaction pre-treatment of eucalypts aiming at its energetic valorisation</b> <i>Solange de Oliveira Araújo, Duarte M. Neiva, Angélica de Cássia Carneiro, Bruno Esteves, Jorge Gominho, Helena Pereira</i>	<b>193</b>
<b>Influence of various polyethylene glycol treatments on the dimensional stability of beech wood.</b> <i>Sabrina Puttmann, Lukan Müller, Bertil Burian, Marcus Müller</i>	<b>199</b>
<b>Adhesion of coatings to plasma modified wood at accelerated weathering</b> <i>Ladislav Reinprecht, rADOVANTiño, Marek Šomšák</i>	<b>205</b>
<b>Measuring Accessibility of OH groups in Scots Pine with Dynamic Vapour Sorption Apparatus</b> <i>Tuuli Uimonen, Saara Hautamäki, Maija Kymäläinen, Lauri RauTkari</i>	<b>210</b>
<b>Plasma treatment of wood veneers: a review</b> <i>Richard Wascher, Georg Avramidis, Holger Militz, Wolfgang Viöl</i>	<b>216</b>
<b>Saturated gaseous ammonia treatment for improved densification of beech wood – Sorption and mechanical properties</b> <i>Mario Zauer, Tobias Dietrich, Herwig Hackenberg, André Wagenführ</i>	<b>224</b>
<b>Water vapour diffusion through acetylated wood with different weight percent gain (WPG)</b> <i>Ava Khodabakhshi Koulaei, Asghar Tarmian, Davood Efhamisisi, Ali Abdulkhani</i>	<b>230</b>
<b>Session 4A: Properties 1</b>	
<b>The potential for use of acetylated wood in musical instruments making</b> <i>Stergios Adamopoulos, Sheikh Ali Ahmed, Chiel Lankveld</i>	<b>236</b>
<b>Influence on acoustical properties of resonant soundboard material through different processes of thermal modification</b> <i>David Zerbst, Lothar Clauder, Dave Olson, Alexander Pfriem</i>	<b>244</b>

## Table of Contents

<b>Measuring the Free Hydroxyl Content in Wood Modified by Acetic or Propionic Anhydride</b>	<b>251</b>
<i>Callum Hill, Greeley Beck, Erik Larnøy, Sarah Strohbusch, Holger Militz</i>	
<b>Pre-treatment with Ionic Liquids or Organic Superbases to Reduce Spring-Back and Set-Recovery of Surface-Densified Scots pine</b>	<b>259</b>
<i>Benedikt Neyses, Olov Karlsson, Dick Sandberg</i>	
<b>Potential solutions for gluing acetylated wood in load bearing constructions</b>	<b>267</b>
<i>Andreas Treu, Ronny Bredesen, Ferry Bongers</i>	
<b>Combustion behaviour of wood chemically modified with DMDHEU-, PF-, and MF-resins</b>	<b>275</b>
<i>Zhijun Zhang, Zefang Xiao, Holger Militz, Carsten Mai, Yanjun Xie</i>	
<b>Session 4B: Thermal Modification</b>	
<b>Potential to limit variation in durability of thermally modified timber</b>	<b>284</b>
<i>Joris van Acker, Jan Van Den Bulcke</i>	
<b>Thermovuoto thermal modification of eight European wood species</b>	<b>292</b>
<i>Ignazia Cuccui, Nasko Terziev, Giovanna Bochicchio, Ottaviano Allegretti</i>	
<b>Differences in the mechanical behaviour of wood after thermal modification in oven-dry or water-saturated state</b>	<b>300</b>
<i>Michael Altgen, Tuuli Uimonen, Lauri Rautkari</i>	
<b>Thermal modification of wax impregnated wood</b>	<b>308</b>
<i>Miha Humar, Davor Kržišnik, Boštjan Lesar, Nejc Thaler, Aleš Ugovše, Gregor Rep</i>	
<b>The role of accessible hydroxyl groups in reversible and irreversible EMC changes by thermal wood modification</b>	<b>316</b>
<i>Wim Willems, Michael Altgen, Lauri Rautkari</i>	
<b>Session 5: COST FP 1407</b>	
<b>Wood Furfurylation as a way to valorise European Beech and promote Circular and Bio-Economy</b>	<b>323</b>
<i>Christine Gérardin, Aurélie Imbert, Prabu Satria Sejati, Emmanuel Fredon, Stéphane Dumarçay, Eric Masson, Arnaud Besserer, Benoit Laibe, Rémi Laibe, Hugo Sellier, Philippe Gérardin</i>	
<b>Dynamic Mechanical Thermal Analysis of Wood Modified with Bio-Polyesters</b>	<b>331</b>
<i>Charlotte Grosse, Morwenna Spear, Simon Curling, Marion Noël, Lauri Rautkari, Tuuli Uimonen, Philippe Gérardin</i>	
<b>Perception and evaluation of modified wood</b>	<b>339</b>
<i>Dean Lipovac, Michael D. Burnard, Andreja Kutnar</i>	

## Table of Contents

<b>Valorization of Beech Wood through Development of Innovative Friendly Environmentally Chemical Modification Treatments</b>	<b>347</b>
<i>Mahdi Mubarak, Stéphane Dumarçay, Holger Militz, Philippe Gérardin</i>	
<b>Infrared spectroscopy and chemometric methods for the evaluation of the thermal/chemical treatment effectiveness of hardwoods</b>	<b>355</b>
<i>Carmen Mihaela Popescu, Davor Kržišni, Miha Hočevár, Miha Humra, Nejc Thelar, Maria-Cristina Popescu, Dennis Jones</i>	
<b>Performance of modified wood in service – multi-sensor and multi-scale evaluation</b>	<b>363</b>
<i>Anna Sandak, Jakub Sandak, Marta Petrillo, Paolo Grossi</i>	
<b>Carbon footprint of decking materials- a comparison of modified wood and preservative treated wood</b>	<b>371</b>
<i>Lars Tellnes, Gry Alfredsen, Per Otto Flæte, Lone Ross Gobakken</i>	
<b>Session Six A: Properties 2</b>	
<b>Strength classification of acetylated radiata pine</b>	<b>380</b>
<i>Ferry Bongers, John Alexander</i>	
<b>Effect of DMDHEU modification on physical and mechanical properties of top-layer lamellas for multi-layer parquet flooring</b>	<b>386</b>
<i>Lukas Emmerich, Holger Militz</i>	
<b>Cutting forces when machining thermally modified poplar – preliminary results</b>	<b>396</b>
<i>Giacomo Goli, Rémi Curti, Bertrand Marcon, Antonio Scippa, Marco Fioravanti, Gianni Campatelli, Louis Denaud</i>	
<b>Properties of MMA treated thermally modified Norway spruce wood</b>	<b>401</b>
<i>Boštjan Lesar, Luka Škrlep, Miha Humar</i>	
<b>Differential expression of <i>Postia placenta</i> wood decay genes in modified wood</b>	<b>410</b>
<i>Rebecka Ringman, Annica Pilgård, Martina Kölle, Klaus Richter</i>	
<b>Session Six B: Chemical Modification</b>	
<b>Suitability of Lignin-Derived Monophenols to Replace Phenol in Phenol-Formaldehyde Resin for the Use in Wood Treatment</b>	<b>419</b>
<i>Vladimirs Biziks, Marco Fleckenstein, Carsten Mai, Holger Militz</i>	
<b>A new method of wood protection by chemical modification with polyglycerol succinate copolymer</b>	<b>427</b>
<i>Clément L'Hostis, Emmanuel Fredon, Marie France Thevenon, Philippe Gérardin</i>	
<b>The effect of humidity and temperature on the dynamic-mechanical behaviour of phenol-formaldehyde impregnated beech wood veneer</b>	<b>435</b>
<i>Leo Felix Munier, Tom Franke, Nadine Herold, Alexander Pfriem</i>	

## Table of Contents

<b>Biopolyesters for wood modification: technical validation towards implementation</b>	<b>441</b>
<i>Marion Nožl, Charlotte Grosse, Ingunn Burud, Marie-France Thévenon, Philippe Gérardin</i>	
<b>The Maillard reaction for wood modification: The influence of reagent concentrations, reaction temperature and soaking time on the leachability and cell wall penetration of reagents</b>	<b>449</b>
<i>Kelly Peeters, Andreja Kutnar, Črtomir Tavzes, Jaka Pečnik, Callum A.S. Hill</i>	
<b>Session Seven: Poster Session 2</b>	
<b>Wood thermal modification and impregnation: some aspects of double treatment</b>	<b>458</b>
<i>Bruno Andersons, Dace Cirule, Nina Kurnosova, Ilze Irbe, Ingeborga Andersone, Oskars Bikovens, Andis Antons, Edgars Kuka, Žanete Zommere</i>	
<b>Hydrophobisation of hardwood surfaces by means of environmentally-friendly fine wax particles</b>	<b>464</b>
<i>Benjamin Arminger, Wolfgang Gindl-Altmutter, Christian Hansmann</i>	
<b>Further Treatment Option after Longitudinal Wood Compression</b>	<b>469</b>
<i>Mátyás Báder, Róbert Németh</i>	
<b>Effect of combined modification processes on the physical properties of wood</b>	<b>475</b>
<i>Miklós Bak, Róbert Németh, Norbert Kelemen</i>	
<b>Bending properties and strain fields around knots in thermally modified timber</b>	<b>481</b>
<i>Joran van Blokland, Stergios Adamopoulos, Anders Olsson, Jan Oscarsson</i>	
<b>Thermomechanical (TM) treatment of beech wood (<i>Fagus sylvatica</i> L.) to substitute Indian rosewood (<i>Dalbergia latifolia</i> ROXB.) in musical instruments - mechanical and acoustic properties</b>	<b>487</b>
<i>Tobias Dietrich, Dr. Mario Zauer, Robert Krüge, Prof. Dr. André Wagenführ</i>	
<b>4 years field study in contact with the ground of thermomodified Scots pine sapwood</b>	<b>493</b>
<i>Andrzej Fojutowski, Andrzej Noskowiak and Aleksandra Kropacz</i>	
<b>Mineralization of wood with calcium oxalate</b>	<b>498</b>
<i>Tom Franke, Thomas Volkmer</i>	
<b>Preparation of thin functional coatings on wood and WPC materials using atmospheric pressure plasma jets</b>	<b>504</b>
<i>Sven Gerullis, Andreas Pfuch, Florian Kettner, Katharina Plaschkies, Bernd Grünler, Mario Beyer, Gennadi G. Volokitin</i>	

## Table of Contents

<b>Investigation of Birch Wood Impregnation with Phenol-Formaldehyde (PF) Resins</b>	<b>510</b>
<i>Juris Grinins, Ilze Irbe, Vladimirs Biziks, Janis Rizikovs, Sascha Bicke, Holger Militz</i>	
<b>Thermal properties and density profile of poplar wood (<i>Populus nigra L.</i>) thermally and thermo-mechanically modified</b>	<b>516</b>
<i>Marek Grzeškiewicz, Karol Poddębski</i>	
<b>Water sorption properties of surface charred wood</b>	<b>522</b>
<i>Maija Kymäläinen, Saara Hautamäki, Lauri Rautkari</i>	
<b>Energy dispersive x-ray fluorescence (ED-XRF) for the multi-elemental analysis of thermally modified wood treated with coatings systems</b>	<b>528</b>
<i>René Herrera Díaz, Marco Fellin, Martino Negri, Jalel Labidi</i>	
<b>Thermowood® vs Termovuoto process – comparison of thermally modified timber in industrial conditions</b>	<b>533</b>
<i>Mohamed Jebrane, Ignazia Cuccui, Ottaviano Allegretti, Ernesto Uetimane Jr., Nasko Terziev</i>	
<b>Study on Drying Characteristics of Poplar Wood Impregnated with Urea-formaldehyde Resin</b>	<b>539</b>
<i>Yang Lihu, Yuan Haiguang</i>	
<b>Life cycle assessment of bio-based façades during and after service life: maintenance planning and re-use</b>	<b>545</b>
<i>Marta Petrillo, Jakub Jakub, Anna Sandak, Paolo Grossi, Andreja Kutnar</i>	
<b>Raman spectral imaging of chemically modified Scots pine</b>	<b>551</b>
<i>Carmen Mihaela Popescu, Lauri Rautkari, Michael Altgen, Tiina Belt, Mikko Mäkelä</i>	
<b>Changes in longitudinal modulus of elasticity of Douglas-fir during low temperature thermal treatment</b>	<b>557</b>
<i>Dan Ridley-Ellis, Carmen-Mihaela Popescu</i>	
<b>Investigation of the effect of moderate heat treatment on wood hygroscopicity by NMR relaxometry</b>	<b>563</b>
<i>Leila Rostom, Denis Courtier-Murias, Stéphane Rodts, Sabine Caré</i>	
<b>Effect of wood modification and weathering progress on the radiation emissivity</b>	<b>569</b>
<i>Anna Sandak, Jakub Sandak, Marta Petrillo, Paolo Grossi</i>	
<b>Composition of monosaccharides in aqueous extracts from thermally modified wood</b>	<b>575</b>
<i>Ekaterina Sidorova, Olov Karlsson, Dick Sandberg</i>	
<b>Insights into stability of glued joints between thermally modified timber: adaptation of an artificial weathering test</b>	<b>581</b>
<i>Morwenna Spear, Raisa Teciu, Graham Ormondroyd</i>	

## Table of Contents

<b>Water resistant tannin polymers</b>	<b>587</b>
<i>Gianluca Tondi, Lukas Sommerauer</i>	
<b>Dynamic and static mechanical properties of <i>Eucalyptus nitens</i> thermally modified in an open and closed reactor system</b>	<b>592</b>
<i>Maximilian Wentzel, Christian Brischke, Holger Militz</i>	
<b>Session 8: Performance</b>	
<b>Enhancing the material properties of wood through furfurylation</b>	<b>600</b>
<i>Wanju Li, Changhua Fang, Hankun Wang, Xuexia Zhang, Dan Ren, Yan Yu</i>	
<b>Comparative studies on the biological durability of identical thermally modified wood from field and laboratory tests</b>	<b>608</b>
<i>Sven Hertrich, Lothar Clauder, Silke Lautner, Alexander Pfriem</i>	
<b>Appearance of solid wood decking: requirements and assessment</b>	<b>616</b>
<i>Wolfram Scheiding, Philipp Flade, Katharina Plaschkies, Björn Weiß</i>	
<b>Monitoring the performance of Accoya in different applications</b>	<b>623</b>
<i>René Klaassen, Bôke Tjeerdsma, René Hillebrink</i>	
<b>Performance of chemically modified wood under marine conditions during nine years of exposure</b>	<b>630</b>
<i>Christian Brischke, Antje Gellerich, André Klüppel, Holger Militz</i>	

## **Performance of modified wood in service – multi-sensor and multi-scale evaluation**

Anna Sandak<sup>1</sup>, Jakub Sandak<sup>2,3,4</sup>, Marta Petrillo<sup>5</sup> and Paolo Grossi<sup>6</sup>

<sup>1</sup>CNR-IVALSA, via Biasi 75, 30010 San Michele all'Adige, Italy [email: anna.sandak@ivalsa.cnr.it]

<sup>2</sup>InnoRenew CoE, Livade 6, 6310 Izola, Slovenia [email: Jakub.Sandak@innorenew.eu]

<sup>3</sup>University of Primorska, Faculty of Mathematics, Natural Sciences and Information Technology, Glagoljaska 8, 6000 Koper, Slovenia

<sup>4</sup>CNR-IVALSA, via Biasi 75, 30010 San Michele all'Adige, Italy [email: sandak@ivalsa.cnr.it]

<sup>5</sup>CNR-IVALSA, via Biasi 75, 30010 San Michele all'Adige, Italy [email: petrillo@ivalsa.cnr.it]

<sup>6</sup>CNR-IVALSA, via Biasi 75, 30010 San Michele all'Adige, Italy [email: grossi@ivalsa.cnr.it]

**Keywords:** service life performance, modified wood, multi-sensor evaluation, weathering, facades

### **ABSTRACT**

The performance of 120 selected façade materials provided by over 30 industrial and academic partners was evaluated during 12-month experimental campaign of natural weathering. A multi-sensor measurement chain for the acquisition of properties at different scales (molecular, microscopic, macroscopic) included both laboratory and on-site techniques. Investigated bio-materials were characterized before, during and after degradation by biotic and abiotic agents in order to provide experimental data to be used for better understanding of the bio-materials performance/degradation as a function of time and/or weather dose. Obtained data were utilized for the development series of numerical models simulating materials appearance changes along the service life of building facade. An original software simulating bio-materials' performance in any geographical location has been developed and is currently under integration with Building Information Modelling. It serves as a tool for demonstrating advantages of using bio-based materials when compared to other commonly utilized alternative resources. Results of the BIO4ever project provide solid technical and scientific knowledge, but also contribute to the public awareness by demonstrating the environmental benefits to be gained from the knowledgeable use of bio-based materials in buildings.

### **INTRODUCTION**

Wood is a traditional material utilized for construction of buildings since beginning of civilisation. Its availability, relatively low maintenance cost and ease of processing, result in the common use as prevalent construction material for both interior and exterior applications. While possessing several advantages, such as aesthetic appeal and positive weight to load-bearing capacity ratio, unprotected wood suffers when exposed to the environmental conditions by changing its dimensions and appearance. The most susceptible parts are unprotected surfaces in outdoor environment, since these are directly subjected to ageing, weathering or decay.

Wood modification processes leads to the enhancement of desired properties by means of chemical, biological or physical agents. Wood properties are essentially determined by its chemical composition, therefore, several modification processes target specific changes of constitutive woody polymers at the molecular level. Nevertheless, some modification processes do not change the chemical composition of wood itself, but focus on the morphological or physical modification (Hill 2006). New developments in the field of wood modification offer assortment of innovative products with highly enhanced properties of natural timber. These include innovative bio-based composite materials, as well as more effective and environmental-

friendly protective treatments, e.g. thermal treatment, densification, impregnation and chemical modifications. Similar revolutionary progress is observed with surface treatments including advanced coatings, or integration of nanotechnology developments in wood protection. Today's bio-based building materials, even if well characterized from the technical point of view, are often lacking of reliable models describing their performance during service life. This paper presents summary of the scientific results obtained within framework of BIO4ever project "Bio-materials for building envelope – expected performance, life cycle costing and controlled degradation".

## EXPERIMENTAL

### *Experimental samples*

Performance of 120 selected façade materials provided by over 30 industrial and academic partners from 17 countries was evaluated in several experimental configurations. The samples were classified in seven categories, according to the treatment applied: natural wood (or other bio-based material), composites, chemically modified, thermally modified, impregnated, coated and/or surface treatment and hybrid modified. The latest include combination of at least two different treatments (Table 1).

*Table 1: Categories of bio-based facades materials tested within BIO4ever project*

Modification process	Examples	Number of materials
natural	wood, bamboo	19
chemical	acetylation, furfurylation	5
composites	panels, bio-ceramics, tricoya, wood plastic composites	7
coating & surface treatments	different coatings, carbonized wood, nanocoatings	16
impregnation	DMDHEU, Knittex, Madurit, Fixapret	28
thermal modification	vacuum, saturated steam, oil heat treatment	20
hybrid modification	thermal treatment + coating, thermal treatment + impregnation, acetylation + coating etc.	25

An example of six radiata pine (*Pinus radiata* D.Don) samples representing different commercially available modification processes was selected for the demonstration. Weathering performance of these materials was compared with the not treated wood of scots pine (*Pinus sylvestris* L.), being usually considered as a reference material (Table 2).

*Table 2: Description of experimental samples*

Sample number	Wood species	Bulk treatment	Surface treatment	Product on the market
09	Radiata pine	thermal treatment + penetrating oil	-	yes
10	Radiata pine	thermal + silicate treatment	-	yes
30	Radiata pine	thermal treatment #1	coating	yes
31	Radiata pine	furfurylation	-	yes
34	Scots pine	-	-	yes
45	Radiata pine	thermal treatment#2	-	yes
51	Radiata pine	acetylation	-	yes

Selected modification processes included: acetylation, furfurylation, thermal treatment with various technologies and thermal treatment combined with impregnation and surface coating. Investigated treatments were classified as chemical, thermal and hybrid modification according

to the categories presented in Table 1. All investigated modified materials are commercially available on the market.

### ***Weathering tests***

Natural weathering tests were performed in San Michele, Italy, (46°11'15''N, 11°08'00''E), in order to provide reference data for simulation of the bio-materials' performance in a function of the exposure time. Samples were exposed on the vertical stands representing building façade. Stands were oriented to 4 cardinal directions. The weathering experiment was carried out for 12 months and the test is still ongoing. Presented results refer to the southern exposure of samples, with the experiment start in March 2017.

### ***Materials characterization***

High resolution photos (Nikon D5500 equipped with lenses Nikor AF-S 35mm) were regularly acquired in a monthly bases to capture the progress of the samples' appearance change. Additionally, part of exposed samples (three replicas per cycle) was exchanged every 3 months and stored in a climatic chamber before characterization. Materials characterization included scanning with office scanner, as well as measurement of the colour (CIE L\*, a\*, b\*), gloss, roughness (in two cardinal fibre directions), and spectroscopy in VIS, NIR and IR ranges with laboratory and portable spectrometers. The NIR bands were assigned according to Schwanninger *et al.* (2011a).

***Table 2: Description of experimental samples***

<b>band number</b>	<b>Wavenumber (cm-1)</b>	<b>Wood component</b>	<b>Functional group</b>
1	4198	holocellulose	CH
2	4280	cellulose	CH, CH <sub>2</sub>
3	4339	holocellulose	CH
4	4404	cellulose, hemicellulose	CH, CH <sub>2</sub> , OH, CO
5	4620	cellulose, hemicellulose	OH, CH
6	4686	acetyl groups in hemicellulose	CH <sub>3</sub> , C=C, C=O
7	4890	cellulose semi-crystalline and crystalline	OH, CH
8	5219	water	OH
9	5464	cellulose semi-crystalline and crystalline	C=O
10	5587	cellulose semi-crystalline and crystalline	CH
11	5658	unassigned	CH <sub>2</sub>
12	5800	hemicellulose (furanose/pyranose)	CH
13	5883	hemicellulose	CH
14	5951	hemicellulose	CH <sub>3</sub>
15	5980	lignin	CH
16	6009	hemicellulose	CH
17	6121	cellulose	OH
18	6287	cellulose crystalline	OH
19	6450	cellulose crystalline	OH
20	6722	cellulose semi-crystalline	OH
21	6785	cellulose	OH
22	7008	amorphous cellulose/water	OH
23	7300	hemicellulose	CH <sub>3</sub>
24	7418	hemicellulose	CH <sub>3</sub>

## RESULTS AND DISCUSSION

### *Materials appearance*

The intensity of weathering depends on timber species, architectural design solutions, function of product, finishing technology applied for wood protection, and on the specific local conditions. All experimental samples were prepared from radiate pine and exposed in same climatic conditions for identical period. Therefore, it can be stated that the difference in performance are modification process dependent. The appearance of investigated materials in the function of time is presented in Figure 1. It can be seen that some of the materials are relatively stable regarding colour and pattern changes. The material #10 become lighter after 3 months exposure period. However, according to the technical sheet provided by producers it was desired to “silver off” the surface due to weathering and then maintain that appearance unchanged during service life. Materials #31, #34, #45 and #51 contain noticeable mould discoloration on their surfaces. The visual assets in materials outlook were confronted with changes in colour coordinates. The lightness (*CIE L*) parameter was constant in materials with relatively stable colour (e.g. #09, #30). Even if the weathering test was performed for 12 months, none of investigated materials became grey, corresponding to the usual colour of wood long-term exposed to natural weathering. However, an increase of gloss parameters (especially across the fibres) was observed with the progress of the weathering process.



*Figure 1: Change of samples appearance due to natural weathering in San Michele all'Adige (Italy)*


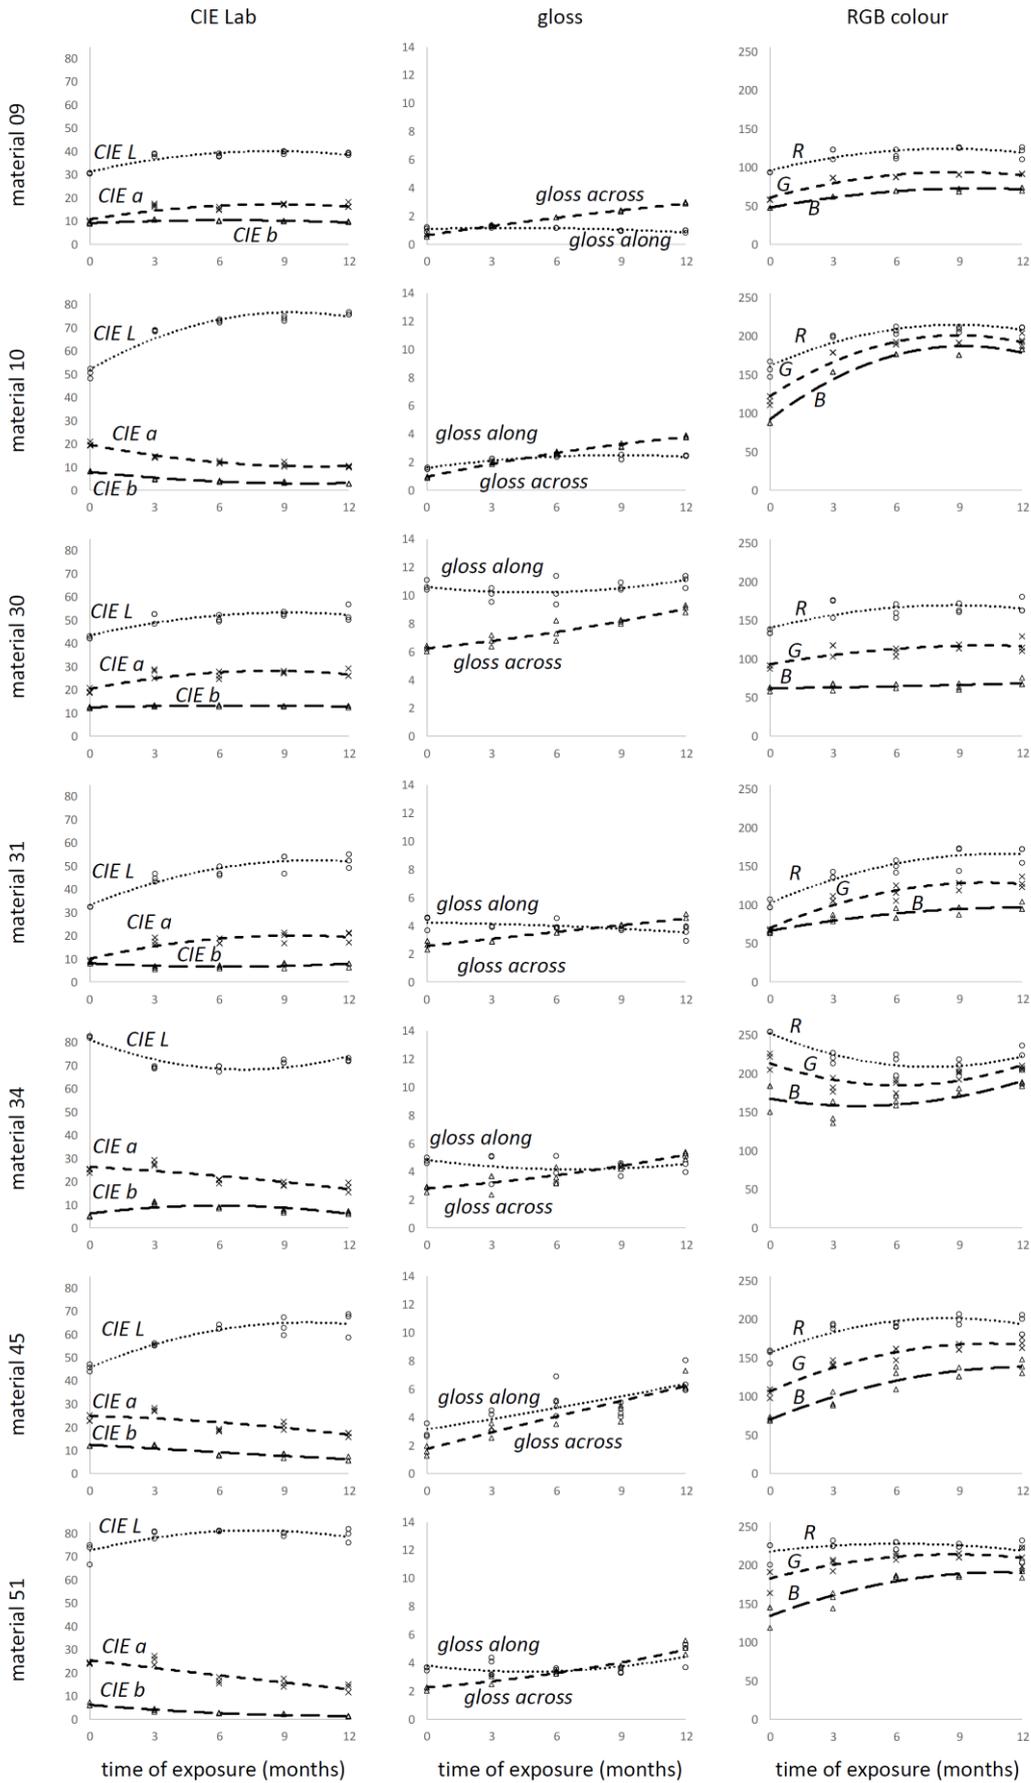


Figure 2: Change of CIE Lab, gloss and RGB parameters due to natural weathering

### Chemical changes


NIR spectroscopy was used for non-destructive investigation of chemical composition of samples at different stages of their exposure. However, investigated materials being modified with several modification methods exhibit noticeable differences in their chemical composition already at the initial stage before any weathering. Consequently, differences in appearance of samples and their performance during service life are associated with their chemical composition. Figure 3 present the second derivative of NIR spectra, where functional groups related to key wood components as well as specific futures being results of wood modification are evidenced. The spectra of chemically modified wood (e.g. furfurylated or acetylated) are clearly varying from the other treatments. The highly branched and cross-linked furan polymers are chemically bonded with the wood chemical components as a result of furfurylation (Lande *et al.* 2008). Investigated furfurylated wood (pink spectrum, material #31) possessed spare peak at  $6121\text{cm}^{-1}$  (17) not detected in other materials. Acetylation of wood results in a decrease of the number of hydroxyl groups as well as in the increase of the acetyl groups (Schwanninger *et al.* 2011b). In case of acetylated wood (material #51, black line on the Figure 3) shift of several peaks (e.g. 4, 8 or 12) toward higher wavenumbers occurred. Additional peaks 14, 16, 23 and 24, being assigned to  $\text{CH}_3$  groups in acetyl ester groups in hemiceluloses, are clearly visible. Likewise, hydroxyl groups detected in the range  $6000\text{-}7000\text{ cm}^{-1}$  are not evident due to reduction of their number caused by acetylation. Other processes (such as thermal modifications) affected the hemicellulose content, evidenced as a slight reducing of CH functional groups (spectral bands 12 and 13).

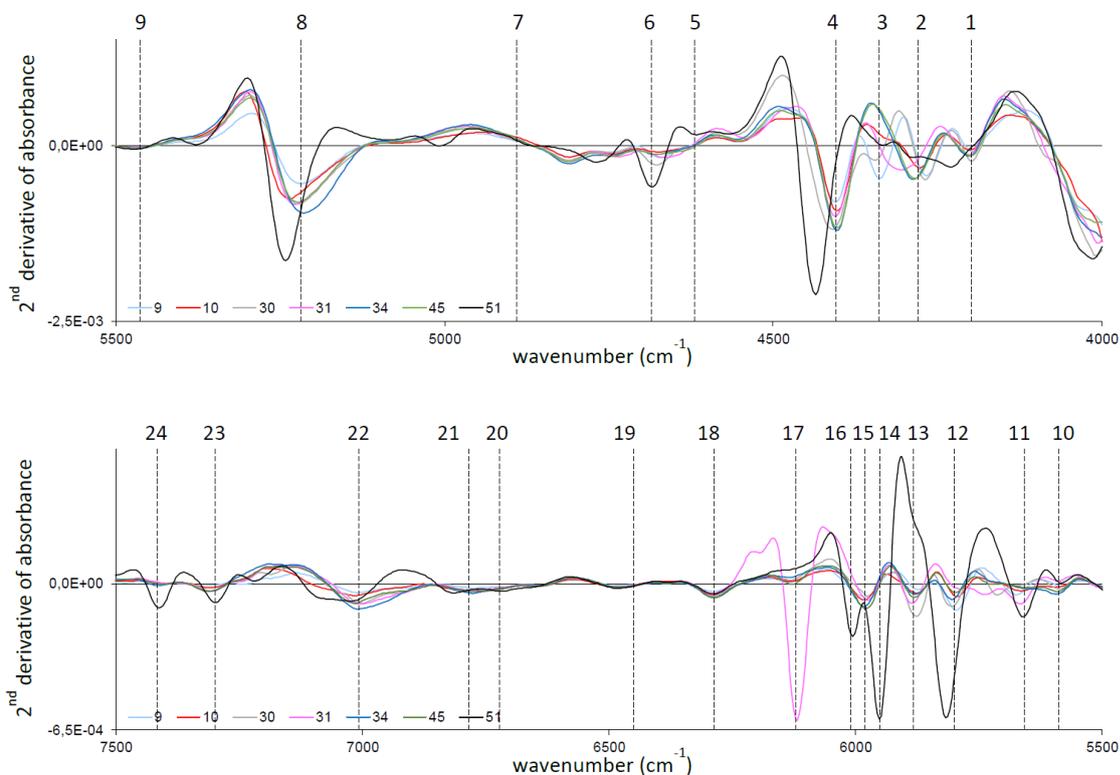

**Figure 3: Second derivative of NIR absorbance spectra of investigated materials at their brand new stage**

It is expected that natural weathering might affect the chemical composition of materials modified in different processes to various extends. It is due to materials' heterogeneity and variances in their response to the weathering mechanisms. Figure 4 presents a summary of such differences as recorded in the second derivative NIR spectra. In this case, subtraction of

reference spectrum from the spectrum of 12 months exposed wood highlights the spectral differences. It is evident that mechanisms of degradation are different for materials after various treatments. Bands 4 and 8 assigned to carbohydrates and water respectively changed in all investigated materials. Even though, the shift of both peaks toward higher wavenumbers is noticed in material #51 (acetylated wood). The presence of positive peak 4 indicates degradation of the functional groups in cellulose and hemicellulose. The reference sample (material #34, pine wood) exhibits the highest changes (positive peaks) for bands: 1, 2, 4 and 8, what indicates decreasing of the functional groups quantity. The distinctive peak 17 observed in furfurylated wood is positive, (as well as bands 1, 3 and 4) what corresponds to the degradation of this component due to weathering. It is important to notice, that functional groups assigned to crystalline and semi-crystalline cellulose (bands: 7, 9, 10, 18, 19 and 20) did not degraded due to weathering in all investigated materials. Cellulose, being more resistant to weathering, became more abundant on the weathered wood surface. According to Kalnins and Feist (1993), the weathering leads to increases of hydroxyl concentration on the wood surface. It is confirmed by slight increase of band 22, assigned to the OH groups in amorphous cellulose. On the contrary, band 15 assigned to functional group of lignin was degraded for all investigated materials, but with different extends. Analysis of the specific degradation kinetics for particular functional groups of wood constituents allow deep understanding of the weathering mechanisms. It highlights weak points of investigated materials that might be further improved by optimizing modification processes.

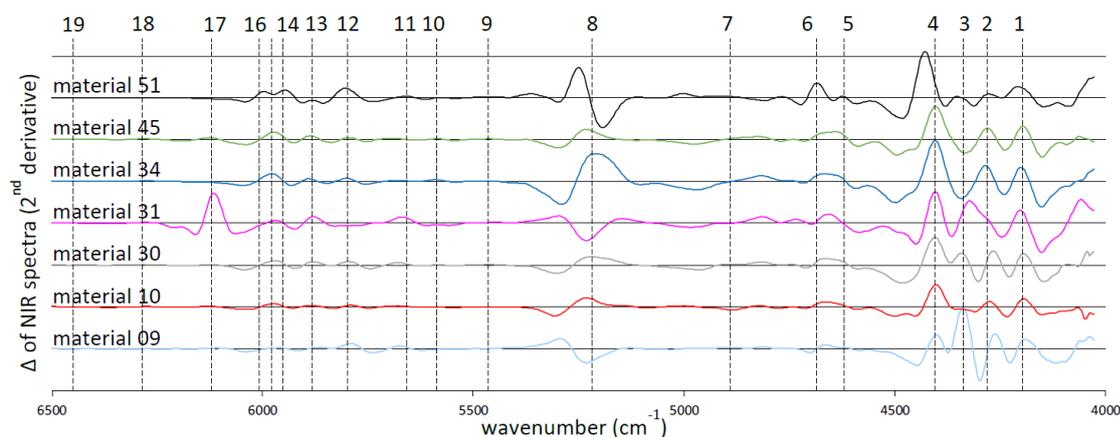

*Figure 4: Change in NIR spectra due to 12 months of natural weathering*

## CONCLUSIONS

The main BIO4ever project output, beside of extensive data base of bio-based materials performance is an interactive software simulating the aesthetic performance of bio-materials integrated with LCA interactive calculation for maintenance operations. At this stage of the software development, all the available data regarding appearance change of each biomaterial in time (CIE Lab, RGB, gloss), weather dose map and specific building layout (UV surface map) are merged together allowing 3D model visualization (Sandak *et al.* 2018a). Time series of pictures that were acquired during exposure of tested materials, presented in Figure 1, are used for the interactive simulation of façades appearance. Software users will be able to choose a material from the database, select the building location and then simulate the structure look at the brand new stage and during its service life (Sandak *et al.* 2018b). The tool, dedicated for investors, architects, construction engineers, professional builders, suppliers and other relevant

parties, including also final customers is now under extensive validation and integration with the BIM software.

### ACKNOWLEDGEMENTS

The BIO4ever (RBSI14Y7Y4) is a project funded within a call SIR (Scientific Independence of young Researchers) by MIUR.

The authors gratefully acknowledge the European Commission for funding the InnoRenew CoE project (Grant Agreement #739574) under the Horizon2020 Widespread-Teaming program. Special acknowledgments to COST FP1303, FP1407 and TU1403 for funding STSMs that contributed to the project and all BIO4ever partners.

### REFERENCES

Hill, C. (2006). Wood modification chemical, thermal and other processes. John Wiley and Sons, Chichester.

Kalnins, M. A., Feist, W. C. (1993) Increase in wettability of wood with weathering. *Forest Product Journal*, **43**(2), 55-57.

Schwanninger, M., Rodrigues, J. and Fackler, K. (2011a). A review of band assignment in near infrared spectra of wood and wood components. *J. Near Infrared Spectroscopy*, **19**(5), 287-308.

Schwanninger, M., Stefke, B. and Hinterstoisser, B. (2011b). Qualitative assessment of acetylated wood with infrared spectroscopic methods. *Journal of Near Infrared Spectroscopy* **19**(5), 349-357.

Lande, S., Westin, M. and Schneider, M. (2008) Development of Modified Wood Products Based on Furan Chemistry, *Molecular Crystals and Liquid Crystals*, **484**, 367-378.

Sandak, J., Sandak, A. Grossi, P. and Petrillo, M. (2018). Simulation and visualization of aesthetic performance of bio-based building skin. *Proceedings IRG Annual Meeting* (ISSN 2000-8953), IRG/WP 18-20633

Sandak, A., Sandak, J. Grossi, P. and Petrillo, M. (2018). A simulation and modelling tool for the evaluation of the façade performance – BIO4ever project approach. FAÇADE 2018, Final conference of COST TU1403 “Adaptive Facades Network”, Lucerne, Switzerland.



zekerheid met meerwaarde



ModWoodLife

ISBN: 978-90-829466-1-1