

Catalytic (de)hydrogenation promoted by non-precious metals - Co, Fe and Mn: recent advances in an emerging field

Received 00th January 20xx,
Accepted 00th January 20xx

Georgy A. Filonenko,^{a,b,*} Robbert van Putten^{a,b}, Emiel J. M. Hensen^a and Evgeny A. Pidko^{b,c,*}

Catalytic hydrogenation and dehydrogenation reactions form the core of modern chemical industry. This vast class of reactions is found in any part of chemical synthesis starting from the milligram-scale exploratory organic chemistry to the multi-ton base chemicals production. Noble metal catalysis has long been the key driving force in enabling these transformations with carbonyl substrates and their nitrogen-containing counterparts. This review is aimed at introducing the reader to the remarkable progress made in the last three years in the development of base metal catalysts for hydrogenations and dehydrogenative transformations.

1. Introduction

Interconversions of organic substrates involving hydrogen transfer constitute a broad class of industrially-relevant chemical reactions. Either in molecular form or in the form of protons and hydrides, hydrogen is added, abstracted or shuffled between organic compounds in reactions that are almost universally catalytic. Efficient catalysis can promote both addition of hydrogen in a reductive process, and hydrogen abstraction in the oxidative one. Moreover, multistep reaction involving oxidative, reductive and bond-forming events are also possible given the right catalyst and conditions are ensured. As a result, a vast number of interconnected reactions are accessible via (de)hydrogenative catalysis (Scheme 1.1). Obtaining control over these reactions would grant chemists the access to a wide variety of useful synthons and building blocks. In this setting, homogeneous catalysis becomes a powerful tool that allows to obtain desired product via multiple catalytic pathways.

In this Review we present a critical analysis of the recent advances in catalytic (de)hydrogenation with 3d transition metal complexes enabling efficient transformations of amines, alcohols and their oxidized counterparts bearing imine, carbonyl or carboxyl functions (Scheme 1.1). As reactions on Scheme 1.1 can be split into several categories depending on their nature, we will structure our Review accordingly.

The first group of reactions are reductive transformations of carbonyl compounds, carboxylic acids and their derivatives. Important products such as alcohols and amines are produced through these transformations. Importantly, the reactivity of

the carbonyl moiety in the reaction substrates varies greatly depending on the nature of the substrate and, related, the electrophilicity of the carbon in the C=O unit: whereas aldehydes are relatively easy to reduce, the carboxylic acid derivatives present a greater challenge for the reduction due to their significantly lower electrophilicity.¹ The common lab-scale synthetic approaches for the reduction of polar oxygenates and their nitrogen-containing counterparts often rely on the use of stoichiometric highly reactive reagents. One of the early protocols for the reduction of esters and carboxylic acids involved the use of metallic sodium in ethanol, known as Bouveault-Blanc-reduction.^{2,3} This method was later abandoned in favour of milder and more versatile metal-hydride reagents such as LiAlH₄ and NaBH₄.⁴ Despite the high efficiency of the respective synthetic protocols, their main drawback is the stoichiometric nature and, as a result, the production of large amounts of inorganic by-products. Furthermore, the high reactivity of inorganic hydrides may present potential safety hazards limiting their larger-scale applicability.⁵

Alternative to stoichiometric methods are catalytic processes that utilize molecular hydrogen as a reducing agent. Indeed, H₂ reductant is atom efficient and cheap and so far a large number of noble metal catalysts for hydrogenation have been developed.^{6,7,8} Because they rely on the use of molecular hydrogen or a less reactive hydrogen source,⁹ catalytic hydrogenations pave the way for sustainable processes with high degree of control over reaction rates and selectivities. Sections 3.1 and 3.2 of this Review will cover these reductive transformations.


^a Inorganic Materials Chemistry Group, Schuit Institute of Catalysis, Eindhoven University of Technology, P.O. Box 513, 5600 MB Eindhoven, The Netherlands;

^b Department of Chemical Engineering, Delft University of Technology, Van der Maasweg 9, 2629 HZ Delft, the Netherlands

^c ITMO University, Lomonosova 9, St. Petersburg, 191002, Russia

* Corresponding authors: g.a.filonenko@tudelft.nl (G.A.F.); e.a.pidko@tudelft.nl (E.A.P.)

Electronic Supplementary Information (ESI) available: extracts of full substrate scopes and reaction conditions for section 3. See DOI: 10.1039/x0xx00000x

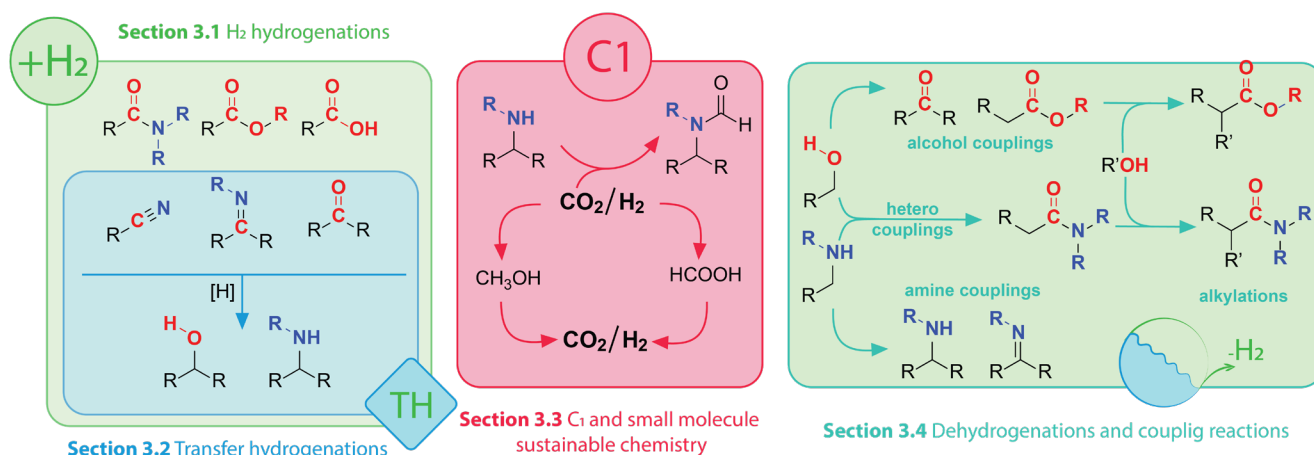

Scheme 1.1. Visual guide to corresponding sub-sections of this Review and schematic layout of selected transformations of polar organic compounds.

Reverse process to the hydrogenation is the oxidative conversion of organic molecules with the release of H_2 commonly referred to as the acceptorless dehydrogenation. In view of the microscopic reversibility principle, both type of processes can potentially be carried out with the same catalysts. Apart from the trivial dehydrogenative transformations, e.g. synthesis of ketones from alcohols, catalytic dehydrogenation is notable for two important applications. The first one includes dehydrogenative coupling reactions (Scheme 1.1)¹⁰ where reaction between several molecules yields a coupling product through a sequence of dehydrogenation and bond-forming reaction. Examples discussed in this review will among others include synthesis of esters from alcohols, or imines and amines via amine/alcohol couplings. As the products of dehydrogenative transformations can be as useful as their fully reduced counterparts we include extensive discussion on the dehydrogenation catalysis in Section 3.4 of this Review.

When acceptorless dehydrogenation is performed on small molecule substrates such as methanol and formic acid,¹¹ the released H_2 is considered to be the target product of the transformation. These substrates are, therefore, acting as hydrogen carriers that produce pure H_2 with carbon dioxide being the only by-product of the dehydrogenation. Such gas feed, provided it is free of catalytic poisons like CO, can be directly utilized for fuel cell applications.^{12, 13} Such processes together with the chemical pathways to regenerate formic acid and methanol substrates from CO_2 have a great potential for energy applications and will be described in Section 3.3 of this Review.


With very few exceptions, Ru-based complexes are currently among the most active homogeneous (de)hydrogenation catalysts.^{8, 14} Many of them allow stable operation at metal loadings below 100 ppm in various reductive and oxidative transformations.¹⁵⁻¹⁷ Nevertheless, the utilization of such

catalysts has several important limitations related to the high price and low abundance of ruthenium and, more importantly, the toxicity of noble metals for the living organisms. The latter represents a particularly important issue when catalytic transformations are being developed for the production of pharmaceuticals. The removal of the toxic metal residues from the final product to acceptable level¹⁸ can drastically increase purification costs. In recognition of these challenges, the focus of the catalytic community had been gradually shifting in the last decade to the development of new catalyst systems based on the first row transition metals, which are both abundant and less- or non-toxic contrasting the conventional noble metal active components.¹⁹


This review will describe the rapid development of the Fe, Co and Mn-based catalysts that occurred within the last few years and gave rise to a new class of noble metal-free (de)hydrogenation protocols. As we aim at encompassing several fields where the progress has been reviewed in the past, we will guide the reader to specialized review works in the introduction to corresponding sections. This review is structured as follows: in Section 2 we will briefly introduce common synthetic and reactivity concepts for the key catalyst motives discussed throughout the review. Section 3 presents an overview of the catalytic properties and substrate scopes of Fe, Co and Mn-based homogeneous catalysts. This section is organized into subsections addressing individual reaction types that for the reader comfort will follow the nomenclature and classification introduced in Scheme 1.1. Each subsection will be concluded with the summary of common reaction conditions, while the substrate scopes *in full* can be found in the Supporting Information for this Review. The overview of the catalytic data is followed by Section 4, where we discuss and critically assess the different mechanistic proposals, which have been put forward to rationalize the observed reactivity trends. The review is concluded with Section 5 where we highlight current

challenges and prospects of catalytic (de)hydrogenation chemistry with non-noble metal homogeneous catalysts.

2. Ligand design, complexation and reactivity features

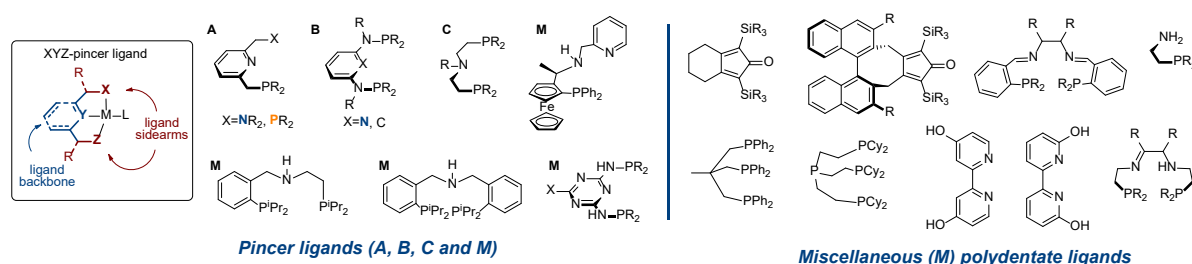

Scheme 2.1. Structural overview of the pincer ligand and ligands employed for non-noble metal promoted (de)hydrogenation discussed in this Review

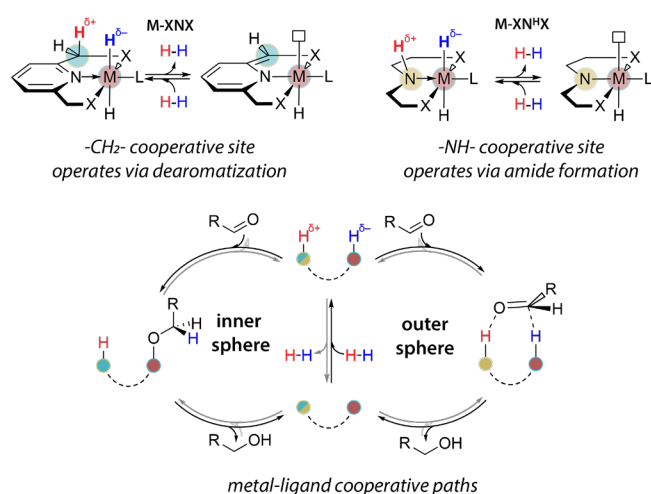

Scheme 2.2. An example of MLC activation of dihydrogen and cooperative (de)hydrogenation steps

2.1. Ligands and metal-ligand cooperation

Ligand systems utilized for the first row transition metal catalyst often resemble or fully mimic those successfully employed for the Ru-based catalysis. Among the various available ligand platforms, pincer ligands hold the upmost prominence and are featured in a vast majority of active catalysts regardless of the metal used. The application of pincer ligands in catalysis^{20–22} and their role in bond activation^{14, 23} have been the subject of several excellent reviews published in the last decade. Defined as tridentate ligands,²⁴ pincers are typically comprised of the backbone and two sidearms. Lutidine-derived pincer ligands put forward by Milstein and co-workers (Scheme 2.1, **A**) were historically among the first pincers used for catalysis by early transition metals.

The replacement of the methylene arms in **A** for the amine linker gives rise to a well-established diaminopyridine-based ligand family **B**,²⁵ while the replacement of the aromatic backbone with the aliphatic one yields ligands family **C**, which in this review will be referred to as the aminopincers. The variations of these three main ligand motifs dominate the current state of the art in the base metal catalysed (de)hydrogenation chemistry. Nevertheless, other remarkable

ligand systems will be given an extensive mention (**M**, for miscellaneous in Scheme 2.1).

The prevalence of pincer ligands is often explained by the combination of the high metal binding strength, expected for a tridentate ligands, and their ability to form a bifunctional reactive ensemble capable of promoting chemical transformations in cooperation with the metal centre upon complexation. This property is inaccessible for the more conventional ligand platforms²⁶ as it yields catalysts with two distinct metal- and ligand-centred functional groups that are both necessary for the catalyst to operate. Such catalysts are typically referred to as bifunctional. Setting aside the debates on the degree of involvement of the cooperative ligands in catalysis,^{27, 28} we will discuss the basic principles behind bifunctional catalysis phenomenon in view of the fact that the vast majority of catalyst systems discussed in this review are at least potentially bifunctional.

The acid-base bifunctionality in pincer complexes is enabled by the presence of the cooperative site in the ligand backbone or sidearm (Scheme 2.2). For the lutidine-based **A**-metal complexes, such reactive site is provided by the pyridylmethylene fragment, *Ar-CH₂-*, that can be deprotonated by a strong base resulting in the dearomatization of the ligand and the formation of a coordinatively unsaturated complex. Similarly, **C**-metal pincers produce five-coordinate species upon deprotonation of the central NH fragment that is transformed into a metal-bound amide. For both **A** and **C** ligand platforms, the reaction with a strong base yields a reactive system containing a highly basic site on the ligand vicinal to the coordinatively unsaturated metal centre exhibiting an elevated Lewis acidity. The formation of such an acid-base pair is often invoked in the mechanistic proposals for the substrate activation over bifunctional catalysts (Scheme 2.2).

To summarize, a vast majority of ligands employed for base-metal catalysis described in this review are tridentate pincer ligands. These pincers are almost exclusively nitrogen-centred and contain strongly donating phosphine ligands as sidearms. The selection of pincer ligands is mainly motivated by their ability to engage in metal-ligand cooperative behaviour (see Scheme 2.2) that is known to facilitate substrate activation in both late and early transition metal complexes. The latter is also

one of the major reasons for the use of the less common bidentate and tetradentate ligands (Scheme 2.1) that can engage in MLC behaviour as well.

2.2. From complexation to reactivity

The coordination chemistry of 3rd row transition metals can be strikingly different from that of their heavier 4d and 5d counterparts. Unlike the preparation of noble metal complexes, that is typically straightforward, complexation of Fe, Co and Mn may require different approach for different metal and face several limitations that we will briefly describe in this section for **A**, **B** and **C** family of pincers. Similar to the noble metal counterparts, base metal catalysts for hydrogenation are often activated by introducing the hydride ligands, therefore this reactivity will be briefly described. The reader is also referred to a series of recent reviews on metal hydride chemistry for further insight.²⁹⁻³¹

All the Fe complexes described in this review are Fe(II) species. Complexation of iron to lutidine-based ligands **A** was described in detail by the group of Milstein.^{32, 33} The authors employed a reaction of the PNP pincer with iron bromide followed by the treatment with CO (Scheme 2.3). Depending on the substitution pattern on the phosphine donors the resulting iron carbonyl dibromides can be transformed into corresponding hydrides via two pathways. A mono hydride (**A-Fe-1**, Scheme 2.3) complex was prepared with ⁱPr substituted PNP ligand by treatment with NaHBET₃ and dihydride species (**A-Fe-2**, Scheme 2.3) were prepared from ^tBu substituted PNP precursor by treatment with NaBH₄.

Similarly, ligands **B** featuring amine linkers also complex readily with FeBr₂ in the presence of CO. A one pot complexation with FeBr₂ followed by NaHBET₃ treatment yields bromohydridocarbonyl species **B-Fe-1**. Further reaction of **B-Fe-1** with sodium borohydride results in elimination of the remaining bromide ligand to produce a BH₄-bound complex.³⁴


In the absence of CO, the complexation with FeBr₂ can be used to generate five-coordinate Fe-PNP dibromide complex,³⁵ which can be further converted to a stable polyhydride complex **B-Fe-H₄**.³⁶ The complexation of aminopincer ligands **C** with iron is typically carried out following reaction pathways analogous to those employed for ligands **A** and **B**.³⁷

Most of the Co catalysts falling in the scope of this Review are prepared in a straightforward reaction via the direct coordination of the CoCl₂, with an appropriate ligand. The reaction typically yields dichloro cobalt (II) species used as a precatalyst; however other oxidation states of Co (+1 and +3) are also encountered across the field. One of the first Co catalysts disclosed by Hanson and co-workers³⁸ is prepared from **C**-type aminopincer ligand and a rather unusual (Py)₂Co(CH₂SiMe₃)₂ precursor (Scheme 2.4).³⁹ The resulting amide complex could be readily protonated with Brookhart's acid⁴⁰ to form the amine-centred Co(II) complex.


The **C** aminopincers also form complexes with Co(I) centres. A typical example of such complexes was described by Bernskoetter and co-workers⁴¹ who studied the formation of Co(I) pincers and isolation of Co(I) hydride complexes. The reaction of methylated **C** ligand with Co(PPh₃)₃Cl precursor

(Scheme 2.4) led to the formation of a tetragonal **C**-Co chloride complex, which converts to a five-coordinate dicarbonyl **C**-Co species with a meridionally bound ligand in the presence of CO. The subsequent treatment with sodium trialkylborohydrides produces the Co(I) hydride complex.

Manganese, similarly to Co is prone to forming complexes in several oxidation states. As we will discuss in the following Sections, the +1 oxidation state of Mn appears to be a strict requirement for the catalytic activity that inflicts considerable synthetic limitations. The preparation of Mn(I) complexes for hydrogenation faces a major and rather unexpected pitfall that is related to the lack of appropriate Mn(I) precursors. More importantly, Mn(II) coordination compounds that are generally prepared with ease from the corresponding halide salts MnX₂ cannot be used to produce Mn(I) species, that restricts the researchers to a very limited selection of Mn(0/I) carbonyl precursors among which Mn₂(CO)₁₀ and Mn(CO)₅Br are the most commonly used. As a result, the carbonyl ligands stabilising the Mn(I) centres are often retained upon the complexation with the pincer ligand. As the replacement of carbonyl ligands is usually difficult, their presence limits potential diversity of the reactions available for the manganese complexes. Nevertheless, Mn hydrides can be prepared from the corresponding L-Mn carbonyl bromides or amide complexes as was demonstrated, for example, by Gauvin and co-workers (Scheme 2.4).⁴²

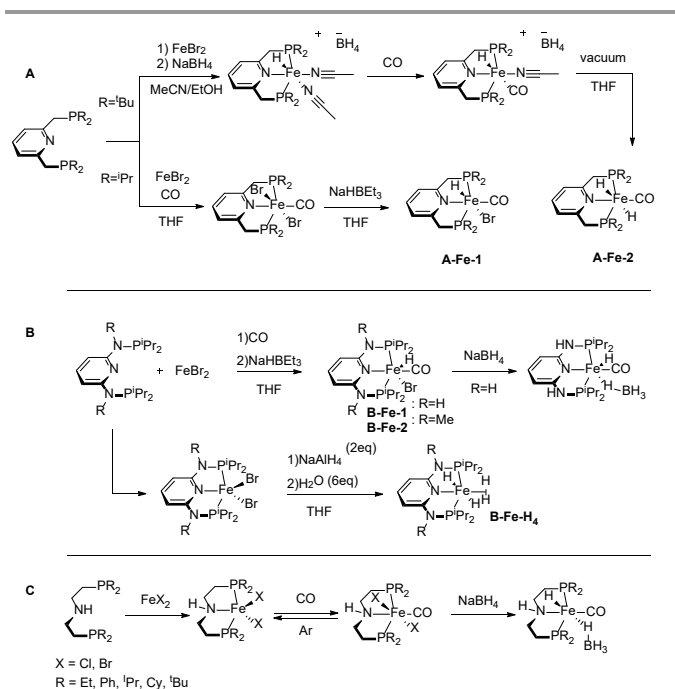

Scheme 2.3. Generation of Iron hydride complexes stabilised with pincer ligands **A**, **B** & **C**.

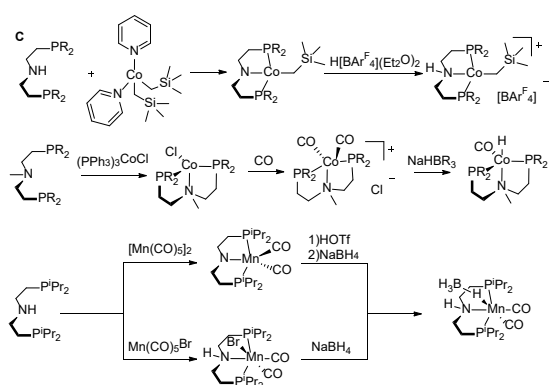

Scheme 2.4. Notable examples of Co and Mn complexes preparation and reactivity.

3. Catalysis: activity, reaction and substrate scopes

Similar to their noble counterparts, base metal complexes catalyse a range of (de)hydrogenative transformations that were classified earlier on Scheme 1.1. In this section we will discuss them starting from reduction with molecular hydrogen (Section 3.1). We will further cover catalytic reduction with other hydrogen donors (Transfer hydrogenation, Section 3.2) and proceed to a more convoluted chemistry.

We will first discuss hydrogenation and dehydrogenation chemistry of simple C1 molecules, most notably CO₂, formic acid and methanol that is related to hydrogen storage and production (Section 3.3). The last Section 3.4 will deal with dehydrogenations and dehydrogenative coupling reactions that can be used in synthesis applications for the production of complex organic molecules.

For readers' comfort, the catalytic results are introduced separately for particular ligand/catalyst classes. Within particular class of catalysts the description is started with more facile transformations and concluded with the challenging ones. Schemes in Section 3 summarize the data described in every sub-section to provide the complete yet condensed overview of recent achievements in the field.

3.1. Reduction with molecular hydrogen

3.1.1. Iron

The application of iron complexes in homogeneous reduction catalysis is the most established among other early transition metals. The reactivity of Fe catalysts in reductive transformations⁴³⁻⁴⁷ and general organic synthesis^{48, 49} have been described in recent comprehensive reviews. In this review we will limit the description of the Fe catalysis to the seminal examples, recent discoveries and related mechanistic concepts. One of the first well-defined Fe catalysts for ketone hydrogenation was reported by Morris and co-workers, who described a large family of Fe complexes based on tetradentate iminophosphine ligands. A representative example of this catalyst family is the **M-Fe-0** complex bearing a tetradentate PNNP ligand (Scheme 3.1) that allowed an efficient reduction of acetophenone to phenylmethanol under very mild conditions, namely in the presence of less than 0.45 %_{mol} Fe at 50°C and


25 bar H₂.⁵⁰ Interestingly, previously described Fe complexes with a cyclohexyl linker connecting the N-donors in the PNNP ligand⁵¹ were much less active for the reduction with molecular H₂, but showed a substantial activity in the transfer hydrogenation reaction, which will be the subject of the next section.

A major advance in catalytic ketone hydrogenation with Fe complexes was made by the group of Milstein who developed an **A-Fe-1** iron PNP pincer catalyst. For this catalyst, a performance comparable to that of the **M-Fe-0** could already be reached when operating at a catalyst loading of only 0.05 %_{mol} at room temperature and a very low H₂ pressure of 4.1 atm.³³ The substrate scope of **A-Fe-1** included substituted acetophenones, conjugated diketones and substrates containing C=C double bonds. While the majority of the substrates were converted in good yields, the presence of amino- and nitrile- functional groups diminished strongly the activity. The **A-Fe-1** catalyst showed only a moderate chemoselectivity in the hydrogenation of unsaturated ketones by retaining at best 20% of the C=C double bonds present in the substrate at full conversion. Finally, authors reported significantly lower activity of **A-Fe-1** in hydrogenation of benzaldehyde, providing 36% yields with an elevated catalyst loading of 0.125%.

Interestingly, the aldehyde hydrogenation with **A-Fe-1** catalyst was later improved. The modest activity of **A-Fe-1** in the hydrogenation of benzaldehyde could be promoted in the presence of trimethylamine or acetophenone. It was proposed that the transient formation of carboxylic acid (presumably via the KO^tBu-mediated Cannizzaro reaction) could deactivate the catalyst, while NEt₃ and acetophenone were preventing the acid formation.⁵²

The dihydrido-Fe complex **A-Fe-2** from the same catalyst family also shows a pronounced activity in the hydrogenation of activated esters under mild conditions (40°C, 5-25 bar H₂ pressure). A range of trifluoroacetates was converted in good yields at ca. 0.5-1%_{mol} **A-Fe-2** catalyst loading in the presence of NaOMe base.⁵³ Subsequent work by the same group have demonstrated that activated amides can also be converted using related **A-Fe-1** catalysts in the presence of KHMDs base promoter.⁵⁴

Bifunctional iron complexes with ligand motif **B**⁵⁵ have also been successfully applied in the hydrogenation catalysis. Catalysts **B-Fe-1** reported by Kirchner and co-workers³⁴ in 2014 showed very good activity in the reduction of ketones and aldehydes at loadings of 0.5%_{mol} at 5 bar H₂ pressure. Remarkably, near quantitative yields of alcohols were achieved in ethanol solvent at room temperature. Building upon these results authors have conducted a scrupulous mechanistic study that allowed them to improve the performance of **B-Fe-1a** by a large margin and establish a chemoselective reduction of aldehydes in the presence of ketones, esters, epoxides, alkynes and nitro aromatic compounds.⁵⁶ In particular, guided by the insights provided by the mechanistic studies, the authors optimized the hydrogenation of 4-fluorobenzaldehyde at 30-60 bar H₂ to reach TOFs up to 20000 h⁻¹ and

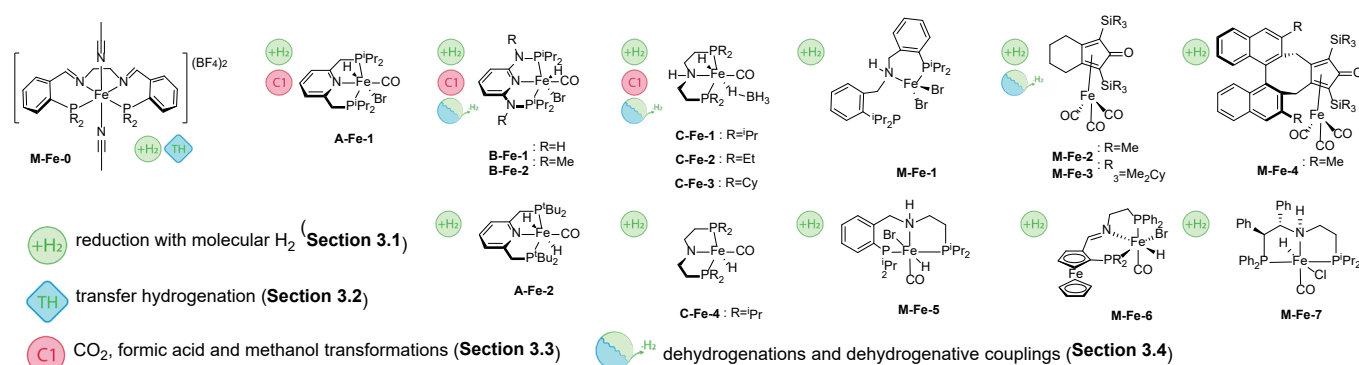

Scheme 3.1 Structures of Fe catalysts introduced in section 3.1.1. Types of transformations described for each particular catalyst are indicated with the sub-section label.

ultimately obtain outstanding TONs of up to 80000. A variety of other aromatic and aliphatic aldehydes could also be fully converted at 50-100 ppm catalyst loading at 30 bar H₂ and 40°C temperature in the presence of DBU base promoter. These results render the **B-Fe** catalysts among the most active systems reported to date for the selective hydrogenation of aldehydes and rival the performance of noble metal catalysts.⁵⁷

The utility of iron-catalysed hydrogenation was later extended to unactivated esters with the development of the aminopincer Fe catalysts based on the ligand family **C** (Scheme 3.1). Groups of Beller⁵⁸ and Guan⁵⁹ independently reported the use of catalyst **C-Fe-1** for the conversion of various esters to corresponding alcohol at 1-3 %_{mol} catalyst loading under 10-50 bar H₂ pressure and temperature of 100-135°C. It was observed that **C-Fe-1** can be successfully employed under base free conditions and its activity is somewhat hampered when alkoxide bases are introduced as additives. It was also shown that the addition of lithium chloride, methylsulfonic acid or CO completely deactivates the catalyst.⁵⁸ Interestingly, the less bulky complex **C-Fe-2** was later found to show improved performance in ester hydrogenation by Beller and co-workers⁶⁰ who showed that the increased steric bulk was negatively affecting the catalytic activity.

Recent work by Langer and co-workers further expanded the utility of Fe-aminopincer catalyst to selective hydrogenation of amides, which constitute particularly challenging substrates for homogeneous hydrogenation. After a careful evaluation of the ligand substituent effects, the authors identified catalyst **C-Fe-2** bearing less bulky ethyl substituents opposed to other catalysts in the study as a potent amide hydrogenation catalyst operating at 2-10 %_{mol} loadings, 50 bar H₂ pressure and 70-100°C under base-free conditions.³⁷ Subsequently, Sanford and co-workers⁶¹ showed that the activity of an analogous catalyst **C-Fe-3** can be significantly improved by using the K₃PO₄ additive. The combination of **C-Fe-3** and K₃PO₄ allowed to achieve a full conversion of a series of formamides to corresponding amines and alcohols at only 0.33%_{mol} catalyst loading that corresponds to ca. 300 catalytic turnovers (TON) at the full substrate conversion and up to 1000 turnovers at lower catalyst loadings. At the same time Bernskoetter and co-workers disclosed a similar five-coordinate Fe hydride catalyst

C-Fe-4 that was particularly efficient for the hydrogenation of formamides, reaching TONs of up to 4430 at 0.018 %_{mol} catalyst loading at 30 atm H₂ pressure and 100°C for a variety of formamides.⁶²

The utilization of Fe-based homogeneous catalysts in a challenging nitrile hydrogenations including that of bisnitriles has been described by Beller and co-workers. High activity of catalysts **C-Fe-3**⁶³ or **C-Fe-1**⁶⁴ could be achieved in isopropanol solvent at 30 bar H₂ and 70-130°C in the absence of base additives. It was noted that the methylation of the NH group of the pincer ligand renders the catalyst inactive in hydrogenation of nitriles. The **C**-ligated iron aminopinners remain among the most versatile hydrogenation catalyst family up to date with the potential to hydrogenate the vast majority of polar substrates discussed in this review.

An elegant extension of the aminopincer ligand family has been recently described by Milstein and co-workers who implemented bis(2-diisopropylphosphinobenzyl)amine ligand forming a more flexible 6-membered ring chelates with iron centres.⁶⁵ The resulting catalyst **M-Fe-1** features only one phosphine donor of the "PNP" ligand bound to the iron centre. In the presence of 1-5 %_{mol} catalyst, NaHBET₃ additive and KHMDS a wide range of aliphatic and aromatic nitriles could be successfully converted into corresponding amines at 140°C and 60 bar H₂ pressure. Interestingly, another representative of the aminopincer platform, catalyst **M-Fe-5** was able to convert nitriles to symmetric imines. Under the optimised conditions at 30 bar H₂ and 90°C **M-Fe-5** provided excellent selectivity to symmetric imines with retention of the C=N double bond and no overreduction of the target product.⁶⁶

Asymmetric ketone hydrogenation with Fe pincer catalysts have been recently described in several reports. Zirakzadeh and co-workers reported a series of **M-Fe-6** catalysts⁶⁷ operating at 1%_{mol} loading under 20 bar H₂ pressure in isopropanol. Further work by Morris and co-workers⁶⁸ focusing on the use **M-Fe-7** and related catalysts reported a significant improvement in catalytic performance. Authors obtained excellent conversions of substituted acetophenones at 50°C and 10 bar H₂ pressure in the presence of only 0.1 %_{mol} catalyst and 1 %_{mol} KO^tBu promoter. Catalysis was highly stereoselective allowing for ee

up to 96%, an improvement over **M-Fe-6** that showed maximal ee of 81%.

Apart from the complexes with pincer ligands, a potent iron hydrogenation catalyst can utilize cyclopentadienone ligand motif that gives rise to a broad family of efficient carbonyl hydrogenation catalysts.⁶⁹⁻⁷³ One of the early reports by Beller and co-workers⁷⁴ demonstrated the utility of **M-Fe-2** cyclopentadienyl iron tricarbonyl catalyst for the reduction of aromatic, aliphatic and unsaturated aldehydes under water-gas shift reaction conditions. The catalyst operated at 100 °C under 10 bar CO pressure in the presence of water and 1-5%_{mol} loading. Further research by the same group resulted in the development of a direct H₂ reduction of similar aldehyde substrates using **M-Fe-2** and **M-Fe-3** catalysts and their analogues. The careful optimization of the reaction conditions that involved the use of ⁱPrOH/H₂O solvent with a K₂CO₃ additive allowed lowering the catalyst loading to <1% level.⁷⁵


An elegant modification of cyclopentadienone ligand motif with an (R)-BINOL backbone was recently described by Pignataro, Piarulli, Gennari and co-workers. Authors obtained catalyst family **M-Fe-4** capable of asymmetric ketone hydrogenation with ee up to 77%.^{76, 77} The utility of iron cyclopentadienone catalysts was recently expanded to the hydrogenation of activated esters.⁷⁸ Lefort and Pignataro and co-workers used **M-Fe-2** at 1%_{mol} loading to convert a series of trifluoroacetates in quantitative yield at 70 bar H₂ and 90 °C. It was found that the presence of a triethylamine base was crucial for the catalytic performance as the base was required for the neutralization of the trifluoroacetic acid that was formed as an intermediate and poisoned the catalyst.

In summary, Fe hydrogenation catalysis reached the extent of development comparable to that of noble metal counterparts when substrate scopes are concerned. However, the activity of the majority of Fe-based catalysts remains inferior to that of Ru catalysts. This difference is pronounced to the large extent for hydrogenation of more challenging substrates, e.g. esters, where Ru-based catalysts outperform the Fe-based ones by a significant margin. For example, typical loadings for Ru ester hydrogenation catalysts vary in the range of 0.00125-0.01 %_{mol}^{16,17} under otherwise similar conditions.

3.1.2. Cobalt

Research on cobalt-catalysed hydrogenation reactions is significantly less abundant compared to that involving Fe and even Mn systems. Nevertheless, the reported cobalt systems show outstanding and often quite unique catalytic performance.

One of the first defined Co catalysts for reduction of polar C=O and C=N bonds with H₂ was described by Hanson and co-workers as early as 2012.³⁸ A Co(II) alkyl species **C-Co-1** showed a remarkable reactivity towards hydrogenation of olefins, ketones and aldehydes. Reactions were carried out at 1-4 atm H₂ pressure, at 25-60 °C and provided >90% yields for most substrates in the presence of 2%_{mol} catalyst.

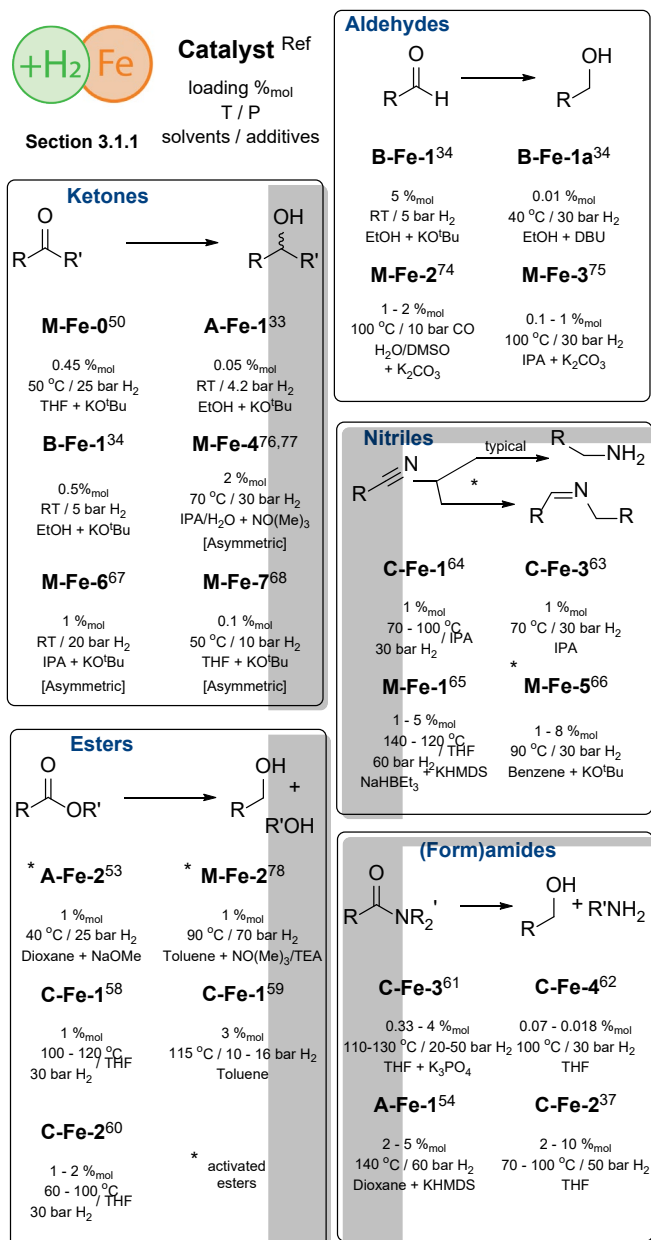


Scheme 3.2 Comparative summary of Fe catalysis performance and scopes in hydrogenations described in section 3.1.1. For the full substrate scopes see the Supporting Information.


Reduction was found to tolerate carboxylic acid, ester, tertiary amine, halide and alcohol functional groups. Remarkably, hydrogenation of styrene was also unaltered by the addition of 10%_{mol} water.

Later work by the group of Milstein established the activity of Co lutidine-based pincers in hydrogenation of esters. Catalyst **A-Co-1** containing a PNN^H pincer ligand with secondary amine sidearm showed a significantly higher activity compared to its PNP or tertiary amine PNN pincer counterparts.⁷⁹

Catalyst operated at 2-4 %_{mol} loading in the presence of 8%_{mol} NaHBEt₃ additive required for catalyst activation and

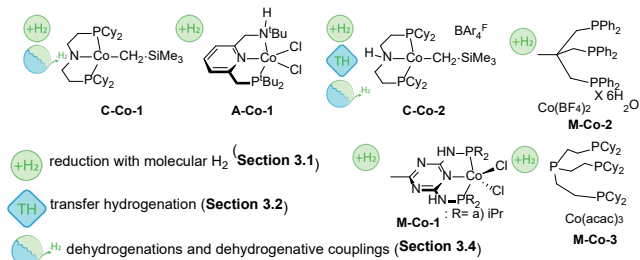

Scheme 3.3 Co catalysts introduced in section 3.1.2. Types of transformations described for each particular catalyst are indicated with the sub-section label.

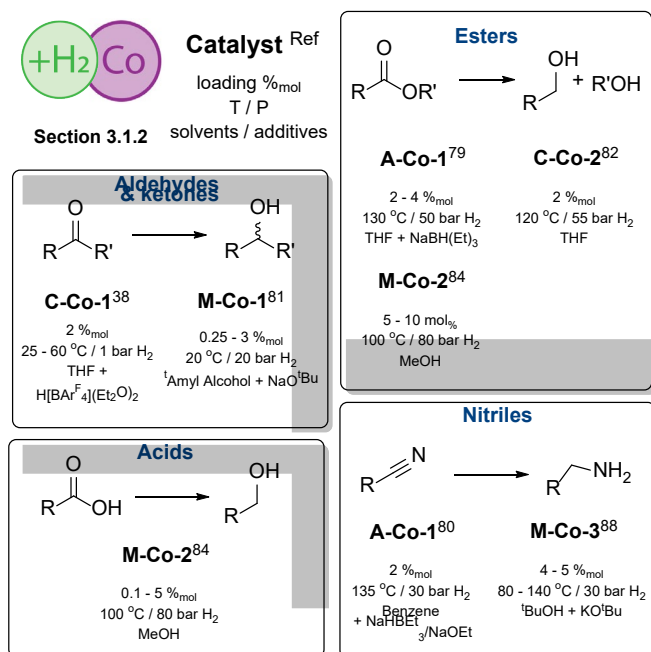

Scheme 3.4 Comparative summary of Co catalysis performance and scopes in hydrogenations described in section 3.1.2. For the full substrate scopes see the Supporting Information.

25%_{mol} KO^tBu base promoter. To achieve moderate-to-good yields **A-Co-1** required 50 bar H_2 pressure and reaction temperature of 130°C. The same catalyst was later shown to promote nitrile hydrogenation to primary amines.⁸⁰

Similar to the case of ester hydrogenation, nitrile reduction with **A-Co-1** required $NaHBEt_3$ for operation as well as moderately low 4.4 %_{mol} loading of sodium ethoxide.

Significant improvement in selective Co-catalysed hydrogenation of ketones and aldehydes was later reported by Kempe and co-workers.⁸¹ An easily accessible complex **M-Co-1** was identified as the most active among its dichlorocobalt (II) PNP analogues with varied substitution pattern. Catalyst **M-Co-1** was active in THF and 2-methyl-2-butanol at room temperature at 20 bar H_2 . At 0.25-3 %_{mol} loadings, excellent yields in hydrogenation of ketones and aldehydes were obtained for the majority of substrates. Authors also demonstrated excellent tolerance of this catalyst system to aromatic and aliphatic N-heteroatom functional groups, halides, unsaturated C=C bonds in conjugation with reduced carbonyl group as well as remote C=C functions.

A more challenging ester hydrogenation was recently established with Co catalyst by the group of Jones.⁸² Using **C-Co-2** catalyst that essentially is a product of Brookhart acid addition to **C-Co-1** authors managed to perform ester hydrogenation in the additive-free manner. Catalytic tests were performed at 55 bar H_2 at 120°C in THF to yield corresponding alcohols. Very importantly, authors observed very similar activities produced by **C-Co-2** and its N-methylated counterpart, suggesting a non-bifunctional mechanism for hydrogenation of esters, while the *NH*-Co cooperation was anticipated for the alcohol dehydrogenation with the same catalyst.⁸³

A large body of work on Co-catalysed hydrogenations relied on the use of tri- and tetradentate P-donor ligands colloquially known as tri- and tetraphos. Elsevier, de Bruin and co-workers⁸⁴ utilized an in situ prepared Co/triphos catalyst **M-Co-2** for the hydrogenation of carboxylic acids and their esters. Operating at 80 bar H_2 pressure and 100°C, the authors used 5-10 %_{mol} Co loadings to convert esters with good yields. No retention of C=C function was observed in these reactions. More importantly, carboxylic acids, that are more challenging for a homogeneous catalyst to hydrogenate compared to their esters⁸ could be converted under the same conditions in the absence of any additives at a lower catalyst loadings of 0.1-10%_{mol}. A model substrate – trifluoroacetic acid could be fully converted at only 125 ppm Co loading providing ca. 50% yield of trifluoroethanol. The performance of an in situ formed Co system was exemplary, as it was comparable to that of Ir⁸⁵ and Ru^{86, 87} based catalysts for carboxylic acid hydrogenation, which at some instances requires higher temperatures or metal loadings compared to the Co case.

Later work by Beller and co-workers⁸⁸ disclosed the use of polydentate phosphine ligands in Co-catalysed hydrogenation of nitriles to primary amines.⁸⁸ It was found that the polydentate phosphine ligand identical to that in **M-Co-2** gave only a low activity in the target reaction, whereas the in situ formed **M-Co-3** based on a tetradentate phosphine allowed quantitative yields in benzonitrile hydrogenation at 100°C, 5 %_{mol} Co loading and 30 bar H_2 . It was observed that a lower reaction temperature of 80°C provides marginally lower yield within identical 18h long tests but leads to a pronounced induction period of ca 4h associated with the formation of the active species from a $Co(acac)_3$ precursor and a tetradentate phosphine. Under optimized conditions **M-Co-3** was shown to hydrogenate aromatic and aliphatic nitriles with quantitative conversion and good isolated yields typically exceeding 80%.

Overall, Co catalysts exhibit somewhat lower activity in H_2 reduction than their Fe counterparts based on identical or similar ligands. However, Co can promote direct reduction of carboxylic acids inaccessible to Fe catalysts and has very few precedents in noble metal catalysis.^{7,8}

3.1.3. Manganese

Reduction of polar bonds promoted by Mn-based homogeneous catalysts was not known until 2016 when several groups disclosed a series of potent Mn pincer catalyst for various hydrogenation reactions. A remarkable rate of Mn hydrogenation catalysis development is exemplified by the

great number of works published on the topic in less than a year since the initial discovery including recent comprehensive review on the application of Mn complexes in organic synthesis.⁸⁹⁻⁹¹

The first example of a defined Mn hydrogenation catalyst was disclosed by the group of Beller who reported manganese aminopincer family of catalysts **C-Mn-1** that were active in hydrogenation of aromatic and aliphatic nitriles, ketones and aldehydes.⁹² A slightly more active, compared to its counterparts from the same family, catalyst **C-Mn-1a** with isopropyl substituents on the phosphine donor groups was extensively characterized in a reactivity survey that demonstrated deprotonation and metal-hydride species formation common for Ru and Fe aminopincers with **C** ligand family. Catalyst operated at 1 %_{mol} loading in hydrogenation of ketones and aldehydes and 3 %_{mol} loading in nitrile hydrogenation with roughly 3 equivalents of Na^tBu base additive per metal loading at 100-120°C and 30-50 bar H₂ pressure. Later work by the same group expanded the scope of related Mn pincers to ester hydrogenation catalysis.⁹³ Interestingly, catalysts **C-Mn-1** were only moderately active in hydrogenation of methyl benzoate at temperatures up to 120°C and H₂ pressures up to 80 bar at 2 %_{mol} catalyst loading. However, the use of a less bulky **C-Mn-2,3** catalysts allowed to reach excellent yields at significantly milder conditions.

Another example of Mn catalyst with an amine centred pincer ligand was described by Clarke and co-workers.⁹⁴ At 1%_{mol} catalyst **M-Mn-2** provided excellent yields in asymmetric ketone hydrogenation and hydrogenation of esters to corresponding alcohols. Interestingly, the reduction of both substrates was performed in alcohol solvents – ethanol for ketones and isopropanol for esters that is typically challenging for common Ru-based catalysts. Notably, reduction of ketones was performed with high stereoselectivity allowing for ee typically over 70% reaching 91% in particular cases.


Recent report by Beller and co-workers⁹⁵ expanded the utility of **C-Mn** catalysts to asymmetric hydrogenation of ketones. Using **C-Mn-4** at a 1 %_{mol} loading a wide range of aromatic and aliphatic ketones could be converted to alcohols in excellent yields at 30-40 °C and 30 bar H₂ pressure with moderate-to-good stereoselectivity up to 92/8 enantiomer ratios.

One of the most recent examples of an Mn-based ester hydrogenation catalyst, **M-Mn-3**, reported by our group features no pincer ligand motif, but instead utilizes a single PN bidentate ligand.⁹⁶ It was noted that [Mn(CO)₂(PN)₂]⁺ cationic complexes were significantly less active than their Mn(PN) tricarbonylbromide counterpart in the hydrogenation of methylbenzoate model substrate. Under optimized reaction conditions, loading of **M-Mn-3** could be reduced to only 0.2%_{mol} for ester hydrogenation reactions carried out at 50 bar H₂ and 100°C. **M-Mn-3** allowed a nearly full retention of remote unsaturated carbon-carbon moieties in unsaturated esters. However, no chemoselectivity was observed in the reduction of α,β-unsaturated esters. An unusual feature of **M-Mn-3** was the reliance on high loadings of the KO^tBu base promotor necessary to achieve full ester conversion. While at 75 %_{mol} loading of


KOtBu the hydrogenation of model substrate yielded 98% of the alcohol product, the decrease of the base concentration to 10%_{mol} resulted to a drop of the yield to 66%. It was demonstrated that the variation of the reaction temperature could not improve the catalysis, while the introduction of additional base to the stalled catalytic reaction reanimated the catalytic system and enabled further reduction of the ester until full conversion was reached.

First examples of Mn catalysts with pincer ligands having an aromatic backbone were reported shortly after the disclosure of **C-Mn** catalyst family. A potent catalyst **A-Mn-1** disclosed by Milstein and co-workers⁹⁷ was shown to hydrogenate esters to corresponding alcohols at 20 bar H₂ pressure and 100°C in the presence of 1 %_{mol} catalyst, which can be regarded as an improvement over the productivity of **C-Mn** catalyst family. An interesting feature of the ligand design in **A-Mn-1** is the presence of the secondary amine donor in the PNN^H pincer, which undergoes deprotonation yielding an amido complex **A-Mn-2** upon reaction with KO^tBu. It was noted that the nature of the base promotor had a profound impact on the catalytic behaviour of **A-Mn-1** with stronger KH base being superior to KO^tBu and KHMDS bases used at a 2%_{mol} loading during the catalytic testing. Importantly, the amido complex **A-Mn-2** showed catalytic activity under base-free conditions. This suggested that the base additive during catalysis with halide complex **A-Mn-1** was necessary to activate the catalyst and allow for further formation of the catalytically active Mn hydride species.

A detailed investigation by Kempe and co-workers⁹⁸ on Mn-catalysed ketone hydrogenation revealed the importance of the oxidation state of the Mn centre and auxiliary ligands bound to it. Authors found that while catalysts **M-Mn-1** were competent ketone hydrogenation catalysts, with **M-Mn-1b** being the most active, the replacement of Mn(I) with Mn(II)

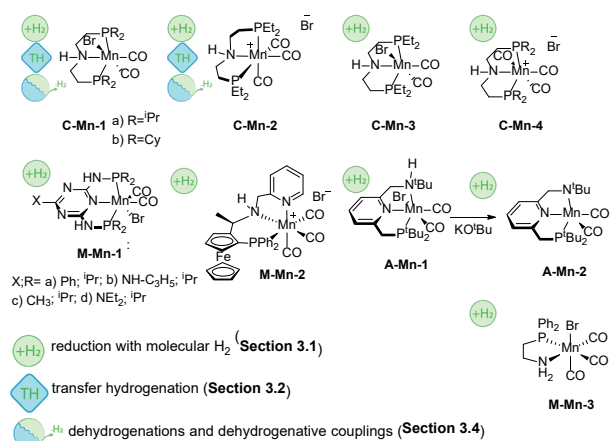

Scheme 3.5 Mn catalysts discussed in section 3.1.3. Types of transformations described for each particular catalyst are indicated with the sub-section label.

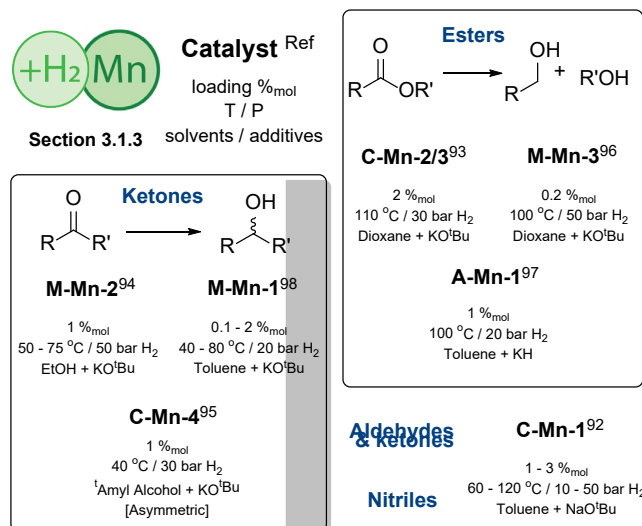

Scheme 3.6 Comparative summary of Mn catalysis performance and scopes in hydrogenations described in section 3.1.3. For the full substrate scopes see the Supporting Information.

carbonyl free metal centre leads to inactive catalysts. Strikingly, even when Mn(II) was reduced, the resulting carbonyl-free Mn(I) species remained inactive in ketone hydrogenation under studied conditions.

As a recent phenomenon, Mn-catalysed homogeneous hydrogenation has made a great progress in a timeframe manifold shorter than that for Fe and Co catalysis. Substrate scopes for Mn-promoter H₂ reduction are very similar to those for Fe and Co, so as the ligand systems utilized for these transformations. The low catalytic activity remains the major drawback of the current state-of-the-art in manganese based hydrogenation.

3.2. Transfer hydrogenation

Alternative to the use of molecular H₂ for reduction are transfer hydrogenation techniques. Instead of pressurized gas they rely on the use of hydrogen donor molecules – isopropanol, formic acid, ammonia borane and others. Recent reviews⁹ extensively discuss transfer hydrogenation catalysis with a particular emphasis on the use of noble metals and Fe-based catalysts. Therefore, below we will focus predominantly on Mn and Co-based systems, while the discussion on the Fe catalysts will be limited to only the key seminal works.

3.2.1. Iron

Iron catalysts developed in the group of Morris were among the first active Fe transfer hydrogenation catalysts. Similar to **M-Fe-0** (Scheme 3.1) complex **TH-Fe-1** was found to promote asymmetric transfer hydrogenation of ketones and imines at room temperature in isopropanol at 0.5%_{mol} loading. Enantiomeric excess in these hydrogenations remained at 8-33 % level for the majority of the substrates.⁵¹ A later improvement from the same group came with the development of complex **TH-Fe-2** that was formed via the template synthesis approach. This catalyst allowed for outstanding TOF values up to 4900 h⁻¹ in room temperature transfer hydrogenation of ketones to

alcohols with up to 99% ee.⁹⁹ Further modification of the same family of catalysts yielded **TH-Fe-3** family of compounds where the PNNP ligand was having mixed amine/imine backbone and a chloride ligand instead of previously utilized neutral acetonitrile ligand.¹⁰⁰ These modifications yielded a set of extremely active catalysts reaching transfer hydrogenation TOF values up to 200 s⁻¹ with good enantioselectivity. Later research by the same group resulted in application of **TH-Fe-3a** for transfer hydrogenation of ketones with aqueous potassium formate. Although showing moderate activity, **TH-Fe-3a** could reach TOFs up to 199 h⁻¹ at 65°C that is comparable with the values achievable with their noble metal-based counterparts under similar conditions.¹⁰¹


3.2.2. Cobalt

Cobalt aminopincer catalyst **C-Co-2** that was active in hydrogenation of ketones, was also found to be a potent transfer hydrogenation catalyst. Zhang and Hanson¹⁰² evaluated its activity at room temperature in THF/isopropanol solvent mixtures at 2 %_{mol} loading. **C-Co-2** was capable of transforming ketones, aldehydes and imines to corresponding alcohols with excellent yields and showed good tolerance to halide, amine and ether functional groups, but still fully reduced olefin functionalities conjugated with the carbonyl moiety.

Cobalt catalysts developed by Zhou and Liu and co-workers¹⁰³ show remarkable reactivity in transfer hydrogenation of nitriles. Catalysts **TH-Co-1** and **-2** both utilized ammonia borane as hydride and proton donor but showed different activity towards the reduction of nitriles. **TH-Co-1** operated at 50°C in hexane and at 1 %_{mol} loading it was capable of reducing aromatic and aliphatic nitriles to primary amines with excellent tolerance to functional group including halides, ethers, thioethers and esters. Catalyst **TH-Co-2** operating in HPIF solvent was capable of converting nitrile substrates at room temperature to symmetric secondary amines. In the presence of a primary or secondary amine, the reduction of nitriles with **TH-Co-2** results in the alkylation of the former to produce unsymmetrical secondary and tertiary amines. Finally, combination of both catalyst allows to perform stepwise synthesis of tertiary amines with three different substituents starting from several nitriles (See corresponding section in Supporting Information). Authors found that N-substituted analogues of this Co catalyst showed similar activities in reactions yielding primary and secondary amines, thus evidencing a non-bifunctional mechanism.

3.2.3. Manganese

Transfer hydrogenation with manganese catalysts have also been recently established. A comprehensive study by Beller¹⁰⁴ and co-workers described a series of Mn catalysts for transfer hydrogenation based on several prominent ligands.

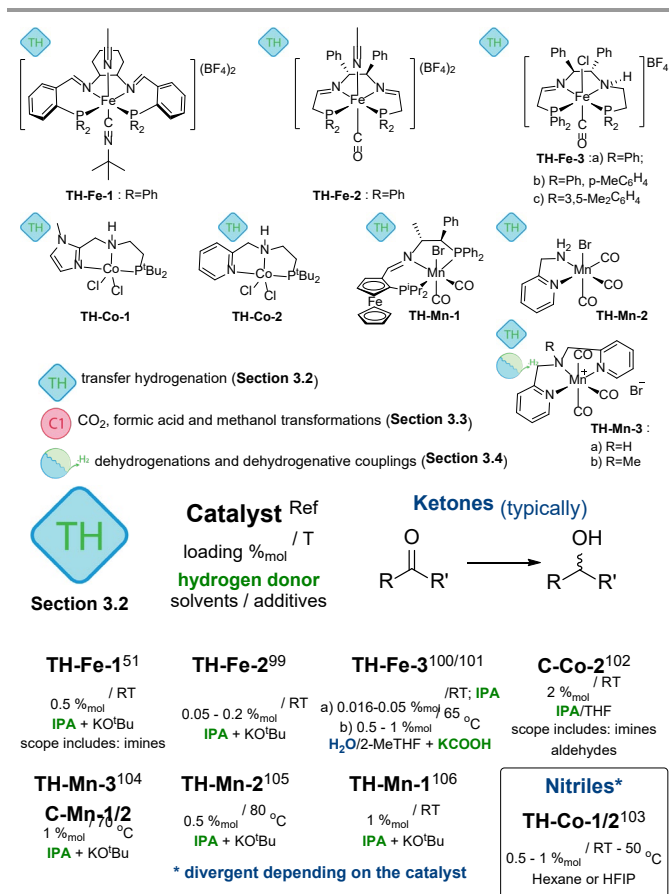

Scheme 3.7 Transfer hydrogenation catalysts introduced in Section 3.2 and the comparative summary of their performance. Types of transformations described for each particular catalyst are indicated with the sub-section label. For the full substrate scopes see the Supporting Information.

Authors found that while catalyst **C-Mn-1-a** showed a rather moderate activity, its less bulky analogues **C-Mn-1-b** and **C-Mn-2** were significantly more active and provided a nearly full acetophenone conversion under similar conditions. This observation is in line with the activity difference noted for the ester hydrogenation catalysis⁹³ suggesting the importance of the steric properties of the PNP aminopincer ligands **C** for the hydrogenation activity of Mn-PNP pincers. Interestingly, authors disclosed aminopincer catalysts **TH-Mn-3a,b** based on an N-donor-based NN^HN aminopincer that outperformed the phosphine based analogues by operating at lower catalyst loadings of 1%_{mol} and requiring lower amount of KO^tBu additive. Strikingly, catalyst **TH-Mn-3b** having the methylated tertiary amine central donor was also an active transfer hydrogenation catalyst despite being not capable of the NH-induced metal ligand bifunctional behaviour.

In a strong contrast to conventional hydrogenation catalysis, transfer hydrogenation with Mn does not rely entirely on the use of strong donor ligands as demonstrated by **TH-Mn-3** pincers. Furthermore, bidentate ligands can also enable an efficient catalysis. A simple Mn catalyst **TH-Mn-2** with aminomethyl pyridine NN chelate disclosed by Sortais and co-workers¹⁰⁵ was shown to achieve excellent TOF values up to 3600 h⁻¹ at 0.5 %_{mol} catalyst loadings operating in isopropanol at

either 80°C or room temperature. The latter required prolonged reaction time of 16 hours compared to 20 minutes time necessary to achieve a full conversion at 80 °C. Authors have shown that the presence of the primary or secondary amine was critical to obtain an active catalyst as the full substitution at the amine donor led to a drastic drop in the catalytic performance.

A major improvement in enabling stereoselectivity in Mn-promoted transfer hydrogenation was described by Zirakzadeh, Kirchner and co-workers¹⁰⁶ using an iminopincer PNP ligand modified with a ferrocenium sidearm (**TH-Mn-1**, Scheme 3.7). Authors reported asymmetric transfer hydrogenation of acetophenone with ee up to 85% using **TH-Mn-1** or its monohydride analogue operating at room temperature in isopropanol solvent with 2-4 equivalents of KO^tBu additive. A broad range of aromatic ketones could also be successfully converted under similar conditions with conversions of 60-96% and ee values up to 85 % for the majority of the substrates.

Transfer hydrogenation stands out among other catalytic reactions described in this review as it is the first class of reactions where base metal catalysts were shown to be highly competitive. The activity of Fe based **TH-Fe-X** and **TH-Mn-2** catalysts (Scheme 3.7 and Supporting Information) reached several thousand turnovers per hour - value that matches or exceeds that for noble-metal dominated state of the art.⁹ A particularly important feature of **TH-Mn-2** is the absence of strong phosphine donors that are commonly used in such catalysts. The use of N-only ligand motif renders **TH-Mn-2** very practical considering low ligand and metal costs and outstanding activity.

3.3. Sustainable chemistry with C1 and small molecules substrates

Catalytic hydrogenation processes can be classified according to their potential applications. The majority of reactions discussed in this Review are used for organic synthesis and therefore primarily aimed at fine chemical industry applications. However, there is an important group of substrates that has a great potential for green energy applications. These substrates include, among others, CO₂, methanol and formic acid that are known to undergo reversible (de)hydrogenations, thus acting as hydrogen carriers.^{10, 11, 107, 108} In this section we will discuss recent progress of the base metal catalysis for these important transformations.

3.3.1. Iron

Among the first Fe catalysts, lutidine-based iron pincer catalysts have been shown to hydrogenate carbon dioxide and bicarbonate to the corresponding formate salts.³² At moderate H₂ or H₂/CO₂ pressures below 10 bar and 80°C catalyst **A-Fe-2** provided TON in extent of several hundreds for both the hydrogenation and the reverse dehydrogenation reactions within 5-16 hours. A related pyrazine-based pincer catalyst **M-Fe-6** disclosed by Milstein and co-workers¹⁰⁹ showed a similar performance in hydrogenation of bicarbonates or CO₂ in the presence of NaOH base in THF/water mixtures under otherwise similar conditions.

Diaminopyridine-based pincer ligands **B** also form potent CO₂ hydrogenation catalysts. Described by groups of Kirchner and Gonsalvi,¹¹⁰ catalysts **B-Fe-1** and **2** show a high activity in

producing formate salts from CO₂ in THF/H₂O or EtOH in the presence of organic amine bases and NaOH. The non-bifunctional complex **B-Fe-2** with N-substituted sidearms of the pincer ligand allowed for TON > 10000 at 80°C at 80 bar pressure (H₂/CO₂=1/1) outperforming its bifunctional “NH” counterpart **B-Fe-1** by a significant margin. Similar reactivity trend was later observed by the same group in formate dehydrogenation reactions, where **B-Fe-2** outperformed its cooperative analogue **B-Fe-1** by at least two-fold margin. The dehydrogenation of formate/amine adducts with **B-Fe-2** at 40–80°C provide up to 10000 turnovers at ca 2635 h⁻¹ TOF in propylene carbonate solvent.¹¹¹

A large body of works was dedicated to the activity of iron aminopincer catalysts with C-type ligands in hydrogenation of CO₂ and formate dehydrogenation with particular focus on the highly beneficial effect of Lewis acid additives on these transformations¹¹² that, in broader context,¹¹³ attracted a significant attention of the homogeneous catalysis community. Hazari and Bernskoetter and co-workers reported on the use of catalysts similar to **C-Fe-1 - 4** for hydrogenation of CO₂ in THF in the presence of DBU at 80°C. Interestingly, authors found that methylation of the central secondary amine in ligands **C** furnished a significantly more active catalysts **C-Fe-5-8** capable of reaching TOF values over 23000 h⁻¹ making in total nearly 60000 turnovers. In all cases the addition of Lewis acids to the reaction mixture proved highly beneficial with LiOTf being the most potent promoter compared to Na and K triflates.¹¹⁴

The promoting effect of the Lewis acids on the Fe aminopincer catalysis have been described in earlier works on the reverse process, namely, the dehydrogenation of formic acid. Hazari and Schneider and co-workers¹¹⁵ reported the use

almost a million turnovers. The catalyst required no external base additive for operation, that further rendered it superior to the vast majority of the noble metal counterparts.


The representatives of the aminopincer catalyst family can promote methanol dehydrogenation that is considered a significantly more difficult process. First demonstrated by Beller and co-workers¹¹⁶ using **C-Fe-1** and its bromide analogue, the performance of Fe-aminopincers was later improved by the groups of Hazari, Bernskoetter and Holthausen¹¹⁷ who developed a base free protocol for methanol dehydrogenation employing a similar **C-Fe-9** in combination with Lewis acid promoter LiBF₄. As a result, authors obtained a highly productive catalyst that performed ca. 51000 turnovers in refluxing ethyl acetate solvent with no basic additives needed.

3.3.2. Cobalt

Cobalt was shown to form highly potent CO₂ hydrogenation catalysts. One of the first well-defined examples described by Beller and co-workers¹¹⁸ as early as in 2012 utilized an in situ formed catalyst **M-Co-4** for generation of formates from CO₂ or bicarbonate with TON up to 3877 at 120°C under 60 bar pressure. The catalyst was also active under significantly lower pressures of 5 bar rendering it one of the best Co-based systems at the time. A significant improvement over the early results was soon reported by Linehan and co-workers.¹¹⁹ A cobalt hydride species **M-Co-5** were shown to operate with exceptional formate production TOF of 3400 h⁻¹ at room temperature at ambient H₂/CO₂=1/1 pressure. This value can be improved up to 74000 h⁻¹ if the reaction takes place under 20 bar pressure. Catalyst was shown to operate in the presence of rather unusual 2,8,9-triisopropyl-2,5,8,9-tetraaza-1-phosphabicyclo[3,3,3]undecane base, commonly referred to as Verkade base, named after its inventor.¹²⁰ Although limiting prospective large scale application, this clearly outlined the high potential of Co-based catalysts for CO₂ conversion. Later work by Linehan and Wiedner and co-workers¹²¹ explored the hydrogenation of CO₂ with **M-Co-6** catalyst containing a macrocyclic amine/phosphine ligand with two additional pendant phosphine arms structurally similar to the very active Co-based CO₂ electrochemical reduction catalysts.¹²² **M-Co-6** operated in the presence of 2-tert-Butyl-1,1,3,3-tetramethylguanidine base promoter in acetonitrile at room temperature. Under a total pressure of 1.7–1.8 bar authors obtained turnover frequencies of 87–180 h⁻¹ depending on the H₂/CO₂ ratio, which varied from 15/85 to 75/25.

Another class of Co complexes, **M-Co-7** inspired by their Ir-based counterparts,¹²³ was also shown to hydrogenate CO₂. Capable of aqueous phase bicarbonate/CO₂ hydrogenation, **M-Co-7** operated at 60–100°C under 40–50 bar pressure reaching moderate maximal TOF of 39 h⁻¹.¹²⁴

Aminopincer complexes of Co, **C-Co**, were also shown to hydrogenate CO₂ to formates. Report by Bernskoetter and co-workers⁴¹ described the activity of precatalyst **C-Co-3** in the presence of LiOTf Lewis acid that was crucial for the catalytic performance. Combination with DBU base promoter and acetonitrile solvent was found to provide the best catalyst productivity that amounted for ca. 29000 turnovers at 45°C.

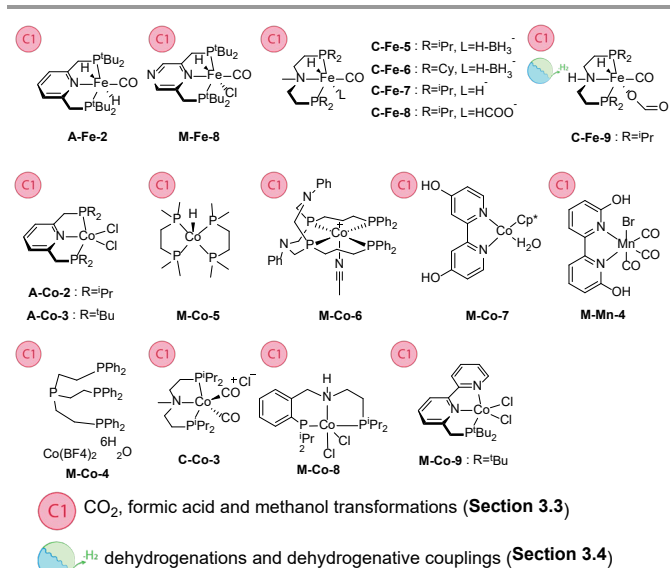

Scheme 3.8 Catalysts introduced in Section 3.3 Types of transformations described for each particular catalyst are indicated with the sub-section label.


of catalyst **C-Fe-9** in combination with LiBF₄ in dioxane at 80°C leading to one of the best formic acid dehydrogenation catalysts reported to date. This catalytic systems exhibits outstanding TOFs of >196000 h⁻¹ and provides a stable performance for

If the reaction is taken a step further, the hydrogenation of CO₂ can yield methanol. A recent report by Beller and co-workers¹²⁵ relies on an in situ formed Co(acac)₃/triphos catalyst to promote this transformation. Catalyst operating in THF/EtOH solvent requires 100-140°C to provide up to 78 turnovers under 70/20 (bar/bar) pressure of H₂/CO₂. Authors identified Co(acac)₃ to be the optimal precursor for catalysis and noted that the use of Co(II) tetrafluoroborate hydrate provides nearly three-fold lower activity. The crucial additive that authors employed was HNTf₂, trifluoromethanesulfonimide that was used in ca. 2.5-fold excess to the Co.

An important extension of the CO₂ reduction chemistry, is the direct utilization of CO₂ as a C1 building block in organic synthesis. A very common example in noble metal catalysis – amine alkylation or formylation – can also be promoted by Co catalysts. Disclosed by Milstein and co-workers,¹²⁶ a series of (L)Co(II) dichlorides were active in amine formylation with 30/30 bar H₂/CO₂ in the presence of NaHBET₃ and KO^tBu additives at 150°C in toluene solvent. Primary and secondary amines were converted to corresponding formamides in the presence of **M-Co-8** catalyst at 5%_{mol} loading. Interestingly, catalysts with lutidine-based PNP pincer ligands **A-Co-2,3** and bipyridine-based **M-Co-9** showed good activity as well, while PNN complex **A-Co-1** featuring the secondary amine sidearm was inactive. An important observation made by the authors suggests the active species to be Co(I) species formed from the Co(II) precatalyst upon treatment with NaHBET₃. The proposed active catalyst species were isolated and shown to be active in the absence of NaHBET₃ additive.

3.3.3. Manganese

Hydrogenation of CO₂ by Mn catalysts was discovered very recently by several groups. The first example of an active catalyst for hydrogenation of CO₂ to formates and amine formylation was reported by Khusnutdinova and co-workers in 2017.¹²⁷ A simple bis-hydroxy bipyridine-based complex **M-Mn-4** was shown to operate in MeCN at 60 bar pressure of equimolar H₂/CO₂. Authors obtained TON values up to 6250 in hydrogenation to formates and up to 588 in the synthesis of diethylformamide from CO₂ and diethylamine.

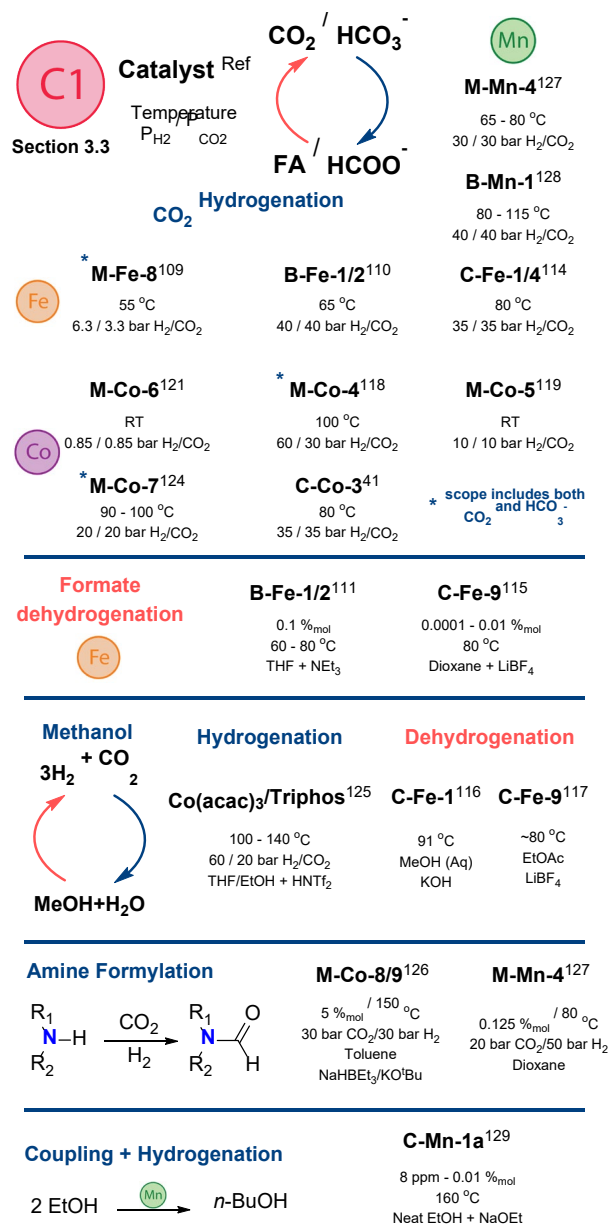

Scheme 3.9 Comparative summary of catalyst performance and scopes in transformations described in section 3.3. For the full substrate scopes see the Supporting Information.

At the same time, the groups of Kirchner and Gonsalvi described the use of **B-Mn-1** catalyst in CO₂ hydrogenation to formates at 80 bar pressure and 80°C.¹²⁸ In THF/H₂O solvent in the presence of lithium triflate and DBU base promoter authors reached high TON values over 30000 using **B-Mn-1** while its non-bifunctional analogue **B-Mn-2** consistently provided much lower TON values beyond 1500. This behaviour of Mn pincers is particularly intriguing as their iron counterparts **B-Fe-1** and **2** showed the inverse reactivity trend with NH-substituted pincers being more active.¹¹⁰

The latest example of a sustainable transformation promoted by Mn catalysts was reported by Liu and co-workers.¹²⁹ An extensive study using several Mn catalysts

identified **C-Mn-1a** as an excellent catalyst for ethanol upgrading that proceeds through dehydrogenative coupling and subsequent hydrogenation to 1-butanol.

Authors unravelled a complex catalyst interconversion network and identified a series of intermediates in this transformation that was ultimately performed with over 114000 catalytic turnovers at an average TOF of 3078 h⁻¹; this is a truly staggering performance for a base metal catalyst operating at 8 ppm loading at 165°C.

Apart from the example of **C-Mn-1a** above, small molecule chemistry has benefited greatly from the base metal catalysis in the recent years. Cobalt catalysts have been shown to promote the hydrogenation of CO₂ to formates at very high TOFs and iron catalysts using **C**-type aminopincer ligands are currently among the most active formic acid dehydrogenation catalysts capable of base-free operation.

3.4. Dehydrogenation and dehydrogenative coupling reactions

In the final part of Section 3 we will discuss dehydrogenative transformations catalysed by base metal species. These reactions can be performed in a simple setting, e.g. producing ketones from alcohols with hydrogen liberation, or can form convoluted reaction networks where dehydrogenated substrates and liberated H₂ can participate in consecutive reactions. These reactions, studied in detail for noble metal catalysts,¹⁰ are becoming increasingly important synthetic tools and currently utilize a large number of base metal catalysts.¹³⁰

3.4.1. Iron

Iron catalysts active in hydrogenation processes producing alcohols, e.g. via ester hydrogenation, were soon found to catalyse the reverse acceptorless dehydrogenation reaction. The group of Jones that earlier described Fe-catalyzed N-heterocycle dehydrogenation¹³¹ found that catalyst **C-Fe-1** or its amido analogue **C-Fe-4** dehydrogenate secondary alcohols to ketones and couple primary alcohols via an acceptorless dehydrogenative pathway to form esters.¹³² Diol substrates could also be converted to lactones using the same catalysts at moderate 0.1–1%_{mol} loadings in refluxing toluene or THF.

Similar catalysts were later found to promote dehydrogenation of glycerol in the presence of alkali hydroxides to form lactic acid salts.¹³³ Complexes **C-Fe-1**, **4** and **9** were found to be the most effective among other analogues with different substitution pattern and provide the lactate formation TONs up to 1050 at varied loadings as low as 0.004–0.2%_{mol}.

Amine substrates can also undergo dehydrogenative coupling in Fe-catalysed transformations. Beller and co-workers reported that **C-Fe-1** can be used to catalyse the synthesis of lactones and lactams through dehydrogenative transformation of diols or aminoalcohols.¹³⁴ Bernskoetter and co-workers¹³⁵ recently described the use of **C-Fe-4** catalyst for dehydrogenative amidation of primary alcohols including methanol with secondary amines to yield corresponding amides with good TON values up to 790.

Iron complexes with aromatic backbones also readily catalyse dehydrogenative coupling reactions. Among the most recent examples, Milstein and co-workers disclosed catalyst **M-**

Fe-5 promoting aldimine formation via the hydrogenative coupling of nitriles and amines.¹³⁶ At 60°C and 10–20 bar H₂ catalyst loadings of 1%_{mol} were sufficient for the selective formation of a wide range of aromatic and aliphatic aldimines. Triazine¹³⁷ and diaminopyridine¹³⁸ based Fe(II) pincers, e.g. **B-Fe-1**, developed by Kirchner and co-workers were also found to catalyse amine/alcohol couplings to yield secondary amines.

Interestingly, non-pincer complexes, e.g. **M-Fe-2**, are potent dehydrogenative coupling catalysts as well. Feringa and Barta and co-workers reported this catalyst to efficiently promote alkylation of aliphatic or aromatic amines with aliphatic alcohols and diols.¹³⁹ In the latter case the coupling leads to the cyclic amine (Scheme 3.11). Catalyst was shown to operate at 5%_{mol} loading at 120–130 °C and required trimethylamine N-oxide additive for activation. Further work by Barta and co-workers extended the utility of **M-Fe-2** to the alkylation of secondary and primary amines with benzyl alcohol derivatives¹⁴⁰ and elegant synthesis of pyrroles from primary amines and unsaturated diols (Scheme 3.11).¹⁴¹

3.4.2. Cobalt

Co catalysis for a more complex coupling chemistry has been developed in the last few years. The aminopincer catalyst **C-Co-2** that was introduced earlier and described as a potent alcohol dehydrogenation catalyst⁸³ was soon found to catalyse coupling of amines and alcohols to form imines with liberation of H₂ and water.¹⁴² The reaction was proposed to proceed through the initial alcohol dehydrogenation step. Catalyst typically operated at a 1%_{mol} loading, 120°C in toluene and was formed in situ from **C-Co-1** species.

Zhang and co-workers¹⁴³ later demonstrated that alcohol-amine coupling mediated by **C-Co-2** can yield secondary amines instead of imines if the reaction was performed in the presence of molecular sieves. Catalyst loadings of 2%_{mol} were required to obtain a variety of secondary amines in good to excellent yields with no imine byproduct obtained in most of the catalytic tests. Similar reaction could also be promoted by Co pincers with an aromatic backbone. Co(II) PCP pincers **B-Co-1** and **2** reported by Kirchner and co-workers¹⁴⁴ could catalyse efficiently aromatic amine alkylation with various aliphatic and aromatic alcohols in the presence of KO^tBu or molecular sieves. Interestingly, the activity was not restricted to Co(II) species; related Co(III)PCP catalysts also showed catalytic activity, although inferior to that of Co(II)PCPs.

Alcohols can also be used for α-alkylation of ketones in Co-catalysis. Zhang and co-workers demonstrated that **C-Co-2** catalyst can be utilized in a multistep reaction involving dehydrogenation, aldol condensation and subsequent hydrogenation steps.¹⁴⁵ Finally, the same group of authors later showed that amine homocoupling to produce secondary and cyclic amines using **C-Co-2** was also possible under similar conditions.¹⁴⁶

Before the implementation of **C**-ligated cobalt pincers, the “hydrogen” borrowing strategy, i.e. sequential dehydrogenation-coupling-hydrogenation, was applied to amine/alcohol coupling by Kempe and co-workers¹⁴⁷ who used **M-Co-10** and related catalyst with varied substitution patterns

for the alkylation of different aromatic amines. Authors employed the **M-Co-10** at 2%_{mol} loading in toluene in the presence of KO^tBu promoter with no molecular sieves required (in contrast to **C-Co-2**). Very recently, a related Co catalyst **M-Co-11** was shown to promote alkylation of secondary alcohols with primary ones at 2-5%_{mol} loadings in the presence of 1.1 equivalents of KHMDS per substrate.¹⁴⁸

A more challenging C-alkylation of amides and esters known to be promoted by noble-metal catalysts^{149, 150} was recently demonstrated by Deibl and Kempe.¹⁵¹ Amides were converted in the presence of 2.5 %_{mol} **M-Co-10** catalyst in THF at 100°C while alkylation of esters was done with **M-Co-11** in toluene at 5%_{mol} loading. For both reactions, the addition of 1.2 – 1.5 equivalents of KO^tBu was necessary to promote the alkylation.

Dehydrogenative coupling promoted by Co took a step further when Milstein and co-workers demonstrated that 1,4-diol and primary amine can be coupled to produce a 1,2,5-substituted pyrrole with liberation of hydrogen and water.¹⁵²


Catalyst **A-Co-4** used in this transformation required 5%_{mol} loading and the same amounts of KO^tBu and NaHBET₃ additives to operate at 150°C in toluene. The scope of transformation included coupling of 2,5-hexanediol, 1,4-butanediol and its 1,4-diphenyl analogue with various aromatic and aliphatic primary amines. Authors observed no activity in the absence of sodium triethylborohydride while some variation of the base loadings and types was possible with KH and KO^tBu providing the highest and nearly identical product yields.

Very recently Beller and co-workers¹⁵³ reported an efficient methoxylation of cyclic imides using a Co-triphos catalyst **M-Co-2**. With this catalyst various substituted and/or N-alkylated


succinimides and phthalimides were methoxylated at the C2 carbonyl group to produce a 2-methoxy functionalized products (See Scheme 3.11). Interestingly, intramolecular alkoxylation was also possible when the starting cyclic imide was the N-substituted with 3-hydroxypropyl unit. The same group later extended their scope of Co-catalyzed transformations to C3-alkenylation of indoles with carboxylic acids in the hydrogen atmosphere using Co(acac)₃/triphos catalyst.¹⁵⁴

3.4.3. Manganese

After the first reports on the activity of manganese pincer catalysts in hydrogenation reactions, dehydrogenation and dehydrogenative coupling applications of Mn catalysts were soon described. Alkylation of amines with alcohols to produce

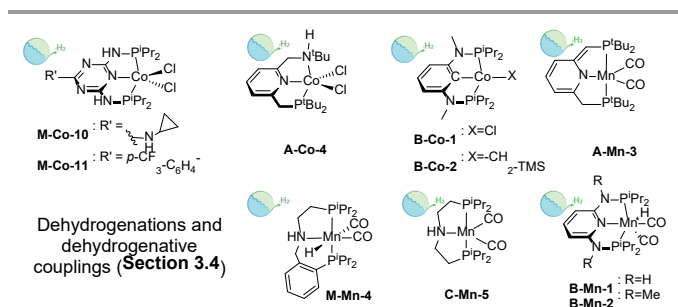

Scheme 3.10 Catalysts introduced in Section 3.4. Types of transformations described for each particular catalyst are indicated with the sub-section label.

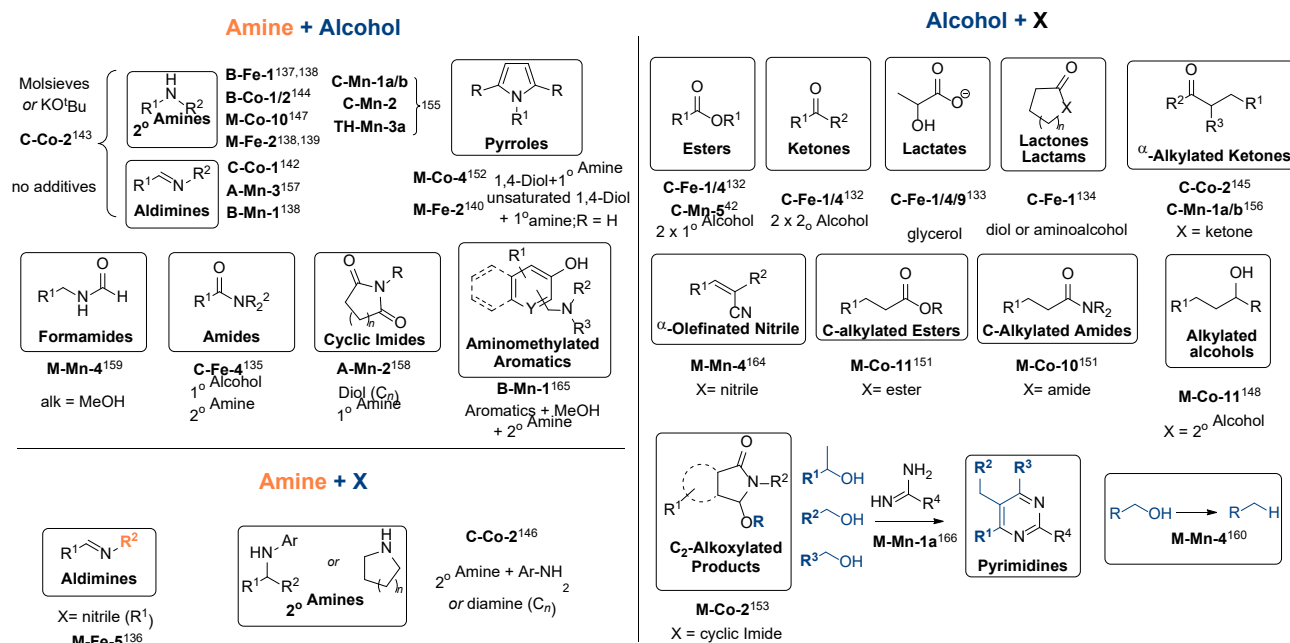

Scheme 3.11 Products of various dehydrogenative coupling reactions described in section 3.4. For the full substrate scopes see the Supporting Information.

secondary amines was shown to be promoted by a series of Mn catalysts including **C-Mn-1a** and **b**, **C-Mn-2** and **TH-Mn-3a**.¹⁵⁵ Catalyst **C-Mn-1a** with ⁱPr substituents was found superior to

the rest of the tested samples in promoting the alkylation of various aromatic amines with benzyl and methyl alcohols. Notably, authors used a large amount of KO^tBu (75%_{mol}) base

additive that was found superior to carbonates, hydroxides and other alcoxides. Operating at 80°C at 3 %_{mol} loading catalyst **C-Mn-1a** allowed a near quantitative yields of benzyl amines and good yields in alkylation of anilines with several other alcohols. It was also shown that **C-Mn-1a** can be employed for the α -alkylation of ketones with primary alcohols.¹⁵⁶

Mn-catalyzed coupling of amines and alcohols can be halted at the aldimine formation stage when no further hydrogenation takes place to yield an amine product. The group of Milstein¹⁵⁷ reported the use of a lutidine-based Mn pincer **A-Mn-3** capable of promoting amine-alcohol coupling to yield aldimines and molecular H₂ and water at 135°C at 3%_{mol} loading. Although reactions were performed in sealed vessels, no further hydrogenation of aldimines was observed and selectivity of the transformation was within 70-100 %. Comparing these results to an open vessel reaction revealed no impact of a hydrogen pressure buildup on the transformation, suggesting no plausible hydrogenation pathway promoted by **A-Mn-3**. Interestingly, catalyst **A-Mn-2** that features the NH function on the sidearm was also active in diol/primary amine coupling but instead produced cyclic imides.¹⁵⁸

Mn pincers based on a 2,6-diaminopyridine scaffold **B**, were also shown to be potent catalysts for coupling amines and alcohols. Aldimine formation was promoted by catalyst **B-Mn-1** at conditions similar to those utilized for a lutidine-based **A-Mn-3** catalyst.¹³⁸ Unlike the iron complex **B-Fe-1**, the isoelectronic **B-Mn-1** was fully selective for aldimine formation while Fe-catalysed coupling led to amines, thus, being hydrogenative.

Formylation of amines using methanol can also be promoted by manganese pincers. Milstein and co-workers¹⁵⁹ disclosed catalyst **M-Mn-4** that features a modified PNP aminopincer ligand. In methanol solvent at 110°C, the disclosed catalyst required a 2%_{mol} loading for near quantitative conversions of starting amines with yields of 50-86% depending on the substrate. The same catalyst was found to be highly active in “dehydrogenative deoxygenation” of alcohols¹⁶⁰ – a combination of alcohol dehydrogenation to produce aldehyde and subsequent Wolff-Kishner reduction of the aldehyde with hydrazine. The same catalyst **M-Mn-4** was shown superior to related **A-Mn-2** and **3** in the latest report describing α -olefination of nitriles with primary alcohols as co-substrates. In sharp contrast with noble metal promoted alcohol/nitrile couplings producing saturated α -substituted nitriles,¹⁶¹⁻¹⁶³ catalysis by **M-Mn-4** furnishes α,β -unsaturated products when operating at 4%_{mol} loading in a closed-vessel setup at 135°C in toluene solvent.¹⁶⁴

The use of methanol as a coupling agent was also explored by Kirchner and co-workers, who described an elegant aminomethylation protocol for the conversion of aromatic compounds into their methyleneamine derivatives.¹⁶⁵ Catalyst **B-Mn-1** introduced earlier was active at 4%_{mol} loading and selectively provided amine products, while the isoelectronic analogue **B-Fe-1** mainly promoted the methylation reaction.

Mn catalysts were recently shown to promote acceptorless dehydrogenative coupling of alcohols producing esters and H₂. Gauvin and co-workers⁴² reported on the use of **C-Mn-5** catalyst operating at temperatures of 110-150°C under base-free

conditions. The extensive mechanistic study performed by the authors will be described in Section 4.

One of the latest reports on Mn-promoted dehydrogenative transformations makes use of **M-Mn-1a** catalyst in a sophisticated coupling of primary alcohol, secondary alcohol and amidine to yield a variety of pyrimidines with highly complex substitution patterns (See Scheme 3.11).¹⁶⁶ Operating at moderate loadings of 2%_{mol} the catalyst could promote a three-component couplings with synthetically viable yields typically in extent of 60-70%. At higher loading of 5%_{mol} even four-component coupling yielding fully substituted pyrimidine products was possible.

4. Mechanistic aspects of (de)hydrogenation

A solid base of mechanistic works on base metal promoted (de)hydrogenations have been formed in the last few years. Either integrated into experimental study or being fully theoretical investigations these works are of crucial importance for understanding the principles underlining the catalytic reactivity. Relying in part on the extensive and well-established knowledge on Ru catalysis, mechanistic works discussed in this section grew more complex with the involvement of the base metal catalysis. One of the reasons for this is that instead of one noble metal, three base metals currently promote similar transformations. The intrinsic differences between Fe, Co and Mn and their impact on the catalytic performance are perhaps the most intriguing topic in the following mechanistic investigations. In this section we will highlight recent findings regarding the reactivity and mechanistic analysis of base metal (de)hydrogenation catalysis.


4.1. Aromatic pincers: Chemically divergent catalysis and involvement of bifunctional action

One of the direct consequences of having different metals promoting similar reactions is their divergence in catalytic performance. The work reported by Kirchner and co-workers provides a good example of this phenomenon.¹³⁸ As described above, authors found that alkylation of amines with alcohol yields imines in the manganese catalysed process, whereas the isoelectronic iron catalyst yields amines as the sole product. The reaction pathway for the manganese-catalysed reaction was studied using DFT calculations (Scheme 4.1). Authors assumed a bifunctional mechanism operative in this case and the highest barrier (33 kcal mol⁻¹) was computed for the transformation of the Mn hydride **1** to a dihydrogen complex **B^{Mn}** taking place via the the deprotonation of the ligand NH sidearm. The hydrogen release from **B^{Mn}** results in a five-coordinate **A^{Mn}** that can either form stable alcoxide adduct **C^{Mn}** or promote the alcohol dehydrogenation via the formation of an alcoxide Mn-PNP complex and inner sphere β -hydride elimination to yield the initial hydride complex **1** via a ca. 38 kcal mol⁻¹ barrier. Alternative pathways with **1** also involved deprotonation of the PNP ligand at the intermediate steps and they were all found to proceed with very similar barriers.


While the manganese catalyst formally promoted the oxidation of alcohol to ketone that further formed the imine product upon water liberation, catalysis by iron complexes was proposed to promote further reduction of imines via a mechanism similar to that earlier disclosed for ketone hydrogenation.³⁴ Most remarkably, the iron catalysed reduction is proposed to proceed via a five-coordinated **A**^{Fe} rather than trans-dihydride complex **B**^{Fe} marking a strong contrast to the report by Yang¹⁶⁷ pointing out the intermediacy of trans-dihydrides in acetophenone hydrogenation that does not

involve ligand participation. A similar behaviour was observed in related CO₂ hydrogenation Ru-PNP catalysts.¹⁶⁸

The key feature of the chemical divergence in **B-Fe/Mn** catalyst family is the apparent inactivity of Mn catalyst in imine hydrogenation also noted for another related Mn systems including **A-Mn-3** PNP pincer.¹⁵⁷ The activity of **C**-type Mn aminopincers described in section 3.4.3. of this Review adds another dimension to the complexity of base metal catalysis as the majority of **C-Mn** pincers favour formation of secondary amines, but not the imines.¹⁵⁵

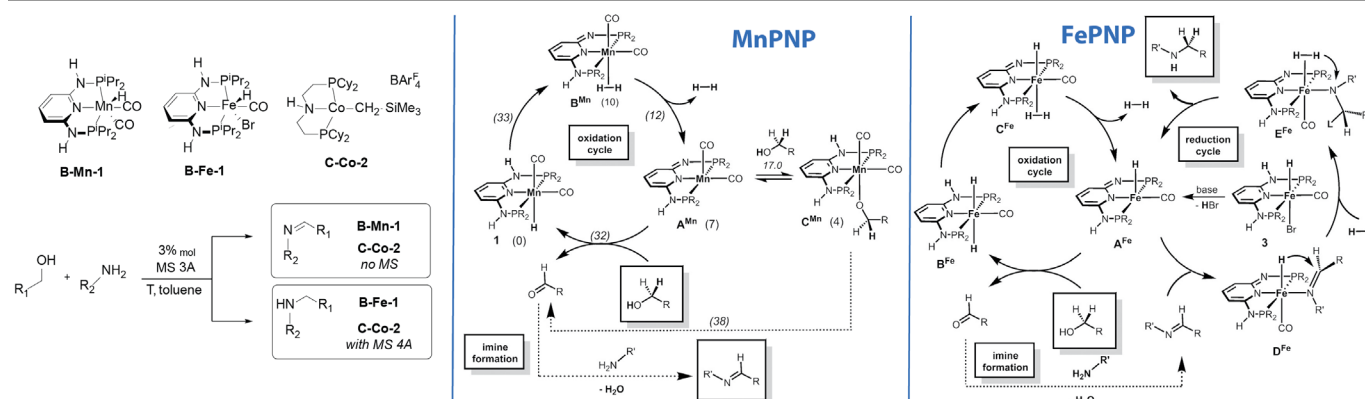

Scheme 4.1 Chemically divergent amine-alcohol coupling with Fe and Mn catalysts. Catalytic cycles reproduced from Ref. 138 (Mastalić et al., *Chem. Eur. J.*, 2016, 22, 12316) with permission from Wiley-VCH Verlag GmbH & Co. KGaA

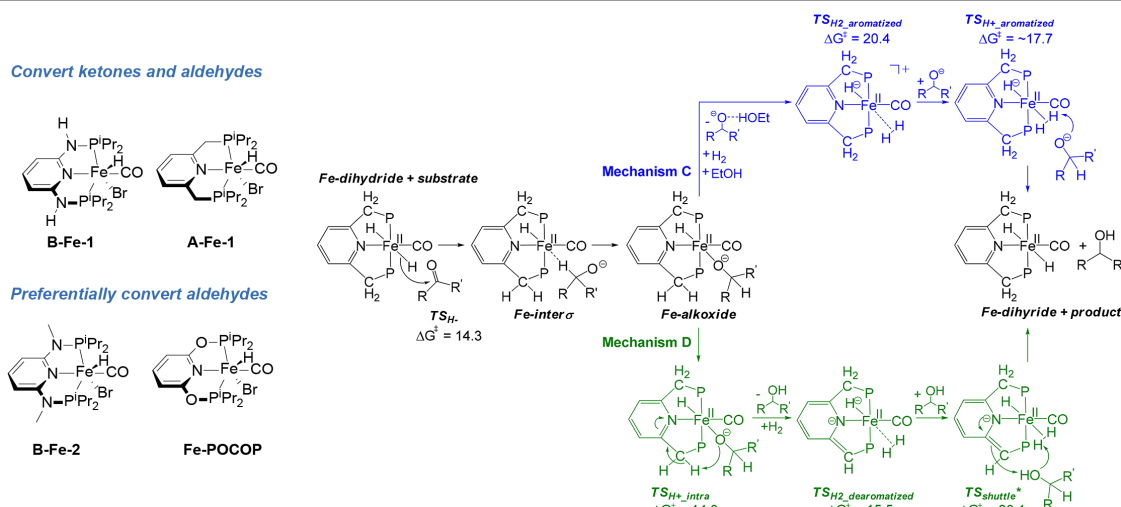

Scheme 4.2 Chemically divergent aldehyde and ketone hydrogenation with Fe PNP pincers. Catalytic cycles reproduced from Ref. 174 (Morello, Hoppman, *ACS Catal.*, 2017, 7, 5847; <http://pubs.acs.org/doi/abs/10.1021/acscatal.7b00764>). Further permissions related to material should be directed to ACS.

Finally, cobalt aminopincer **C-Co-2** provides an example of chemical divergence controlled solely by the reaction conditions. In the presence of molecular sieves the amine alcohol coupling produces amines.¹⁴⁶ In the absence of molecular sieves when **B-Mn** catalysts lose a great fraction of their activity **C-Co-2** promotes clean formation of imines.¹⁴²

Cases of divergent catalytic activity can be observed for catalysts containing the same metal centres but bound to different ligands. A good example of this behaviour is ketone and aldehyde hydrogenation by Fe-PNP pincers (Scheme 4.2). Described above, catalysts **A** and **B-Fe** reduce both substrates if

bifunctional behaviour is enabled by the ligand structure – e.g. in complexes **B-Fe-1** and **A-Fe-1**. When cooperative function of the PNP ligand is blocked by substitution (**B-Fe-2**) or complete replacement of the cooperative motive (**Fe-POCOP**¹⁶⁹) the carbonyl reduction is selective to aldehydes and does not transform ketones.

The involvement of metal-ligand bifunctional transformations in noble metal catalysis has been extensively studied and heavily debated.^{27, 170-173} Mechanistic studies of the Fe-PNP-catalysed chemoselective reduction of aldehydes in the presence of ketones were conducted by the authors of the

original reports as well as by independent groups,^{33, 34, 167} but were not able to find a clear consensus on the nature of reduction selectivity and, importantly, the active species in catalysis.


Recent mechanistic study by Morello and Hopmann¹⁷⁴ integrates previous findings and elegantly tackles this challenge by identifying two reaction pathways operative in aldehyde-selective and general carbonyl reduction cases. In both cases Fe cis-dihydride complex (Scheme 4.2) is assumed to be the active species. The bifunctional mechanism D (Green path, Scheme 4.2) involves a hydride transfer to the carbonyl substrate followed by a proton transfer from the ligand sidearm to the bound alkoxy ligand. This leads to the alcohol release and the formation of five-coordinate intermediate. The latter coordinates H₂ to facilitate its heterolytic dissociation assisted by an alcohol product resulting in the regeneration of the initial dihydride complex.

For the non-bifunctional pincers the reaction also starts with the Fe-alkoxide formation (Mechanism C, blue path, Scheme 4.2). The alkoxide-metal bond is then cleaved with the concomitant insertion of a dihydrogen molecule, which is then readily split heterolytically with the hydride taken up by the metal centre and proton transferred to the product. As authors rightfully noted in the paper “iron-alkoxide has earlier been

dismissed in computations on FePNPCH₂, because its formation would result in an increase of the hydrogenation barrier”, however, “the low energy of the iron-alkoxide intermediate and the low barrier for its formation make it very likely that this intermediate will be formed” thus making a convincing case for the intermediacy of the Fe-alkoxide species in either mechanism C or D. Authors concluded that the relative stability of Fe-alkoxide compared to that of iron-dihydride can be the main selectivity-determining factor. Having observed that non-bifunctional catalysts form alkoxides that are typically less stable than the initial dihydride, while bifunctional catalysts form stable alkoxides that results in higher hydrogenation barriers and diminishes the selectivity based on the intrinsic substrate reactivity that is higher for aldehydes and activated ketones.

4.2. Aminopincers: substrate activation complexity and relation to Ru catalysis

Aminopincer base metal catalysts have also been subjected to thorough mechanistic studies that revealed a complexity of catalytic performance of **C-Fe,Co,Mn** species sometimes described as “uncanny”.¹⁷⁵ Among representative examples are

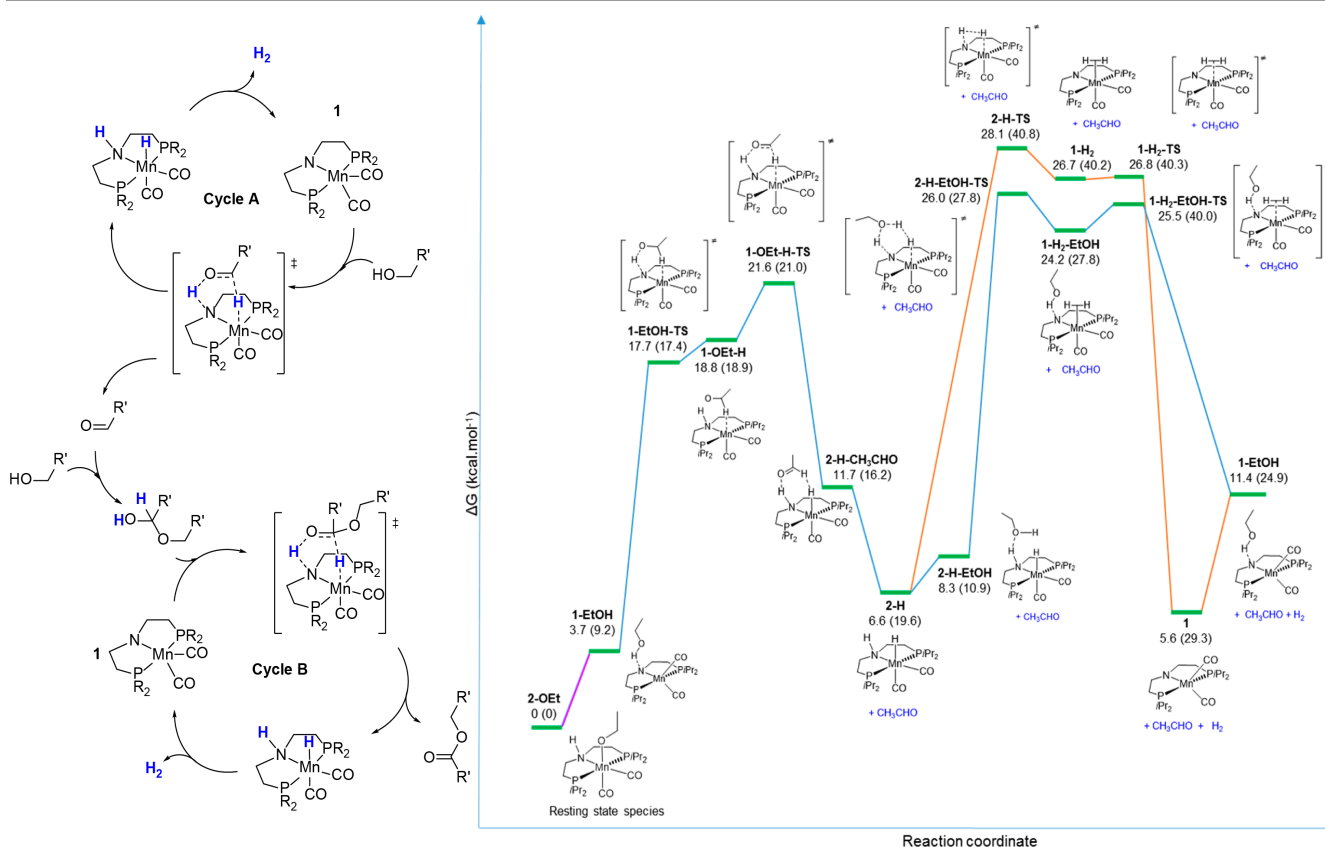

Scheme 4.3. Mechanism of Mn-catalysed dehydrogenative coupling described by Gauvin and co-workers. Reproduced with permission from Ref. 42 (Nguyen et al., *ASC Catal.*, 7, 2017), © 2017 American Chemical Society

Fe aminopincers shown to promote dehydrogenation and hydrogenation of N-heterocycles¹³¹ that were later found to adopt different dehydrogenation pathways depending on the C-

N bond polarity in the substrate. Bellows showed that more polar C-N bonds are dehydrogenated through a stepwise mechanism while relatively unpolarised C-N bonds are

dehydrogenated in a concerted manner.¹⁷⁵ Interestingly, the methylation of the central NH amine in **C** led to a complete loss of dehydrogenation activity, while the opposite took effect in **C-Fe** catalysed CO₂ hydrogenation reported by Hazari and Bernskoetter and co-workers who described the methylation of aminopincer ligand to provide significantly more active hydrogenation catalyst.¹¹⁴

The understanding of **C**-aminopincer-based catalysis have progressed in recent years in part due to the presence of large number of works addressing closely related reactions. This allowed authors to provide extensive comparison between several state-of-the-art systems in a unified framework. An elegant example of such synergy is the extensive report by Gauvin and co-workers⁴² on the **C-Mn** promoted acceptorless dehydrogenative coupling (ADC) of alcohols. In the mechanistic section of their report, authors construct an ADC reaction network and carefully identify similarities and differences with Mn-,⁹² Ru-,^{17, 176-178} and Fe-based^{117, 132, 179} catalysts for ADC or reverse hydrogenation reaction.

Authors proposed an amido complex **C-Mn-5** (complex **1** on Scheme 4.3) to be the active species in the dehydrogenation cycle. Complex **1** was proposed to act as a hydrogen acceptor leading to the formation of aldehyde product and a hydride complex **2** (Scheme 4.3). Authors observed the reversible reaction between **1** and alcohol substrate that protonates the amide nitrogen and yields a more stable Mn-bound alkoxide complex. However, authors found no direct reaction pathway yielding aldehyde product from this alkoxide complex and proposed that alkoxide formation merely “masks” the active species. The catalytic cycle is further closed by the hydrogen elimination from hydride **2**. Aldehyde was further proposed to be converted to hemiacetal that is dehydrogenated to ester in a similar cycle. Similar to the Ru-catalyzed ester hydrogenation,¹⁶ authors experimentally observed the intermediate aldehyde formation that additionally justifies their mechanistic proposal. Although hemiacetal formation was not discussed in detail, Jones and Schneider¹³² in their study on **C-Fe** system identified several mechanisms including direct aldehyde-alcohol coupling as well as substrate-assisted and metal-catalysed generation of hemiacetal among which the metal catalysed path was favoured by significant margin. This observation makes an important addition to the ADC and ester hydrogenation chemistry, as the non-catalysed hemiacetal formation or decomposition, often implied in the catalytic cycles throughout the field, is not necessarily a facile process that can be omitted.¹⁸⁰

The DFT-computed reaction pathway for Mn-promoted dehydrogenation (Scheme 4.3) features two steps that are energetically demanding. First one is the alcohol dehydrogenation sequence (Scheme 4.3, **1-EtOH**→**2-H**, 17.9 kcal·mol⁻¹) leading to the aldehyde formation and generation of metal hydride aminopincer **2-H**. The second event includes the dehydrogenation of **2-H** to regenerate the active species and produce H₂. Two pathways – unassisted and substrate-promoted – were identified for this metal-ligand cooperative transformation. The substrate-promoted dehydrogenation had somewhat lower barrier of 19.4 kcal·mol⁻¹ that was the highest

overall barrier in computed mechanism. The presence of two closely matched energy demanding steps in Mn-catalyzed ADC marks a significant difference with Ru and Fe systems that feature significantly lower alcohol dehydrogenation barrier compared to that for H₂ release.

4.3. Metal oxidation state – Cobalt and Manganese

A remarkable feature of base metals that distinguish them from their late counterparts is the accessibility of multiple oxidation states that can show drastically different catalytic activity. For example, Co/triphos precatalyst and its analogues are typically formed in situ from either Co(II) or Co(III) precursors. Groups of Elsevier and de Bruin observed formation of Co(II) species that were proposed to be the resting state during carboxylic acid hydrogenation with Co/triphos.⁸⁴ On the other hand Beller and co-workers observed the accumulation of Co(I) species in related catalytic system utilizing Co(III) metal precursor for nitrile hydrogenation.⁸⁸ Similar intermediacy of Co(I) species was also observed by Milstein and co-workers who addressed the use of a series of Co(II) precatalysts in dehydrogenative coupling. Authors found that Co(I) was likely the actual active species in catalysis that were formed upon reaction of Co(II) precatalyst with NaHBET₃ additive. Independent verification using isolated Co(I) catalyst confirmed this suggestion. This trend somewhat contrasts the observation that **C-Co** type catalysts disclosed by Zhang and Hanson (Section 3) are believed to operate as Co(II) species. In addition, an extensive study of Kempe and co-workers on C=O bond hydrogenation revealed that **M-Co-1** remain in 2+ oxidation upon activation, likely preserving this oxidation state throughout the catalytic cycle.⁸¹ Finally, Co catalysts for transfer hydrogenation were recently studied by Zhao and Ke and co-workers¹⁸¹ who identified the inner-sphere non-bifunctional mechanism as operational and, importantly, compared their findings to those for Fe catalysts that operate bifunctionally. Authors identified a high energy penalty for Fe catalysts to operate in the inner sphere and ascribed it to the tendency of Fe to maintain an 18 electron configuration that is in part stabilized by carbonyl ligands that are non-present in the Co case.

The case of Mn catalysts may likely prove to be even more convoluted than that of cobalt as manganese tends to adopt a larger number of oxidation states. One of the notable recent works by Kempe and co-workers⁹⁸ highlighted the importance of maintaining the +1 oxidation state of manganese centre and demonstrated that dihalide Mn(II) species were catalytically inert. More strikingly, the reduction of Mn(II) to produce the carbonyl-free Mn(I) species does not enable catalytic activity, that additionally emphasizes the importance of auxiliary ligands for the activity of Mn (I).

4.4. Notable features of base metal catalysis - the role of additives and catalyst deactivation

With the large number of works addressing the base metal catalysis it became evident that additives and promoters are often critically important to improve the activity of these catalysts. In several cases described in this Review the

magnitude of this effect in manifold greater than that observed in noble metal catalysis.

One of the earliest catalysts relying heavily on the additives were **C-Fe** aminopincers for dehydrogenation and hydrogenation catalysis. Bernskoetter and Hazari summarized the studies on the highly beneficial effect of Lewis acid (LA) additives in their recent account.¹¹² A truly outstanding performance of **C-Fe** in abovementioned reactions was in large part defined by the LA promotion that was also demonstrated to be efficient in **C-Co**-promoted hydrogenations.⁴¹

Another common additive in base metal catalysis, shared with their noble metal counterparts, is the basic promoter. Commonly, alkoxide bases are employed for the activation of precatalysts and triggering the bifunctional transformations that require rather low base loadings in extent of few equivalents with respect to the catalyst. Several Mn catalysis, however, require much higher base concentrations. The **M-Mn-3** catalyst⁹⁶ shows elevated activity at 75%mol loading of the KO^tBu that amounts to ca. 375 equivalents per metal cite, indicating the potential involvement of base in catalytic cycle. Comparable loadings of base can be found in Co catalysis – **M-Co-11** catalysing alcohol alkylation required 1.1 equivalents of KHMDS.¹⁴⁸ Similarly high loadings of KO^tBu were also required by **M-Co-10, 11** to promote amide and ester alkylation.¹⁵¹


Non-anionic bases are also often applied as additives in base metal catalysis. Nitrogen bases in particular were shown to perform several functions in enhancing the catalytic performance. For example, DBU base was successfully used as

acid intermediates formed during the Fe-catalysed aldehyde hydrogenation.⁵²

Organic and inorganic bases together with borohydrides discussed in the previous section are the most common additives found in (de)hydrogenative catalysis. Although the exact role of these additives is often debated, the majority of works imply their involvement in catalyst activation. This activation may involve the reduction of the metal centres, as in the case of Co catalysts, or may trigger the metal-ligand bifunctional reactivity, necessary to bring the dormant precatalyst into the active cycle. Another example of the additive that is believed to be a catalyst activator is encountered in Fe catalysis, most notably, **M-Fe-2**. As this complex is a neutral tris-carbonyl one, decarbonylation step is necessary to liberate the vacant site and allow for the complex to function as a catalyst. A number of works demonstrated that selective and mild decarbonylation can be performed in the presence of trimethylamine N-oxide that can clearly be considered a catalyst activator.¹³⁹⁻¹⁴¹

An important feature of base metal catalysts that has only been addressed recently is the catalyst deactivation. Despite the tremendous hardship associated with conducting such studies, significant progress is being made to unravel the chemistry behind catalyst activation and deactivation. For example the stability of iron transfer hydrogenation catalysts closely related to **TH-Fe-2** was found to depend strongly on the substitution pattern.¹⁸² Namely, ligands with diethylphosphine donors were yielding less stable catalysts compared to diphenylphosphine-based analogues. Authors identified a major pathway for deactivation to be the partial or full reduction of the tetradentate iminophosphine ligand that was preferential for ethyl substituted complexes. Interestingly, the reduction of iminophosphine ligand producing two metal bound NH ligands makes the complex catalytically inert despite one would expect the presence of bifunctional NH-PR₂ chelate to enable the activity to some extent.

An extensive work by Langer and co-workers³⁷ on **C-Fe**-catalysed amide hydrogenation provides another deep insight into catalyst (de)activation pathways. Apart from catalytic application itself, authors studied the reactivity of **C-Fe** complexes towards dehydrogenation and activation by borane elimination (Scheme 4.4). Importantly, it was found that the ligand structure had a profound effect on the catalyst stability with less sterically demanding ligands being superior to the bulky PNP aminopincers. It was demonstrated that increased bulk of the PNP ligand produces less solution-stable complexes that can undergo sequential dehydrogenation to form deactivated complexes **6** and **7** (Scheme 4.4). Complexes with low steric demand were shown to be *activated* via the BH₃ loss to form catalytically competent Fe dihydride species **4** that readily interconvert with isolable amido complex **5**. The accessibility of **4**, however does not necessarily provide stable complex as **4** can in fact lose hydrogen and decompose as well. In addition, formation of inactive Fe(0) PNP complexes and the free ligand was observed by Langer in case of **C-Fe** and **A-Fe**³³ hydrogenation catalysts, suggesting the reduction of metal centre to be highly unfavourable.

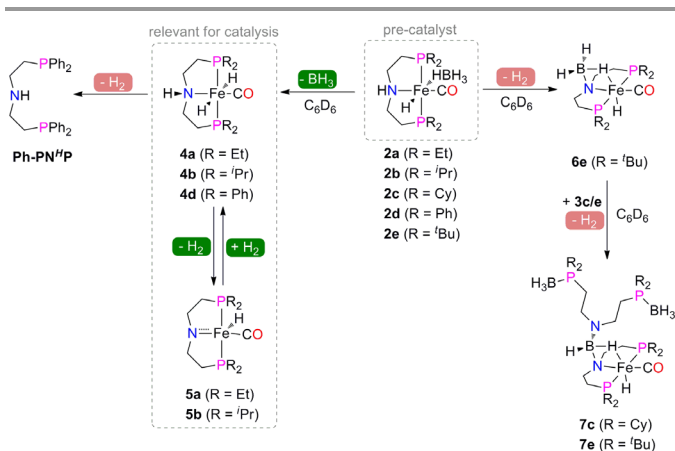

Scheme 4.4. Activation and deactivation pathways of an Fe-PNP catalyst described by Langer and co-workers. Reproduced with permission from Ref. 37 (Schneck et al., *Organometallics*, 35, 2016), © 2017 American Chemical Society

a basic promoter in CO₂ hydrogenation by a series of Fe and Mn catalysts and reduction of aldehydes by **B-Fe-1a**.⁵⁶ The latter case is a rare precedent when a nitrogen base can provide catalytic activity comparable to that achievable with anionic KO^tBu base. Interestingly, while room temperature activities of **B-Fe-1a** in the presence of KO^tBu and DBU were different, the performance of both base promoters was nearly identical at 40°C that implies significantly different promotion mechanism by anionic and neutral bases. Weaker bases like trimethylamine are also employed as additives. For example, NEt₃ was proposed to prevent the catalyst poisoning by neutralizing the carboxylic

5. Present standing and future prospects

In the last three years we have witnessed a tremendous burst in research devoted to the base metal promoted catalysis. Especially remarkable is the surge in the catalytic systems using manganese that were disclosed within last year, while the comparable base of reports on took five years for Co- and nearly a decade for Fe-based catalysis to build up. To a large extent we owe this progress to the universal ligand platforms that allow using seemingly different metals in a surprisingly similar framework from both synthetic and catalytic prospective. As a result, at this point nearly all (de)hydrogenative catalytic transformations accessible to noble metals can be promoted by at least one of the base metal catalysts based on similar ligand systems. This renders the demand for replacement of the noble metals in (de)hydrogenative catalysis with base metals well met indeed.

Mechanistic investigations of the base metal catalysis have played a notable role in establishing the field at the current level. In particular, we have started to understand the origins of unusual selectivity patterns that distinguish base metal catalysts from their noble counterparts. However, as we inherited much of the methodology from the noble metal based catalytic systems, our outlook on the base metal chemistry under study may be limited. In this respect, deviation from the conventional mechanistic framework may bring about new exciting knowledge on the reactivity of base metals in catalysis that could have been overlooked. As we currently have numerous catalytic systems based on several distinctly different early transition metals, we may expect new mechanistic proposals to take root in the field.

With metals utilized in (de)hydrogenative catalysis becoming increasingly cheaper, the future incentive might be aimed at improving the ligands that still rely heavily on the use of strong phosphine donors. We believe the developments of simple yet efficient ligands based on C,H,N,O elements could be the next step towards making the base metal catalysis practical. On one hand, the use of cheap and simple ligands could justify generally lower activities of base metal catalysts. In addition, the rational ligand design also holds a promise for improving the performance of base-metal catalysts in the first place. Indeed, while the well-established pincer ligand platforms could very rapidly furnish a sound proof-of-principle catalysts, they often fell short in providing the activity matching that of noble metals, for which the conventional pincer ligands have been originally developed. In this respect, the development of new metal- and reaction-tailored ligands is truly promising.

In recent years we have been given several examples of a departure from conventional ligands that was highly rewarding. This is best exemplified by the case of Fe catalysis that is now unmatched in transfer hydrogenation¹⁰⁰ and formic acid dehydrogenation reactions.¹¹⁵ Having these reports as an inspiration we can expect the coming breakthrough in Co and Mn catalysis in the near future.

Acknowledgements

This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement No. 725686). G.A.F. is sincerely thankful to J. Hutt for valuable discussion during the preparation of this manuscript. E.J.M.H. acknowledges the support from the Netherlands Center for Multiscale Catalytic Energy Conversion (MCEC). Partial support from the Government of the Russian Federation (Grant 074-U01) and the Ministry of Education and Science of the Russian Federation (Project 11.1706.2017/4.6) is acknowledged.

Notes and references

- 1 J. Clayden, N. Greeves, S. Warren and P. Wothers, *Organic Chemistry*, Oxford University Press, 2000.
- 2 L. Bouveault and G. Blanc, *Compt. rend.*, 1903, **136**, 1676-1678.
- 3 J. J. Li, *Name Reactions: A Collection of Detailed Mechanisms and Synthetic Applications*, Third Edition, Springer, 2007, 77.
- 4 B. S. Bodnar and P. F. Vogt, *J. Org. Chem.*, 2009, **74**, 2598-2600.
- 5 P. Urben, *Bretherick's Handbook of Reactive Chemical Hazards*, Sixth Edition, Academic Press, 2006, 2, 8.
- 6 R. Noyori and T. Ohkuma, *Angew. Chem. Int. Ed.*, 2001, **40**, 40-73.
- 7 S. Werkmeister, K. Junge and M. Beller, *Org. Process Res. Dev.*, 2014, **18**, 289-302.
- 8 J. Pritchard, G. A. Filonenko, R. van Putten, E. J. M. Hensen and E. A. Pidko, *Chem. Soc. Rev.*, 2015, **44**, 3808-3833.
- 9 D. Wang and D. Astruc, *Chem. Rev.*, 2015, **115**, 6621-6686.
- 10 R. H. Crabtree, *Chem. Rev.*, 2017, **117**, 9228-9246.
- 11 F. Joó, *ChemSusChem*, 2008, **1**, 805-808.
- 12 G. Centi, E. A. Quadrelli and S. Perathoner, *Energy Environ. Sci.*, 2013, **6**, 1711-1731.
- 13 Y.-N. Li, R. Ma, L.-N. He and Z.-F. Diao, *Catal. Sci. Technol.*, 2014, 1498-1512.
- 14 C. Gunanathan and D. Milstein, *Chem. Rev.*, 2014, **114**, 12024-12087.
- 15 G. A. Filonenko, R. van Putten, E. N. Schulpen, E. J. M. Hensen and E. A. Pidko, *ChemCatChem*, 2014, **6**, 1526-1530.
- 16 G. A. Filonenko, M. J. B. Aguilá, E. N. Schulpen, R. van Putten, J. Wiecko, C. Müller, L. Lefort, E. J. M. Hensen and E. A. Pidko, *J. Am. Chem. Soc.*, 2015, **137**, 7620-7623.
- 17 D. Spasyuk, S. Smith and D. G. Gusev, *Angew. Chem. Int. Ed.*, 2013, **52**, 2538-2542.
- 18 Appropriate guidelines can be found at: a) GUIDELINE ON THE SPECIFICATION LIMITS FOR RESIDUES OF METAL CATALYSTS OR METAL REAGENTS, European Medicines Agency guideline in effect as per September 1st, 2008; http://www.ema.europa.eu/docs/en_GB/document_library/Scientific_guideline/2009/09/WC500003586.pdf; b) Elemental Impurities in Drug Products, Food and Drug Administration draft guidance; <https://www.fda.gov/ucm/groups/fdagov-public/@fdagov-drugs-gen/documents/document/ucm509432.pdf>
- 19 P. Chirik and R. Morris, *Acc. Chem. Res.*, 2015, **48**, 2495-2495.
- 20 S. Werkmeister, J. Neumann, K. Junge and M. Beller, *Chem. Eur. J.*, 2015, **21**, 12226-12250.
- 21 G. Bauer and X. Hu, *Inorg. Chem. Front.*, 2016, **3**, 741-765.
- 22 M. Asay and D. Morales-Morales, *Dalton Trans.*, 2015, **44**, 17432-17447.
- 23 C. Gunanathan and D. Milstein, *Acc. Chem. Res.*, 2011, **44**, 588-602.

- 24 G. van Koten, in *Organometallic Pincer Chemistry*, eds. G. van Koten and D. Milstein, Springer Berlin Heidelberg, Berlin, Heidelberg, 2013.
- 25 D. Benito-Garagorri and K. Kirchner, *Acc. Chem. Res.*, 2008, **41**, 201-213.
- 26 J. R. Khusnutdinova and D. Milstein, *Angew. Chem. Int. Ed.*, 2015, **54**, 12236-12273.
- 27 P. A. Dub, B. L. Scott and J. C. Gordon, *J. Am. Chem. Soc.*, 2017, **139**, 1245-1260.
- 28 P. A. Dub and J. C. Gordon, *ACS Catal.*, 2017, DOI: 10.1021/acscatal.7b01791
- 29 S. J. C. Robinson and D. M. Heinekey, *Chem. Commun.*, 2017, **53**, 669-676.
- 30 E. S. Wiedner, M. B. Chambers, C. L. Pitman, R. M. Bullock, A. J. M. Miller and A. M. Appel, *Chem. Rev.*, 2016, **116**, 8655-8692.
- 31 N. V. Belkova, L. M. Epstein, O. A. Filippov and E. S. Shubina, *Chem. Rev.*, 2016, **116**, 8545-8587.
- 32 R. Langer, Y. Diskin-Posner, G. Leitus, L. J. W. Shimon, Y. Ben-David and D. Milstein, *Angew. Chem. Int. Ed.*, 2011, **50**, 9948-9952.
- 33 R. Langer, G. Leitus, Y. Ben-David and D. Milstein, *Angew. Chem. Int. Ed.*, 2011, **50**, 2120-2124.
- 34 N. Gorgas, B. Stöger, L. F. Veiros, E. Pittenauer, G. Allmaier and K. Kirchner, *Organometallics*, 2014, **33**, 6905-6914.
- 35 D. Benito-Garagorri, L. G. Alves, M. Puchberger, K. Mereiter, L. F. Veiros, M. J. Calhorda, M. D. Carvalho, L. P. Ferreira, M. Godinho and K. Kirchner, *Organometallics*, 2009, **28**, 6902-6914.
- 36 N. Gorgas, L. G. Alves, B. Stöger, A. M. Martins, L. F. Veiros and K. Kirchner, *J. Am. Chem. Soc.*, 2017, **139**, 8130-8133.
- 37 F. Schneck, M. Assmann, M. Balmer, K. Harms and R. Langer, *Organometallics*, 2016, **35**, 1931-1943.
- 38 G. Zhang, B. L. Scott and S. K. Hanson, *Angew. Chem. Int. Ed.*, 2012, **51**, 12102-12106.
- 39 D. Zhu, F. F. B. J. Janssen and P. H. M. Budzelaar, *Organometallics*, 2010, **29**, 1897-1908.
- 40 M. Brookhart, B. Grant and A. F. Volpe, *Organometallics*, 1992, **11**, 3920-3922.
- 41 A. Z. Spentzos, C. L. Barnes and W. H. Bernskoetter, *Inorg. Chem.*, 2016, **55**, 8225-8233.
- 42 D. H. Nguyen, X. Trivelli, F. Capet, J.-F. Paul, F. Dumeignil and R. M. Gauvin, *ACS Catal.*, 2017, **7**, 2022-2032.
- 43 S. Chakraborty, P. Bhattacharya, H. Dai and H. Guan, *Acc. Chem. Res.*, 2015, **48**, 1995-2003.
- 44 D. S. Mérel, M. L. T. Do, S. Gaillard, P. Dupau and J.-L. Renaud, *Coord. Chem. Rev.*, 2015, **288**, 50-68.
- 45 L. C. Misal Castro, H. Li, J.-B. Sortais and C. Darcel, *Green Chem.*, 2015, **17**, 2283-2303.
- 46 T. Zell and D. Milstein, *Acc. Chem. Res.*, 2015, **48**, 1979-1994.
- 47 P. J. Chirik, *Acc. Chem. Res.*, 2015, **48**, 1687-1695.
- 48 I. Bauer and H.-J. Knölker, *Chem. Rev.*, 2015, **115**, 3170-3387.
- 49 E. McNeill and T. Ritter, *Acc. Chem. Res.*, 2015, **48**, 2330-2343.
- 50 C. Sui-Seng, F. N. Haque, A. Hadzovic, A.-M. Pütz, V. Reuss, N. Meyer, A. J. Lough, M. Zimmer-De Iuliis and R. H. Morris, *Inorg. Chem.*, 2009, **48**, 735-743.
- 51 C. Sui-Seng, F. Freutel, A. J. Lough and R. H. Morris, *Angew. Chem. Int. Ed.*, 2008, **47**, 940-943.
- 52 T. Zell, Y. Ben-David and D. Milstein, *Catal. Sci. Technol.*, 2015, **5**, 822-826.
- 53 T. Zell, Y. Ben-David and D. Milstein, *Angew. Chem. Int. Ed.*, 2014, **53**, 4685-4689.
- 54 J. A. Garg, S. Chakraborty, Y. Ben-David and D. Milstein, *Chem. Commun.*, 2016, **52**, 5285-5288.
- 55 B. Bichler, C. Holzhaacker, B. Stöger, M. Puchberger, L. F. Veiros and K. Kirchner, *Organometallics*, 2013, **32**, 4114-4121.
- 56 N. Gorgas, B. Stöger, L. F. Veiros and K. Kirchner, *ACS Catal.*, 2016, **6**, 2664-2672.
- 57 L. Bonomo, L. Kermorvan and P. Dupau, *ChemCatChem*, 2015, **7**, 907-910.
- 58 S. Werkmeister, K. Junge, B. Wendt, E. Alberico, H. Jiao, W. Baumann, H. Junge, F. Gallou and M. Beller, *Angew. Chem. Int. Ed.*, 2014, **53**, 8722-8726.
- 59 S. Chakraborty, H. Dai, P. Bhattacharya, N. T. Fairweather, M. S. Gibson, J. A. Krause and H. Guan, *J. Am. Chem. Soc.*, 2014, **136**, 7869-7872.
- 60 S. Elangovan, B. Wendt, C. Topf, S. Bachmann, M. Scalone, A. Spannenberg, H. Jiao, W. Baumann, K. Junge and M. Beller, *Adv. Synth. Catal.*, 2016, **358**, 820-825.
- 61 N. M. Rezayee, D. C. Samblanet and M. S. Sanford, *ACS Catal.*, 2016, **6**, 6377-6383.
- 62 U. Jayarathne, Y. Zhang, N. Hazari and W. H. Bernskoetter, *Organometallics*, 2017, **36**, 409-416.
- 63 S. Lange, S. Elangovan, C. Cordes, A. Spannenberg, H. Jiao, H. Junge, S. Bachmann, M. Scalone, C. Topf, K. Junge and M. Beller, *Catal. Sci. Technol.*, 2016, **6**, 4768-4772.
- 64 C. Bornschein, S. Werkmeister, B. Wendt, H. Jiao, E. Alberico, W. Baumann, H. Junge, K. Junge and M. Beller, *Nat Commun*, 2014, **5**.
- 65 S. Chakraborty, G. Leitus and D. Milstein, *Chem. Commun.*, 2016, **52**, 1812-1815.
- 66 S. Chakraborty and D. Milstein, *ACS Catal.*, 2017, **7**, 3968-3972.
- 67 A. Zirakzadeh, K. Kirchner, A. Roller, B. Stöger, M. Widhalm and R. H. Morris, *Organometallics*, 2016, **35**, 3781-3787.
- 68 S. A. M. Smith, P. O. Lagaditis, A. Lüpke, A. J. Lough and R. H. Morris, *Chem. Eur. J.*, 2017, **23**, 7212-7216.
- 69 C. P. Casey and H. Guan, *J. Am. Chem. Soc.*, 2007, **129**, 5816-5817.
- 70 C. P. Casey and H. Guan, *J. Am. Chem. Soc.*, 2009, **131**, 2499-2507.
- 71 J. P. Hopewell, J. E. D. Martins, T. C. Johnson, J. Godfrey and M. Wills, *Org. Biomol. Chem.*, 2012, **10**, 134-145.
- 72 A. Pagnoux-Ozherelyeva, N. Pannetier, M. D. Mbaye, S. Gaillard and J.-L. Renaud, *Angew. Chem. Int. Ed.*, 2012, **51**, 4976-4980.
- 73 S. Zhou, S. Fleischer, K. Junge and M. Beller, *Angew. Chem. Int. Ed.*, 2011, **50**, 5120-5124.
- 74 A. Tlili, J. Schranck, H. Neumann and M. Beller, *Chem. Eur. J.*, 2012, **18**, 15935-15939.
- 75 S. Fleischer, S. Zhou, K. Junge and M. Beller, *Angew. Chem. Int. Ed.*, 2013, **52**, 5120-5124.
- 76 P. Gajewski, M. Renom-Carrasco, S. V. Facchini, L. Pignataro, L. Lefort, J. G. de Vries, R. Ferraccioli, A. Forni, U. Piarulli and C. Gennari, *Eur. J. Inorg. Chem.*, 2015, **9**, 1887-1893.
- 77 P. Gajewski, M. Renom-Carrasco, S. V. Facchini, L. Pignataro, L. Lefort, J. G. de Vries, R. Ferraccioli, U. Piarulli and C. Gennari, *Eur. J. Inorg. Chem.*, 2015, **25**, 2015, 5526-5536.
- 78 P. Gajewski, A. Gonzalez-de-Castro, M. Renom-Carrasco, U. Piarulli, C. Gennari, J. G. de Vries, L. Lefort and L. Pignataro, *ChemCatChem*, 2016, **8**, 3431-3435.
- 79 D. Srimani, A. Mukherjee, A. F. G. Goldberg, G. Leitus, Y. Diskin-Posner, L. J. W. Shimon, Y. Ben David and D. Milstein, *Angew. Chem. Int. Ed.*, 2015, **54**, 12357-12360.
- 80 A. Mukherjee, D. Srimani, S. Chakraborty, Y. Ben-David and D. Milstein, *J. Am. Chem. Soc.*, 2015, **137**, 8888-8891.
- 81 S. Rösler, J. Obenauf and R. Kempe, *J. Am. Chem. Soc.*, 2015, **137**, 7998-8001.
- 82 J. Yuwen, S. Chakraborty, W. W. Brennessel and W. D. Jones, *ACS Catal.*, 2017, 3735-3740.
- 83 G. Zhang, K. V. Vasudevan, B. L. Scott and S. K. Hanson, *J. Am. Chem. Soc.*, 2013, **135**, 8668-8681.
- 84 T. J. Korstanje, J. Ivar van der Vlugt, C. J. Elsevier and B. de Bruin, *Science*, 2015, **350**, 298-302.
- 85 T. P. Brewster, A. J. M. Miller, D. M. Heinekey and K. I. Goldberg, *J. Am. Chem. Soc.*, 2013, **135**, 16022-16025.

- 86 F. M. A. Geilen, B. Engendahl, M. Hölscher, J. Klankermayer and W. Leitner, *J. Am. Chem. Soc.*, 2011, **133**, 14349-14358.
- 87 T. vom Stein, M. Meuresch, D. Limper, M. Schmitz, M. Hölscher, J. Coetzee, D. J. Cole-Hamilton, J. Klankermayer and W. Leitner, *J. Am. Chem. Soc.*, 2014, **136**, 13217-13225.
- 88 R. Adam, C. B. Bheeter, J. R. Cabrero-Antonino, K. Junge, R. Jackstell and M. Beller, *ChemSusChem*, 2017, **10**, 842-846.
- 89 J. R. Carney, B. R. Dillon and S. P. Thomas, *Eur. J. Inorg. Chem.*, 2016, 3912-3929.
- 90 B. Maji and M. K. Barman, *Synthesis*, 2017, **49**, 3377-3393.
- 91 M. Garbe, K. Junge and M. Beller, *Eur. J. Inorg. Chem.*, 2017, 4344-4362.
- 92 S. Elangovan, C. Topf, S. Fischer, H. Jiao, A. Spannenberg, W. Baumann, R. Ludwig, K. Junge and M. Beller, *J. Am. Chem. Soc.*, 2016, **138**, 8809-8814.
- 93 S. Elangovan, M. Garbe, H. Jiao, A. Spannenberg, K. Junge and M. Beller, *Angew. Chem. Int. Ed.*, 2016, **55**, 15364-15368.
- 94 M. B. Widegren, G. J. Harkness, A. M. Z. Slawin, D. B. Cordes and M. L. Clarke, *Angew. Chem. Int. Ed.*, 2017, **56**, 5825-5828.
- 95 M. Garbe, K. Junge, S. Walker, Z. Wei, H. Jiao, A. Spannenberg, S. Bachmann, M. Scalone and M. Beller, *Angew. Chem. Int. Ed.*, 10.1002/anie.201705471.
- 96 R. van Putten, E. A. Uslamin, M. Garbe, C. Liu, A. Gonzalez-de-Castro, M. Lutz, K. Junge, E. J. M. Hensen, M. Beller, L. Lefort and E. A. Pidko, *Angew. Chem. Int. Ed.*, 2017, **56**, 7531-7534.
- 97 N. A. Espinosa-Jalapa, A. Nerush, L. J. W. Shimon, G. Leitius, L. Avram, Y. Ben-David and D. Milstein, *Chem. Eur. J.*, 2017, **23**, 5934-5938.
- 98 F. Kallmeier, T. Irrgang, T. Dietel and R. Kempe, *Angew. Chem. Int. Ed.*, 2016, **55**, 11806-11809.
- 99 A. Mikhailine, A. J. Lough and R. H. Morris, *J. Am. Chem. Soc.*, 2009, **131**, 1394-1395.
- 100 W. Zuo, A. J. Lough, Y. F. Li and R. H. Morris, *Science*, 2013, **342**, 1080-1083.
- 101 K. Z. Demmans, O. W. K. Ko and R. H. Morris, *RSC Adv.*, 2016, **6**, 88580-88587.
- 102 G. Zhang and S. K. Hanson, *Chem. Commun.*, 2013, **49**, 10151-10153.
- 103 Z. Shao, S. Fu, M. Wei, S. Zhou and Q. Liu, *Angew. Chem. Int. Ed.*, 2016, **55**, 14653-14657.
- 104 M. Perez, S. Elangovan, A. Spannenberg, K. Junge and M. Beller, *ChemSusChem*, 2017, **10**, 83-86.
- 105 A. Bruneau-Voisine, D. Wang, V. Dorcet, T. Roisnel, C. Darcel and J.-B. Sortais, *Org. Lett.*, 2017, **19**, 3656-3659.
- 106 A. Zirakzadeh, S. R. M. M. de Aguiar, B. Stöger, M. Widhalm and K. Kirchner, *ChemCatChem*, 2017, **9**, 1744-1748.
- 107 G. A. Olah, *Angew. Chem. Int. Ed.*, 2005, **44**, 2636-2639.
- 108 S. Enthaler, *ChemSusChem*, 2008, **1**, 801-804.
- 109 O. Rivada-Wheelaghan, A. Dauth, G. Leitius, Y. Diskin-Posner and D. Milstein, *Inorg. Chem.*, 2015, **54**, 4526-4538.
- 110 F. Bertini, N. Gorgas, B. Stöger, M. Peruzzini, L. F. Veiros, K. Kirchner and L. Gonsalvi, *ACS Catal.*, 2016, **6**, 2889-2893.
- 111 I. Mellone, N. Gorgas, F. Bertini, M. Peruzzini, K. Kirchner and L. Gonsalvi, *Organometallics*, 2016, **35**, 3344-3349.
- 112 W. H. Bernskoetter and N. Hazari, *Acc. Chem. Res.*, 2017, **50**, 1049-1058.
- 113 A. Maity and T. S. Teets, *Chem. Rev.*, 2016, **116**, 8873-8911.
- 114 Y. Zhang, A. D. MacIntosh, J. L. Wong, E. A. Bielinski, P. G. Williard, B. Q. Mercado, N. Hazari and W. H. Bernskoetter, *Chem. Sci.*, 2015, **6**, 4291-4299.
- 115 E. A. Bielinski, P. O. Lagaditis, Y. Zhang, B. Q. Mercado, C. Würtele, W. H. Bernskoetter, N. Hazari and S. Schneider, *J. Am. Chem. Soc.*, 2014, **136**, 10234-10237.
- 116 E. Alberico, P. Sponholz, C. Cordes, M. Nielsen, H.-J. Drexler, W. Baumann, H. Junge and M. Beller, *Angew. Chem. Int. Ed.*, 2013, **52**, 14162-14166.
- 117 E. A. Bielinski, M. Förster, Y. Zhang, W. H. Bernskoetter, N. Hazari and M. C. Holthausen, *ACS Catal.*, 2015, **5**, 2404-2415.
- 118 C. Federsel, C. Ziebart, R. Jackstell, W. Baumann and M. Beller, *Chem. Eur. J.*, 2012, **18**, 72-75.
- 119 M. S. Jeletic, M. T. Mock, A. M. Appel and J. C. Linehan, *J. Am. Chem. Soc.*, 2013, **135**, 11533-11536.
- 120 P. B. Kisanga and J. G. Verkade, *Tetrahedron*, 2001, **57**, 467-475.
- 121 S. A. Burgess, K. Grubel, A. M. Appel, E. S. Wiedner and J. C. Linehan, *Inorg. Chem.*, 2017, **56**, 8580-8589.
- 122 S. Roy, B. Sharma, J. Pécaut, P. Simon, M. Fontecave, P. D. Tran, E. Derat and V. Artero, *J. Am. Chem. Soc.*, 2017, **139**, 3685-3696.
- 123 J. F. Hull, Y. Himeda, W.-H. Wang, B. Hashiguchi, R. Periana, D. J. Szalda, J. T. Muckerman and E. Fujita, *Nat Chem*, 2012, **4**, 383-388.
- 124 Y. M. Badiel, W.-H. Wang, J. F. Hull, D. J. Szalda, J. T. Muckerman, Y. Himeda and E. Fujita, *Inorg. Chem.*, 2013, **52**, 12576-12586.
- 125 J. Schneidewind, R. Adam, W. Baumann, R. Jackstell and M. Beller, *Angew. Chem. Int. Ed.*, 2017, **56**, 1890-1893.
- 126 P. Daw, S. Chakraborty, G. Leitius, Y. Diskin-Posner, Y. Ben-David and D. Milstein, *ACS Catal.*, 2017, **7**, 2500-2504.
- 127 A. Dubey, L. Nencini, R. R. Fayzullin, C. Nervi and J. R. Khusnutdinova, *ACS Catal.*, 2017, **7**, 3864-3868.
- 128 F. Bertini, M. Glatz, N. Gorgas, B. Stöger, M. Peruzzini, L. F. Veiros, K. Kirchner and L. Gonsalvi, *Chem. Sci.*, 2017, **8**, 5024-5029.
- 129 S. Fu, Z. Shao, Y. Wang and Q. Liu, *J. Am. Chem. Soc.*, 2017, DOI: 10.1021/jacs.7b05939.
- 130 J.-L. Renaud and S. Gaillard, *Synthesis*, 2016, **48**, 3659-3683.
- 131 S. Chakraborty, W. W. Brennessel and W. D. Jones, *J. Am. Chem. Soc.*, 2014, **136**, 8564-8567.
- 132 S. Chakraborty, P. O. Lagaditis, M. Förster, E. A. Bielinski, N. Hazari, M. C. Holthausen, W. D. Jones and S. Schneider, *ACS Catal.*, 2014, **4**, 3994-4003.
- 133 L. S. Sharninghausen, B. Q. Mercado, R. H. Crabtree and N. Hazari, *Chem. Commun.*, 2015, **51**, 16201-16204.
- 134 M. Peña-López, H. Neumann and M. Beller, *ChemCatChem*, 2015, **7**, 865-871.
- 135 E. M. Lane, K. B. Uttley, N. Hazari and W. Bernskoetter, *Organometallics*, 2017, **36**, 2020-2025.
- 136 S. Chakraborty, G. Leitius and D. Milstein, *Angew. Chem. Int. Ed.*, 2017, **56**, 2074-2078.
- 137 M. Mastalir, B. Stöger, E. Pittenauer, M. Puchberger, G. Allmaier and K. Kirchner, *Adv. Synth. Catal.*, 2016, **358**, 3824-3831.
- 138 M. Mastalir, M. Glatz, N. Gorgas, B. Stöger, E. Pittenauer, G. Allmaier, L. F. Veiros and K. Kirchner, *Chem. Eur. J.*, 2016, **22**, 12316-12320.
- 139 T. Yan, B. L. Feringa and K. Barta, *Nat. Commun.*, 2014, **5**, 5602.
- 140 T. Yan, B. L. Feringa and K. Barta, *ACS Catal.*, 2016, **6**, 381-388.
- 141 T. Yan and K. Barta, *ChemSusChem*, 2016, **9**, 2321-2325.
- 142 G. Zhang and S. K. Hanson, *Org. Lett.*, 2013, **15**, 650-653.
- 143 G. Zhang, Z. Yin and S. Zheng, *Org. Lett.*, 2016, **18**, 300-303.
- 144 M. Mastalir, G. Tomsu, E. Pittenauer, G. Allmaier and K. Kirchner, *Org. Lett.*, 2016, **18**, 3462-3465.
- 145 G. Zhang, J. Wu, H. Zeng, S. Zhang, Z. Yin and S. Zheng, *Org. Lett.*, 2017, **19**, 1080-1083.
- 146 Z. Yin, H. Zeng, J. Wu, S. Zheng and G. Zhang, *ACS Catal.*, 2016, **6**, 6546-6550.
- 147 S. Rösler, M. Ertl, T. Irrgang and R. Kempe, *Angew. Chem. Int. Ed.*, 2015, **54**, 15046-15050.

- 148 F. Freitag, T. Irrgang and R. Kempe, *Chem. Eur. J.*, 2017, DOI: 10.1002/chem.201701211
- 149 L. Guo, X. Ma, H. Fang, X. Jia and Z. Huang, *Angew. Chem. Int. Ed.*, 2015, **54**, 4023-4027.
- 150 Y. Iuchi, Y. Obora and Y. Ishii, *J. Am. Chem. Soc.*, 2010, **132**, 2536-2537.
- 151 N. Deibl and R. Kempe, *J. Am. Chem. Soc.*, 2016, **138**, 10786-10789.
- 152 P. Daw, S. Chakraborty, J. A. Garg, Y. Ben-David and D. Milstein, *Angew. Chem. Int. Ed.*, 2016, **55**, 14373-14377.
- 153 J. R. Cabrero-Antonino, R. Adam, V. Papa, M. Holsten, K. Junge and M. Beller, *Chem. Sci.*, 2017, **8**, 5536-5546.
- 154 J. R. Cabrero-Antonino, R. Adam, K. Junge and M. Beller, *Chem. Sci.*, 2017, **8**, 6439-6450
- 155 S. Elangovan, J. Neumann, J.-B. Sortais, K. Junge, C. Darcel and M. Beller, *Nat. Commun.*, 2016, **7**, 12641.
- 156 M. Peña-López, P. Piehl, S. Elangovan, H. Neumann and M. Beller, *Angew. Chem. Int. Ed.*, 2016, **55**, 14967-14971.
- 157 A. Mukherjee, A. Nerush, G. Leitus, L. J. W. Shimon, Y. Ben David, N. A. Espinosa Jalapa and D. Milstein, *J. Am. Chem. Soc.*, 2016, **138**, 4298-4301.
- 158 N. A. Espinosa-Jalapa, A. Kumar, G. Leitus, Y. Diskin-Posner and D. Milstein, *J. Am. Chem. Soc.*, 2017, **139**, 11722-11725.
- 159 S. Chakraborty, U. Gellrich, Y. Diskin-Posner, G. Leitus, L. Avram and D. Milstein, *Angew. Chem. Int. Ed.*, 2017, **56**, 4229-4233.
- 160 J. O. Bauer, S. Chakraborty and D. Milstein, *ACS Catal.*, 2017, **7**, 4462-4466.
- 161 M. L. Buil, M. A. Esteruelas, J. Herrero, S. Izquierdo, I. M. Pastor and M. Yus, *ACS Catal.*, 2013, **3**, 2072-2075.
- 162 B. Anxionnat, D. Gomez Pardo, G. Ricci and J. Cossy, *Org. Lett.*, 2011, **13**, 4084-4087.
- 163 K. Motokura, D. Nishimura, K. Mori, T. Mizugaki, K. Ebitani and K. Kaneda, *J. Am. Chem. Soc.*, 2004, **126**, 5662-5663.
- 164 S. Chakraborty, U. K. Das, Y. Ben-David and D. Milstein, *J. Am. Chem. Soc.*, 2017, **139**, 11710-11713
- 165 M. Mastalir, E. Pittenauer, G. Allmaier and K. Kirchner, *J. Am. Chem. Soc.*, 2017, **139**, 8812-8815.
- 166 N. Deibl and R. Kempe, *Angew. Chem. Int. Ed.*, 2017, **56**, 1663-1666.
- 167 X. Yang, *Inorg. Chem.*, 2011, **50**, 12836-12843.
- 168 G. A. Filonenko, E. J. M. Hensen and E. A. Pidko, *Catal. Sci. Technol.*, 2014, **4**, 3474-3485.
- 169 S. Mazza, R. Scopelliti and X. Hu, *Organometallics*, 2015, **34**, 1538-1545.
- 170 G. A. Filonenko, M. P. Conley, C. Copéret, M. Lutz, E. J. M. Hensen and E. A. Pidko, *ACS Catal.*, 2013, **3**, 2522-2526.
- 171 H. Li and M. B. Hall, *ACS Catal.*, 2015, **5**, 1895-1913.
- 172 F. Hasanayn and A. Baroudi, *Organometallics*, 2013, **32**, 2493-2496.
- 173 X. Yang, *ACS Catal.*, 2012, **2**, 964-970.
- 174 G. R. Morello and K. H. Hopmann, *ACS Catal.*, 2017, **7**, 5847-5855
- 175 S. M. Bellows, S. Chakraborty, J. B. Gary, W. D. Jones and T. R. Cundari, *Inorg. Chem.*, 2017, **56**, 5519-5524.
- 176 X. Yang, *ACS Catal.*, 2013, **3**, 2684-2688.
- 177 X. Yang, *ACS Catal.*, 2014, **4**, 1129-1133.
- 178 E. Alberico, A. J. J. Lennox, L. K. Vogt, H. Jiao, W. Baumann, H.-J. Drexler, M. Nielsen, A. Spannenberg, M. P. Checinski, H. Junge and M. Beller, *J. Am. Chem. Soc.*, 2016, **138**, 14890-14904.
- 179 S. Qu, H. Dai, Y. Dang, C. Song, Z.-X. Wang and H. Guan, *ACS Catal.*, 2014, **4**, 4377-4388.
- 180 L. M. Azofra, I. Alkorta, J. Elguero and A. Toro-Labbé, *J. Phys. Chem. A*, 2012, **116**, 8250-8259.
- 181 C. Hou, J. Jiang, Y. Li, Z. Zhang, C. Zhao and Z. Ke, *Dalton Trans.*, 2015, **44**, 16573-16585.
- 182 P. O. Lagaditis, P. E. Sues, A. J. Lough and R. H. Morris, *Dalton Trans.*, 2015, **44**, 12119-12127.



Georgy A. Filonenko

Georgy Filonenko (Elizovo, Russia, 1988) received PhD in 2015 from Prof. Emiel Hensen at Eindhoven University of Technology. After completing a two-year research at Okinawa Institute of Science and Technology he joined the team of Evgeny Pidko in July 2017 as a postdoctoral researcher. His research interests include physical organometallic chemistry and mechanistic

studies in catalytic hydrogenation reactions.



Robbert van Putten

Robbert van Putten (The Netherlands, 1992) received his MSc from Eindhoven University of Technology in 2017. During his work in the Inorganic Materials Chemistry group at TU/e, he contributed to the development of homogeneous catalysts for the hydrogenation of CO₂ and carboxylic acid esters based on Ru and Mn metals. After completing industrial internships at Shell and

ASML, he joined the PhD program at Delft University of Technology with the group of Evgeny Pidko in 2017.



Emiel J. M. Hensen

Emiel Hensen (Geleen, The Netherlands, 1971) obtained his PhD from Eindhoven University of Technology in 2000. After working as an assistant professor at the University of Amsterdam he returned to Eindhoven in 2001 and became a full professor in 2009. From 2006-2008, he was a visiting research scientist at Shell, Amsterdam. He is chairman of the Netherlands Institute for

Catalysis Research (NIOK), board member of the European Research Institute on Catalysis (ERIC) and management team member of the Netherlands gravitation centre on Multiscale Catalytic Energy Conversion (MCEC). His research interests include mechanisms of heterogeneous catalysis for natural and syngas conversion, biomass conversion, solar fuels and topics related to synthesis of porous catalysts.



Evgeny A. Pidko

Evgeny Pidko (Moscow, Russia, 1982) received PhD from Eindhoven University of Technology in 2008, where in 2011-2017 he was an Assistant Professor of Catalysis for Sustainability. In 2016 he became a part-time professor of theoretical chemistry at ITMO University, St. Petersburg. Since September 2017 he is an Associate Professor and head of the Inorganic Systems Engineering group at the

Chemical Engineering Department of Delft University of Technology. In his research he successfully combines experiments and theory to understand molecular mechanisms underlying the behaviour of various chemical systems ranging from heterogenous and homogeneous catalysis to inorganic functional materials.