

AVEIRO - PORTUGAL



**This paper must be cited as:**

Bastos, A.R.N., Brites, C. D. S., Carlos, Rojas-Gutierrez, P.A, Ferreira, R.A.S. Longo, R.L. DeWolf, C. Capobianco, J.A., Carlos, L.D., Nanoscale, 2020,12, 24169-24176, <https://doi.org/10.1039/D0NR06989B>

# Thermal properties of lipid bilayers derived from the transient heating regime of upconverting nanoparticles

*Ana R. N. Bastos,<sup>†</sup> Carlos D.S. Brites,<sup>†</sup> Paola A. Rojas-Gutierrez,<sup>‡</sup> Rute A.S. Ferreira,<sup>†</sup> Ricardo  
L. Longo,<sup>\*,§</sup> Christine DeWolf,<sup>‡</sup> John A. Capobianco,<sup>\*,‡</sup> and Luís D. Carlos<sup>\*,†</sup>*

<sup>†</sup>Phantom-g, CICECO - Aveiro Institute of Materials, Department of Physics, University of  
Aveiro, 3810-193, Aveiro, Portugal

<sup>§</sup>Departamento de Química Fundamental, Universidade Federal de Pernambuco, Cidade  
Universitária, 50740-560, Recife, PE, Brazil

<sup>‡</sup>Department of Chemistry and Biochemistry, and Centre for NanoScience Research, Concordia  
University, 7141 Sherbrooke St. West, Montreal, Quebec, H4B 1R6, Canada

**ABSTRACT:** Heat transfer and thermal properties at the nanoscale can be challenging to obtain experimentally. These are particularly relevant for understanding thermoregulation in cells. Experimental data from the transient heating regime in conjunction with a model based on the energy conservation enable the determination of the specific heat capacities for all components of a nanoconstruct, namely an upconverting nanoparticle and its conformal lipid bilayer coating. This approach benefits from a very simple, cost-effective and non-invasive optical setup to measure the thermal parameters at the nanoscale. The time-dependent model developed herein lays the foundation to describe the dynamics of heat transfer at the nanoscale, which can, in turn, be used to describe heat dissipation at the cellular level.

**KEYWORDS:** transient regime, heat transfer, upconversion nanoparticle, lipid bilayer, heat capacity, nanothermometry

During metabolism cells undergo continuous heat transfer. However, very little is known about the heat transfer at the cellular level, and in particular about the thermal properties of each of the cellular components.<sup>1-5</sup> Frequently the thermal conductivity and/or heat transfer coefficients of the lipid membrane, proteins, and intracellular fluid are all assumed to be the same, an inaccuracy highlighted by Suzuki and Plakhotnik.<sup>5</sup> The thermal properties of the cell membrane are important in thermoregulation, *i.e.* the heat transfer from the cell to the surrounding environment and vice versa. The cell membrane is best approximated by a phospholipid bilayer that has been employed extensively for investigating the membrane thermodynamic and thermal properties both experimentally<sup>6,7</sup> and computationally.<sup>8-10</sup> While much of the phospholipid literature is focused on the thermotropic phase behavior, absolute measurements of intrinsic thermodynamic properties are less accessible.

Luminescent nanothermometry<sup>11-15</sup> has been widely used in the determination of cell temperature, which relies on luminescent probes such as proteins, dyes, fluorescent gold nanoclusters and nanoparticles.<sup>5, 16-19</sup> Furthermore, the technique has been recently used to measure the core temperature of upconverting nanoparticles (UCNPs) coated with a lipid bilayer enabling the direct determination of the thermal conductivity of the coating, with advantages relative to the established experimental electrical methods.<sup>20</sup> However, simply measuring the temperature, a state variable, does not provide an insight into the dissipation of heat which is dynamic thus, requiring that the transient regime be studied.

Herein, we employ a nanoconstruct comprising a UCNP ( $\text{LiYF}_4:\text{Er}^{3+}/\text{Yb}^{3+}$ ) surrounded by a conformal supported lipid bilayer (containing dioleoylphosphatidylcholine, DOPC, dioleoylphosphatidic acid, DOPA, cholesterol, and oleate)<sup>20, 21</sup> to develop a model and demonstrate experimentally that the transient regime permits to obtain the specific heat capacity of both the lipid bilayer and the UCNP. In contrast, the steady-state regime only yields an estimate of the conduction heat transfer of both components of the nanoconstruct. The determination of the specific heat capacity at the nanoscale is challenging, less explored and important to clarify why nanofluids show enhanced specific heat capacities. This property has been observed upon the addition of nanoparticles to a molten salt, that have technological relevance in energy storage, however the mechanism is not yet understood.<sup>22</sup>

## RESULTS AND DISCUSSION

Laser heating of nanofluids containing upconversion nanoparticles, UCNPs, including capped-UCNPs, has been performed and by analyzing the temperature increase at steady-state, the thermal conductivities of the nanofluids were determined.<sup>20, 21</sup> However, for analysis of the transient regime a time-dependent approach is necessary and additional considerations are in order.

**Modeling laser heating of nanofluids: power balance.** As a laser beam travels through a nanofluid, photons are absorbed by the medium and this absorbed energy is converted into heat, which will cause an increase of temperature. Under the experimental conditions, the optical pathlength is ca. 100 times larger than the diameter of the laser spot, so the laser beam can be considered as a long cylinder and the heat will be dissipated radially from the surface of this cylinder. As a result, the heat dissipation along the laser path is negligible and considering that only the particles within this cylinder will absorb and cause heating, the process can be described by a one-dimensional (radial) heat transfer with cylindrical symmetry. To model this heating process, each of the components of the nanofluid (UCNPs, lipid bilayer and solvent) will be considered as independent. The total absorption cross-section will then be the sum of the absorption cross-sections of the individual components. This applies similarly to the heat transfer properties of the nanofluid, particularly, heat capacity.

The time at which the irradiation starts (the initial time) is denoted by  $t_0$ . The temperature,  $T(t)$ , increases up to a constant value, the so-called steady-state regime,  $T(t_{ss}) \equiv T_{ss}$ . The period during which the temperature increases from the initial equilibrium temperature of the sample,  $T(t_0) \equiv T_0$ , to its steady-state value,  $T_{ss}$ , denoted by  $\Delta t = t_{ss} - t_0$ , defines the transient regime.

Energy conservation dictates that, on average, the total energy of an isolated system is constant, *i.e.* it is conserved over time. Thus, the power (or energy rate) gained,  $W_{\text{gain}}$ , has to be equal the power lost (or dissipated),  $W_{\text{lost}}$ :

$$W_{\text{gain}} = W_{\text{lost}} \quad (1)$$

This is the power balance equation, which can be obtained from the transient heat transfer differential equation derived using, for example, the shell balance approach<sup>23</sup> under homogeneous

conditions of the thermal conductivity and of the temperature gradient. The power balance equation has been successfully applied to several nanosystems, particularly in describing processes such as laser induced incandescence.<sup>24,25</sup> The simplicity to setup and to solve this equation is one of its appeals, because only the processes of power gains and power losses associated with the experimental conditions are required. In the case of laser heating of nanofluids, the power gain is basically that absorbed from laser beam, so that  $W_{\text{gain}} = W_{\text{abs}}$ , where the rate of energy absorption,  $W_{\text{abs}}$ , can be determined as (see Supporting Information)

$$W_{\text{abs}} \cong (N_{\text{p,b}}\sigma_{\text{p}} + N_{\text{p,b}}\sigma_{\text{L}} + \sigma_{\text{S,b}})P_{\text{D}} \quad (2)$$

where  $N_{\text{p,b}}$  is the number of nanoparticles exposed to the laser beam,  $\sigma_{\text{p}}$  (in  $\text{m}^{-2}$ ) is the absorption cross section of a single nanoparticle,  $\sigma_{\text{L}}$  (in  $\text{m}^{-2}$ ) is the absorption cross section of the lipid bilayer coating,  $\sigma_{\text{S,b}}$  (in  $\text{m}^{-2}$ ) is the absorption cross section of the solvent within the path of the laser beam, and  $P_{\text{D}}$  (in  $\text{W m}^{-2}$ ) is the incident power density. The absorption cross sections were determined from the absorption spectra of the nanofluids and the number density of each species was calculated from its concentration in solution and its mass or from its molar mass and density for a pure substance. The power dissipation has several pathways and mechanisms that need to be identified, quantified, and evaluated.

#### *Power lost or dissipated*

The main mechanisms and pathways of energy dissipation are: *i*) heat transfer via conduction, convection, and thermal radiation, *ii*) increase of internal energy due to heat capacity, and *iii*) upconversion emission by the UCNPs. Other sources of heat dissipation such as evaporation, ionization, dissociation, etc. will not be considered because of the stability of the systems and the relatively small temperature increase. In addition, the effects of the coupling between the flow of

heat and the flow of matter, e.g. the Soret (or thermophoresis, or thermal diffusion) and the Dufour (heat flow caused by a concentration gradient) will not be considered. Derivations and calculations of the main contributions to heat dissipation are presented in the Supporting Information.

*Power dissipation via heat transfer*

The heating of the nanofluid within the path of the laser beam creates a temperature gradient between the excitation cylinder and the bulk of the sample that is at room temperature. So, the temperature varies radially from  $T(t)$  at the surface of the cylinder to  $T_0$ . According to Fourier's law of heat conduction,<sup>26</sup> the rate of heat dissipation by conduction,  $W_{\text{cond}}$  (in W), is proportional to the temperature gradient. Given the spatial homogeneity of the system and the small temperature increase cause by the laser heating, the temperature gradient can be approximated by its finite difference form as

$$W_{\text{cond}}(t) = A_{\text{cs}}\kappa_{\text{m}} \frac{\partial T(r, t)}{\partial r} \cong A_{\text{cs}}\kappa_{\text{m}} \frac{\Delta T(t)}{\Delta r} = A_{\text{cs}}h_{\text{cond}}\Delta T(t), \quad h_{\text{cond}} = \frac{\kappa_{\text{m}}}{\Delta r} \quad (3)$$

where  $A_{\text{cs}}$  (in  $\text{m}^2$ ) is the cross-sectional area of the heat flux,  $\kappa_{\text{m}}$  (in  $\text{W m}^{-1} \text{K}^{-1}$ ) is related to the thermal conductivity of the medium,  $h_{\text{cond}}$  (in  $\text{W m}^{-2} \text{K}^{-1}$ ) is the thermal conduction coefficient, and  $\Delta r$  is a radial distance over which the temperature decreases from  $T(t)$  to room temperature  $T_0$ . Notice that this typical radial distance,  $\Delta r$ , relates the thermal conduction coefficient,  $h_{\text{cond}}$ , with the thermal conductivity,  $\kappa_{\text{m}}$ .

A hotter region can also dissipate heat to a colder region via convection. So, according to Newton's cooling law the convective heat dissipation,  $W_{\text{conv}}(t)$ ,<sup>26</sup> by the laser heated nanofluid is

$$W_{\text{conv}}(t) = A_{\text{cs}}h_{\text{conv}}\Delta T(t) \quad (4)$$

where  $h_{\text{conv}}$  (in  $\text{W m}^{-2} \text{K}^{-1}$ ) is the convection heat transfer coefficient. In general, the convection process can be classified as free, forced, and phase change (e.g. boiling or condensation).

Matter at a temperature above 0 K emits thermal radiation with an upper limit to its emissive power given by the Stefan-Boltzmann law, which is proportional to the fourth power of the temperature. It also absorbs thermal radiation from the environment, which is governed by the same law. However, when the body is at a temperature  $T(t)$  higher than its surroundings  $T_0$ , a net power dissipation,  $W_{\text{rad}}(t)$ , will be established due to thermal radiation, which can be expressed as<sup>26</sup>

$$W_{\text{rad}}(t) = \varepsilon\sigma_{\text{SB}}A_{\text{cs}}[T^4(t) - T_0^4] = A_{\text{cs}}h_{\text{rad}}\Delta T(t) \quad (5)$$

where  $0 \leq \varepsilon \leq 1$  is the emissivity of the heated region and  $\sigma_{\text{SB}}$  (in  $\text{W m}^{-2} \text{K}^{-4}$ ) is the Stefan-Boltzmann constant. The last equality in Eq. (4) is obtained when the thermal radiation coefficient,  $h_{\text{rad}}$  (in  $\text{W m}^{-2} \text{K}^{-1}$ ), is defined as

$$h_{\text{rad}} = \varepsilon\sigma_{\text{SB}}[T(t) + T_0][T^2(t) + T_0^2] \quad (6)$$

It is noteworthy that all three contributions to the power dissipation via heat transfer, namely, the approximated expression in Eq. (3) for conduction, Eq. (4) for convection, and Eq. (5) for thermal radiation have the same functional form, so they can be combined into

$$W_{\text{ht}}(t) = h_{\text{ht}}A_{\text{cs}}\Delta T(t) \quad (7)$$

where  $W_{\text{ht}}$  is the power loss due to heat transfer and  $h_{\text{ht}}$  (in  $\text{W m}^{-2} \text{K}^{-1}$ ) is the heat transfer coefficient, which is a sum of the conduction, convection and thermal radiation coefficients. Given the experimental conditions, one of these coefficients might dominate and thus determine the main mechanism of heat transfer.

#### *Power loss via upconversion emission*

The UCNPs in the nanofluid absorb radiation from the near-infrared laser and emit radiation in the visible region. This process will then decrease the amount of absorbed energy that is transformed into heat, so it will not contribute to the heating of the nanofluid and can be considered



as dissipated power. From the definition of the quantum yield and the energies of the absorbed and emitted photons during the upconversion (UC) process, the power loss due to upconversion emission,  $W_{UC}$ , can be expressed as

$$W_{UC} = \frac{\tilde{\nu}_{em}}{\tilde{\nu}_{abs}} \phi_{UC} N_{P,b} \sigma_P P_D \cong 0.015 N_{P,b} \sigma_P P_D \quad (8)$$

where  $\tilde{\nu}_{abs}$  and  $\tilde{\nu}_{em}$  are the absorption and emission wavenumbers,  $\phi_{UC}$  is the quantum yield of the upconversion process,  $N_{P,b}$  is the number of UCNPs within the path of the laser beam,  $\sigma_P$  is the absorption cross section of a single UCNP,  $P_D$  is the power density of the incident laser beam. The last approximation is valid for UCNP nanofluids (e.g. LiYF<sub>4</sub>:6%Er<sup>3+</sup>/29%Yb<sup>3+</sup>) for which  $\tilde{\nu}_{em}/\tilde{\nu}_{abs} \cong 0.5$  and  $\phi \cong 0.03$ .

#### *Power loss via increase of internal energy*

Because the nanofluid within and surrounding the excitation cylinder of the laser beam has a heat capacity,  $c_N$ , it can store energy and the rate of energy storage or the rate of internal energy increase,  $W_{int}(t)$ , is

$$W_{int}(t) = m_N c_N \frac{dT(t)}{dt} \quad (9)$$

where  $m_N$  (in kg) is the mass of the nanofluid and  $c_N$  (in J K<sup>-1</sup> kg<sup>-1</sup>) is the heat capacity of the region where the temperature is increasing. As it was assumed that the species constituting the nanofluid are independent, its capacity to store heat can be separated into two contributions

$$m_N c_N = m_P c_P + m_S c_S \quad (10)$$

with  $m_P$  and  $c_P$  being the mass and heat capacity of the nanoparticles,  $m_S$  and  $c_S$  the mass and heat capacity of the solvent. Furthermore, when the nanoparticles are capped by a lipid bilayer, then

$$m_N c_N = m_P c_P + m_S c_S + m_L c_L \quad (11)$$

where  $m_L$  and  $c_L$  are the mass and heat capacity of the lipid bilayer.

**Power balance equation and analysis.** The power dissipated from the laser heated nanofluid can then be approximated by the sum of contributions in Eqs. (7), (8), and (9), that is,  $\mathbf{W}_{\text{lost}} \cong \mathbf{W}_{\text{ht}}(t) + \mathbf{W}_{\text{UC}} + \mathbf{W}_{\text{int}}(t)$ . Considering that the power gain for the laser heating of the nanofluid is due to absorption from the laser beam:  $\mathbf{W}_{\text{gain}} = \mathbf{W}_{\text{abs}}$ , which is assumed to be completely converted into heat, the following expression for the power balance, Eq. (1), can be obtained

$$W_{\text{abs}} = h_{\text{ht}} A_{\text{cs}} \Delta T(t) + W_{\text{UC}} + m_N c_N \frac{d\Delta T(t)}{dt} \quad (12)$$

where  $\Delta T(t) = T(t) - T_0$ , so  $d\Delta T(t)/dt = dT(t)/dt$ . This equation has the following solution

$$\Delta T(t) = \Delta T_{\text{ss}} (1 - e^{-t/\tau}), \quad \frac{1}{\tau} = \frac{W_{\text{abs}} - W_{\text{UC}}}{m_N c_N \Delta T_{\text{ss}}} \cong \frac{W_{\text{abs}}}{m_N c_N \Delta T_{\text{ss}}} \quad (13)$$

for the initial condition:  $\Delta T(0) = 0$ , with  $W_{\text{abs}}$  being the power absorbed from the laser beam.

From Eq. (8), it is evident that the power dissipated by the upconversion process,  $W_{\text{UC}}$ , is ca. 1.5% of the power absorbed by the UCNPs within the laser beam. However, if the contribution of the solvent is taken into consideration, then the ratio  $W_{\text{UC}}/W_{\text{abs}}$  is  $1.6 \times 10^{-4}$  for the dispersion in  $\text{H}_2\text{O}$  and  $4.1 \times 10^{-3}$  for the dispersion in  $\text{D}_2\text{O}$  at a concentration of 0.6 (g of UCNPs)/L. Thus, the approximation in Eq. (13) is justified.

The solution of the equation describing the laser heating of a nanofluid also provides the following expression for the increase of temperature at the steady-state regime

$$\Delta T_{\text{ss}} \cong \frac{W_{\text{abs}}}{h_{\text{ht}} A_{\text{cs}}}, \quad W_{\text{abs}} = (N_{\text{P,b}} \sigma_{\text{P}} + N_{\text{P,b}} \sigma_{\text{L}} + \sigma_{\text{S}}) P_{\text{D}} \quad (14)$$

where the approximation  $W_{\text{abs}} - W_{\text{UC}} \cong W_{\text{abs}}$  was used. Considering the sample temperature  $T_0 = 300$  K and a temperature increase  $\Delta T = 10$  K, the flux of heat dissipation via thermal radiation,  $W_{\text{rad}}/A_{\text{CS}}$ , is negligible (100 times smaller) compared to the flux of heat dissipation via conduction,  $W_{\text{cond}}/A_{\text{CS}}$ , for a dilute aqueous dispersion. Since the dispersions are not stirred during the laser heating process, the heat transfer via convection may be considered negligible, so that conduction becomes the main mechanism of heat transfer and  $h_{\text{ht}} \cong h_{\text{cond}}$ . Therefore, analysis of the steady-state regime yields Eq. (14), which is consistent with previous work that reported this property the thermal conductivity properties of luminescent and composite nanofluids.<sup>20</sup>

It is noteworthy that the transient regime described by Eq. (13) does not require the determination of the heat transfer properties of the nanofluids, as long as  $\Delta T_{\text{ss}}$  is considered a parameter that can be determined experimentally. In other words, the transient regime is fully described by  $\Delta T_{\text{ss}}$  and  $\tau$  which can be related to the heat transfer properties and to the heat capacities of nanofluids, respectively. In fact, the heat capacity,  $c_{\text{N}}$ , of the nanofluid can be obtained as

$$c_{\text{N}} = \frac{W_{\text{abs}}\tau}{\Delta T_{\text{ss}}m_{\text{N}}}, \quad W_{\text{abs}} = \sigma_{\text{N}}P_{\text{D}} = (N_{\text{P,b}}\sigma_{\text{P}} + N_{\text{P,b}}\sigma_{\text{L}} + \sigma_{\text{S}})P_{\text{D}} \quad (15)$$

where, as mentioned before, the power absorbed,  $W_{\text{abs}}$ , can be determined from the laser power density,  $P_{\text{D}}$ , and the absorption cross section of the nanofluid,  $\sigma_{\text{N}} = N_{\text{P,b}}\sigma_{\text{P}} + N_{\text{P,b}}\sigma_{\text{L}} + \sigma_{\text{S}}$ . The temperature increase at steady-state,  $\Delta T_{\text{ss}}$ , can be measured for each laser power density employed<sup>20</sup>, whereas  $\tau$  can be obtained from the fitting of the temperature increase during the transient regime. Regarding the determination of  $\tau$ , it is relevant to notice that the  $\Delta T(t)$  vs.  $t$  data are dominated by the steady-state regime, as shown in **Figure 1b,c** and Figure S2a. Thus, a direct fit of Eq. (13) is not appropriate and the following linearized form using the reduced temperature,  $\theta(t)$ , was employed

$$\ln[1 - \theta(t)] = -\frac{1}{\tau}t, \quad \theta(t) \equiv \frac{\Delta T(t)}{\Delta T_{ss}} \quad (16)$$

where  $\tau$  was obtained from the inverse of the slope of the linear regime (**Figure 2** and Figure S2b). As shown in **Figure 2** and Figure S2b, the transient regime is accurately described by the linearized model which enables establishment of the limits of the first regime of the transient curve. This analysis was applied to samples of pure water, and dispersions of uncapped and capped UCNPs in H<sub>2</sub>O and D<sub>2</sub>O for several laser power densities. An example of the transient properties are shown in **Table 1**. The complete data related to these properties are presented the Supporting Information (Tables S1 and S6-S8).

As expected from the absorption spectra of the fluids, the absorbed power,  $W_{\text{abs}}$ , is dominated by H<sub>2</sub>O, and even for D<sub>2</sub>O its contribution is significant. The lipid bilayer also has a significant impact in the optical properties of the UCNPs. In fact, the lipid bilayer doubles the absorption cross section of the UCNPs, from 0.16 to 0.32 nm<sup>2</sup>, despite the small increase of ca. 14% of the geometrical cross section, from 2,255 nm<sup>2</sup> for the uncapped UCNP to 2,570 nm<sup>2</sup> for the capped UCNP. This significant increase of the absorption cross section at 980 nm is due to the presence of high energy oscillators such as O–H, N–H, and C–H associated with the lipid bilayer and with hydration molecules in the nanoconstruct (supported lipid bilayer-coated UCNPs). However, despite  $W_{\text{abs}}$  being dominated by water, the nanoparticles have a significant effect on the thermal properties of the fluid, causing a steep increase of  $\Delta T_{\text{ss}}$  and  $\tau$ .

Analysis of the transient regime at three power densities for water (Figure S4 and Table S1) yielded a heat capacity of 4177±367 J·kg<sup>-1</sup>·K<sup>-1</sup>, which agrees within the uncertainty with the reported value of 4181±4 J·kg<sup>-1</sup>·K<sup>-1</sup> at 298 K,<sup>27</sup> showing the reliability of the proposed approach. For the nanofluid comprising uncapped UCNPs in H<sub>2</sub>O, the heat capacity of water shown above was subtracted and a value of 715±57 J·kg<sup>-1</sup>·K<sup>-1</sup> for the uncapped UCNPs was obtained. This

value is in reasonable agreement with that reported for LiYF<sub>4</sub> crystals at room temperature (790 J·kg<sup>-1</sup>·K<sup>-1</sup>).<sup>28-30</sup> Despite the instability of the suspension of UCNPs dispersed in D<sub>2</sub>O, a value for the heat capacity of uncapped UCNPs of 709±93 J·kg<sup>-1</sup>·K<sup>-1</sup> could be derived from measurements at two laser power densities which is also in agreement with the reported value for LiYF<sub>4</sub> crystals. Through this analysis, the main sources of the uncertainty of the heat capacity are the quantities appearing in Eq. (15), namely: i) mass of the UCNPs; ii) number of species exposed to the laser beam; iii) absorption cross-sections; iv) power density, and v) measured parameters  $\tau$  and  $\Delta T_{ss}$ . Note that this analysis also considers the specific heat capacity to be independent of temperature. Nonetheless, because the temperature increase over the transient regime is at most *ca.* 10 K (Figure 1c and Figure S4), this limitation causes a small relative uncertainty of *ca.* 0.03% and 3% in the final values for water and the uncapped UCNPs, respectively.

To the best of our knowledge, this is the first time that the heat capacity of a UCNP has been measured. The similarity of the heat capacity of the UCNPs to that of the bulk LiYF<sub>4</sub> may be attributed to the size of the nanoparticles employed. Specifically, although the literature provides very little data (experimental and computational) for the heat capacities of nanomaterials, it has been reported that particles with sizes larger than *ca.* 70 nm have thermal properties similar to the bulk material, while particles smaller than *ca.* 20 nm display a drastic increase in the specific heat capacity.<sup>31-33</sup>

To determine the specific heat capacity of the lipid bilayer we consider that the heat capacity of the lipid bilayer-capped UCNPs dispersed in H<sub>2</sub>O also comprises a contribution from the lipid bilayer, namely,  $m_N c_N = m_p c_p + m_s c_s + m_L c_L$ , where  $m_L$  and  $c_L$  are the mass and specific heat capacity of the lipid bilayer, respectively. The values of the heat capacity of the lipid bilayer are similar when determined using either the calculated photophysical (715±57 J·kg<sup>-1</sup>·K<sup>-1</sup>) or the

**Commented [CD1]:** Why Tss and not deltaTss?

reported ( $790 \text{ J}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$ )<sup>28-30</sup>  $c_p$  values of  $\text{LiYF}_4$ . Analysis of the transient regime for six laser power densities provided an average value of  $5039\pm 211 \text{ J}\cdot\text{kg}^{-1}\cdot\text{K}^{-1}$  ( $1.20\pm 0.06 \text{ cal}\cdot\text{g}^{-1}\cdot\text{K}^{-1}$ ) for the specific heat capacity of the lipid bilayer, which corresponds to a molar heat capacity of  $2.93\pm 0.12 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ . This value of the molar heat capacity is similar to those obtained by atomistic molecular dynamics simulations<sup>34</sup> for a dipalmitoylphosphatidylcholine (DPPC) lipid bilayer (**Table 2**). Note that the differences in values for the specific heat capacities derive from the significant compositional differences (and hence molecular weight) between our multicomponent bilayer and pure DPPC. Both the current work and the molecular dynamics simulation values are higher than the molar heat capacities measured by differential scanning calorimetry.<sup>35</sup> Even with correction proposed by Blume for lipid phase and chain length, the estimated molar heat capacity of DOPC only increases to  $1.98 \text{ kJ}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$ . However, molar heat capacities obtained herein are not necessarily directly comparable with the calorimetric results owing not only to significant differences in the composition of the bilayer but also to potential differences in hydrophobic hydration.<sup>35</sup> Notably, prior work has focused on single component ('pure') systems rather than the more biologically relevant and complex, mixed-lipid bilayers studied here.

## CONCLUSIONS

Using direct measurements of the transient regime under NIR irradiation of an aqueous dispersion of the nanoconstruct comprising upconverting  $\text{LiYF}_4:\text{Er}^{3+}/\text{Yb}^{3+}$  nanoparticles coated with a conformal lipid bilayer and a power balance model, we demonstrate that the transient regime permits to determine the specific heat capacities of the nanoparticle and the lipid bilayer. The model developed can be considered the first step towards a quantitative description of the dynamics of heat transfer at the nanoscale, which can, in turn, be used to describe heat dissipation

at the cellular level. The approach described is quite versatile because different solvents can be selected that absorb in the NIR region and which can form stable nanofluids with a diversity of nanoparticles which do not need to be luminescent for this generalized model. Moreover, the model can be used to obtain valuable fundamental biophysical characteristics of different lipid and membrane compositions, such as those in mammalian cells, bacterial cells, and viral lipid envelopes.

## METHODS

**Nanofluids:** Dispersions of tetragonal phase  $\text{LiYF}_4:\text{Er}^{3+}/\text{Yb}^{3+}$  were synthesized via thermal decomposition. Capped UCNPs have been coated with a conformal supported lipid bilayer coating. The capped and uncapped (oleate-free<sup>36</sup>) nanoparticles are dispersed in either ultrapure  $\text{H}_2\text{O}$  or  $\text{D}_2\text{O}$ . Nanoparticles were characterized using transmission and scanning electron microscopy and X-ray diffraction. Properties of the UCNPs are provided in Tables S2 and S3. Details of the synthesis and characterization of the nanoparticles have been reported previously.<sup>21</sup>

**Dynamic Temperature Measurements:** The temperature increase ( $\Delta T$ ) when the nanofluid is under NIR irradiation at 980 nm depends on the laser power density ( $P_D$ ) and on the composition of the nanofluid (presence or absence of a conformal lipid bilayer, and the solvent used, as previously observed<sup>20</sup>). The nanofluids were irradiated for 600 s by a pulsed laser (BrixX 980-1000 HD, 1.5 MHz) at 980 nm, with power densities ranging from *ca.* 65 to 250  $\text{W cm}^{-2}$ . The resulting temperature increase was measured over time using an immersed thermocouple (K-type, 0.1 K accuracy) placed *ca.* 0.5 cm away from the limits of the laser spot and always at the same place along the optical pathlength (**Figure 1a**). Because the size of the thermocouple is small (*ca.* 1.5 mm), there is a small variation ( $< 4\%$ ) of  $\Delta T$  along the laser beam path, so  $\Delta T$  monitored by

the thermocouple can be considered uniform (Supporting Information). The laser power density was calculated as described in the Supporting Information.

It is relevant to determine how the temperature increase,  $\Delta T$ , associated with absorption, varies across and along the excitation cylinder of the laser beam path, which will determine the accuracy and reliability of the derived properties as well as establish the temperature monitoring. Assuming constant thermal conductivity, and that the power absorbed from the laser beam is converted into heat, the temperature variation across the laser beam path is  $T_{\text{surface}} - T_{\text{center}} = (N_{\text{p,b}}\sigma_{\text{p}} + \sigma_{\text{s}})P_{\text{D}}/(4\pi\kappa L)$ , which under the experimental conditions used corresponds to a temperature variation of 0.061 K. Given the small size of the focal point,  $\Delta T$  can be assumed to be spatially homogenous within this region (Supporting Information). Regarding the temperature variation along a cylinder defined by the path of the laser beam, the exponential attenuation of the radiant power of the laser beam causes a monotonic decrease of  $\Delta T$  along the optical pathlength by *ca.* 1.6 times (Supporting Information). Therefore, it is very important to ensure that the temperature is always monitored at the same position. Note that temperature monitoring by ratiometric luminescence using the UCNPs will not be addressed in these experiments.

**Description of the Fitting Procedure:** The experimental data were fitted to a first-order exponential decay function. The fit was limited to the first regime of each transient curve, which was established through the linearized representation of the data (**Figure 2**). For each sample, a multi-fit was performed in which all of the transient curves were fitted simultaneously to Eq. (13). As  $\Delta T_{\text{ss}}$  depends on the laser power density, it was fixed for each curve and constrained by the respective errors. In the multi-fit, the parameter  $\tau$  was set as a free variable and identical for all the curves enabling the determination of the  $c_{\text{p}}$  and  $c_{\text{L}}$  values.



## ASSOCIATED CONTENT

### Supporting Information

The Supporting Information is available free of charge on the ACS Publications website.

Additional figures and tables, determination of the laser power density, transient heating curves of UCNPs, determination of properties of the UCNPs and nanofluids, power gain via absorption, energy losses via heat transfer, thermal radiation, increase of internal energy, and upconversion radiation, energy balance rate equation, temperature variations within the excitation cylinder, and additional analysis.

## AUTHOR INFORMATION

### Corresponding Authors

**Luís D. Carlos** – Phantom-g, CICECO - Aveiro Institute of Materials, Department of Physics, University of Aveiro, 3810-193, Aveiro, Portugal; [orcid.org/0000-0003-4747-6535](https://orcid.org/0000-0003-4747-6535); E-mail: [lcarlos@ua.pt](mailto:lcarlos@ua.pt)

**Ricardo L. Longo** – Departamento de Química Fundamental, Universidade Federal de Pernambuco, Cidade Universitária, 50740-560, Recife, PE, Brazil; E-mail: [longo@ufpe.br](mailto:longo@ufpe.br)

**John A. Capobianco** – Department of Chemistry and Biochemistry, and Centre for NanoScience Research, Concordia University, 7141 Sherbrooke St. West, Montreal, Quebec, H4B 1R6, Canada; E-mail: [John.Capobianco@concordia.ca](mailto:John.Capobianco@concordia.ca)

### Authors

**Ana R. N. Bastos** – Phantom-g, CICECO - Aveiro Institute of Materials, Department of Physics, University of Aveiro, 3810-193, Aveiro, Portugal

**Carlos D.S. Brites** – Phantom-g, CICECO - Aveiro Institute of Materials, Department of Physics, University of Aveiro, 3810-193, Aveiro, Portugal

**Paola A. Rojas-Gutierrez** – Department of Chemistry and Biochemistry, and Centre for NanoScience Research, Concordia University, 7141 Sherbrooke St. West, Montreal, Quebec, H4B 1R6, Canada

**Rute A.S. Ferreira** – Phantom-g, CICECO - Aveiro Institute of Materials, Department of Physics, University of Aveiro, 3810-193, Aveiro, Portugal

**Christine DeWolf** – Department of Chemistry and Biochemistry, and Centre for NanoScience Research, Concordia University, 7141 Sherbrooke St. West, Montreal, Quebec, H4B 1R6, Canada

#### **Author Contributions**

A.R.N.B., C.D.S.B., R.A.S.F. and L.D.C. designed the experiments. P.A.R.G., C.D. and J.A.C. designed, synthesized and characterized the nanoconstruct. C.D. and J.A.C provided the analysis of and applicability to biophysical properties. A.R.N.B., C.D.S.B. and L.D.C. performed the transient experiments and analysis. R.L.L. performed the theoretical analysis. Data interpretation and writing of the manuscript was through contributions by all authors. All authors have given approval to the final version of the manuscript.

#### **Notes**


The authors declare no competing financial interest.

#### **ACKNOWLEDGMENTS**


This work has received funding from the European Union's Horizon 2020 FET Open program under grant agreement N° 801305 and was partially developed in the scope of the projects CICECO–Aveiro Institute of Materials UIDB/50011/2020 & UIDP/50011/2020, financed by

Portuguese funds through the FCT/MEC and when appropriate co-financed by FEDER under the PT2020 Partnership Agreement. Financial support from FCT (PTDC/CTM-NAN/4647/2014, NANOHEATCONTROL - POCI-01-0145-FEDER-031469) is acknowledged. J.A. Capobianco is a Concordia University Research Chair in Nanoscience and is grateful to Concordia University and Natural Science and Engineering Research Council (NSERC) of Canada for the sustained support of his research. C. DeWolf is grateful to NSERC for the support of her research. R. Longo is grateful for the Brazilian Agencies CNPq, CAPES, FACEPE, FINEP, and Pronex for providing partial financial support under grants: Pronex APQ-0675-1.06/14, INCT-NANOMARCS APQ-0549-1.06/17, APQ-1007-1.06/15, and CNPq-PQ fellowship (Proc. 309177/2018-9).

FIGURES

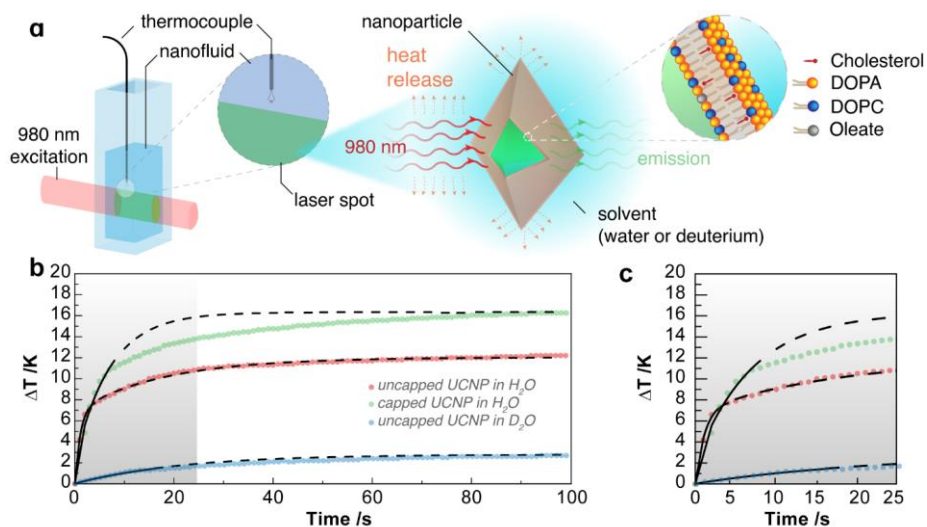

**Figure 1.** (a) Schematic of the experimental setup used to record the temporal dependence of the temperature of the nanofluids under 980 nm excitation. The magnification of the laser spot on the nanofluid represents the heat exchange between the solvent ( $H_2O$  or  $D_2O$ ) and the nanoparticle due to 980 nm excitation, and the composition of the conformal lipid bilayer coating the surface of the nanoparticle. (b) Temperature profiles of the uncapped UCNPs and lipid bilayer-capped UCNPs dispersed in  $H_2O$ , and uncapped UCNPs dispersed in  $D_2O$ , measured under 980 nm excitation ( $222 \text{ W}\cdot\text{cm}^{-2}$ ) using the immersed thermocouple. Dashed lines are fits for the entire data set and continuous lines are fits of the initial period of NIR irradiation. (c) Magnification of the first 25 s (shaded area) of (c) highlighting the fit of the model in the initial period of 980 nm irradiation.

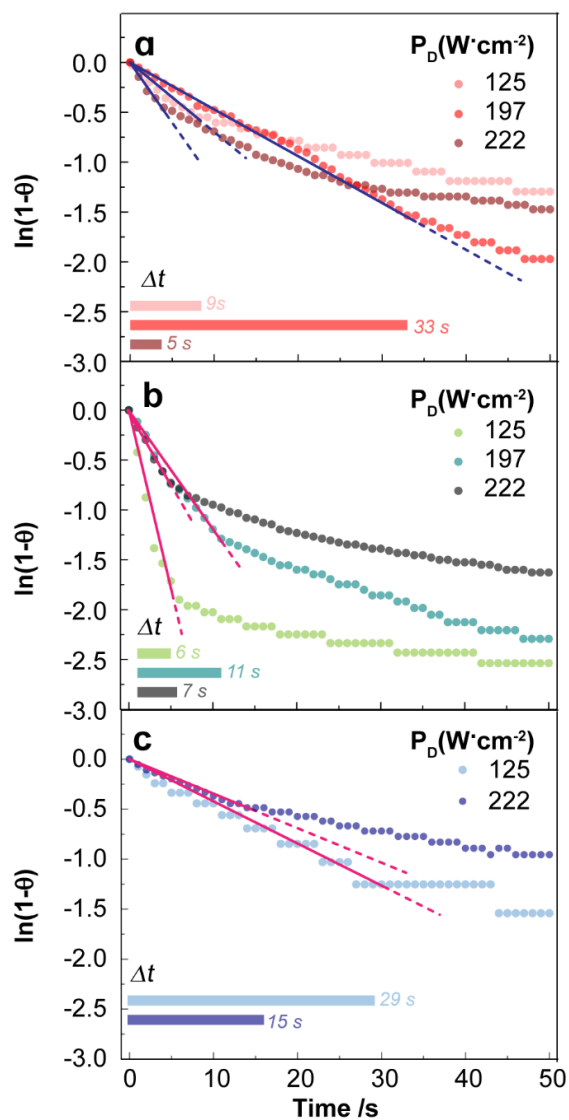

**Figure 2.** Time-dependence of the reduced temperature for the (a) uncapped UCNPs and (b) lipid bilayer-capped UCNPs dispersed in  $H_2O$ , and (c) uncapped UCNPs dispersed in  $D_2O$ , measured by the immersed thermocouple. The logarithmic representation of the reduced temperature,

$\theta(t) \equiv \Delta T(t)/\Delta T_{ss}$ , profiles allows the identification of the time range in which  $\ln[1 - \theta(t)]$  is linear. The horizontal bars mark the time interval,  $\Delta t$ , in which these linear fits are verified. The solid lines are the best fits to Eq. (16) ( $r^2 > 0.970$ ) and the dashed lines are guides for the eyes.

## TABLES

**Table 1.** Properties of nanofluids derived from laser heating for power density of  $222 \text{ W cm}^{-2}$ .

Fluid	$W_{\text{abs}}$ (mW)	$\Delta T_{ss}$ (K)	$\tau$ (s)
Pure water	$8.93 \pm 0.83$	$8.2 \pm 0.1$	$0.31 \pm 0.01$
UCNPs in H <sub>2</sub> O	$9.03 \pm 0.60$	$13.8 \pm 0.1$	$0.51 \pm 0.03$
Capped-UCNPs in H <sub>2</sub> O	$9.08 \pm 0.52$	$16.2 \pm 0.1$	$0.60 \pm 0.03$
UCNPs in D <sub>2</sub> O	$0.35 \pm 0.17$	$3.9 \pm 0.1$	$4.21 \pm 0.39$

**Table 2.** Comparison of the heat capacity values of lipid bilayers,  $c_L$ , obtained using different techniques.

Compound	$c_L$		Technique	Ref.
	( $\text{J} \cdot \text{kg}^{-1} \cdot \text{K}^{-1}$ )	( $\text{kJ} \cdot \text{mol}^{-1} \cdot \text{K}^{-1}$ )		
oleate:DOPA:DOPC:cholesterol (21:51:5:24)	$5039 \pm 211$	$2.93 \pm 0.12$	transient heating of nanofluids	This work
DPPC	3678	2.7	atomistic molecular dynamics simulations	34
DPPC	2166	1.59	differential scanning calorimetry <sup>b</sup>	35
DPPE <sup>a</sup>	2268	1.57		

<sup>a</sup> DPPE: dipalmitoylphosphatidylethanolamine; <sup>b</sup> measured at 293 K.


## REFERENCES

1. Baffou, G.; Rigneault, H.; Marguet, D.; Jullien, L. A Critique of Methods for Temperature Imaging in Single Cells. *Nat. Methods* **2014**, *11*, 899-901.
2. Kiyonaka, S.; Sakaguchi, R.; Hamachi, I.; Morii, T.; Yoshizaki, T.; Mori, Y. Validating Subcellular Thermal Changes Revealed by Fluorescent Thermosensors. *Nat. Methods* **2015**, *12*, 801-802.
3. Suzuki, M.; Zeeb, V.; Arai, S.; Oyama, K.; Ishiwata, S. The  $10^5$  Gap Issue between Calculation and Measurement in Single-Cell Thermometry. *Nat. Methods* **2015**, *12*, 802-803.
4. Rajagopal, M. C.; Brown, J. W.; Gelda, D.; Valavala, K. V.; Wang, H.; Llano, D. A.; Gillette, R.; Sinha, S. Transient Heat Release During Induced Mitochondrial Proton Uncoupling. *Commun. Biol.* **2019**, *2*.
5. Suzuki, M.; Plakhotnik, T. The Challenge of Intracellular Temperature. *Biophys. Rev.* **2020**, *12*, 593-600.
6. Huang, C. H.; Li, S. S. Calorimetric and Molecular Mechanics Studies of the Thermotropic Phase Behavior of Membrane Phospholipids. *Biochim. Biophys. Acta, Rev. Biomembr.* **1999**, *1422*, 273-307.
7. Demetzos, C. Differential Scanning Calorimetry (DSC): A Tool to Study the Thermal Behavior of Lipid Bilayers and Liposomal Stability. *J. Liposome Res.* **2008**, *18*, 159-173.
8. Youssefian, S.; Rahbar, N.; Lambert, C. R.; Van Dessel, S. Variation of Thermal Conductivity of DPPC Lipid Bilayer Membranes around the Phase Transition Temperature. *J. R. Soc. Interface* **2017**, *14*, 20170127.
9. Youssefian, S.; Rahbar, N.; Van Dessel, S. Thermal Conductivity and Rectification in Asymmetric Archaeal Lipid Membranes. *J. Chem. Phys.* **2018**, *148*, 174901.
10. Nakano, T.; Kikugawa, G.; Ohara, T. A Molecular Dynamics Study on Heat Conduction Characteristics in DPPC Lipid Bilayer. *J. Chem. Phys.* **2010**, *133*, 154705.
11. Brites, C. D. S.; Lima, P. P.; Silva, N. J. O.; Millán, A.; Amaral, V. S.; Palacio, F.; Carlos, L. D. Thermometry at the Nanoscale. *Nanoscale* **2012**, *4*, 4799-4829.
12. Jaque, D.; Vetrone, F. Luminescence Nanothermometry. *Nanoscale* **2012**, *4*, 4301-4326.
13. del Rosal, B.; Ximendes, E.; Rocha, U.; Jaque, D. In Vivo Luminescence Nanothermometry: From Materials to Applications. *Adv. Opt. Mater.* **2017**, *5*, 1600508.
14. Dramićanin, M., *Luminescence Thermometry: Methods, Materials, and Applications*. Elsevier: Cambridge, 2018.
15. Brites, C. D. S.; Balabhadra, S.; Carlos, L. D. Lanthanide-Based Thermometers: At the Cutting-Edge of Luminescence Thermometry. *Adv. Opt. Mater.* **2019**, *7*, 1801239.
16. Bai, T. T.; Gu, N. Micro/Nanoscale Thermometry for Cellular Thermal Sensing. *Small* **2016**, *12*, 4590-4610.
17. Uchiyama, S.; Gota, C.; Tsuji, T.; Inada, N. Intracellular Temperature Measurements with Fluorescent Polymeric Thermometers. *Chem. Commun.* **2017**, *53*, 10976-10992.
18. Yang, J. M.; Yang, H.; Lin, L. W. Quantum Dot Nano Thermometers Reveal Heterogeneous Local Thermogenesis in Living Cells. *ACS Nano* **2011**, *5*, 5067-5071.
19. Shang, L.; Stockmar, F.; Azadfar, N.; Nienhaus, G. U. Intracellular Thermometry by Using Fluorescent Gold Nanoclusters. *Angew. Chem. Int. Ed.* **2013**, *52*, 11154-7.
20. Bastos, A. R. N.; Brites, C. D. S.; Rojas-Gutierrez, P. A.; DeWolf, C.; Ferreira, R. A. S.; Capobianco, J. A.; Carlos, L. D. Thermal Properties of Lipid Bilayers Determined Using Upconversion Nanothermometry. *Adv. Funct. Mater.* **2019**, *29*, 1905474.

21. Rojas-Gutierrez, P. A.; DeWolf, C.; Capobianco, J. A. Formation of a Supported Lipid Bilayer on Faceted LiYF<sub>4</sub>: Tm<sup>3+</sup>/Yb<sup>3+</sup> Upconversion Nanoparticles. *Part. Part. Syst. Char.* **2016**, *33*, 865-870.
22. Hentschke, R. On the Specific Heat Capacity Enhancement in Nanofluids. *Nanoscale Res. Lett.* **2016**, *11*.
23. Roselli, R. J.; Diller, K. R., *Biotransport: Principles and Applications*. Springer: New York, 2011.
24. Michelsen, H. A. Understanding and Predicting the Temporal Response of Laser-Induced Incandescence from Carbonaceous Particles. *J. Chem. Phys.* **2003**, *118*, 7012-7045.
25. Michelsen, H. A.; Liu, F.; Kock, B. F.; Bladh, H.; Boiarciuc, A.; Charwath, M.; Dreier, T.; Hedef, R.; Hofmann, M.; Reimann, J.; Will, S.; Bengtsson, P. E.; Bockhorn, H.; Foucher, F.; Geigle, K. P.; Mounaim-Rousselle, C.; Schulz, C.; Stirn, R.; Tribalet, B.; Suntz, R. Modeling Laser-Induced Incandescence of Soot: A Summary and Comparison of LII Models. *Appl. Phys. B-Lasers O* **2007**, *87*, 503-521.
26. Bergman, T. L.; Lavine, A. S.; Incropera, F. P.; DeWitt, D. P., *Fundamentals of Heat and Mass Transfer*. 7 ed.; Wiley: New York, 2011.
27. Haynes, W. M., *Crc Handbook of Chemistry and Physics*. CRC Press: Boca Raton, FL, 2017.
28. Ballard, S. S.; Browder, J. S., Optical Materials. In *Handbook of Laser Science and Technology*, Weber, M. J., Ed. CRC: Boca Raton, FL, 1986; Vol. IV, p 52.
29. L. G. DeShazer, S. C. R., B. A. Wechsler, Optical Materials. In *Handbook of Laser Science and Technology*, Weber, M. J., Ed. CRC: Boca Raton, FL, 1987; Vol. V, p 328.
30. Aggarwal, R. L.; Ripin, D. J.; Ochoa, J. R.; Fan, T. Y. Measurement of Thermo-Optic Properties of Y<sub>3</sub>Al<sub>5</sub>O<sub>12</sub>, Lu<sub>3</sub>Al<sub>5</sub>O<sub>12</sub>, YAlO<sub>3</sub>, LiYF<sub>4</sub>, LiLuF<sub>4</sub>, BaY<sub>2</sub>F<sub>8</sub>, KGd(WO<sub>4</sub>)<sub>2</sub>, and KY(WO<sub>4</sub>)<sub>2</sub> Laser Crystals in the 80–300 K Temperature Range. *J. Appl. Phys.* **2005**, *98*, 103514.
31. Saeedian, M.; Mahjour-Shafiei, M.; Shojaei, E.; Mohammadizadeh, M. R. Specific Heat Capacity of TiO<sub>2</sub> Nanoparticles. *J. Comput. Theor. Nanos.* **2012**, *9*, 616-620.
32. Wu, X. M.; Wang, L.; Tan, Z. C.; Li, G. H.; Qu, S. S. Preparation, Characterization. And Low-Temperature Heat Capacities of Nanocrystalline TiO<sub>2</sub> Ultrafine Powder. *J. Solid State Chem.* **2001**, *156*, 220-224.
33. Gafner, S. L.; Redel, L. V.; Gafner, Y. Y.; Samsonov, V. M. Peculiar Features of Heat Capacity for Cu and Ni Nanoclusters. *J. Nanopart. Res.* **2011**, *13*, 6419-6425.
34. Sun, L. P.; Bockmann, R. A. Membrane Phase Transition During Heating and Cooling: Molecular Insight into Reversible Melting. *Eur. Biophys. J.* **2018**, *47*, 151-164.
35. Blume, A. Apparent Molar Heat-Capacities of Phospholipids in Aqueous Dispersion - Effects of Chain-Length and Head Group-Structure. *Biochemistry* **1983**, *22*, 5436-5442.
36. Bogdan, N.; Vetrone, F.; Ozin, G. A.; Capobianco, J. A. Synthesis of Ligand-Free Colloidally Stable Water Dispersible Brightly Luminescent Lanthanide-Doped Upconverting Nanoparticles. *Nano Lett.* **2011**, *11*, 835-840.



## TABLE OF CONTENTS

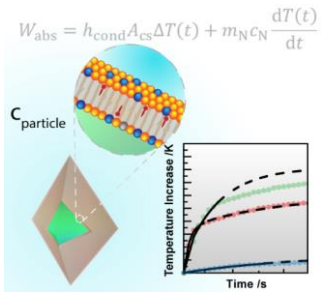

A simple, cost-effective experimental method and associated model that uses the transient heating regime to derive the nanoscale thermal properties of a nanoconstruct in which a conformal lipid bilayer is supported on a upconverting nanoparticle can be used to described heat dissipation at the cellular level.