

8 November, 1898.

WILLIAM HENRY PREECE, C.B., F.R.S., President,  
in the Chair.

(*Paper No. 3137.*)

“The Extraction of Nickel from its Ores by the  
Mond Process.”

By WILLIAM CHANDLER ROBERTS-AUSTEN, C.B., D.C.L., F.R.S.,  
Assoc. Inst. C.E.

THE rules of the Institution enact that those elected into it shall submit a Paper within a year of election. In complying with this direction, the Author was satisfied that no better subject could be selected for consideration than the interesting process which marks an entirely new departure, in metallurgical practice, from the principles which have hitherto guided it. This process depends on the remarkable property possessed by nickel of forming a volatile compound with carbonic oxide, or, as it is called in modern chemical nomenclature, carbon-monoxide. When this gaseous compound is heated to  $180^{\circ}$  C. nickel is released in the metallic form.

The Author was much impressed during a recent visit to Canada with the Imperial importance of the great nickeliferous district of Sudbury, Ontario. In view of the magnitude of this deposit, the annual production of metallic nickel in Canada seems inadequate, as it has hitherto not exceeded 2,750 tons. The description therefore of any new process which affords a hope of hastening the development of this remarkable district should prove to be interesting. The deposit itself presents many points of interest. According to Professor Coleman of Toronto, the nickel ores of Ontario resemble the gold ores of Rossland in British Columbia, as they consist of a mixture of pyrrhotite (magnetic pyrites) and copper pyrites. These sulphides form enormous masses near the margin of large areas of diorite, or weathered gabbro of Huronian age, the amount of nickel contained in the ore averaging between  $2\frac{1}{2}$  per cent. and 10 per cent., the lower proportion being the

more common. It is worthy of note that pyrrhotine from other parts of the country, found in association with Laurentian rocks, is almost barren of nickel. The importance of the nickel deposits of Ontario may be judged from the fact that, until the mines in the Sudbury region were worked, the world's supply of the metal was drawn chiefly from the mines of New Caledonia, an island in the Southern Pacific, supplemented by the Gap mine in Pennsylvania, and a few isolated mines in Norway and Hungary. The extent of the Sudbury deposits is greater than any of these, and New Caledonia, which belongs to France, is virtually the only rival of Ontario in the production of nickel.

The ore at Sudbury is smelted into a regulus, or matte, which contains between 12 per cent. and 20 per cent. of nickel, and about the same amount of copper, although usually there is rather more copper than nickel. This matte may be enriched by suitable treatment, and is "Bessemerized" into a regulus which contains about 40 per cent. of nickel, and is specially free from iron, as the following analyses show:—

ANALYSES OF BESSEMER MATTE UNROASTED.

—	I.	II.
	Per cent.	Per cent.
Nickel . . . . .	40·938	31·35
Copper . . . . .	45·714	48·86
Iron and ( $\text{Al}_2\text{O}_3$ ) . .	0·405	0·81
Cobalt . . . . .	0·136	..
Sulphur . . . . .	11·960	..

It is unnecessary to give a history of the metallurgy of nickel, but it may be well to state that Chronstet isolated the metal in the year 1751, and that Bergman confirmed his discovery in 1774. The methods hitherto employed for extracting the metal from its ores are very complicated; they have involved concentrating the nickel either as a sulphide (matte or regulus), or as arsenide (speise) followed by either "dry" or "wet" treatment. In the case of certain ores, wet methods only have been employed. The metallic nickel has always to be subjected to a process of refining, mainly, as in the case of cast iron, with a view to separate it from associated carbon.

As regards the process which forms the subject of this Paper a few brief historical details may be offered. In 1889 Dr.

Ludwig Mond, F.R.S., in collaboration with Dr. Carl Langer, was engaged in working out a method for eliminating the carbon-monoxide from gases containing hydrogen<sup>1</sup> which they wanted for use in their gas battery.<sup>2</sup> In attempting to effect this, they were guided by the observation they had previously made that finely divided nickel has the remarkable property of removing carbon from carbon-monoxide at a temperature of 350° C., converting it into carbon-dioxide, while the dissociation of carbon-monoxide by heat alone, according to Victor Meyer and Carl Langer, remains incomplete at the high temperature of 1,690° C. In the course of these experiments, which they carried out in conjunction with Dr. Friedrich Quincke,<sup>3</sup> finely divided nickel, formed by reducing nickel oxide at 350° C. by hydrogen, was treated with pure carbon-monoxide in a glass tube at varying temperatures. In order to keep the poisonous carbon-monoxide out of the atmosphere of the laboratory the gas escaping from the apparatus was ignited. They found to their surprise that while the tube containing the nickel was cooling, the flame of the escaping gas became luminous and increased in luminosity as the temperature sank below 100° C. Metallic spots were, moreover, deposited on a cold plate of porcelain held in this luminous flame, just as spots of arsenic are obtained in applying the Marsh test for that metal. It was also observed that on heating the tube through which the gas was escaping, a metallic mirror was obtained, while the luminosity of the flame disappeared. On examination these metallic deposits were found to be pure nickel. The next step was to endeavour to isolate this curious and interesting nickeliferous compound, by preparing nickel with great care at the lowest possible temperature, and treating it with carbon-monoxide at about 50° C. The amount of the volatile nickel compound in the gases passing through the apparatus was thus gradually increased. The gases issuing from the apparatus were treated with a solution of cuprous chloride to absorb the excess of carbon-monoxide, and in this way a residue of several cubic centimetres of a colourless gas was obtained, containing the volatile nickel compound. By passing this gas through a heated tube the nickel and carbon-monoxide were again separated, and the volume of the carbon-mon-

<sup>1</sup> Ludwig Mond and C. Langer. "Improvements in obtaining Hydrogen," British Patent No. 12,608, 1888.

<sup>2</sup> Ludwig Mond and C. Langer. "A new form of gas battery." Proceedings of the Royal Society, vol. xlv. p. 296.

<sup>3</sup> Ludwig Mond, C. Langer, and F. Quincke. Journal of the Chemical Society, vol. lvii. p. 749.

oxide thus set free was found to correspond to about four equivalents of carbon-monoxide to one equivalent of nickel. By further improving the method of preparing the finely divided nickel, and by passing the resulting gases through a refrigerator cooled by snow and salt, the investigators at last succeeded in obtaining the new compound in a liquid state, and were able to produce it with facility in any desired quantity.

Nickel carbonyl in its pure state is a colourless liquid boiling at  $43^{\circ}$  C.; it has a specific gravity of 1.3185 at  $17^{\circ}$  C., and solidifies at  $-25^{\circ}$  C. into needle-shaped crystals. It is soluble in alcohol, petroleum and chloroform; and it is not acted upon by dilute acids or alkalies. It can be readily distilled without decomposition, but on heating the vapour to  $150^{\circ}$  C., it is completely dissociated into its components, pure carbon-monoxide being obtained, while the nickel is deposited in a dense metallic film upon the sides of the vessel in which the compound is heated.

After the production of nickel carbonyl had become easy, Drs. Mond, Langer, and Quincke directed their attention to the action of carbon-monoxide on other metals. A series of experiments was made with a view to obtain a similar compound with cobalt, which in its chemical and physical behaviour so much resembles nickel. The experiments gave, however, the unexpected result that, unlike nickel, cobalt will not combine with carbon-monoxide. Experiments were then made with iron, and indications were soon obtained of the existence of a volatile compound of iron and carbon-monoxide; a long time elapsed before this new compound was obtained in a pure state. It was finally isolated in a way similar to that by which the nickel carbonyl had been prepared, and proved to be a somewhat viscous liquid of pale yellow colour.<sup>1</sup> Its specific gravity at  $18^{\circ}$  C. is 1.4664; and it distils completely without decomposition at  $102.8^{\circ}$  C. under a pressure of 749 millimetres of mercury. When cooled to  $-21^{\circ}$  C. it solidifies into a mass of yellowish needle-shaped crystals. Its chemical composition is somewhat different from the nickel carbonyl, as it contains five equivalents of carbon-monoxide to one of iron. The liquid compound, to which the name of iron penta-carbonyl was given, undergoes no change when protected from the action of light, but exposure to daylight for several hours in a sealed tube is attended with the formation of gold-coloured, tabular crystals, and carbon-monoxide is evolved, so that the

---

<sup>1</sup> Ludwig Mond and Carl Langer on "Iron Carbonyls." Journal of the Chemical Society, vol. lix. p. 1090.

pressure in the tube rises considerably. The crystals have, when dried, a metallic lustre, and resemble flakes of gold; they contain two equivalents of iron to seven equivalents of carbon-monoxide. None of the other metals which were submitted to investigation showed indications of combining directly with carbon-monoxide.

The discovery that in a mixture of metals only nickel and iron would form volatile compounds with carbon-monoxide, and that they could, therefore, be separated from the other metals, was sufficiently important to induce Dr. Mond to arrange laboratory experiments with ores containing nickel, cobalt, iron, copper, &c., such as "kupfer-nickel" and "pyrrhotite." The experiments afforded such promising results that apparatus of considerable size, though still well within the limits of the resources of a laboratory, was set up, and in it several pounds of ore could be treated with carbon-monoxide.<sup>1</sup> A patent was also applied for on the 12th August, 1890, which describes the way in which such ores may be treated. It is pointed out that the principal nickel ores which are metallurgically treated contain the nickel in combination with arsenic and sulphur besides other metals and gangue. These ores have first to be submitted to the process of calcination, in order that the nickel may be present in the form of oxide, and to drive off, as far as is practicable, the arsenic, sulphur, and other volatile bodies. The resulting oxide of nickel is treated with reducing gases, such as water-gas or producer-gas, in order to convert the oxide of nickel into finely divided metallic nickel; the material containing it then is cooled to about 50° C., and is treated with carbon-monoxide. In dealing with nickel ores which contain nickel oxide in chemical combination with silicic acid, arsenic acid, or other substances which cannot be removed by calcination, the ores are so treated as to convert the nickel into nickel speise or nickel matte, which is then subjected to calcination.

In 1892 an experimental plant on a large scale was erected at Smethwick, near Birmingham. After some years of patient work, during which the plant had several times to be reconstructed, in order to meet all the conditions of this somewhat delicate process, the plant gradually assumed the shape shown in Figs. 1, Plate 1. Before describing it in detail it will be well to give a brief account of the operations involved in the process, which are the outcome of many years of practical experience.


---

<sup>1</sup> Ludwig Mond on "Metallic Carbonyls." Proceedings of the Royal Institution, vol. xiii. p. 668.

The process is more especially suitable for the extraction of nickel from ores which contain copper in addition to nickel and iron. These ores, which have on an average between 2 per cent. and 6 per cent. of nickel and about the same amount of copper, are first subjected to "heap roasting," to eliminate the greater part of the sulphur, and to convert the iron which forms their chief constituent into oxide. The roasting is necessary to enable the iron in the following operation of smelting to combine with the silica present in the ore to form a slag, and thus to effect the separation of the iron from the nickel and copper which unite with the remainder of the sulphur to form a regulus or matte. This matte contains the nickel and copper in a more concentrated form, the amount of each metal being usually 15 per cent. to 20 per cent., the residue consisting mainly of sulphur and iron. To concentrate the nickel and copper still further, the matte is "Bessemerized." A sample of such "Bessemerized" matte is exhibited; it contains 31·37 per cent. of nickel, 48·62 per cent. of copper and 0·70 per cent. of iron. It was prepared by the Canadian Copper Company, Sudbury, Ontario, from their ores, which contain an average of 4 per cent. of nickel and 4 per cent. of copper. This "Bessemerized" matte is crushed, ground, and subjected to a calcining operation so as to convert the sulphides into oxides, and it is then passed through a mill and dresser. This calcined Bessemer matte then consists practically of nickel oxide and copper oxide in varying quantities. It has been found in the practical working of the process to be advantageous to further concentrate the nickel by extracting part of the copper at this stage by treating the mixtures of oxides with dilute sulphuric acid, which dissolves about two-fifths of the copper present without taking up more than 1 per cent. to 2 per cent. of the nickel. The copper thus dissolved is in the form of copper sulphate and is obtained in a marketable form by crystallization. The undissolved residue from this operation contains between 45 per cent. and 60 per cent. of nickel, and after drying it is subjected to a carefully regulated reducing process by means of water-gas, after which it is treated with carbon-monoxide to extract part of the nickel present. In this first treatment with carbon-monoxide about two-thirds of the nickel can be easily extracted; after this amount is volatilized the extraction becomes much slower, so that it has been found advantageous to recalcine the residues and repeat the copper extraction, the reduction, and the nickel extraction.

The five operations involved are diagrammatically illustrated in *Fig. 2*. The process begins, as will be seen, at one

end with the material to be treated, "Bessemerized" matte; it ends with the market product nickel. The "Bessemerized" matte proceeds, as the arrow indicates, to the first operation (1) of dead roasting, and for this purpose any suitable furnace may be employed. After roasting, the matte contains 35 per cent. of nickel, 42 per cent. of copper, and about 2 per cent. of iron.<sup>1</sup> It then passes to the second operation (2) for the extraction of part of the copper (about two-thirds) by sulphuric acid, the copper being sold as crystallized sulphate of copper. The residue from this process contains about 51 per cent. of nickel and 21 per cent. of copper, and passes to the third operation (3) for reducing the nickel and incidentally the remaining copper, to the metallic state, care being taken to avoid reducing the iron. This is effected in a tower provided with shelves, over which mechanical rabblers pass, the reducing agent being the hydrogen contained in water-gas. The temperature does not exceed 300° C., and should be kept lower when much iron is present. From this tower the ore is conveyed continuously to the fourth operation (4) of volatilization, in which part of the nickel is taken away by carbon-monoxide and forms the com-

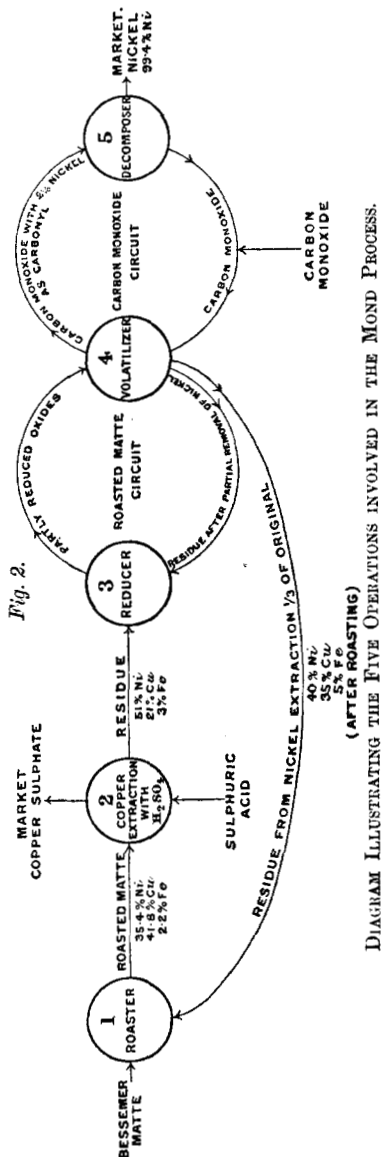

<sup>1</sup> Average results are given in the Fig. rather than the best which have been obtained.

pound nickel carbonyl. The formation of this volatile compound is effected in a tower similar to the reducing tower, but the temperature is much lower, and does not exceed  $100^{\circ}\text{C}$ . From the volatilizer, the ore is returned to the reducer (3), and it continues to circulate between stages (3) and (4) for a period varying between 7 days and 15 days, until about 60 per cent. of the nickel has been removed as nickel carbonyl. The residue from this operation, amounting to about one-third of the original calcined matte, and not differing much from it in composition, is returned to the first operation and then naturally follows the same course as before. The nickel carbonyl produced in the fourth operation, passes to the decomposer (5). This appliance is either a tower or a horizontal retort, which is heated to a temperature of  $180^{\circ}\text{C}$ ., so as to decompose the nickel carbonyl and release the nickel in the metallic form, either on thin sheets of iron or, preferably, on granules of ordinary commercial nickel. Carbon-monoxide is also released, and is returned to the volatilizer to take up a fresh charge of nickel. It will be evident that, when the operation is in progress, the gaseous carbon-monoxide and the partially reduced oxides of nickel and copper are continuously revolving in two separate circuits which join and cross each other in the volatilizer (4). The commercial product contains between 99.4 per cent. and 99.8 per cent. of nickel.

It will now be possible to proceed to a description of the working as the Author saw it in full operation in Smethwick a few months ago. The details are clearly indicated in the plan of the works, Figs. 1, Plate 1. The material under treatment during the Author's visit was of Canadian origin, and had been received as calcined Bessemer matte containing 35.4 per cent. of nickel, 41.8 per cent. of copper, and about 2 per cent. of iron. This material was first passed through a ball mill and dresser with a sixty-mesh riddle, and was then treated in quantities of 3 cwt. in a small lead-lined mixer with 200 lbs. of ordinary sulphuric acid, which had previously been diluted with about 20 cubic feet of mother liquor from previous operations. These appliances are shown in the right-hand portion of the plan and elevation, Figs. 1. The temperature of the mixture soon rises by the action between the copper oxide and the sulphuric acid, and is kept, by means of a steam-jet, at a temperature of about  $85^{\circ}\text{C}$ . for  $\frac{1}{2}$  hour. From this mixer, the charge is run out into a centrifugal hydro-extractor, provided with a filtering cloth, in which the solution of copper sulphate is separated from the solid residue containing



the nickel. After the filtration of the charge is finished, the speed of the hydro-extractor is increased, and the residue is thus rendered sufficiently free from the liquor.

The solution containing the extracted copper runs from the hydro-extractor into a well, from which it is pumped into the crystallizing vats shown in the Figs. After a period of about 8 days to 10 days, the crystals of copper sulphate are taken out of the vats and the mother liquor is mixed with fresh acid and is again used for the extraction of copper. As already mentioned, a small amount of nickel and a little iron are also dissolved in the sulphuric acid during the copper extraction, so that the mother liquor from which the copper sulphate has crystallized becomes gradually contaminated with these two metals. It is therefore necessary to replace some of the mother liquor from time to time by fresh water, and to recover the nickel from the solution. The simplest method is to evaporate the solution to dryness and to roast the nickel and copper sulphates so obtained. The oxidized material is again introduced into the main process. The copper sulphate crystals from the crystallizing vats are charged into a second hydro-extractor, where they are washed with a little clean water to remove all acidity; they are then dried and are ready for packing. The copper sulphate thus obtained is sufficiently pure for the market, as it contains only 0.05 per cent. of nickel and 0.048 per cent. of iron.

The residue from the copper extraction is taken from the hydro-extractor and stored in a bin until a sufficient quantity has been collected to make up a charge of 5 tons to 6 tons for the nickel-extracting plant. It now contains 52.5 per cent. of nickel, 20.6 per cent. of copper, and 2.6 per cent. of iron. The material is charged by hand at the rate of  $\frac{1}{2}$  ton per hour into a feeding-hopper, described as the matte inlet in the lower part of the plan, Figs. 1, Plate 1, which communicates, through a rotary valve, with the conveyor, consisting of a tube enclosing a revolving spiral, which transports the material to an elevator. This lifts the material to the top of the reducing tower, and discharges it through another rotary valve into this reducing tower.

The reducer and the volatilizer (shown in the centre of Figs. 1) in which the treatment with carbon-monoxide takes place, are fully described in Dr. Mond's patent (No. 23,665 of December 10th, 1895). The reducer consists of a vertical tower about 25 feet high, containing a series of shelves, which are hollow so as to admit of their being raised to a temperature of 250° C. by producer gas. The roasted matte falling on these shelves from above is


stirred and made to descend from one shelf to that below it by rabblies actuated by a central vertical shaft. Water-gas passes up the tower to effect the reduction of the material. There are about fourteen of these shelves or trays in the tower. The five lower shelves are not heated by producer gas, but are cooled by a stream of water in order to reduce the temperature of the roasted and reduced matte to the temperature at which the volatilizer is worked.

The volatilizing tower resembles the reducer, but the shelves are not hollow, as there is no necessity to heat them. The reduced nickel requires a temperature of only  $50^{\circ}$  C. to enable it to combine with carbon monoxide and form a volatile compound, and the matte and gas are sufficiently hot to maintain this temperature. In the plant at Smethwick the volatilizer was made the same size as the reducer, but in the new plant it is somewhat smaller.

The decomposer has been devised with much care, and has, in its present form, only recently been patented. The nickel is deposited in it, from its gaseous compound with carbon-monoxide, on granules of ordinary commercial metal. The arrangements by which this is effected are very ingenious, and may be described almost in the words of Dr. Mond's latest patent. The object is to obtain metallic nickel from nickel carbonyl in the form of pellets, which are specially suitable for the production of nickel alloys. For this purpose gases containing nickel carbonyl are passed through granulated nickel, which is kept at the temperature required for the decomposition of the carbonyl—about  $200^{\circ}$  C. The nickel which thus separates from the carbonyl becomes deposited on the granulated nickel, which consequently increases in size. In order to prevent cohesion of the granulated nickel, it is kept in motion. When a number of the pellets have attained a convenient size, they are separated by sifting without interrupting the depositing operation, the smaller granules being returned to receive a further deposit from the nickel carbonyl. A convenient form of apparatus for effecting the process described is shown in *Figs. 3*, which represent vertical sections of the apparatus on planes at right angles to each other. A is a cylindrical vessel, preferably built up of short cylinders, *a a*, bolted together; it contains a central tube, C, provided with gas outlet holes, O, through which the gas containing nickel carbonyl, entering at the gas inlet, B, passes into the vessel which is filled with shot, or small granules, of nickel. The gas permeates through the interstices between these granules, and is brought into intimate contact with them, and when the nickel carbonyl is decomposed, the nickel is deposited

on the granules. The gases finally escape through the outlets, L, into the gas-exit pipe, M. In order to prevent the granules from cohering, they are kept slowly moving by continuously withdrawing some of the granules from the bottom of the cylindrical vessel, A, by means of a right- and left-handed worm conveyor, U, which delivers the granules into two sifting-drums, N. The smaller granules fall on to the inclined plane, W, and collect at

*Figs. 3.*

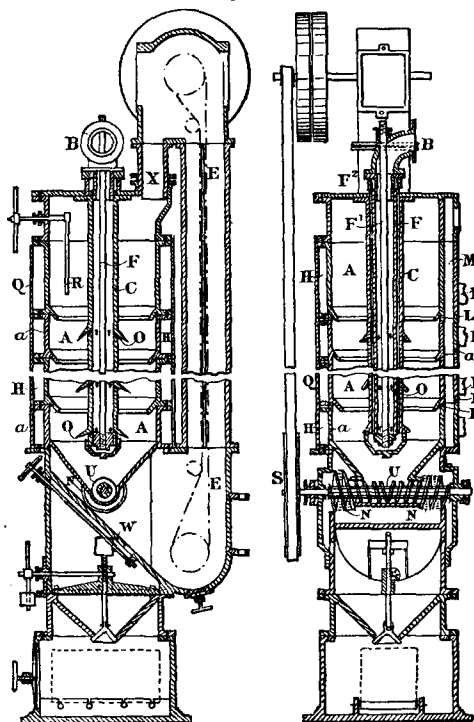

VERTICAL SECTIONS THROUGH THE DECOMPOSER.

the base of the elevator, E, which conveys them again to the top of the cylinder, A, and feeds them through the feeding-hole, X. In order to avoid the deposition of nickel from the nickel carbonyl in the central tube, C, it is kept cool by causing water to circulate down the tube, F, and up through passages, F<sup>1</sup>, formed in the central tube, to the water outlet, F<sup>2</sup>. The cylindrical vessel, A, is surrounded by a wrought-iron casing, Q, which forms heating-spaces, H, communicating with heating-flues, P, which are so

arranged that the temperature of each cylinder can be separately regulated by dampers, so as to maintain the temperature of the granules of nickel contained in the vessel, A, at about  $200^{\circ}$  C., at which temperature the nickel carbonyl is decomposed. With a view to ascertain whether the cylinder, A, is full of granules, a rod, R, is fixed to the spindle of an external handle, which can be turned partly round, so that if the operator feels resistance to the motion of the R, it is certain that the granules extend to that height. The appliance used for depositing the nickel originally consisted of a series of retorts lined with thin steel sheets, on which the nickel was deposited in layers. It was found, however, that the metal so obtained was very difficult to cut, and the

Fig. 4.



PHOTO-MICROGRAPH OF A GRANULE OF NICKEL,  
MAGNIFIED THREE DIAMETERS.

apparatus above described was accordingly devised.

A magnified section of a granule of nickel, which was about  $\frac{3}{4}$  inch in diameter, is shown in Fig. 4. It will be seen that there is a core of nickel which under higher magnification shows a crystalline and convoluted structure, and this core is surrounded by concentric layers. The central core is ordinary commercial nickel, and the layers are nickel deposited from its carbonyl.

In some cases granules of

deposited nickel are found without any central core. These have grown from minute fragments of deposited nickel which have become detached during the course of deposition.

The water-gas used in the reducer is generated in gas-producers, three of which are shown on the left of the plan, Fig. 1, Plate 1. Anthracite is used to decompose the steam, and the water-gas is collected in a gas-holder, whence it is taken to the reducing tower, to which reference has just been made. This gas contains, on entering the reducer, about 60 per cent. of hydrogen.

The reducing operation is so regulated that only a small quantity of hydrogen remains in the escaping gas, as a rule not more than 5 per cent. to 10 per cent. This waste gas is subjected to the action of a fine water-spray (not shown in the Fig.), which

condenses the steam generated by the combustion of the hydrogen in the water-gas. Part of this waste gas is used for making the carbon-monoxide required in the volatilizer, by passing it through the CO retort charged with incandescent charcoal, Fig. 1, which reduces the carbon-dioxide contained in the waste gas, and this increases the amount of carbon-monoxide in it. The gas issuing from this retort contains about 80 per cent. of carbon-monoxide, and is stored in another gasholder, which communicates with the main circuit of the carbon-monoxide gas. This main circuit of the carbon-monoxide passes through the volatilizer already referred to, where the nickel is taken up. The carbon-monoxide, now charged with nickel, passes through a filter to separate the fine particles of matte-dust from the gases, then through an apparatus called the decomposer, and so described in the figure. In this decomposer the nickel taken up in the volatilizer is deposited. The gas now deprived of its nickel passes to the CO blower, Figs. 1, which sends the carbon-monoxide to the volatilizer in order that it may take up a fresh charge of nickel.

The solid material from which the nickel is being extracted is kept circulating through the reducer and volatilizer for a period varying between 7 days and 15 days, during which time the oxides are gradually reduced to the metallic state and the nickel volatilized. When the material originally charged in has had the bulk of its nickel extracted it is run out through a rotary calciner roaster, Figs. 1, which converts the metals into oxides, so that they may be treated for the second time with sulphuric acid and carbon-monoxide. The ratio between the nickel and copper in the residues from the nickel extraction is practically the same as in the calcined Bessemer matte, with which the operations were started, but the amount of iron has increased by the removal of the copper and nickel, as the following figures show:—Original matte contains, nickel, 35·27 per cent., copper, 41·87 per cent., iron, 2·13 per cent. After the first treatment of copper and nickel extraction, the quantities are, nickel, 35·48 per cent., copper, 38·63 per cent., iron, 4·58 per cent.; and after the second copper and nickel extraction, nickel, 35·83 per cent., copper, 35·56 per cent., and iron, 7·82 per cent. The amount of nickel extracted in these two cases was, after the first treatment 61 per cent., and after the second treatment 80 per cent. of the nickel present in the original matte. It must be remembered, however, that in the second treatment only one-third of the original amount remains to be treated, while the final residue is only one-tenth. To avoid the formation of iron carbonyl, the temperature in the

reducer has to be kept very low, and if this is done, the nickel extracted from a matte originally containing as much as between 6 per cent. and 10 per cent. of iron will not contain more than 0.5 per cent. of iron. If the amount of iron in the residues rises above this percentage, the extraction of the nickel is very much delayed, on account of the low temperature which must be maintained in the reducer. It is necessary, in such a case, to re-smelt the residues before proceeding with the extraction of the nickel and copper. The following are analyses of the deposited nickel :—

	I.	II.
	Per cent.	Per cent.
Nickel . . . . .	99.82	99.43
Iron and ( $\text{Al}_2\text{O}_3$ ) . .	0.10	0.43
Sulphur . . . . .	0.0068	0.0099
Carbon . . . . .	0.07	0.087
Insoluble residue . .	..	0.026

The experimental plant at Smethwick has been working for some time, and about 80 tons of nickel have already been extracted in it from different kinds of matte. The results obtained were quite satisfactory, and they point to the conclusion that the process is fully able to compete with any other process at present in use for the production of metallic nickel.

By the kindness of Dr. Mond, the Author is able to exhibit plans for a large manufacturing plant, and Figs. 5, Plate 1, show a vertical elevation, sectional plan and cross-section of it. This plant will, it is estimated, produce 1,000 tons of nickel per year. The plant is so arranged that the matte is continuously charged into the first reducer and traverses the whole set of appliances. When the matte issues from the last volatilizer the first nickel extraction is finished. The matte is re-roasted and submitted to the second copper and nickel extraction. There are ten appliances, consisting of one large reducer, eight combined reducers and volatilizers, and one large volatilizer. They are so arranged that the matte has first to pass through the large reducer, and is then lifted, by means of an elevator and conveyor, into a volatilizer (erected on the top of the next reducer). The relative positions of the reducers and volatilizers are best shown in the cross section, Figs. 5. It passes through the volatilizer into the upper portion of the reducer and in traversing this it is further reduced. It is then lifted again to the next volatilizer, and so on till it finally reaches the larger volatilizer

at the end of the whole series, and, after passing through this, it is discharged into the roasting furnace. The conveyor on the top of the volatilizers into which the elevators discharge, is common to the whole set of volatilizers and reducers, so that, in case any portion of the plant has to be disconnected, the rotary valve through which the material is discharged from the conveyor into the volatilizer is stopped. The material then passes on through the conveyor into the next volatilizer. The two gases, carbon-monoxide in the volatilizers and water-gas in the reducers, are kept separate by rotary valves of the same construction as in the small plant. The water-gas connections are so arranged that each reducer receives fresh gas from the main, with the exception of the first large reducer, through which the waste gas of all the other reducers is passed, so as to burn completely all the hydrogen in the water-gas. The carbon-monoxide passes through the volatilizers from a common main, and is collected, after it has passed through the filters, in a main leading to the blower. From the blower the carbon-monoxide charged with nickel passes through a set of decomposers, and again into the main which feeds the volatilizers.

With regard to the application of steel containing between 1 per cent. and 7 per cent. of nickel in constructive work, the Author need not remind members of the Institution of the importance of nickel steel not only for the manufacture of armour-plates but for all purposes where strength and lightness are essential. One manufacturer in the United States used in 1 year no less than 178 tons of nickel in the form of nickel steel, and it has been stated by a competent authority that "if propeller shafts were made of nickel steel the question of failures would seldom or never be raised." An attempt to deal adequately with the application of nickel would lead far beyond the scope of the present Paper, and the Author only adds that the extraordinary properties of these alloys have formed the subject of elaborate investigations by the late Dr. John Hopkinson<sup>1</sup> and by Mr. Guillaume.<sup>2</sup>

The Author acknowledges his indebtedness to Dr. Mond and to Dr. Langer for enabling him to examine the Smethwick Works in detail and for the drawing they prepared for him of the plant. The Author's assistant, Dr. Stansfield, was by Dr. Mond's kindness

<sup>1</sup> Proceedings of the Royal Society, vol. xlvii. p. 23; vol. xlvii. p. 138; vol. xlviii. p. 1.

<sup>2</sup> Comptes rendus, vol. cxxiv. pp. 176, 752 and 1515, and vol. cxxv. p. 235.

able to watch every stage of the process during a prolonged visit to the Works.

It will have been evident that the process possesses unusual interest as being the only one, in the whole range of metallurgy, in which a metal is obtained from its ores by causing it to combine with a gas to form a gaseous product from which it is subsequently released. Not the least remarkable feature of the process is presented by the fact that the temperature at which the whole operation is conducted never exceeds  $300^{\circ}$  C., which is far below dull redness. As a consequence, the plant, which may still admit of simplification, is not, as is usually the case with metallurgical appliances, subjected to alterations of temperature extending through a considerable range. The repairs needed are therefore inconsiderable, and the amount of fuel required is but small. The process works more or less automatically, and the amount of labour involved in conducting it can be reduced within very narrow limits. The main operation is, moreover, a regenerative one; the carbon-monoxide moves in a cycle and is the vehicle for continuously transferring the nickel from the ore or matte, and converting it into a marketable form. It follows that in the extraction of the nickel no new material except the reducing agent, water-gas, has to be introduced into the system. This is true even of the granules of commercial nickel which fill the decomposer and serve as a basis for the deposition of the nickel from the carbonyl. Their presence is essential in starting the process; but their place is, as has already been pointed out, gradually taken by fragments of the deposited metal which becomes detached as the operation proceeds. The process will always occupy a prominent place in chemical history, and there would seem to be no reason why it should not play an important part in metallurgical practice.

As regards the application of the process in Canada, the Author trusts that this attempt to make it better known may contribute to develop one of the resources of the great Dominion.

The Paper is accompanied by six drawings and a photomicrograph, from which Plate 1 and the Figures in the text have been prepared.



---




EXTRACTION OF NICKEL.

Fig. 5.


Fig. 1.

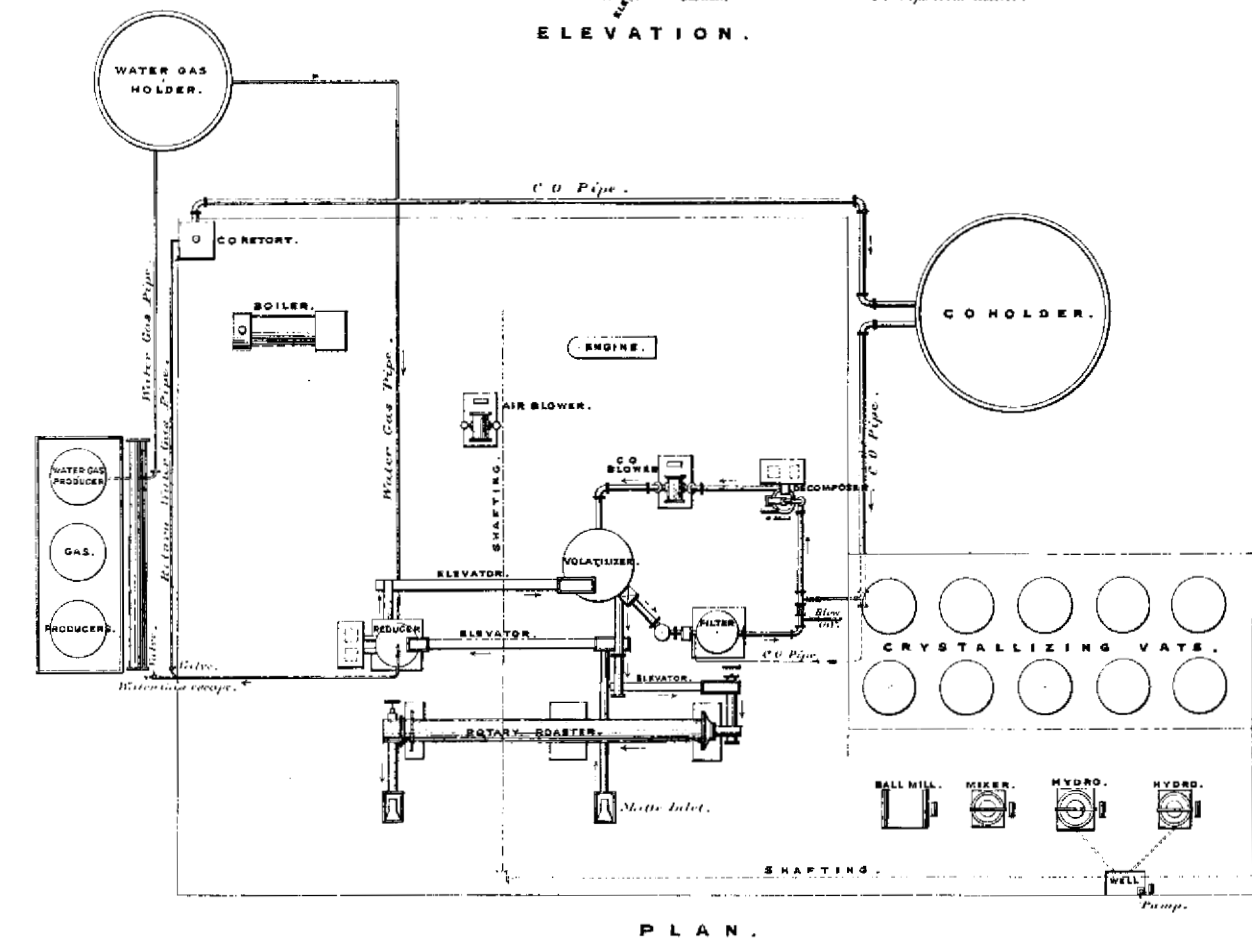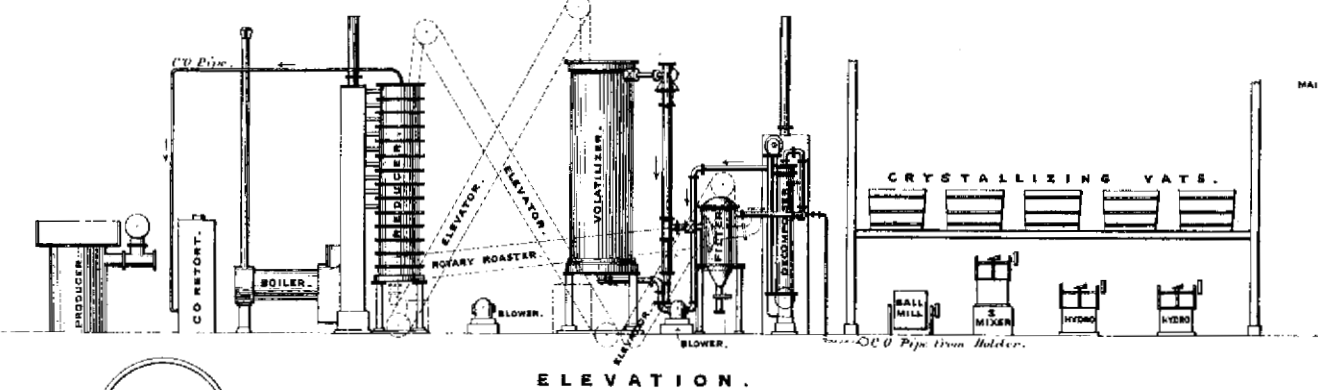


PLAN.

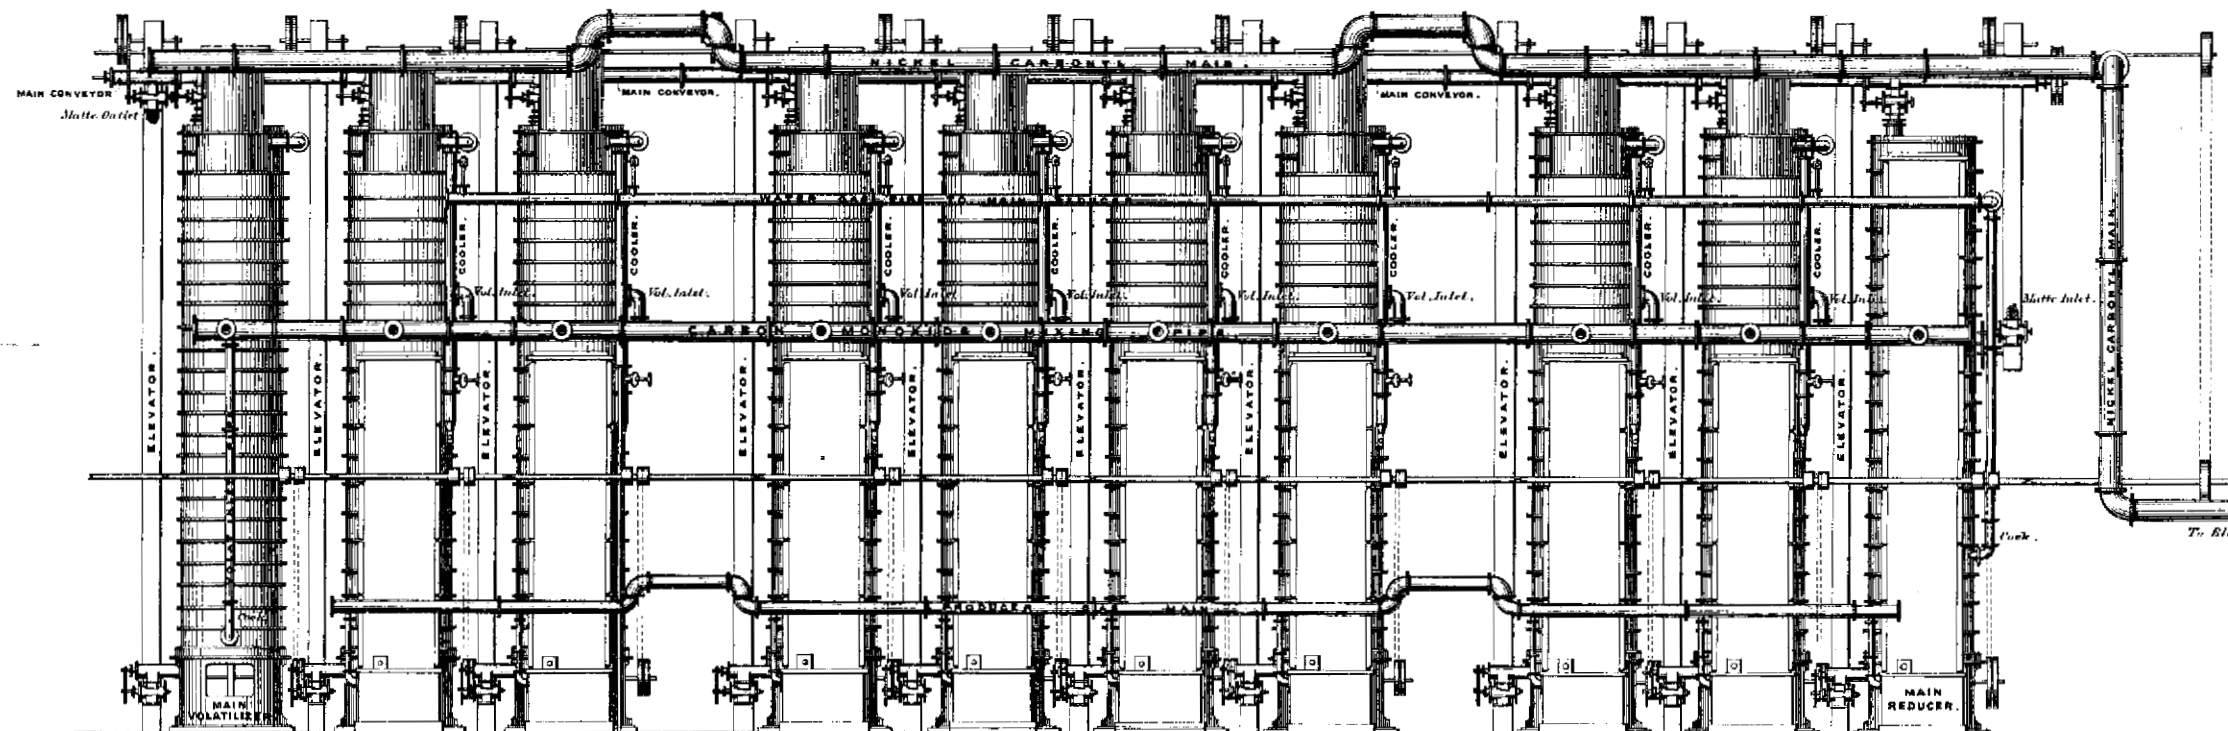

SECTIONAL ELEVATION ON C C.

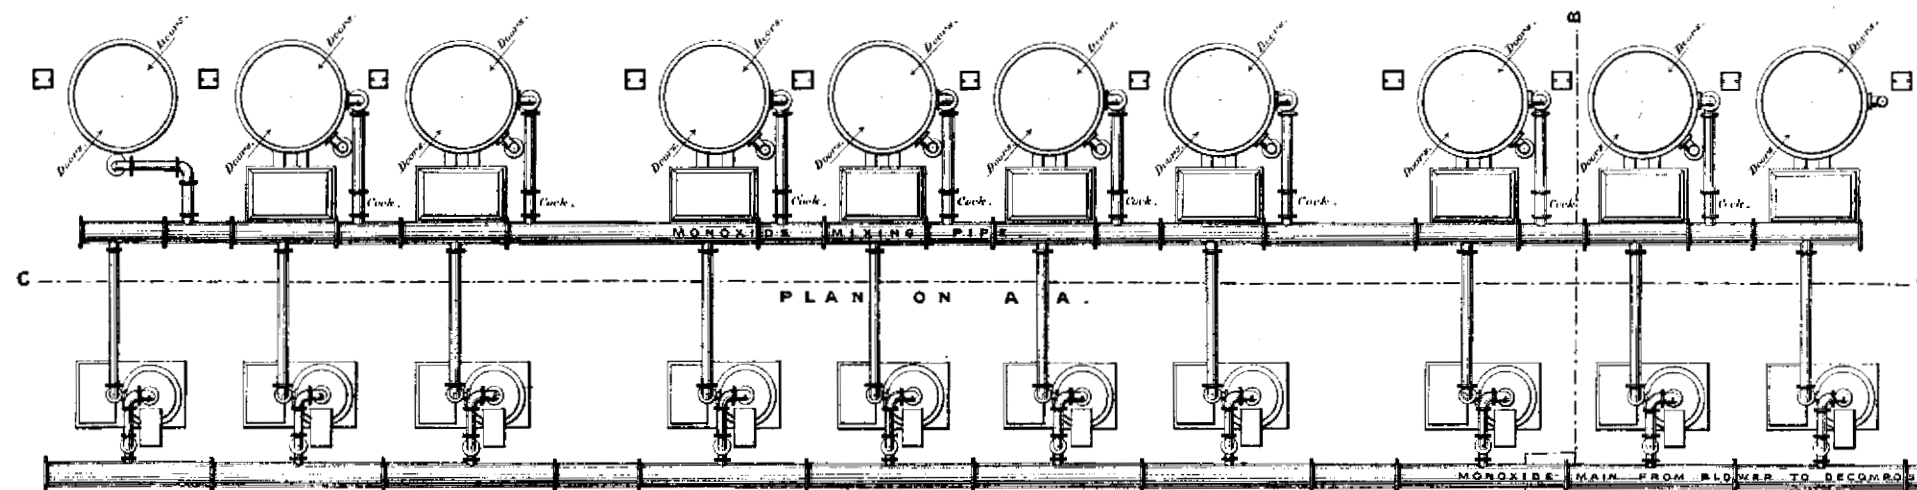

PLAN ON A A.

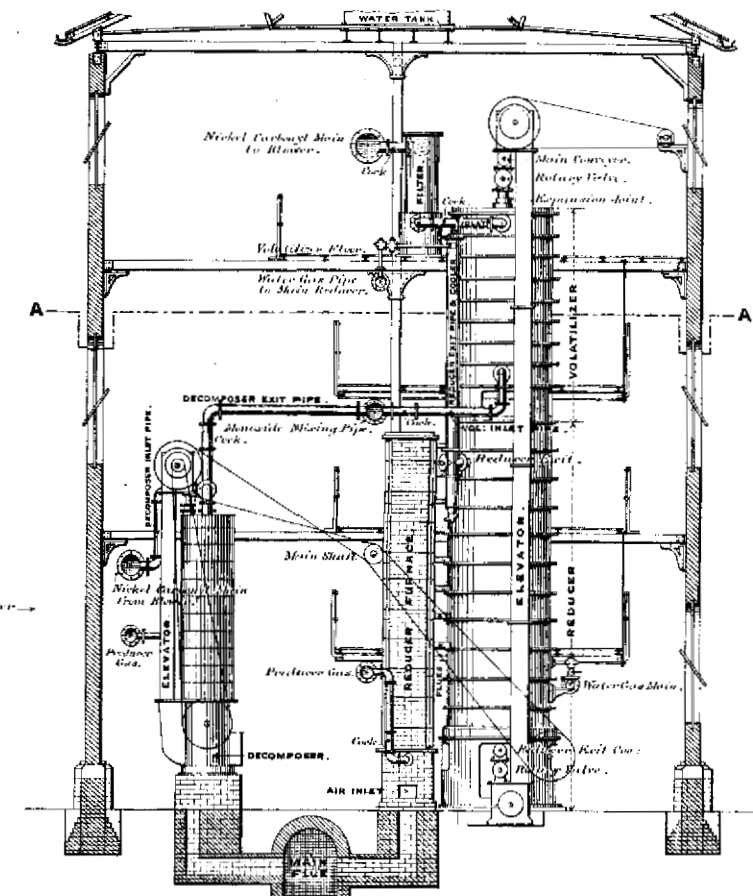

CROSS SECTION ON B B.

SCALES

Scale for Fig. 1, 1 inch = 20 feet.

Scale for Fig. 5, 1 inch = 1 foot.