



## Green synthesis, characterization of silver sulfide nanoparticles and antibacterial activity evaluation

Akl M. Awwad<sup>1\*</sup>, Nidá M. Salem<sup>2</sup>, Marwa M. Aqarbeh<sup>3</sup> and Fatin M. Abdulaziz<sup>1</sup>

<sup>1</sup>Department of Nanotechnology, Royal Scientific Society, Amman, Jordan

<sup>2</sup>Plant Protection Department, College of Agriculture, the University of Jordan, Amman, Jordan

<sup>3</sup>National Agricultural Research Center, Al-Baqa, Jordan

\*Corresponding author's E. mail: [akl.awwad@yahoo.mail](mailto:akl.awwad@yahoo.mail), [akl.awwad@rss.jo](mailto:akl.awwad@rss.jo)

### ARTICLE INFO

#### Article type:

Research article

#### Article history:

Received April 2019

Accepted June 2019

January 2020 Issue

#### Keywords:

Green synthesis

Silver sulfide

Nanoparticles

Rosemary leaves

Antimicrobial activity

### ABSTRACT

This research work presents a facile and green route for synthesis silver sulfide ( $\text{Ag}_2\text{SNPs}$ ) nanoparticles from silver nitrate ( $\text{AgNO}_3$ ) and sodium sulfide nonahydrate ( $\text{Na}_2\text{S}\cdot 9\text{H}_2\text{O}$ ) in the presence of *rosemary* leaves aqueous extract at ambient temperature ( $27\text{ }^\circ\text{C}$ ). Structural and morphological properties of  $\text{Ag}_2\text{SNPs}$  nanoparticles were analyzed by X-ray diffraction (XRD) and transmission electron microscopy (TEM). The surface Plasmon resonance for  $\text{Ag}_2\text{SNPs}$  was obtained around 355 nm.  $\text{Ag}_2\text{SNPs}$  was spherical in shape with an effective diameter size of 14 nm. Our novel approach represents a promising and effective method to large scale synthesis of eco-friendly antibacterial activity silver sulfide nanoparticles.

© 2020 International Scientific Organization: All rights reserved.

**Capsule Summary:** A green and fast-route for the synthesis of silver sulfide nanoparticles using rosemary leaves at room temperature was reported and NPs showed promising antimicrobial activity.

**Cite This Article As:** A. M. Awwad, N. M. Salem, M. M. Aqarbeh and F. M. Abdulaziz. Green synthesis, characterization of silver sulfide nanoparticles and antibacterial activity evaluation. Chemistry International 6(1) (2020) 42-48. <https://doi.org/10.5281/zenodo.3243157>

### INTRODUCTION

Silver sulfide ( $\text{Ag}_2\text{S}$ ) nanomaterial is an important material used in solar cell batteries, thermoelectric sensors, infrared detectors, photovoltaic cells, conductors and antimicrobial activity (Bruhwiler et al., 2002; Fakhri et al., 2015; Kumari et al., 2014). Several methods have been reported for synthesis silver sulfide nanoparticles ( $\text{Ag}_2\text{SNPs}$ ) such a template-based method at room temperature and ambient pressure (Xiao et al., 2002), water-in- $\text{CO}_2$  microemulsions (Liu et al., 2004), a microwave-assisted template-free method (Su et al., 2016), modified homogenous precipitation route (Xaba et al., 2017),

sonochemical synthesis (Du et al., 2007), hydrothermal method (Yu et al., 2012), by multi-solvent thermal decomposition method (Sahib et al., 2017), *via* a one-pot method in ethylene glycol with 3-mercaptopropionic acid (Kubie et al., 2011), modified chemical bath deposition technique (Jadhav et al., 2013), synthesis of silver sulfide nanoparticles capped with either chitosan, green tea, *Combretum molle* or black wattle extracts (Sibiya and Moloto, 2018), conversion of silver thiolate polymers with sodium sulfide in a dual-phase solution preparation (Schaaff and Rodinone, 2003), metal-reducing bacterium *Shewanella oneidensis* MR-1 (Debabova et al., 2013), chemical method (Zhao and Song, 2014), multi-solvent thermal decomposition

method (Khaleelullah et al., 2017), sonochemistry method (Kang et al., 2018) hydrochemical bath deposition from aqueous solutions (Sadovnikov et al., 2016) and nucleation process (León-Velázquez et al., 2010). These methods and routes for synthesis silver sulfide nanoparticles have many disadvantages due to toxic chemicals used and waste products, which create a problem to environment, also high energy consumption, difficulty of large-scale of processes and wasteful purifications (Cárdenas Riojas et al., 2019; Deshmukh et al., 2019; Fletcher et al., 2019; Huang et al., 2019; Maharubin et al., 2019; Sadovnikov, 2019). Recently, green approach in synthesis of nanomaterials has given significant attention to protect environment from hazardous wastes. Herein, the objective of the present research work was to synthesize silver sulfide nanoparticles by green route using *rosemary* (*Rosmarinus officinalis*) leaves aqueous extract at room temperature and studying antibacterial activity.

## MATERIAL AND METHODS



Fig. 1: Rosemary leaves and their aqueous extract

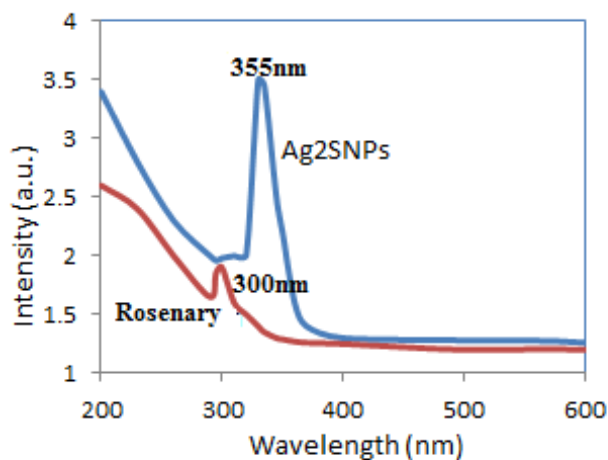


Fig. 2: UV-vis absorption spectra of silver sulfide

## Reagents and chemicals

Silver nitrate ( $\text{AgNO}_3$ , 99%), sodium sulfide nonahydrate ( $\text{Na}_2\text{S}\cdot 9\text{H}_2\text{O}$ , 99.99%) were purchased from Sigma-Aldrich. Ethanol was purchased from Merck (Darmstadt-Germany). Ultrapure water from with a resistivity of  $18.2 \text{ M}\Omega/\text{cm}$  was used for the preparation of solutions. *Rosemary* plant leaves were collected from different gardens at the Royal Scientific Society, Amman City, Jordan.

## Rosemary leaves aqueous extract

Rosemary leaves were dried in our laboratory for one week at room temperature and then crushed to small pieces. 20g of rosemary was mixed with 400 ml deionized-water and boiled for 10m. Afterwards, the aqueous extract was obtained by filtration on Whitman filter paper No. 1 and kept in a stoppered bottle for further experimental work (Fig. 1).

## Green synthesis of silver sulfide ( $\text{Ag}_2\text{SNPs}$ )


Silver sulfide nanoparticles were synthesized by mixing silver nitrate with *rosemary* aqueous extract and sodium sulfide at ambient temperature. In a typical synthesis, 1g of silver nitrate was dissolved in 100ml of rosemary aqueous extract under magnetic stirring at room temperature ( $27^\circ\text{C}$ ) for  $\sim 10$ min. Afterwards, the sodium sulfide solution (1g/100ml de-ionized water) was added dropwise to the solution of  $\text{AgNO}_3$ /rosemary aqueous extract under continuous magnetic stirring. A yellow color of  $\text{AgNO}_3$ /rosemary leaves aqueous extract started changing to a suspended gray-black color indicating the formation of silver sulfide nanoparticles.

## Characterization techniques


Ultraviolet-visible (UV-vis) spectra from 200 to 700 nm were measured on a Shimadzu UV-vis spectrophotometer (UV-3600, Japan). The morphology of  $\text{Ag}_2\text{SNPs}$  was observed using transmission electron microscopy (TEM, a Hitachi H7500 at 80 kV and transmission electron microscopy (SEM, a Quanta FEI 450 SEM machine). The elemental mapping of imaged objects was characterized using an energy-dispersive X-ray (EDX) detector. Powder X-ray diffraction was performed using a X-ray diffractometer (Shimadzu) XRD-6000 with  $\text{CuK}\alpha$  radiation  $\lambda = 1.5405 \text{ \AA}$  over a wide range of Bragg angles ( $3^\circ \leq 2\theta \leq 80^\circ$ ). Fourier transform infrared spectroscopic measurements were done using Shimadzu, IR-Prestig-21 spectrophotometer.

## Antibacterial activity and minimum inhibitory concentration (MIC)

The antibacterial activity of  $\text{Ag}_2\text{SNPs}$  was investigated using the disc diffusion method. About 20 mL of sterile molten Mueller Hinton agar was poured into sterile petri dishes.

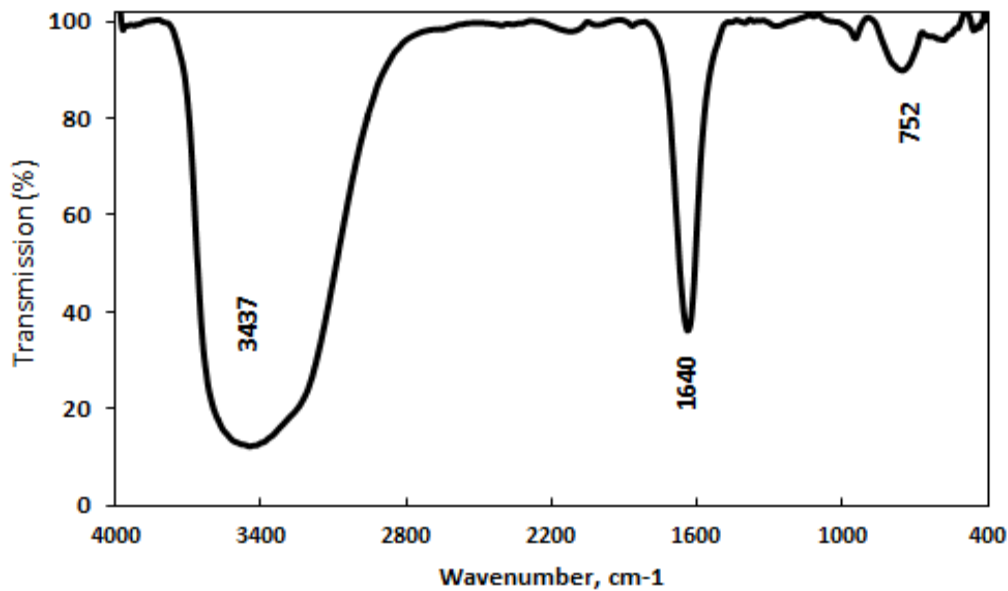

**Fig. 3:** FT-IR of rosemary leaves aqueous extract

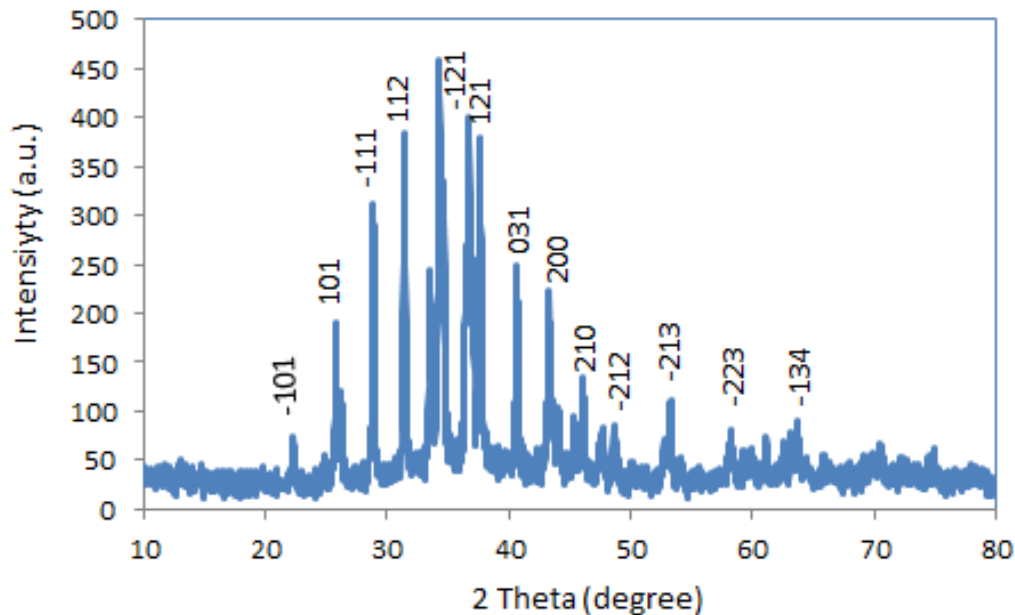


**Fig. 4:** XRD pattern of synthesized silver sulfide nanoparticles ( $\text{Ag}_2\text{SNPs}$ )

Triplicate plates were swabbed with the overnight culture ( $10^5$  cells/mL) of *Escherichia coli* and *Staphylococcus aureus* bacteria. 5mg/mL of  $\text{Ag}_2\text{S}$  nanoparticle samples capped with rosemary leaves extract was added into the discs, placed in the petri dishes and incubated for 24 hours at a temperature of  $37 \pm 2^\circ\text{C}$ . The zone of inhibition, expressed as millimeter in diameter, was measured after 24 hours of incubation. The


MIC was investigated using different concentrations of  $\text{Ag}_2\text{SNPs}$ . The experiments were performed in triplicates.

## RESULTS AND DISCUSSION

### Ultraviolet-visible spectroscopy (UV-Vis) analysis

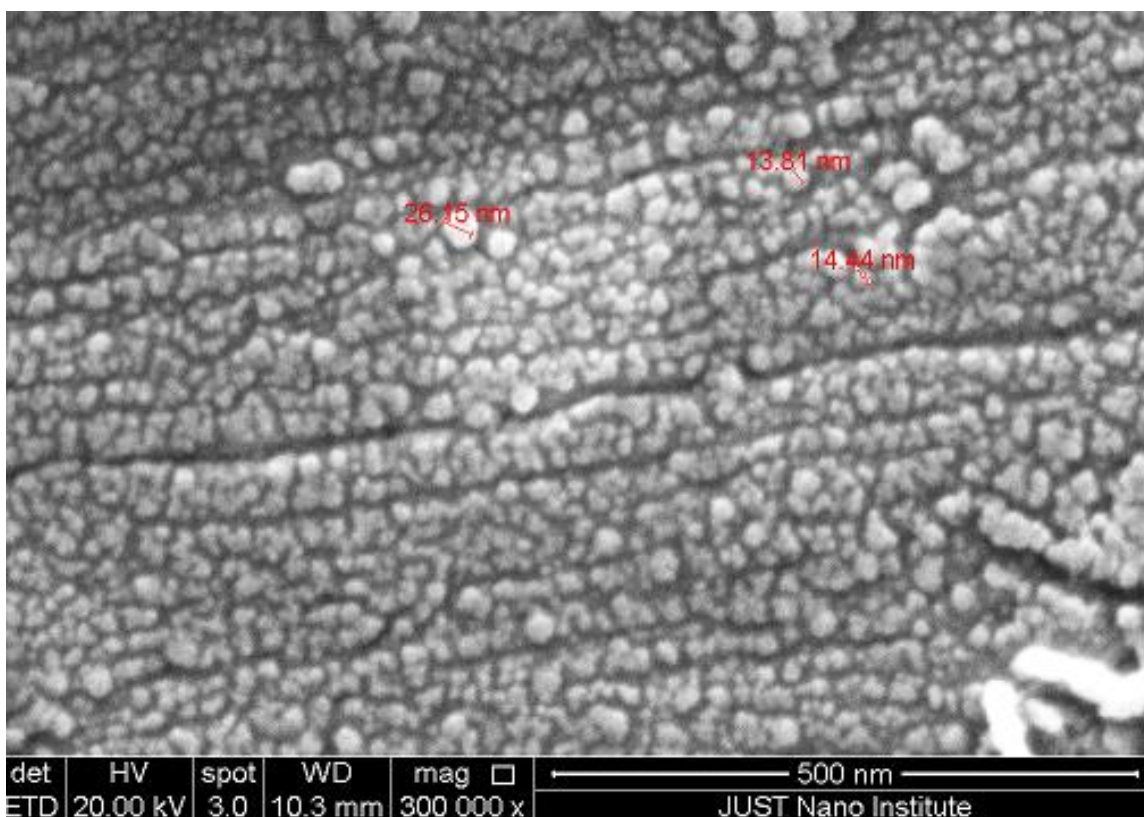

**Fig. 5:** SEM pattern of synthesized Ag<sub>2</sub>SNPs

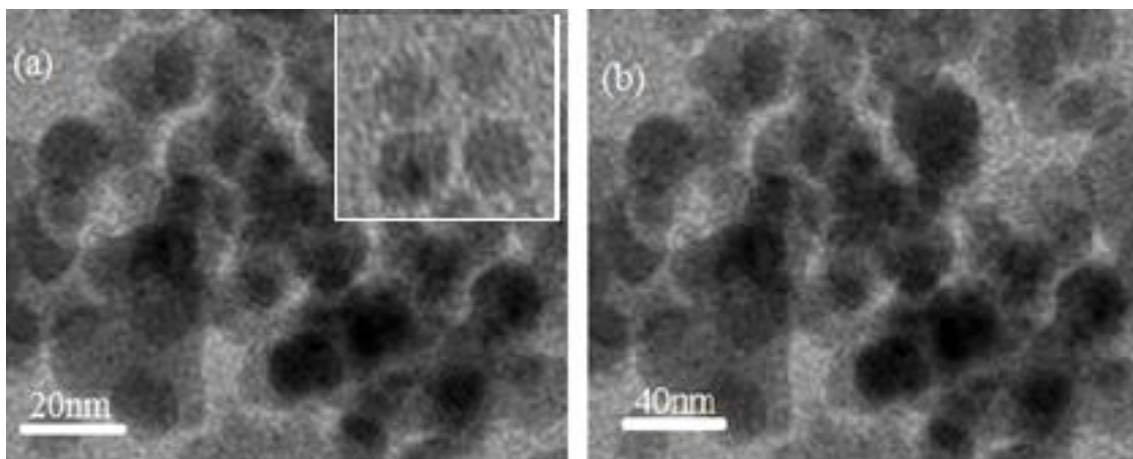

**Fig. 6:** TEM images of synthesized Ag<sub>2</sub>SNPs

In the present study, the absorption spectrum of silver sulfide (Ag<sub>2</sub>S) nanoparticles synthesized by green route using rosemary leaves aqueous extract revealed the conversion of silver and sulfur ions to silver sulfide nanoparticles with almost 100% as evidenced by qualitative testing of supernatant after the purification of silver sulfide nanoparticles. The difference in the rate of Ag<sub>2</sub>S formation observed may be assigned to the differences in the activities of the amino acids, poly phenols and

flavonoids present in rosemary leaves extract. The entire reaction mixture is turned to black color, and exhibit an absorbance peak around 355 nm characteristic of Ag<sub>2</sub>SNPs nanoparticle, due to its surface Plasmon resonance absorption band. In present investigation, the reaction mixtures showed a single SPR band revealing spherical shape of silver sulfide nanoparticles, which was further confirmed by SEM and TEM images. Fig. 2 showed SPR bands of the colloidal silver sulfide nanoparticles were

centered at around 355 nm and rosemary aqueous extract at 300 nm.

#### Fourier transforms infrared analysis

FT-IR spectrum of rosemary leaves aqueous extract, Fig. 3 showed a number of peaks thus reflecting its complex nature. Strong broad absorption band at  $3437\text{ cm}^{-1}$  is characteristic of the alcohol/phenol -OH stretching vibration, carboxylic acid -OH stretch and N-H stretching of amides. The strong peak at  $1640\text{ cm}^{-1}$  is characterized to -NH stretch of primary amines. Peak at  $\sim 752\text{ cm}^{-1}$  refers to O-C=O bending in carboxylic acids, N-C=O, and C-N-C bending mines.

#### X-ray diffraction (XRD) analysis

A comparison of XRD spectrum, Fig. 4 with the standard confirmed that the silver sulfide particles formed in our experiments were in the form of nanocrystals, as evidenced by the peaks at  $2\theta$  values of  $22.8^\circ$ ,  $25.7^\circ$ ,  $28.9^\circ$ ,  $31.4^\circ$ ,  $34.6^\circ$ ,  $36.7^\circ$ ,  $37.8^\circ$ ,  $40.7^\circ$ ,  $43.3^\circ$ ,  $45.4^\circ$ ,  $48.6^\circ$ ,  $53.2^\circ$ ,  $57.9^\circ$  and  $63.9^\circ$  corresponding to (-101),(101), (111), (112), (-121), (121), (031), (200), (210), (-212), (-213), (-223), and (-134) Bragg reflections, respectively, which may be indexed based on the structure of silver sulfide. X-ray diffraction results clearly show that the silver sulfide nanoparticles formed by using rosemary leaves extract are crystalline in nature. It was found that the average size from XRD data and using the Debye-Scherrer equation (Eq. 1) (Klug and Alexander, 1959) is 20 nm.

$$D = \frac{K\lambda}{\beta \cos\theta} \quad (1)$$

Where, D is the crystallite size of silver sulfide nanoparticles,  $\lambda$  represents wavelength of x-ray source (0.1541 nm) used in XRD,  $\beta$  is the full width at half maximum of the diffraction peak, K is the Scherrer constant with value from 0.9 to 1 and  $\theta$  is the Bragg angle.

#### Scanning electron microscopy (SEM) analysis

The suspended silver sulfide nanoparticles in sterile distilled water were used for scanning electron microscope analysis by fabricating a drop of suspension onto a clean electric stubs and allowing water to completely evaporate.

Fig. 5 shows the SEM images of the silver sulfide nanoparticles synthesized by different concentrations are homogeneously dispersed and ranges approximately from 5-40 nm. The shape of the silver sulfide nanoparticles is spherical with few exceptional as ellipsoidal. The larger silver sulfide particles may be due to the aggregation of the smaller ones, due to the SEM measurements.

#### Transmission electron microscopy (TEM) analysis

Typical TEM micrograph for as prepared Ag<sub>2</sub>SNPs is shown in Fig. 6. The TEM micrograph clearly showed nanostructure homogeneities with spherical morphologies of Ag<sub>2</sub>SNPs. The TEM observation showed the nanospheres with an average diameter of 14 nm. This slight deviation of the particle size estimation compared to that calculated from XRD analysis can be attributed to the deviation of the spherical shape of the particles that is required for the Debye-Scherrer formula and the detection limit of the XRD diffractometer. From the Fig. 6, spherical particles with 5-40 nm have been observed. The magnified TEM image as shown confirms the uniform and regular spherical morphology.

#### Antibacterial activity

Biosynthesized silver sulfide nanoparticles by this method were studied for antimicrobial activity against pathogenic bacteria by disc diffusion method; it was observed that silver sulfide nanoparticles have antibacterial activities at different concentration. Chloromphenical was used as a control antimicrobial agent. The silver sulfide nanoparticles biosynthesized by rosemary leaves aqueous extract showed inhibition zone against Gram negative *Escherichia coli*, and Gram positive *Staphyococcus aureus*, *Shigella*, *Listeria bacteria*. Maximum zone of inhibition (MZI) are listed in Table 1. It was observed that an increase in Ag<sub>2</sub>SNPS concentration increases the MZI of *Escherichia coli*, *S. aureus*, *Shigella* and *Listeria* bacteria. Our results showed that the MZI for bacteria are higher than those reported in the literature (Jafari et al., 2017 and Sibiya and Moloto, 2018). This difference is due to the particles size of NPs prepared and capping agents used in the preparation process (Andra et al., 2019; Baygar et al., 2019; Manjunath Hulikere and Joshi, 2019; Soliman et al., 2018; Soto et al., 2019).

**Table 1:** Antibacterial activity of silver sulfide nanoparticles

Ag <sub>2</sub> S NPs Conc.	Zone of inhibition (mm)			
	<i>E. coli</i>	<i>S. aureus</i>	<i>Shigella</i>	<i>Listeria</i>
80 mg/ml	14	16	12	17
40 mg/ml	14	16	11	16
20 mg/ml	13	14	10	14
10 mg/ml	12	13	9	13
Ref. Drug	18	20	16	20

## CONCLUSIONS

Green chemistry approach towards the synthesis of nanoparticles has many advantages such as, ease with which the process can be scaled up and economic viability. We have developed a fast, eco-friendly and convenient method for the synthesis of silver sulfide nanoparticles using rosemary leaves aqueous extract with a diameter range of 5-40 nm. These particles are monodispersed and spherical. No chemical reagent or surfactant template was required in this method, which consequently enables the bioprocess with the advantage of being environmental friendly. Color change occurs due to the reaction with the plant components present in the plant leaves extract results in the formation of silver sulfide nanoparticles which is confirmed by UV-vis, XRD, FT-IR and TEM, having average mean size of 14 nm had fcc structure. The antibacterial activity of synthesized silver sulfide nanoparticles was evaluated against *E. coli* and *S. aureus*, *shigella* and *listeria* showing an effective bactericidal activity.

## ACKNOWLEDGEMENTS

The authors are thankful to SRF (SRF-Jordan Agr/2/13/2013) Program-Jordan and Royal Scientific Society for financial support and having given feasibilities to carry out this research work.

## REFERENCES

- Andra, S., Balu, S., Ramoorthy, R., Muthalagu, M., Manisha, V.S., 2019. Terminalia bellerica Fruit Extract Mediated Synthesis of Silver Nanoparticles and Their Antimicrobial Activity. *Materials Today: Proceedings* 9, 639-644.
- Baygar, T., Sarac, N., Ugur, A., Karaca, I.R., 2019. Antimicrobial characteristics and biocompatibility of the surgical sutures coated with biosynthesized silver nanoparticles. *Bioorganic Chemistry* 86, 254-258.
- Bruhwieler, D., Leigener, C., Glaus, S., Calzaferri, G., 2002. Luminescent silver sulfide clusters. *Journal of Physical Chemistry B* 106, 3770-3777.
- Cárdenas Riojas, A.A., Wong, A., Planes, G.A., Sotomayor, M.D.P.T., La Rosa-Toro, A., Baena-Moncada, A.M., 2019. Development of a new electrochemical sensor based on silver sulfide nanoparticles and hierarchical porous carbon modified carbon paste electrode for determination of cyanide in river water samples. *Sensors and Actuators B: Chemical* 287, 544-550.
- Debabova, V.G., Tvoeikovaa, T.A., Shebanovab, A.S., Shaitanb, K.V., Emelyanovaa, L.K., Novikovaa, L.M., Kirpichnikovb, M.P., 2013. Bacterial synthesis of silver sulfide nanoparticles. *Nanotechnologies in Russia* 8, 269-276.
- Deshmukh, S.P., Patil, S.M., Mullani, S.B., Delekar, S.D., 2019. Silver nanoparticles as an effective disinfectant: A review. *Materials Science and Engineering C* 97, 954-965.
- Du, N., Zhang, H., Sun, H., Yang, D., 2007. Sonochemical synthesis of amorphous long silver sulfide nanowires. *Materials Letters* 61, 235-238.
- Fakhri, A., Pourmand, M., Khakpour, R., Behrouz, S., 2015. Structural, optical, photoluminescence and antibacterial properties of copper-doped silver sulfide nanoparticles. *Journal of Photochemistry and Photobiology B* 149, 78-83.
- Fletcher, N.D., Lieb, H.C., Mullaugh, K.M., 2019. Stability of silver nanoparticle sulfidation products. *Science of the Total Environment* 648, 854-860.
- Huang, Z., He, K., Song, Z., Zeng, G., Chen, A., Yuan, L., Li, H., Chen, G., 2019. Alleviation of heavy metal and silver nanoparticle toxicity and enhancement of their removal by hydrogen sulfide in *Phanerochaete chrysosporium*. *Chemosphere* 224, 554-561.
- Jadhav, U.M., Patel, S. N., Patil, R. S., 2013. Synthesis of silver sulfide nanoparticles by modified chemical route for solar cell applications. *Research Journal of Chemical Science* 3, 69-74.
- Jafari, L., Pourahmad, A., Asadpour, L., 2017. Rice husk based MCM-41 nanoparticles loaded with Ag<sub>2</sub>S nanostructures by a green and room temperature method and its antimicrobial property. *Journal Inorganic and Nano-Metal Chemistry* 47, 1552-1559.
- Kang, M., Kim, S.H., Jang, S., Lim, J.E., Chang, H., Kong, K-i., Myung, S., Park J.K., 2018. Synthesis of silver sulfide nanoparticles and their photodetector applications. *RSC Advance* 8, 28447-28452.
- Khaleelullah, M.M.S.I., Dheivasigamani, T., Natarajana, P., Masuda, Y., Inamib, W., Kawataa, Y., Hayakawa, Y., 2017. Size controlled synthesis of silver sulfide nanostructures by multi-solvent thermal decomposition method. *Journal of Crystal Growth* 468, 119-124.
- Klug, H.P., Alexander, L.E., 1959. X-ray diffraction procedures, Wiley/Interscience, New York.
- Kubie, L., King, L.A., Kern, M. E., Murphy, J. R., Kattel, S., Yang, Q., Stecher, W. D., Parkinson, B. A., 2017. Synthesis and characterization of ultrathin silver sulfide nanoplatelets. *ACS Nano* 11, 8471-8477.
- Kumari, P., Chandran, P., Khan, S.S., 2014. Synthesis and characterization of silver sulfide nanoparticles for photocatalytic and antimicrobial applications. *Journal of Photochemistry and photobiology B* 141, 235-240.
- León-Velázquez, M.S., Irizarry, R., Miguel E. Castro-Rosario, M.E., 2010. Nucleation and growth of silver sulfide

- nanoparticles. *Journal of Physical Chemistry C* 114, 5839–5849.
- Liu, J.C., Raveendram, P., Shervani, Z., Ikushima, Y., 2004. Synthesis of Ag<sub>2</sub>S quantum dots in water-in-CO<sub>2</sub> microemulsions. *Chemical Communications* 22, 2582-2588.
- Maharubin, S., Zhou, Y., Tan, G.Z., 2019. Integration of silver nanoparticles and microcurrent for water filtration. *Separation and Purification Technology* 212, 57-64.
- Manjunath Hulikere, M., Joshi, C.G., 2019. Characterization, antioxidant and antimicrobial activity of silver nanoparticles synthesized using marine endophytic fungus- *Cladosporium cladosporioides*. *Process Biochemistry* 82, 199-204.
- Sadovnikov S.I., Kuznetsova Y.V., Rempel A. A., 2016. Ag<sub>2</sub>S silver sulfide nanoparticles and colloidal solutions: Synthesis and properties. *Nano-Structures and Nano-Objects* 7, 81-91.
- Sadovnikov, S.I., 2019. Thermal stability and recrystallization of semiconductor nanostructured sulfides and sulfide solid solutions. *Journal of Alloys and Compounds* 788, 586-599.
- Sahib IKMM, Thangaraju D, Prakash N, Masuda Y., 2017. Size controlled synthesis of silver sulfide nanostructures by multi-solvent thermal decomposition method. *Journal of Crystal Growth* 468, 119–124.
- Schaaff TG, Rodinone A J., 2003. Preparation and characterization of silver sulfide nanocrystals generated from silver (I)-thiolate polymers. *Journal of Physical Chemistry B* 107, 10416-10422.
- Sibiya P N, Moloto MI., 2018. Green synthesis of Ag<sub>2</sub>S nanoparticles: Effect of pH and capping agent on size and shape of NPs and their antibacterial activity. *Digest Journal of Nanomaterials and Biostructures* 13, 411-418.
- Soliman, H., Elsayed, A., Dyaa, A., 2018. Antimicrobial activity of silver nanoparticles biosynthesised by *Rhodotorula* sp. strain ATL72. *Egyptian Journal of Basic and Applied Sciences* 5, 228-233.
- Soto, K.M., Quezada-Cervantes, C.T., Hernández-Iturriaga, M., Luna-Bárcenas, G., Vazquez-Duhalt, R., Mendoza, S., 2019. Fruit peels waste for the green synthesis of silver nanoparticles with antimicrobial activity against foodborne pathogens. *LWT-Food Science and Technology* 103, 293-300.
- Su, W., Li, R., Xing, Y-J., 2016. Preparation and characterization of hollow carambola-shaped silver sulfide microspheres using a microwave-assisted template-free method. *Chinese Chemical Letters* 27, 451-453.
- Xaba, T., Moloto, M. J., Nchoe, O. B., Nate, Z., Moloto, N., 2017. Synthesis of silver sulfide nanoparticles through homogenous precipitation route and the preparation of the Ag<sub>2</sub>S-chitosan nanocomposites for the removal of iron (II) ion from wastewater. *Chalcogenide Letters* 14, 337-346.
- Xiao, J., Xie, Y., Tang, R., Luo, W., 2002. Template-based synthesis of nanoscale Ag<sub>2</sub>E (E = S, Se) dendrites. *Journal of Materials Chemistry* 12, 1148-1151.
- Yu, C., Leng, M., Liu, M., Yu, Y., Liu, D., Wang, C., 2012. Synthesis of normal and flattened rhombic dodecahedral Ag<sub>2</sub>S particles. *Crystal Engineering Communications* 14, 3772-3777.
- Zhao, Y., Song, Z., 2014. Phase transfer-based synthesis of highly stable, biocompatible and the second near-infrared-emitting silver sulfide quantum dots. *Materials Letters* 126, 78-80.

Visit us at: <http://bosajournals.com/chemint/>  
Submissions are accepted at: [editorci@bosajournals.com](mailto:editorci@bosajournals.com)