

Synthesis of Telechelic Poly(p-benzamide)s

*Mahshid Alizadeh and Andreas F.M. Kilbinger**

University of Fribourg, Chemistry Department, Chemin du Musée 9, Ch-1700 Fribourg,
Switzerland

andreas.kilbinger@unifr.ch

ABSTRACT: Well-defined telechelic poly(benzamide)s were synthesized by chain-growth polycondensation of phenyl-4-amino benzoate and pentafluorophenyl-4-amino benzoate derivatives with a bifunctional initiator in the presence of LiTMP as base. The polymerization was carried out at -70°C to prevent self-initiated polymerization. To confirm the control over molecular weight, different defined molecular weight polymers were synthesized and analyzed by GPC. Taking advantage of the labile ester end groups of these poly(benzamide)s, we carried out post-polymerization modifications to introduce different end functional groups such as alkyne, amine, alcohol, alkyl halide and olefin suitable for different types of post-polymerization reactions. Successful end group modification was confirmed by $^1\text{H-NMR}$ spectroscopy and isotopically resolved MALDI-ToF mass spectrometry.

INTRODUCTION

Polycondensation is an important method for the synthesis of commercial polymers such as polyamides and polyesters. Conventional polycondensations proceed in a step-growth manner

with broad polydispersities and control over the molecular weight can often be difficult.^{1,3} Yokozawa et al. developed a polycondensation method using a chain-growth mechanism to synthesize well defined aromatic polyamides with narrow polydispersity.^{4,8} Many other well-defined polymers with narrow polydispersity have also been synthesized using chain-growth polycondensation mechanisms such as polyesters,^{9, 10} polyethers,¹¹⁻¹³ poly(ether sulfone)s,¹⁴ polythiophenes,¹⁵⁻¹⁷ polyethylenes¹⁸ and polyfluorenes¹⁹.

The strategy used here for the synthesis of poly(benzamide)s relies on polymer end groups being more reactive than the monomer itself resulting in a kinetically controlled living chain-growth polymerization. Due to good control over the polydispersity and the molecular weight a number of different polymer architectures have previously been reported using well-defined poly(benzamide)s. Block copolymers between polyaramides and different monomers polymerized by ATRP and RAFT were investigated using chain-growth polycondensation.^{20,21} Graft copolymers were prepared by radical polymerization of styrene and a styryl monomer attached to poly(benzamide)s yielding polystyrenes grafted with poly(benzamide)s. Poly(benzamide)s carrying poly(tetrahydrofuran) grafts were synthesized from a 4-aminobenzoate macromonomer via chain-growth polycondensation.^{22,23} Aramide star polymers were synthesized by either the core-first or the arm-first method.²⁴⁻²⁶ Hyperbranched aromatic polyamides were synthesized via convergent chain-growth polycondensations of AB_2 monomers.²⁷⁻³⁰

Additionally, telechelic aromatic polyamides were prepared to make di- and tri block copolymers of polyamides and poly(tetrahydrofuran).³¹ The well-defined poly(benzamide)s were used as macromonomers or macroinitiators in ATRP, RAFT and other copolymerization methods to obtain di and triblock copolymers.^{32,33}

Here, we report the synthesis of well-defined telechelic aromatic polyamides using a bifunctional initiator and a variety of monomers using the chain-growth polycondensation method. Two monomers, phenyl-4-(*N*-ethylhexylamino)benzoate carrying a solubilizing side chain on the amide nitrogen atom and phenyl-4-(*N*-dimethoxybenzylamino)benzoate carrying an *N*-protective group were synthesized. The telechelic polymer prepared possesses two phenyl esters as the reactive end groups which are easily modifiable in one step to a variety of functional end groups. We present different post-polymerization modifications to functionalize the polymer chain ends. This provides a facile way to synthesize telechelic poly(benzamide)s. Their functional end groups can allow subsequent post- polymerization modifications or copolymerization reactions.

EXPERIMENTAL SECTION

Materials and Instrumentation. Matrix assisted laser desorption and ionization (MALDI) mass spectra were recorded on a Bruker ultrafleXtreme and electrospray ionization (ESI) mass spectra on a Bruker-Ion Trap MS esquire HCT mass spectrometer. Standard ^1H , ^{13}C , and ^{19}F nuclear magnetic resonance spectra were recorded either on a Bruker Avance III 300 at a frequency of 300 and 75 MHz or at 400 MHz (^1H), 100 MHz (^{13}C), and 376 MHz (^{19}F) on a Bruker DPX 400 spectrometer. All NMR signals were referenced internally to residual solvent signals. Gel permeation chromatography (GPC) in THF was used. The instrument is an automated Viscotek GPCmax VE-2001 with a set of two Viscotek T6000 M linear columns (300 × 8 mm, 5 μm particle size). Signal detection occurred by use of a Viscotek Smartline 2600 UV detector (set to 254 nm wavelengths) and a Viscotek VE 3580 RI detector (refractive index). Solvents of analytical grade were purchased from Sigma-Aldrich, Honeywell, Fisher Scientific, Acros Organics, and Fluka and were used without further purification. Deuterated solvents (CDCl_3 , DMSO-d_6 , DCM-d_2) were purchased from Cambridge Isotope Laboratories, Inc. or ARMAR AG. Solvents of technical grade

were purified by distillation, if necessary. THF (extra dry) was purchased from Sigma-Aldrich. All chemicals were purchased from Acros Organics, Sigma-Aldrich, or Alfa Aesar and used as received.

4-((2-ethylhexyl) amino) benzoic acid (1a). 4-Aminobenzoic acid (10g, 73 mmol) and 2-ethylhexanal (10.3g, 82.2 mmol) were dissolved in 175 mL DCM and 20 mL acetic acid (365 mmol) and stirred for 1 h at room temperature. $\text{NaBH}(\text{CH}_3\text{COO})_3$ (30.94g, 146 mmol) was added to the solution portion by portion. The solution stirred for further 12 h. The reaction was quenched with sodium bicarbonate and extracted three times with DCM. The organic layer was dried over magnesium sulfate and the solvent was removed under reduced pressure. The product was purified by column chromatography using ethylacetate / hexane (1: 4) as eluent to obtain a yellow oil (14.7g, 81%). $^1\text{H NMR}$ (300 MHz, DMSO-d_6) δ , ppm: 0.83 - 0.90 (m, 6 H) 1.20 - 1.39 (m, 9 H) 1.53 (d, $J=5.59$ Hz, 1 H) 2.95 (t, $J=5.82$ Hz, 2 H) 6.33 (t, $J=5.32$ Hz, 1 H) 6.57 (d, $J=8.89$ Hz, 2 H) 7.67 (d, $J=8.71$ Hz, 2 H).

4-((2, 4-dimethoxybenzyl) amino) benzoic acid (1b). 4-Aminobenzoic acid (10g, 73 mmol) and 2,4-dimethoxy benzaldehyde (13.34, 80.3 mmol) were dissolved in 175 mL DCM and 20 mL acetic acid (365 mmol) and stirred for 1 h at room temperature. $\text{NaBH}(\text{CH}_3\text{COO})_3$ (30.94g, 146 mmol) was added to the solution portion by portion. The solution was stirred for further 12 h. The reaction was quenched with sodium bicarbonate and extracted three times with DCM. The organic layer was dried over magnesium sulfate and the solvent was removed under reduced pressure. The white solid was obtained without purification (20g, 94.5 %). $^1\text{H NMR}$ (300 MHz, DMSO-d_6) δ , ppm: 3.63 (s, 3 H) 3.78 (s, 3 H) 4.25 (d, $J=6.05$ Hz, 2 H) 6.56 (m, $J=8.80$ Hz, 2 H) 6.72 - 6.88 (m, 3 H) 6.88 - 6.98 (m, 1 H) 7.64 (m, $J=8.80$ Hz, 2 H).

General synthesis procedure for pentafluorophenyl ester M1 and M2. The acid (1 eq), DMAP (0.1 eq) and pentafluorophenol (1.1 eq) were dissolved in dry DCM. DCC (1.2 eq) was added to solution at 0 °C for 5 min and then allowed to warm up to room temperature for 12 h.

Phenyl 4-((2-ethylhexyl) amino) benzoate (M3). 4-((2-Ethylhexyl) amino) benzoic acid (5g, 20 mmol), DMAP (0.24g, 2 mmol) and phenol (4.42 g, 24 mmol) were dissolved in dry DCM. DCC (5g, 24 mmol) was added to the stirred solution at 0 °C. The solution was stirred at 0 °C for 5 min and then allowed to warm up to room temperature for 12 hours. The suspension was filtered and the solvent removed under reduced pressure. The residue was dissolved in DCM and washed with sodium bicarbonate. The organic layer was dried over magnesium sulfate and the solvent was removed. The product was purified by column chromatography using ethyl acetate / hexane (1: 4) as eluent to obtain a yellow oil (5.2 g, 79 %). ¹H NMR (400 MHz, DMSO-d₆) δ, ppm: 0.81 - 0.92 (m, 6 H) 1.23 - 1.41 (m, 8 H) 1.51 - 1.61 (m, 1 H) 3.01 (t, J=5.99 Hz, 2 H) 6.62 - 6.71 (m, 3 H) 7.19 (dd, J=8.44, 0.98 Hz, 2 H) 7.23 - 7.29 (m, 1 H) 7.40 - 7.47 (m, 2 H) 7.83 (d, J=8.93 Hz, 2 H) ¹³C NMR (101 MHz, DMSO-d₆) δ, ppm: 10.58 (s, 1 C) 13.89 (s, 1 C) 20.76 (s, 1 C) 23.68 (s, 1 C) 28.30 (s, 1 C) 30.43 (s, 1 C) 37.99 (s, 1 C) 45.58 (s, 1 C) 110.87 (s, 1 C) 114.05 (s, 1 C) 121.75 (s, 1 C) 121.98 (s, 1 C) 125.37 (s, 1 C) 125.72 (s, 1 C) 129.35 (s, 1 C) 129.42 (s, 1 C) 131.74 (s, 1 C) 150.46 (s, 1 C) 151.00 (s, 1 C) 153.75 (s, 1 C) 164.66 (s, 1 C) 169.25 (s, 1 C).

Phenyl 4-((2, 4-dimethoxybenzyl) amino) benzoate (M4). 4-((2, 4-Dimethoxybenzyl) amino) benzoic acid (7g, 24mmol), DMAP(0.3g, 2.4 mmol) and phenol(2.5g, 26.4 mmol) were dissolved in dry DCM. DCC (6g, 28.8 mmol) was added to the stirred solution at 0 °C. The solution was stirred at 0 °C for 5 min and then allowed to warm up to room temperature for 12 hours. The suspension was filtered and the solvent removed under reduced pressure. The product was recrystallized from ethyl acetate to give colorless crystals (7.23g, 83%). ¹H NMR (400 MHz,

DMSO-*d*₆) δ , ppm: 3.74 (s, 3 H) 3.83 (s, 3 H) 4.23 (d, J=5.75 Hz, 2 H) 6.48 (dd, J=8.31, 2.32 Hz, 1 H) 6.58 (d, J=2.45 Hz, 1 H) 6.65 (m, J=8.93 Hz, 2 H) 7.03 (t, J=5.75 Hz, 1 H) 7.12 (d, J=8.31 Hz, 1 H) 7.16 - 7.21 (m, 2 H) 7.23 - 7.29 (m, 1 H) 7.39 - 7.46 (m, 2 H) 7.81 (m, J=8.93 Hz, 2 H)
¹³C NMR (101 MHz, DMSO-*d*₆) δ , ppm: 40.68 (s, 1 C) 55.38 (s, 1 C) 55.64 (s, 1 C) 98.58 (s, 1 C) 104.63 (s, 1 C) 111.44 (s, 1 C) 114.70 (s, 1 C) 118.54 (s, 1 C) 122.26 (s, 2 C) 125.60 (s, 1 C) 129.00 (s, 3 C) 129.57 (s, 1 C) 131.90 (s, 2 C) 151.22 (s, 1 C) 153.62 (s, 1 C) 158.11 (s, 1 C) 159.99 (s, 1 C) 164.78 (s, 1 C).

2-((tert-butoxycarbonyl) amino) Ethyl 2-bromo-2-methylpropanoate. To the solution of ethanolamine (5g, 82 mmol) in dry DCM was added di-tert-butyl dicarbonate (19.65 g, 9 mmol) dropwise at 0 °C then allowed to warm up to room temperature for 12 h. Triethylamin (12.4 g, 12.27 mmol) was added to the solution and α -bromoisobutyryl bromide (20.68 g, 9 mmol) was added to reaction mixture dropwise at 0 °C. The solution was stirred at room temperature for 5 h. The salt was filtered off and the filtrate was extracted three times with water. The organic layer was dried over magnesium sulfate and evaporated. The resulting t-Boc-aminoethyl 2-bromoisobutyrate was dissolved in DCM/ TFA (1:1) and stirred at room temperature for 4 h. The solvent was evaporated under reduced pressure to yield *2-aminoethyl 2-bromoisobutyrate trifluoroacetate* as a white solid (23.54 g, 88%).¹H NMR (400 MHz, DMSO-*d*₆) δ ppm 1.92 (s, 6 H) 3.15 (br. s., 2 H) 4.16 - 4.40 (t, 2 H) 8.18 (br. s., 3 H).

Exo-N-(2-Aminoethyl)-5-norbornene-2,3-dicarboximide. To freshly distilled ethylenediamine (3.84 g, 64 mmol) a solution of *exo*-carbocyclic anhydride (2 g, 8 mmol) in toluene (50 mL) was added dropwise over 1h under mechanical stirring. The mixture was held under Dean–Stark conditions overnight. Before the solvent as well residual ethylenediamine was removed via distillation. Purification was achieved by column chromatography with dichloromethane: methanol (10: 1) as

eluent(1.15 g, 71 %). ¹H NMR (300 MHz, Chloroform-d) δ , ppm: 1.21 (br. s., 2 H) 1.32 (d, J=9.81 Hz, 1 H) 1.42 - 1.55 (m, 1 H) 2.66 (t, 2 H) 2.79 - 2.93 (m, 2 H) 3.15 - 3.28 (m, 2 H) 3.51 (td, J=6.37, 2.38 Hz, 2 H) 6.18 - 6.36 (m, 2 H).

General procedure for polymerization. Monomer (12 eq) and diphenyl benzoate as an initiator (1 eq) were dissolved in dry THF. The reaction mixture was cooled to - 70 °C. LiTMP (14.4 eq) was dissolved in dry THF and added dropwise to the reaction solution. The solution was stirred at - 70 °C for 12 h. The reaction was quenched with excess of dissolved phenol in THF at - 70 °C and warmed up to room temperature, then extracted with DCM. The organic layer was dried over magnesium sulfate and the solvent evaporated under reduced pressure.

General procedure for end -functionalized modifications of polymer. Polymer (1eq) and functionalized amine (30 eq) were dissolved in acetonitrile. The solution was stirred at 80 °C for 12 h. The solution was extracted with DCM, dried over magnesium sulfate and the solvent evaporated under reduced pressure.

RESULTS and DISCUSSION

The polycondensations described by Yokozawa et al. proceed in a chain-growth polymerization manner if the monomer reacts selectively with polymer chain ends.³¹ To achieve this, an activated monomer first reacts with an initiator by means of a reactive site that increases the reactivity of the propagating polymer end group, and therefore the next monomer reacts with the propagating chain end rather than another monomer. The direct polymerization of primary amines within aromatic amino acid ester monomers is difficult with this method, as the resulting polyamides will be easily deprotonated to give insoluble polyanionic amides (the acidity of the obtained secondary amide during the polymerization is higher than that of the primary amine of the monomer). In addition to a reduced solubility, the deprotonated amide would also deactivate the terminal ester

site, due to a strong electron donating ability, thereby slowing down the polymerization. Therefore, all monomers were secondary amines substituted by *N*-alkyl or *N*-alkoxybenzyl protecting groups.

N-substituted monomers were synthesized in two steps as shown in **Figure 1**. Reductive alkylation of 4-aminobenzoic using 2-ethyl hexanal gave 4-((2-ethylhexyl) amino) benzoic acid (**1a**, 81%). Using the same substrate and 2,4-dimethoxybenzaldehyde in a reductive alkylation gave 4-((2,4-dimethoxybenzyl) amino) benzoic acid (**1b**, 94.5%). Steglich esterification of **1a** and **1b** with pentafluorophenol yielded the corresponding ester monomers **M1** (88 % yield) and **M2** (79 % yield) respectively. Esterification with phenol yielded the monomers **M3** (79 % yield, from **1a**) and **M4** (83 % yield, from **1b**).

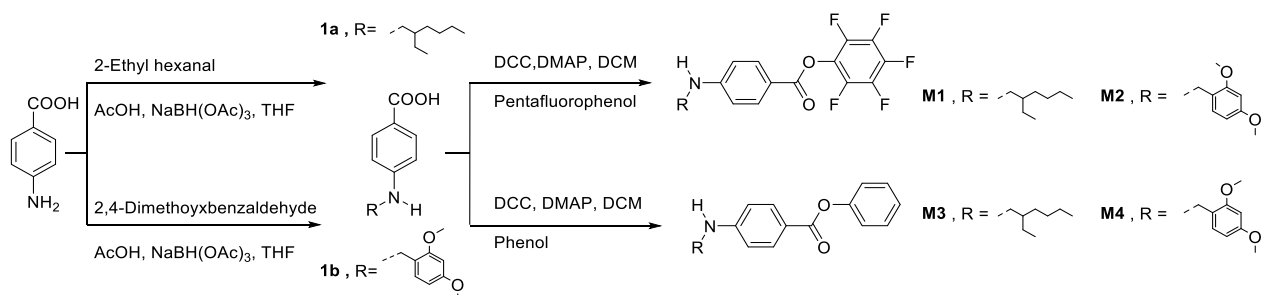


Figure 1. Synthesis of monomers **M1-M4**.

To obtain a telechelic polymer chain, we used diphenyl terephthalate as a bifunctional initiator. Either a phenyl or pentafluorophenyl ester would constitute the end groups of the telechelic polyaramid depending on which monomer **M1-M4** was employed. The possibility of post-functionalization would depend on the reactivity of the ester end group towards nucleophiles. We therefore decided to investigate the more reactive monomers **M1** and **M2** carrying pentafluorophenyl esters first.

To synthesize the diester telechelic poly(benzamide), a LiTMP solution in THF was added to the diphenyl terephthalate initiator and monomer **M1** in dry THF at -70°C. As shown in **Table 1** (entries **P1**, **P1a**, **P1b**), different molecular weight polymers could be synthesized via this method. All polymers obtained showed narrow molecular weight dispersities by GPC (THF) (Figure 2). MALDI-ToF mass spectrometry revealed three different distributions belonging to telechelic polymers with either two pentafluorophenyl ester end groups, one phenyl ester and one pentafluorophenyl ester end group and also a small amount of self-initiated polymer carrying one pentafluorophenyl ester end group (see supporting information Figure S15). This investigation proved the lability of the pentafluorophenyl ester end group, which was most likely replaced by the phenolate ion of the diphenyl terephthalate initiator. The presence of self-initiated polymer also shows the high reactivity of the pentafluorophenyl ester monomers. The monomer **M2** carrying an *N*-protective DMB group was also polymerized (Table 1) under the same conditions as **P1**.

Nonetheless, the post-polymerization modification was examined with polymer **P1** and excess of ethanolamine (30 eq) in acetonitrile at 80°C for 12 hours. MALDI-ToF mass spectrometry confirmed full conversion of both, the phenolate and the pentafluorophenolate ester end group to the amide of ethanolamine (see supporting information Figure S16). As the phenolate ester was easily replaced by ethanolamine in a post-polymerization reaction, we next investigated phenyl ester monomers **M3** and **M4** in the synthesis of telechelic poly(benzamides).

Table 1. Results for the polymerization of different monomers.

Entry	Monomer	LiTMP(equiv)	[M]/[I]	Mn (g/mol)	Mw (g/mol)	PDI ^a
P1	M1	1.2	12	2900	3050	1.07

P1a	M1	1.2	24	6000	6770	1.14
P1b	M1	1.2	56	11000	12400	1.12
P2	M2	1.2	12	2900	3110	1.07
P3	M3	1.2	12	2900	3120	1.08
P4	M4	1.2	12	3100	3290	1.06

^aDetermined by GPC (THF) relative to polystyrene standards.

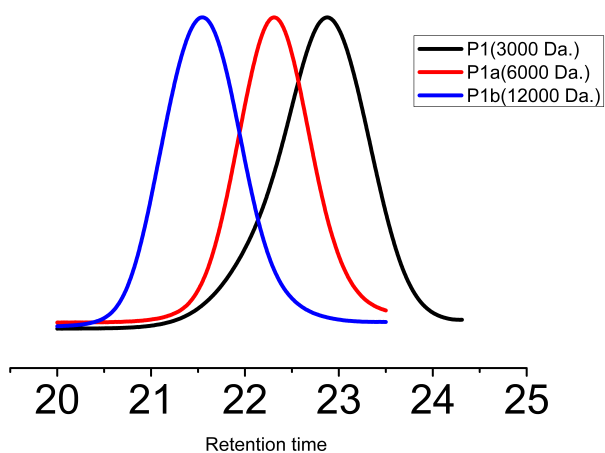


Figure 2. THF GPC elugram of the bifunctional initiated polymer using the **M1** monomer.

A phenolate monomer (**M3** or **M4**) and the diphenyl terephthalate initiator were dissolved in dry THF at -70 °C, and a solution of LiTMP in THF was added and stirred for 12 h and then quenched with a phenol solution in THF (Figure 3). THF GPC data shows the control over the molecular weight with narrow polydispersity for both polymers **P3** and **P4** (Table 2). The MALDI-ToF spectrum exclusively showed phenolate end groups. (see supporting information Figure S17)

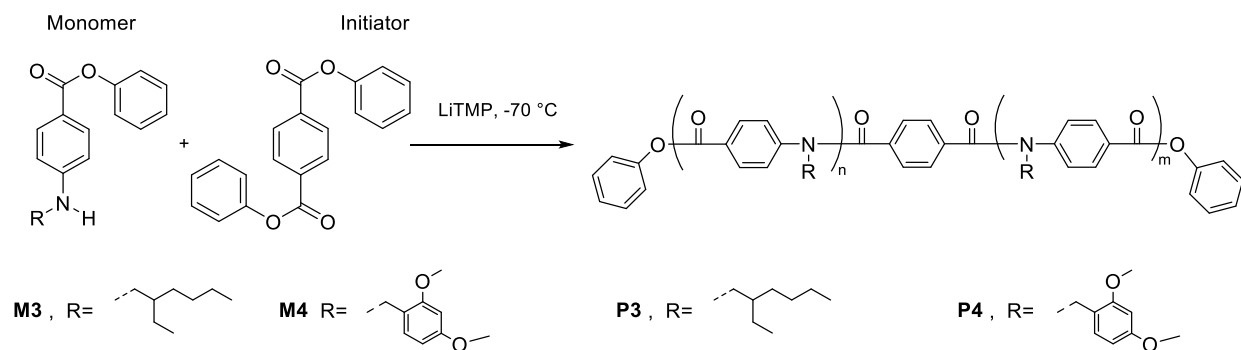


Figure 3. The chain growth polycondensation of **M3** or **M4** with a bifunctional initiator results in functionalizable telechelic polymers **P3** and **P4**.

Telechelic aramide polymers were obtained by reacting the polymers with different functional amines in acetonitrile at 80°C for 12 h. GPC (THF) data before and after post-polymerization modification showed no difference in molecular weight, thereby indicating that no cleavage of the amide bonds in the polymer chain due to transamidation had occurred (Table 2).

Table 2. GPC (THF) data of the functionalized polymers.

reactive polymer	modified polymer	Mn (g/mol) before modification	Mn (g/mol) after modification	PDI after modification ^{a)}
P3	P5	2800	2900	1.07
P4	P6	3100	2700	1.05
P4	P7	3100	2700	1.08
P3	P8	2900	2600	1.06
P3	P9	2900	2800	1.06

^{a)} Determined by GPC (THF) relative to polystyrene standards.

Different functional groups were chosen for post-polymerization modification such as propargylamine, ethylenediamine, ethanolamine, *exo-N*-(2-aminoethyl)-5-norbornene-2,3-dicarboximide and 2-aminoethyl 2-bromo-2-methylpropanoate (Figure 4). These telechelic aramide polymers are currently being investigated for the synthesis of ABA triblock copolymer synthesis via atom transfer radical polymerization (ATRP), click reactions, as diol components for polyurethane syntheses or the preparation of cross-linked networks via the olefin metathesis reaction. Such materials might furthermore prove to be useful as shape persistent end-functional rod-like building blocks in particular after cleavage of the *N*-dimethoxybenzyl protective group of polymer **P4**.

All post-polymerization end-group modified polymers **P5-P9** (Table 2, Figure 4) were characterized by GPC (THF) and MALDI-ToF mass spectrometry (see supporting information).

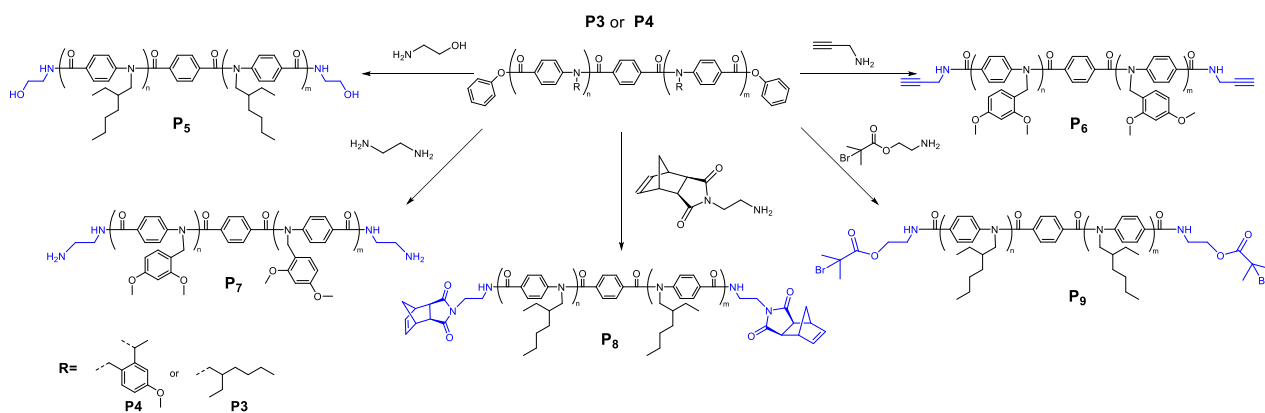


Figure 4. Post polymerization modification of **P3** and **P4**.

Figure 5 shows the MALDI-ToF mass spectrum of polymer **P3** (before) and polymer **P5** (after end-group modification with ethanolamine) as an example illustrating the clean end-group conversion feasible with the method described here.

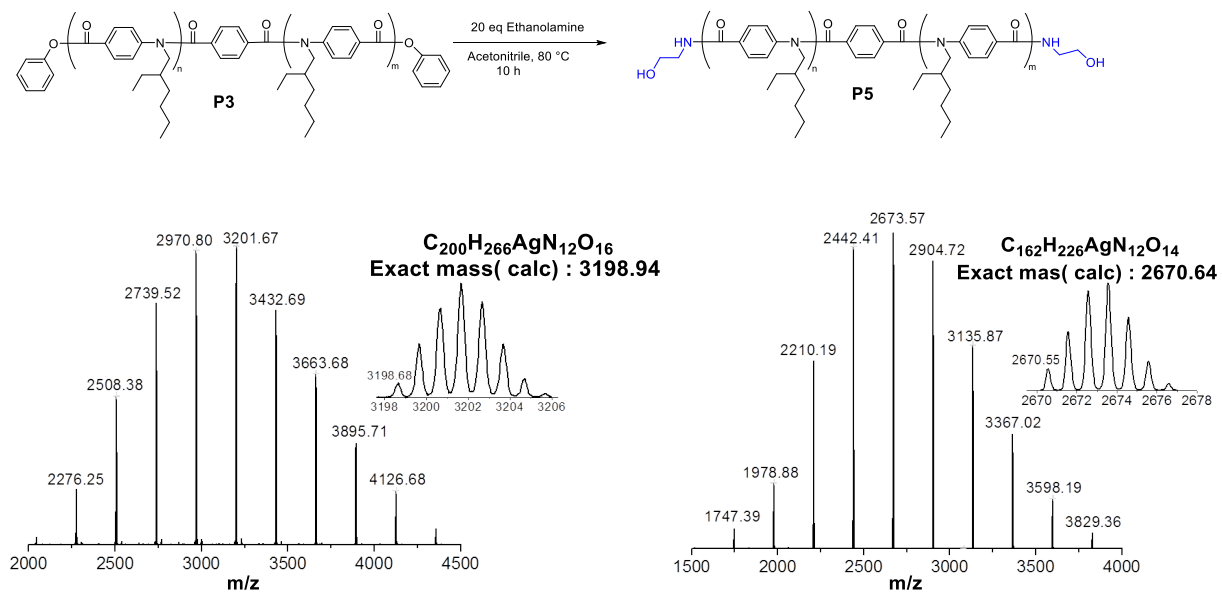


Figure 5. *Left:* MALDI-ToF mass spectrum of the bifunctional-initiated ethyl hexyl polymer **P3** as an Ag^+ adduct. *Right:* MALDI-ToF mass spectrum of the modified bifunctional-initiated ethyl hexyl polymer **P5** as an Ag^+ adduct. The insets show the most intense peak of the distribution isotopically resolved.

From these results, we propose phenyl esters as excellent leaving groups for the synthesis of poly(benzamide)s via chain-growth polycondensation using LiTMP as a non-nucleophilic base and for post-polymerization end-group modification using derivatives of aliphatic amines. For monomers carrying *N*-protected secondary amine groups this method represents a facile route to end-functional shape-persistent building blocks for the construction of supramolecular architectures. For alkyl chain *N*-substituted amine monomers this method opens a pathway to soluble macromonomers that can be utilized in subsequent step-growth polymerization processes.³⁴

³⁸ These end-functional polymers are currently investigated as macromonomers in step-growth polymerizations in our group.

CONCLUSION

Here we presented the synthesis of end-functional telechelic poly(benzamide)s. Phenyl or pentafluorophenyl end groups could easily be modified with a range of suitable aliphatic amines allowing us the introduction of alcohol, alkyne, alkyl bromide, amine or norbornene end groups. The poly(benzamide)s were *N*-alkyl or *N*-dimethoxy benzyl substituted to either ensure excellent organo-solubility or provide the possibility of later *N*-deprotection. The latter would result in the synthesis of rigid-rod-like shape persistent telechelic polymers. Such materials could be useful supramolecular building blocks for the construction of nano-scale architectures. *N*-alkyl chain carrying soluble telechelic polybenzamide on the other hand are good macromonomer candidates for incorporation into step-growth polymers such as polyesters, polyamides or polyurethanes.

All polymers were fully characterized before and after end-group modification by GPC and isotopically resolved MALDI-ToF spectrometry.

ASSOCIATED CONTENT

Supporting Information.

The Supporting Information is available free of charge on the website.

¹H and ¹³C NMR spectra and MALDI ToF MS (PDF).

AUTHOR INFORMATION

Corresponding Author

* andreas.kilbinger@unifr.ch

ORCID

Andreas. F. M. Kilbinger: 0000-0002-2929-7499

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENT

The authors thank the Swiss National Science Foundation and the National Center for Competence in Research (NCCR) "Bioinspired Materials" for financial support.

REFERENCES

- (1) Yamazaki, N.; Higashi, F. Studies on reactions of *N*-phosponium Salts of Pyridines. VIII. Preparation of Polyamides by Means of Diphenyl Phosphite in Pyridine. *J. Polym. Sci., Part C: Polym. Lett. Ed.* **1974**, *12*, 185-191.

- (2) Wu, G.-C.; Tanaka, H.; Sanui, K.; Ogata, N. Synthesis of Poly (*p*-benzamide) with Triphenylphosphine and Hexachloroethane Reagents Reaction Conditions. *Polym. J.* **1982**, *14*, 571-574.
- (3) Seyler, H.; Kilbinger, A. F. M. Linear Organo-Soluble Poly (pbenzamide). *Macromolecules* **2009**, *42*, 9141-9146.
- (4) Yokozawa, T.; Yokoyama, A. Chain-Growth Condensation Polymerization for the Synthesis of Well-Defined Condensation Polymers and π -Conjugated Polymers. *Chem. Rev.* **2009**, *109*, 5595-5619.
- (5) Yokozawa, T.; Horio, S. Condensative Chain polymerization. Chemo selectivity of Aryloxysilane toward Substituted Aromatic Acid Chlorides in a Model Reaction. *Polym. J.* **1996**, *28*, 633-636.
- (6) Yokozawa, T.; Shimura, H. Condensative Chain Polymerization. II. Preferential Esterification of Propagating End Group in Pd-Catalyzed CO-Insertion Polycondensation of 4-Bromophenol Derivatives. *J. Polym. Sci., Part A: Polym. Chem.* **1999**, *37*, 2607-2618.
- (7) Yokozawa, T.; Suzuki, H. Condensative Chain Polymerization in Solid-Liquid Phase. Synthesis of Polyesters with a Defined Molecular Weight and a Narrow Molecular Weight Distribution by Polycondensation. *J. Am. Chem. Soc.* **1999**, *121*, 11573-11574.
- (8) Yokozawa, T.; Asai, T.; Sugi, R.; Ishigooka, S.; Hiraoka, S. Chain-Growth Polycondensation for Nonbiological Polyamides of Defined Architecture. *J. Am. Chem. Soc.* **2000**, *122*, 8313-8314.
- (9) Yokoyama, A.; Iwashita, K.; Hirabayashi, K.; Aiyama, K.; Yokozawa, T. Investigation of Aromatic Polyester Synthesis by the Chain-Growth Polycondensation Method. *Macromolecules* **2003**, *36*, 4328-4336.

(10) Iwashita, K.; Yokoyama, A.; Yokozawa, T. Synthesis of Well-Defined Aromatic Polyesters by Chain-Growth Polycondensation under Suppression of Transesterification. *J. Polym. Sci. Pol. Chem.* **2005**, *43*, 4109-4117.

(11) Yokozawa, T.; Suzuki, Y.; Hiraoka, S. Aromatic Polyethers with Low Polydispersities from Chain-Growth Polycondensation. *J. Am. Chem. Soc.* **2001**, *123*, 9902-9903.

(12) Suzuki, Y.; Hiraoka, S.; Yokoyama, A.; Yokozawa, T. Chain-Growth Polycondensation for Aromatic Polyethers with Low Polydispersities: Living Polymerization Nature in Polycondensation *Macromolecules* **2003**, *36*, 4756-4765.

(13) Suzuki, Y.; Hiraoka, S.; Yokoyama, A.; Yokozawa, T. Solvent Effect on Chain-Growth Polycondensation for Aromatic Polyethers. *J. Polym. Sci. Pol. Chem.* **2004**, *42*, 1198-1207.

(14) Yokozawa, T.; Taniguchi, T.; Suzuki, Y.; Yokoyama, A. Chain-Growth Polycondensation of Monomer Consisting of Two Aromatic Rings: Synthesis of Well-Defined Poly (ether sulfone) from 4-Fluoro-4-hydroxydiphenyl Sulfone. *J. Polym. Sci. Pol. Chem.* **2002**, *40*, 3460-3467.

(15) Miyakoshi, R.; Yokoyama, A.; Yokozawa, T. Precision Synthesis of n-Type π -Conjugated Polymers in Catalyst-Transfer Condensation Polymerization. *Macromol. Rapid. Comm.* **2004**, *25*, 1663-1666.

(16) Yokoyama, A.; Miyakoshi, R.; Yokozawa, T. Chain-Growth Polymerization for Poly (3-hexylthiophene) with a Defined Molecular Weight and a Low Polydispersity. *Macromolecules* **2004**, *37*, 1169-1171.

(17) Miyakoshi, R.; Yokoyama, A.; Yokozawa, T. Catalyst-Transfer Polycondensation. Mechanism of Ni-Catalyzed Chain-Growth Polymerization Leading to Well-Defined Poly (3-hexylthiophene). *J. Am. Chem. Soc.* **2005**, *127*, 17542-17547.

(18) Miyakoshi, R.; Shimono, K.; Yokoyama, A.; Yokozawa, T. Catalyst-Transfer Polycondensation for the Synthesis of Poly (p-phenylene) with Controlled Molecular Weight and Low Polydispersity. *J. Am. Chem. Soc.* **2006**, *128*, 16012-16013.

(19) Yokoyama, A.; Suzuki, H.; Kubota, Y.; Ohuchi, K.; Higashimura, H.; Yokozawa, T. Chain-Growth Polymerization for the Synthesis of Polyfluorene via Suzuki Miyaura Coupling Reaction from an Externally Added Initiator Unit. *J. Am. Chem. Soc.* **2007**, *129*, 7236-7241.

(20) Huang, C.; Ohta, Y.; Yokoyama, A.; Yokozawa, T. Efficient Low-Temperature Atom Transfer Radical Coupling and Its Application to Synthesis of Well-Defined Symmetrical Polybenzamides. *Macromolecules* **2011**, *44*, 4140-4148.

(21) Masukawa, T.; Yokoyama, A.; Yokozawa, T. Synthesis of Well-Defined Polybenzamide-block-Polystyrene by Combination of Chain-Growth Condensation Polymerization and RAFT Polymerization. *Macromol. Rapid. Commun.* **2009**, *30*, 1413-1418.

(22) Sugi, R.; Tate, D.; Yokozawa, T. Synthesis of Well-Defined Aromatic Polyamide-graft-Poly(tetrahydrofuran) by Chain-Growth Condensation Polymerization of *Macromonomer*. *J. Polym. Sci. Polym. Chem.* **2013**, *51*, 2725-2729.

(23) Ohta, Y.; Shirakura, T.; Yokoyama, A.; Yokozawa, T. Synthesis of Polystyrene-graft-Poly (p-benzamide) by Chain-Growth Condensation Polymerization and Radical Polymerization: Improvement of Thermal Properties of Polystyrene. *J. Polym. Sci. Polym. Chem.* **2013**, *51*, 1887-1892.

(24) Yoshino, K.; Yokoyama, A.; Yokozawa, T. Synthesis of a Variety of Star-Shaped Polybenzamides via Chain-Growth Condensation Polymerization with Tetrafunctional Porphyrin Initiator. *J. Polym. Sci. Polym. Chem.* **2011**, *49*, 986-994.

(25) Ohishi, T.; Masukawa, T.; Fujii, S.; Yokoyama, A.; Yokozawa, T. Synthesis of Core Cross-Linked Star Polymers Consisting of Well-Defined Aromatic Polyamide Arms. *Macromolecules* **2010**, *43*, 3206-3214.

(26) Yamazaki, Y.; Ajioka, N.; Yokoyama, A.; Yokozawa, T. Synthesis of Well-Defined Miktoarm Star Copolymers of Aromatic Polyether and Polystyrene by Chain-Growth Condensation Polymerization and Atom Transfer Radical Polymerization. *Macromolecules* **2009**, *42*, 606-611.

(27) Ohta, Y.; Fujii, S.; Yokoyama, A.; Furuyama, T.; Uchiyama, M.; Yokozawa, T. Synthesis of Well-Defined Hyperbranched Polyamides by Condensation Polymerization of AB₂ Monomer through Changed Substituent Effects. *Angew. Chem. Int. Ed.* **2009**, *48*, 5942-5945

(28) Ohta, Y.; Kamijyo, Y.; Fujii, S.; Yokoyama, A.; Yokozawa, T. Synthesis and Properties of a Variety of Well-Defined Hyperbranched N-Alkyl and N-H Polyamides by Chain-Growth Condensation Polymerization of AB₂ Monomers. *Macromolecules* **2011**, *44*, 5112-5122.

(29) Irzhaka, T.; Deberdeev, T.; Irzhak, V. Structural Kinetics of the Formation of Hyperbranched Polymers via Condensation Polymerization in the Presence of the Substitution Effect. *J. Polym. Sci.* **2015**, *57*, 55-60.

(30) Ohta, Y.; Kamijyo, Y.; Akihiro Yokoyama, A.; Yokozawa, T. Synthesis of Well-Defined, Water-Soluble Hyperbranched Polyamides by Chain-Growth Condensation Polymerization of AB₂ Monomer. *Polymers* **2012**, *4*, 1170-1182.

(31) Sugi, R.; Yokoyama, A.; Yokozawa, T. Synthesis of Well-Defined Telechelic Aromatic Polyamides by Chain-Growth Polycondensation: Application to the Synthesis of Block Copolymers of Polyamide and Poly(tetrahydrofuran). *Macromol. Rapid Commun.* **2003**, *24*, 1085-1090.

- (32) Yokozawa, T.; Ogawa, M.; Sekino, A.; Sugi, R.; Yokoyama, A. Chain-Growth Polycondensation for Well-Defined Aramide. Synthesis of Unprecedented Block Copolymer Containing Aramide with Low Polydispersity. *J. Am. Chem. Soc.* **2002**, *124*, 15158-15159.
- (33) Yokozawa, T.; Ohta, Y. Transformation of Step-Growth Polymerization into Living Chain-Growth Polymerization. *Chem. Rev.* **2016**, *116*, 1950-1968.
- (34) Tanatani, A.; Yokoyama, A.; Azumaya, I.; Takakura, Y.; Mitsui, C.; Shiro, M.; Uchiyama, M.; Muranaka, A.; Kobayashi, N.; Yokozawa, T. Helical Structures of N-Alkylated Poly(p-benzamide)s. *J. Am. Chem. Soc.* **2005**, *127*, 8553-8561.
- (35) Yokoyama, A.; Yokozawa, T. Converting Step-Growth to Chain-Growth Condensation Polymerization. *Macromolecules* **2007**, *40*, 4903-4101.
- (36) Schulze, M.; Kilbinger, A. F. M. Toward Large Tubular Helices Based on the Polymerization of Tri (benzamide)s. *J. Polym. Sci., Part A: Polym. Chem.* **2016**, *54*, 1731-1741.
- (37) Konig, H.; Gorelik, T.; Kolb, U.; Kilbinger, A. F. M. Supramolecular PEG-co-Oligo (p-benzamide)s Prepared on a Peptide Synthesizer. *J. Am. Chem. Soc.* **2007**, *129*, 704-708.
- (38) Badoux, M.; Kilbinger, A. F. M. Synthesis of High Molecular Weight Poly(p-benzamide)s. *Macromolecules* **2017**, *50*, 4188-4197.

Graphical abstract

