



Green synthesis of copper oxide nanoparticles using *Bougainvillea* leaves aqueous extract and antibacterial activity evaluation

Ahid M. Al-Fa,ouri¹, Mahmoud H. Abu-Kharma¹ and Akl M. Awwad^{2,*}

¹Department of Physics, Al-Balqa Applied University, El Salt, Jordan

²Department of Materials Science, Royal Scientific Society, Amman, Jordan

*Corresponding author's E. mail: akl.awwad@yahoo.com

ARTICLE INFO

Article type:

Research article

Article history:

Received November 2020

Accepted February 2021

July 2021 Issue

Keywords:

Green synthesis

Copper oxide nanoparticles

Bougainvillea leaves

Aqueous extract

Antibacterial activity

ABSTRACT

The aim of present study is based on low cost, efficient, non-toxic and eco-friendly method for green synthesis of copper oxide nanoparticles (CuONPs) using *Bougainvillea* leaves aqueous extract. The green synthesized nanoparticles were subjected to characterization techniques UV-visible spectroscopy (UV-vis), X-ray diffraction (XRD), Fourier transform Infrared spectroscopy (FT-IR) and transmission electron microscope (TEM). The synthesized CuONPs were pure, predominantly spherical with sizes ranges from 8-20 nm. CuONPs showed excellent antimicrobial activity against various bacterial strains *Escherichia coli*, *Enterococcus faecalis*, and *Staphylococcus aureus*. Moreover, *E. coli* and *E. faecalis* exhibited the highest sensitivity to CuONPs while *Staphylococcus aureus* was the least sensitive. Possible mechanisms of antimicrobial activity of CuONPs should be further investigated.

© 2021 International Scientific Organization: All rights reserved.

Capsule Summary: *Bougainvillea* leaves aqueous extract mediated green synthesis of copper oxide nanoparticles was investigated. The prepared CuONPs was of spherical shape with 8-20 nm size and active antibacterial agents.

Cite This Article As: A. M. Al-Fa,ouri, M. H. Abu-Kharma and A. M. Awwad. Green synthesis of copper oxide nanoparticles using *Bougainvillea* leaves aqueous extract and antibacterial activity evaluation. Chemistry International 7(3) (2021) 155-162. <https://doi.org/10.5281/zenodo.4899095>

INTRODUCTION

The CuONPs with different morphological structures was developed using various synthetic routes such as nonionic water-in-oil micro-emulsions (Dodoo-Arhin et al., 2012), precipitation method (Phiwdang et al., 2013; Ahamed et al. 2014; Mayekar et al., 2014), electrochemical method (Katwai et al., 2015), hydrothermal synthesis (Arun et al., 2015), solid state thermal decomposition (Shahsavani et al., 2016), sonochemical method (Silva et al., 2019), chemical and biogenic methods (Muthuvel et al., 2020), microwave-assisted method (Kannan et al., 2020), wet precipitation technique (Parekh et al., 2021), green and traditional

chemical methods (Keabadile et al., 2020). These methods for synthesis of CuONPs have many disadvantages: Difficulty of scale up the process, separation and purification of nanoparticles. Developing facile and green routes for synthesizing copper oxide nanoparticles are of importance and still a challenge for materials researchers. Plants such leaves, seeds, bark, flowers and fruits have been suggested as valuable alternatives to chemical and physical methods for synthesis of CuONPs, i.e., *Polyalthia longifolia* (Nagore et al., 2021), *Ocimum basilicum* (Altikatoglu et al., 2017), *Catha edulis* (Anduaalem et al., 2020), *Juglans regia* (Asemami and Anarjan, 2019), *Ailanthus altissima* (Awwad and Amer, 2020), *Catharanthus roseus* (Begum et al., 2019), *Malva sylvestris* (Benhammada and Trache, 2021), *Adhatoda vasica*

nees (Bhavyasree and Xavier, 2020), *Beta vulgaris L* (Chandrasekaran et al., 2020), *Lantana camara* (Chowdhury et al., 2020), *Psidium guajava* (Das and Goswami, 2019), *Chamomile* (Duman et al., 2016), *Catha edulis* (Gebremedhn et al., 2019), *Punica granatum* (Ghidan et al., 2016), *Ziziphus mauritiana L.* (Ghotekar et al., 2017), *Desmodium gangeticum* aqueous (Guin et al., 2015), *Abutilon indicum* (Ijaz et al., 2017), *Camellia Sinensis* (Jeronsia et al., 2019), *Cinnamomum malabratrum* (Krishna et al., 2020), *Andean blackberry* (*Rubus glaucus* Benth.) (Kumar et al. 2017) extracts have been employed for the green synthesis of NPs.

Aloe vera (Kumar et al., 2015), *Saraca indica* (Prasad, et al., 2017), *Anthemis nobilis* (Nasrollahzadeh, et al., 2015), *Papaya* (Phang et al., 2021), *Bougainvillea* (Shammout and Awwad, 2021), *Calotropis gigantean* (Sharma et al., 2015), *Tecoma castanifolia* (Sharmila et al., 2016), oak fruit hull (Sorbiun et al., 2018), *Cordia myxa L.* (Thamer et al., 2018), herbal tea (*Stachys Lavandulifolia*) (Veisi et al., 2021), *Ixiro coccinea* (Vishveshvar et al., 2018; Yedurkar et al., 2017), *Syzygium alternifolium* (Wt.) Walp (Yugandhar et al., 2018), *Punica granatum* (Vidovix et al., 2019), *Adiantum lunulatum* (Sarkar et al., 2020) also showed promising potential for the synthesis of NPs via green route. Moreover, *Cassia fistula* and *Melia azedarach* (Nasser et al., 2021). *Enicostemma axillare* (Lam.) (Mali et al., 2019), *Psidium guajava* (Singh et al., 2019), *Eletteria Cardamomum* (Venkatramanan et al., 2020), *Catharanthus roseus* (Dayana et al., 2021) and *Simaroubaglauca* (Deepthi et al., 2021) different plant parst showed promising efficiency for the synthesis of NPs.

Based on aforementioned facts, an eco-friendly and green route for the synthesis of copper oxide nanoparticles (CuONPs) using an abundantly available *Bougainvillea* leaves plants in Jordan is reported, which has not been reported previously. The CuONPs was characterized by various techniques (FT-IR, XRD, SEM and TEM) and antibacterial activity was also investigated against selected strains.

MATERIAL AND METHODS

Chemical, reagents and sample collection

Copper acetate $\text{Cu}(\text{CH}_3\text{COO})_2$ was purchased from Sigma-Aldrich, Germany with purity $\geq 99.0\%$. *Bougainvillea* fresh leaves were collected from the plants at Al-Salt province, Jordan, which was washed with distilled water. Afterwards, leaves were dried at laboratory temperature (27°C) for 7 days. Dried leaves were ground in a mortar and pestle to obtain powder leave particles $\leq 44 \mu\text{m}$.

Preparation of *Bougainvillea* leaves aqueous extract

5-10 g of the dried powder of leaves was boiled in 100 ml of de-ionized water for 10 min. The aqueous solution of *Bougainvillea* leaves was cooled at laboratory temperature and then filtered with Whatman No. 1 filter paper. The filtrate was kept in refrigerator for the experimental work.

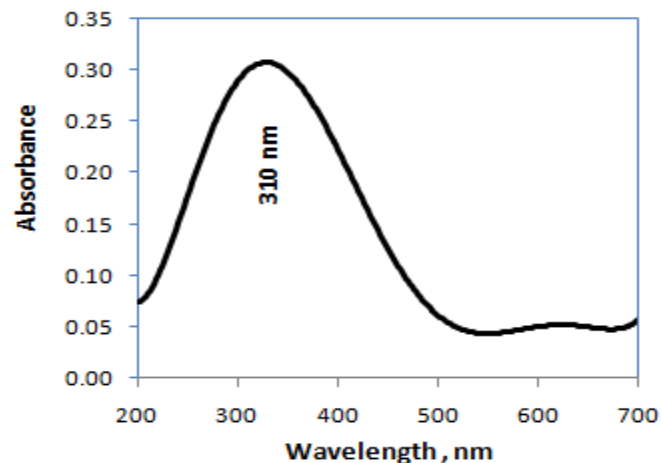


Fig. 1: UV-vis spectrum of CuONPs synthesized by green *Bougainvillea* leaves aqueous extract

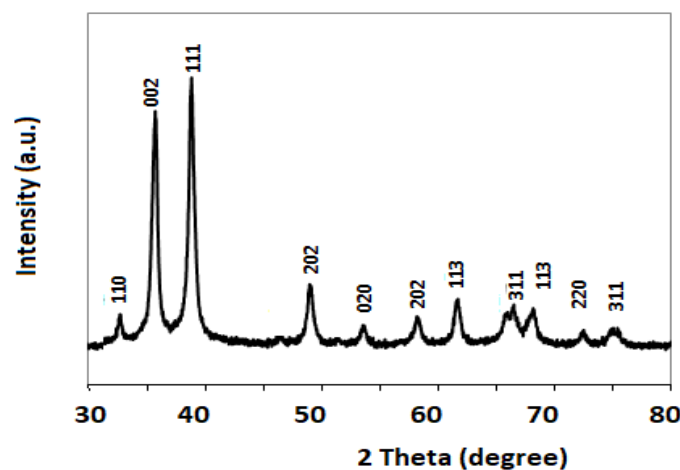


Fig. 2: XRD pattern of green synthesized CuONPs by *Bougainvillea* leaves aqueous extract

Synthesis of copper oxide nanoparticles (CuONPs)

A 5 g of copper acetate $\text{Cu}(\text{CH}_3\text{COO})_2$ was dissolved in 100 ml de-ionized water in a glass beaker with stirring for 5 min. Afterwards, *Bougainvillea* leaves aqueous extract was added drop wise and mixed homogeneously by magnetic stirrer for 10 min. The blue color of copper acetate solution changes to green deep color due to the formation of CuOHNPs. Under continuous magnetic stirring for 4 h, the deep green color of the mixture changed to brown-black. Afterwards, the brown-black mixture cooled to attain laboratory temperature and with centrifuging at 10,000 rpm for 10 min, the resulting paste was transferred into silica crucible for heating in furnace at 80°C for 4 h, subsequently black color powder material achieved. Powder obtained was subjected to FT-IR, XRD, SEM and TEM analysis (Scheme 1).

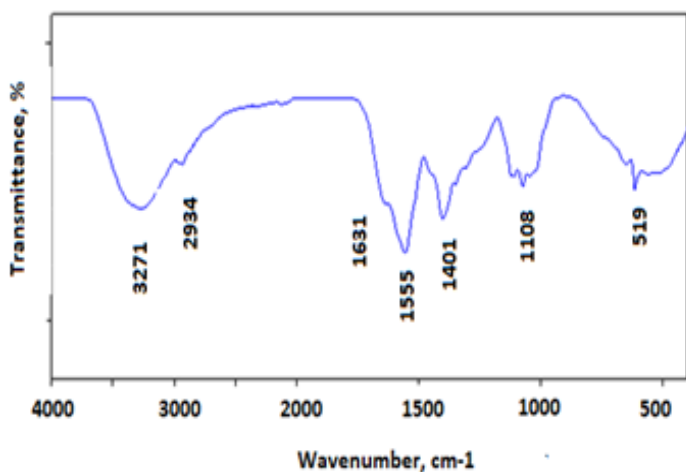


Fig. 3: FT-IR analysis of *Bougainvillea* aqueous leaf extract

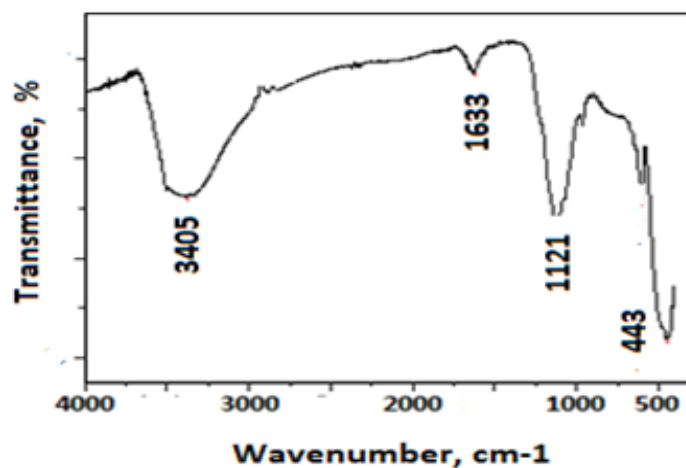


Fig. 4. FT-IR analysis of green synthesized CuONPs

Characterization

UV-vis spectrum of copper oxide nanoparticles was recorded, by taking 0.1 ml of the sample and diluting it with 2 ml de-ionized water, as a function of time of reaction using a Shimadzu 1601 spectrophotometer in the wave length region 200 to 700 nm operated at a resolution of 1 nm. Transmission electron microscopy was done using TEM CM 200, Philips. Powder X-ray diffraction (XRD) was performed using X-ray diffractometer, Shimadzu, XRD6000 with CuK α radiation $\lambda = 1.5405 \text{ \AA}$ over a wide range of Bragg angles ($3^\circ \leq 2\theta \leq 80^\circ$). Fourier transform infrared (FTIR) spectroscopic measurements were done using Shimadzu, IR-Prestige-21 spectrophotometer.

Antibacterial activities of CuONPs

The synthesized copper oxide nanoparticles (CuONPs) synthesized by *Bougainvillea* leaves aqueous extract effect on bacterial strains Gram negative bacteria *Escherichia coli* (ATCC 27853), *Enterococcus faecalis* (ATCC 29212) and gram-positive bacterium *Staphylococcus aureus* (ATCC 25923). *E. coli*, *E. faecalis* and *S. aureus* were assayed by agar well diffusion and disc diffusion methods. All of the data from three independent replicate trials were subjected to analysis using statistical package. The data are reported as the mean \pm SD and significant differences between mean values were determined with one way analysis of variance. The minimum inhibitory concentration (MIC) was determined.

RESULTS AND DISCUSSION

UV-vis analysis

The green synthesis of copper oxide nanoparticles (CuONPs) using *Bougainvillea* leaves aqueous extract were studied. Formation of copper oxide nanoparticles were confirmed by UV-vis spectrophotometer (Fig. 1). UV-vis absorption spectrum of synthesized copper oxide nanoparticles was recorded for the sample in the range of 200–700 nm. The spectrum showed that the absorbance peak at 310 nm corresponding to the characteristic band of copper oxide nanoparticles.

X-ray diffraction (XRD) analysis

The XRD analysis of green synthesized copper oxide nanoparticles (CuONPs) using *Bougainvillea* leaves aqueous extract as reducing and stabilizing agent (Fig. 2). The 2θ peaks at 32.5° , 35.8° , 38.4° , 48.3° , 58.3° , 61.9° , 64.9° , 66.7° , 72.7° and 75.4° are attributed to the crystal planes of copper oxide at (110), (002), (111), (202), (020), (202), (113), (311), (113), (220), and (311), respectively. The copper oxide nanoparticles are well crystalline. The position and the relative intensity of the diffraction peaks match well with the standard phase CuONPs diffraction pattern of the International Center of Diffraction Data card (JCPDS-80-1916). The average particle sizes of the synthesized CuO nanoparticles were calculated using Debye-Scherrer formula (Eq. 1).

$$D = K\lambda/\beta\cos\theta \quad (1)$$

Where, D is the mean diameter of nanoparticles, β is the full width at half-maximum value of XRD diffraction lines, λ is the wavelength of X-ray radiation source 0.15405 nm, θ is the half diffraction angle–Bragg angle and K is the Scherrer constant with value from 0.9 to 1. The crystalline size of green synthesized copper oxide nanoparticles using *Bougainvillea* leaves aqueous extract calculated from Scherrer equation was in the range 8-20 nm.

FT-IR analysis of extract and CuONPs

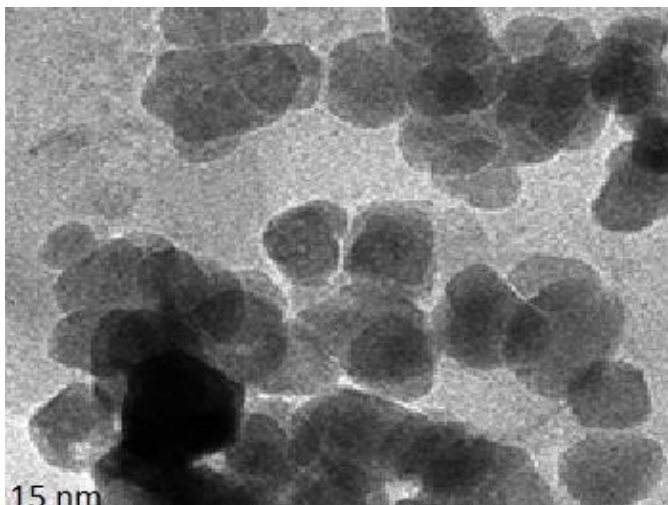


Fig. 5: TEM of green synthesized CuONPs by *Bougainvillea* leaves aqueous extract

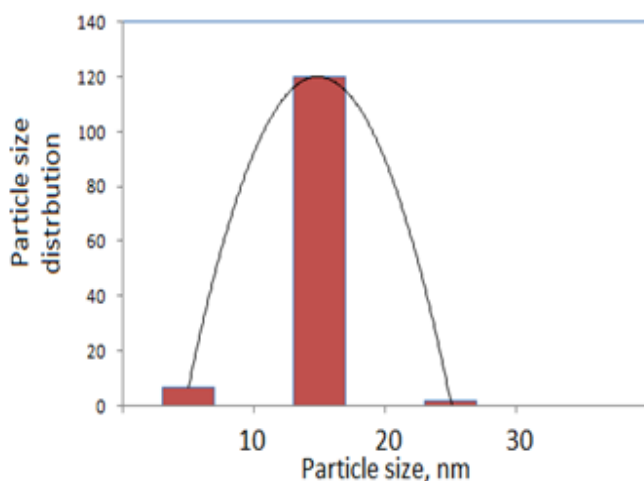


Fig. 6: Particle size distribution histogram of synthesized CuONPs

The FT-IR analysis of *Bougainvillea* leaves aqueous extract and the synthesized copper oxide nanoparticles to identify the biomolecules responsible for the bioreduction copper salts to copper oxide nanoparticles. The FT-IR spectrum of

Bougainvillea leaves aqueous extract showed that *Bougainvillea* spectrum have the peaks at 3271, 2934, 1631, 1555, 1401, 1108 and 519 cm^{-1} (Fig. 3). Strong broad peak at 3271 cm^{-1} is due to the O-H groups of water, alcohols, or phenols and the presence of N-H amides stretching vibration. The band at 2934 cm^{-1} is assigned to $-\text{CH}_2$ and C-H stretching mode in alkenes. The strong peak at 1631 cm^{-1} in *Bougainvillea* leaves aqueous extract could be attributed to C=C stretching vibrations about C=O amide conjugated C=O of the proteins that are responsible for reducing, capping and stabilizing of CuONPs. The bands at 1631, 1555, 1401, 1108 and 519 cm^{-1} can be allocated to the stretching vibration of C-OH bond from proteins (amide I) of the leaves extract. Peak in the region 1601 cm^{-1} may be attributed to the presence of the stretching vibrations of carboxylic acids and amino groups. The band at 519 cm^{-1} assigned for aromatic compounds residue in protein of *Bougainvillea* leaves aqueous extract. The FT-IR analysis of synthesized copper oxide nanoparticles showed strong peaks at 3405 cm^{-1} , 1633, 1121 and 443 cm^{-1} . The bands at 3405 cm^{-1} and 1633 cm^{-1} represent C-O-H or C-N-H groups in the plant extract, which aid on the converting copper acetate to copper oxide nanoparticles. The band 443 cm^{-1} is due to the presence CuO nanoparticles (Fig. 4).

Transmission electron microscopy (TEM)

The morphology and size determination of green synthesized CuONPs by *Bougainvillea* leaves aqueous extract was done by transmission electron microscopes (TEM). TEM of green synthesized CuONPs showed the nanoparticles are spherical in shape (Fig. 5). TEM analysis also reveals the green synthesized CuONPs are in size range 8–20 nm. Moreover, TEM pattern of green synthesized CuONPs confirmed the crystalline nature of copper oxide nanoparticles. The particle size distribution of the synthesized nanoparticles is ranging between 5 nm and 20 nm (Fig. 6). A narrow size distribution of the CuONPs was observed with average size 15 nm.

Antibacterial activity

Minimum inhibitory concentration (MIC) values were obtained for tested against *E. coli*, *E. faecalis* and *S. aureus*. The results are presented in Table 1 and Fig. 7, it can be seen that the copper oxide nanoparticles present the best antibacterial activity against the three strains tested in

Table 1: Antimicrobial activity (zone of inhibition) of synthesized CuONPs

Microorganisms	CuONPs concentration			
	20 μl	40 μl	60 μl	80 μl
<i>E. coli</i>	12	18	20	26
<i>E. faecalis</i>	10	17	18	22
<i>S. aureus</i>	8	11	16	18


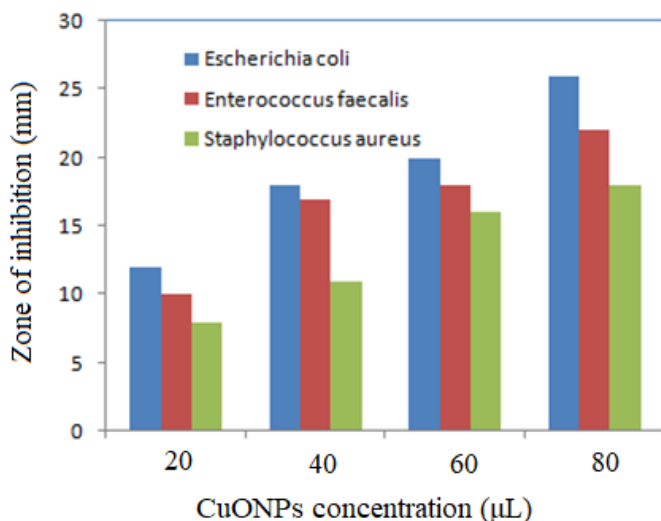


Fig. 7: Zone of inhibition (Well diffusion assay for CuONPs against microbial strains)

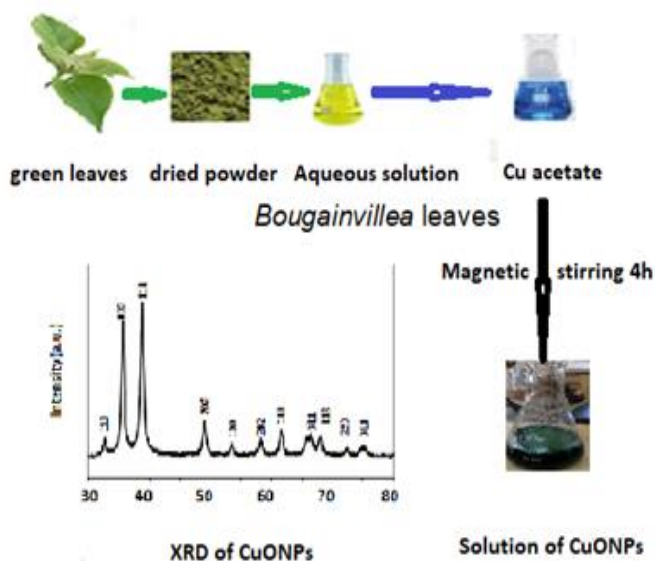

Scheme 1: Graphical presentation for the green synthesis of CuONPs

comparison with *Bougainvillea* leaves aqueous extract and the reference drug. The MIC of the copper oxide nanoparticles is higher when it is tested against *E. coli* and *E. faecalis* than when tested against *S. aureus*. These results refer to differences in the cell wall of each strain; the cell wall of Gram-negative strains (*E. coli* and *E. faecalis*) are wider than the cell wall of Gram-positive strains (*S. aureus*). This is probably of the toxicity of copper oxide ions on *E. coli* and *E. faecalis* include a rapid DNA degradation, followed by a reduction of bacterial respiration; it is also known that copper oxide ions inhibit certain cytochromes

in the membrane. The *Bougainvillea* leaves aqueous extract was found to be highly efficient for the synthesis of CuONPs at nanoscale and the prepared CuONPs showed promising antimicrobial activity, which could have practical application to control bacterial infections. This study observed results reveal that the green synthesized CuONPs showed a significant effect as antibacterial studied compared with positive drug control. It could be explained by large surface area of CuONPs and partially its decomposition in wet medium to copper hydroxide ($\text{Cu}(\text{OH})_3$) which gives better contact with microorganisms thus alter the microbial metabolism and penetrated inside the microorganisms. The equal volume (20 μl) of antibiotic: tetracycline (Das and Goswami, 2019). Hence, green synthesis is an efficient route to prepare CuONPs for biomedical application (Akintelu et al., 2020; Chandrasekar et al., 2021; Sathiyavimal et al., 2018).

CONCLUSIONS

Green synthesis of copper oxide nanoparticles (CuONPs) is an eco-friendly, safer to environment and easy method. A fast, eco-friendly and convenient green method for the synthesis of CuONPs nanoparticles from copper acetate in aqueous extract of *Bougainvillea* leaves at ambient temperature. Spherical, polydispersity of CuONPs of particle sizes ranging from 8 to 20 nm with an average size of 15 nm are obtained. These results could be used in developing novel antibacterial agent, which may find potential applications in different fields with more safety since NPs could be prepared using green synthesis route and same route can be adopted for the fabrication of NPs based on different NPs metals.

ACKNOWLEDGEMENTS

AMA is thankful to the financial support by the Royal Scientific Society and the Physics department, the Al Balqa University, El Salt, Jordan.

REFERENCES

- Ahamed, M., Alhadlaq, H.A., Khan, M.A., Karuppiah, P., N.A. Al-Dhabi, N.A., 2014. Synthesis, characterization and antimicrobial activity of copper oxide nanoparticles. *Journal of Nanomaterials* 2014, 637858.
- Akintelu, S.A., Folorunso, A.S., Folorunso, F.A., Oyebamiji, A.K., 2020. Green synthesis of copper oxide nanoparticles for biomedical application and environmental remediation. *Heliyon* 6, e04508.
- Altikatoglu, M., Attar, A., Erci, F., Cristache, C.M., I. Isildak, I., 2017. Green synthesis of copper oxide nanoparticles using *Ocimum basilicum* extract and their antibacterial activity. *Fresenius Environmental Bulletin* 26, 7832-7837.
- Andualem, W.W., Sabir, F.K., Mohammed, E.T., Belay, H.H., B. A. Gonfa, B.A., 2020. Synthesis of copper oxide

- nanoparticles using plant leaf extract of *Catha edulis* and its antibacterial activity. *Journal of Nanotechnology* 2020, 2932434.
- Arun, K.J., Batra, A.K., Krishna, A., Bhat, K., Aggarwal, M.D., Francis, P.J., 2015. Surfactant free hydrothermal synthesis of copper oxide nanoparticles. *American Journal of Materials Science* 5, 36-38.
- Asemani, M., Anarjan, N., 2019. Green synthesis of copper oxide nanoparticles using *Juglans regia* leaf extract and assessment of their physico-chemical and biological properties. *Green Processing and Synthesis* 8, 1-7.
- Awwad, A.M., Amer, M.W., 2020. Biosynthesis of copper oxide nanoparticles using *Ailanthus altissima* leaf extract and antibacterial activity. *Chemistry International* 6, 210-217.
- Begum, S.N., Esakkiraja, A., Asan, A., Muthumari, S.M., Raj, G.V., 2019. Green synthesis of copper oxide nanoparticles using *Catharanthus roseus* leaf extract and their antibacterial activity. *International Journal of Scientific Research in Multidisciplinary Studies* 5, 21-27.
- Benhammad, A., Trache, D., 2021. Green synthesis of CuO nanoparticles using *Malva sylvestris* leaf extract with different copper precursors and their effect on nitrocellulose thermal behavior. *Journal of Thermal Analysis and Calorimetry* 99, 1-10.
- Bhavyasree, P.G., Xavier, T.S., 2020. Green synthesis of copper oxide/carbon nanocomposites using the leaf extract of *Adhatoda vasica* Nees, their characterization and antimicrobial activity. *Heliyon* 6, e03323.
- Chandrasekar, A., Vasantharaj, S., Jagadeesan, N.L., Shankar, S.N., Pannerselvam, B., Bose, V.G., Arumugam, G., Shanmugavel, M., 2021. Studies on phytomolecules mediated synthesis of copper oxide nanoparticles for biomedical and environmental applications. *Biocatalysis and Agricultural Biotechnology* 33, 101994.
- Chandrasekaran, R., Yadav S.A., Sivaperumal S., 2020. Phytosynthesis and characterization of copper oxide nanoparticles using the aqueous extract of *Beta vulgaris* L and evaluation of their antibacterial and anticancer activities. *Journal of Cluster Science* 31, 221-230.
- Chowdhury, R., Khan, A., Rashid, M.H., 2020. Green synthesis of CuO nanoparticles using: *Lantana camara* flower extract and their potential catalytic activity towards the aza-Michael reaction. *RSC Advances* 10, 14374-14385.
- Das, D., Goswami, S., 2019. Antifungal and antibacterial property of Guava (*Psidium guajava*) leaf extract: Role of phytochemicals. *International Journal of Health Sciences and Research* 9, 39-45.
- Dayana, K.S., Jothimani, R., Dural, S.C.V., 2021. Green synthesis of copper oxide nanoparticles from *Catharanthus roseus* plant leaf extract and its investigation. *Journal of Nano and Electronic Physics* 13, 01014.
- Deepthi, P., Kumar, P Naresh., Prema, P, 2021. Synthesis of copper oxide nanoparticles using leaf extract of *Simaroubaglauca* and its antibacterial study. *Indian Journal of Chemical Technology* 28, 123-127.
- Dodoo-Arhin, D., Leoni, M., Scardi, P., 2012. Microemulsion synthesis of copper oxide nanorod-like structures. *Molecular Crystals and Liquid Crystals* 555, 17-31.
- Duman, F., Ocsoy, I., Kup, F.O., 2016. *Chamomile* flower extract-directed CuO nanoparticle formation for its antioxidant and DNA cleavage properties. *Mater Sci Eng C* 60, 333-338.
- Gebremedhn, K., Kahsay, M.H., Aklilu, M., 2019. Green synthesis of copper nanoparticles using leaf extract of *Catha edulis* and its antibacterial activity. *Journal of Pharmacy and Pharmacology* 7, 327-342.
- Ghidan, A.Y., Al-Antary, T.M., Awwad, A.M., 2016. Green synthesis of copper oxide nanoparticles using *Punica granatum* peels extract: Effect on green peach Aphid. *Environmental Nanotechnology, Monitoring and Management* 6, 95-98.
- Ghotekar, S.K., Pansambal, S., Ghotekar, S., Oza, R., Deshmukh, K., 2017. Green synthesis of copper nanoparticles using *Ziziphus mauritiana* L. extract and its characterizations. *International Journal of Scientific Research in Science and Technology* 3, 1388-1392.
- Guin, R., Banu, S., Kurian, G.A., 2015. Synthesis of copper oxide nanoparticles using *Desmodium gangeticum* aqueous root extract. *International Journal of Pharmacy and Pharmaceutical sciences* 7, 60-65.
- Ijaz, F., Shahid, S., Khan, S.A., Ahmad, W., Zaman, S., 2017. Green synthesis of copper oxide nanoparticles using *Abutilon indicum* leaf extract: Antimicrobial, antioxidant and photocatalytic dye degradation activities. *Tropical Journal of Pharmaceutical Research* 16, 743-753.
- Jeronsia, J.M., Joseph, L.A., Vinosha, P.A., Mary, A.J., Das, S.J., 2019. *Camellia Sinensis* leaf extract mediated synthesis of copper oxide nanostructures for potential biomedical applications. *Materials today Proceedings* 8, 214-222.
- Kannan, K., Radhika, D., Vijayalakshmi, S., Sadasivuni, K.K., A. Ojaku, A., Verma, U.J.I.J.o.E.A.C., 2020. Facile fabrication of CuO nanoparticles via microwave-assisted method: photocatalytic, antimicrobial and anticancer enhancing performance. 1-14.
- Katwai, R., Kaur, H., Sharma, G., Naushad, M., Pathania, D., 2015. Electrochemical synthesized copper oxide nanoparticles for enhanced photocatalytic and antimicrobial activity. *Journal of Industrial and Engineering Chemistry* 31, 173-184.
- Keabadile, O.P., Aremu, A.O., Elugoke, S.E., Fayemi, O.E, 2020. Green and traditional synthesis of copper oxide nanoparticles: Comparative study. *Nanomaterials* 10, 2502.
- Krishna, B.A., Kumar, P.N., Prema, P., 2020. Green synthesis of copper oxide nanoparticles using *Cinnamomum malabratrum* leaf extract and its antibacterial activity. *Indian Journal of Chemical Technology* 27, 525-530.
- Kumar, B., Smita, L., Cumbal, A., Debut, A., Angulo, Y., 2017. Biofabrication of copper oxide nanoparticles using *Andean blackberry* (*Rubus glaucus* Benth.) fruit and leaf. *Journal of Saudi Chemical Society* 21, S475-S480.

- Kumar, P.P.N.V., Shameem, U., Kollu, P., Kalyani, R.L., Pammi, N., 2015. Green synthesis of copper oxide nanoparticles using *Aloe vera* leaf extract and its antibacterial activity against fish bacterial pathogens. *BioNanoScience* 5, 135-139.
- Mali, S.C., Raj, S., Trive, R., 2019. Biosynthesis of copper oxide nanoparticles using *Enicostemma axillare (Lam.)* leaf extract. *Biochemistry and Biophysics Reports* 20, 100699.
- Mayekar, J., Dhar, V., Radha, S., 2014. Synthesis of copper oxide nanoparticles using simple chemical route. *International Journal of Scientific and Engineering Research* 5, 928-930.
- Muthuvel, A., Jothibas, M., Manoharan, C., 2020. Synthesis of copper oxide nanoparticles by chemical and biogenic methods: photocatalytic degradation and in vitro antioxidant activity. *Nanotechnology for Environmental Engineering* 5, 14.
- Nagore, P., Ghotekar, S., Mane, K., Ghoti, A., Bilal, M., Roy, A., 2021. Structural Properties and Antimicrobial Activities of Polyalthia longifolia Leaf Extract-Mediated CuO Nanoparticles. *BioNanoScience* 11, 1-11.
- Naseer, M., Ramadan, R., Xing, J., Samak, N.A., 2021. Facile green synthesis of copper oxide nanoparticles for the eradication of multidrug resistant *Klebsiella pneumonia* and *Helicobacter pylori* biofilms. *International Biodeterioration & Biodegradation* 159, 105201.
- Nasrollahzadeh, M., Sajadi, S.M., Rostami-Vartooni, A., 2015. Green synthesis of CuO nanoparticles by aqueous extract of *Anthemis nobilis* flowers and their catalytic activity for the A3 coupling reaction. *Journal of Colloid and Interface Science* 459, 183-188.
- Parekh, Z.R., Chaki, S.H., Patel, G.H., Kannaujiya, R.M., Khimani, A.J., Deshpande, M.P., 2021. CuO nanoparticles –Synthesis by wet precipitation technique and its characterization, *Physica B: Condensed Matter* 610, 412950.
- Phang, Y-K., Aminuzzaman, M., Akhtaruzzaman, Md., Muhammad, G., Ogawa, S., Watanabe, A., L-H. Tey, L-H., 2021. Green synthesis and characterization of CuO nanoparticles derived from *Papaya* peel extract for the photocatalytic degradation of palm oil mill effluent (POME). *Sustainability* 13, 796.
- Phiwdang, K., Suphankij, S., Mekprasart, W., Pecharapa, W., 2013. Synthesis of CuO nanoparticles by precipitation method using different precursors. *Energy Procedia* 34, 740-745.
- Prasad, S., Patra, A., Govindaraju, S., Shivamallu, C., 2017. Aqueous Extract of *Saraca indica* Leaves in the Synthesis of Copper Oxide Nanoparticles: Finding a Way towards Going Green., *Journal of Nanotechnology* 2017, 1-6.
- Sarkar, J., Chakraborty, N., Chatterjee, A., Bhattacharjee, D., K. Acharya, K., 2020. Green synthesized copper oxide nanoparticles ameliorate defence and antioxidant enzymes in lens ciliaris. *Nanomaterials* 10, 312, doi:10.3390/nano10020312.
- Sathiyavimal, S., Vasantharaj, S., Bharathi, D., Saravanan, M., Manikandan, E., Kumar, S.S., Pugazhendhi, A., 2018. Biogenesis of copper oxide nanoparticles (CuONPs) using *Sida acuta* and their incorporation over cotton fabrics to prevent the pathogenicity of Gram negative and Gram-positive bacteria. *Journal of Photochemistry and Photobiology B: Biology* 188, 126-134.
- Shahsavani, E., Feizi, N., A.D. Khalaji, A.D., 2016. Copper oxide nanoparticles prepared by solid state thermal decomposition: Synthesis and characterization. *Journal of Ultrafine Grained and Nanostructured Materials* 49, 48-50.
- Shammout, M.W., Awwad., A.A., 2021. A novel route for the synthesis of copper oxide nanoparticles using *Bougainvillea* plant flowers extract and antifungal activity evaluation. *Chemistry International* 7, 71-78.
- Sharma, J.K., Akhtar, M.S., Ameen, S., Srivastava, P., G. Singh, G., 2015. Green synthesis of CuO nanoparticles with leaf extract of *Calotropis gigantea* and its dye-sensitized solar cells applications. *Journal of Alloys and Compounds* 632, 321-325.
- Sharmila, G., Thirumarimurugan, M., Sivakumar, V.M., 2016. Optical, catalytic and antibacterial properties of phytofabricated CuO nanoparticles using *Tecoma castanifolia* leaf extract. *Optik* 127, 7822-7828.
- Silva, N., S. Ramírez, S., Díaz, I., Garcia, A., Hassan, N., 2019. Easy, quick, and reproducible sonochemical synthesis of CuO nanoparticles. *Materials* 12, 804.
- Singh, J., Kumar, V., Kim, K-H., Rawat, M., 2019. Biogenic synthesis of copper oxide nanoparticles using plant extract and its prodigious potential for photocatalytic degradation of dyes. *Environmental Research* 177, 108569.
- Sorbiun, M., Mehr, E.S., Ramazani, A., S.T. Fardood, S.T., 2018. Green synthesis of zinc oxide and copper oxide nanoparticles using aqueous extract of Oak fruit hull (Jaft) and comparing their photocatalytic degradation of basic violet. *International Journal of Environmental Research* 12, 29-37.
- Thamer, N.A., Muftin, N.Q., Salwa, H.N., Al-Rubae, I., 2018. Optimization properties and characterization of green synthesis of copper oxide nanoparticles using aqueous extract of *Cordia myxa L.* leaves. *Asian Journal of Chemistry* 30, 1559-1563.
- Veisi, H., Karmakar, B., Tamoradi, T., 2021. Biosynthesis of CuO nanoparticles using aqueous extract of herbal tea (*Stachys Lavandulifolia*) flowers and evaluation of its catalytic activity. *Scientific Reports* 11, 1983.
- Venkatramanan, A., Green synthesis of copper oxide nanoparticles (CuONPs) from aqueous extract of seeds of *Elettaria Cardamomum* and its antimicrobial activity against Pathogens. *Current Biotechnology Journal* 9, 1-8. Vidovix, T.B., Quesada, H.B., Januario, E.F.D., Bergamasco, R., Vieira, A.M.S., 2019. Green synthesis of copper oxide nanoparticles using *Punica granatum* leaf extract applied to the removal of methylene blue. *Materials Letters* 257, 126685.

- Vishveshvar, K., Krishnan, M.V.A., Krishnan, H., Selvaraj, V., 2018. Green synthesis of copper oxide nanoparticles using *Ixora coccinea* plant leaves and its characterization. *BioNanoScience* 8, 554-558.
- Yedurkar, S.M., Maurya, C.B., Mahanwar, P.A., 2017. A biological approach for the synthesis of copper oxide nanoparticles by *Ixora coccinea* leaf extract, *Journal of Materials and Environmental Sciences* 8, 1173-1178.
- Yugandhar, P., Vasavi, T., Y. Jayavardhanrao, Y., 2018. Cost effective green synthesis of copper oxide nanoparticles using fruit extract of *Syzygium alternifolium* (Wt.) Walp: Characterization and evaluation of antiviral activity. *Journal of Cluster Science* 29, 743-755.

Visit us at: <http://bosaljournals.com/chemint/>
Submissions are accepted at: editorci@bosaljournals.com
