

# Use of GGBS as Partial Replacement of Cement in Concrete While using Master REHO Build 823PQ

Praveen Kumar Gahlot, Suresh singh Sankhla, Krishan Kumar Saini

**Abstract:** *Currently cement is the most important material in the construction sector. Ordinary Portland cement is one of the main ingredients used for the production of concrete. Unfortunately, production of cement involves emission of large amounts of carbon-dioxide gas into the atmosphere, a major contributor of greenhouse effect and consequent global warming. While, cement typically comprises only 12% of the concrete mass, it accounts for approximately 93% of the total embodied energy of concrete and 6% to 7% of the world wide Carbon dioxide (CO<sub>2</sub>) emissions. Hence, it is of utmost importance to either search for another cementitious material or partially replace it by some other material. Currently there is a trend of usage of waste products such as fly ash from coal industries, GGBS from iron smelting process, paper ash from paper industry etc as supplementary cementitious materials to enhance the properties of concrete while also effectively reducing the carbon foot print. Ground Granulated Blast Furnace Slag (GGBS) is a by-product from iron smelting process using the blast-furnace. The present paper is prepared to study the effect on compressive strength of concrete due to partial replacement of cement with GGBS as supplementary cementitious material while using master REHO build 823PQ.*

**Keywords:** *Concrete, Strength, Ground Granulated Blast Furnace Slag, greenhouse effect, Cement.*

## I. INTRODUCTION

The most widely used construction material in today's world is concrete. It is primarily composed of Portland cement, aggregates and water. Although Portland cement typically comprises only 12% of the concrete mass, it accounts for approximately 93% of the total embodied energy of concrete and accounts for 6% to 7% of the world wide Carbon dioxide (CO<sub>2</sub>) emissions. If this embodied energy of concrete can be lowered without deteriorating the performance and/or increasing the cost, significant environmental and economic benefits may be reaped. Immense benefits have been reaped due to utilization of Pozzolanic materials in concrete as a partial replacement of cement, mainly on account of the improvements in the

long-term durability of concrete. With the aim of conserving energy by way of promoting the use of industrial wastes or by-products, which contain amorphous silica in its chemical composition, as mineral admixture for use as partial replacement of cement, many efforts are being made throughout the world

During hydration of cement, Tricalcium silicates (C<sub>3</sub>S) and Dicalcium silicates (C<sub>2</sub>S) react with water and produces calcium silicate hydrates (CSH gel as it is popularly known) and calcium hydroxide. This calcium hydroxide (Ca(OH)<sub>2</sub>) is not a desirable product in the concrete mass and it constitutes 20 to 25% of the volume of solids in the hydrated phase which is soluble in water. Due to its soluble nature calcium hydroxide may get leached out and thus it makes the concrete porous, weak and non-durable. Ca(OH)<sub>2</sub> also reacts with sulphates present in water or soil to form calcium sulphates which further react with Tricalcium Aluminates (C<sub>3</sub>A) and cause deterioration of concrete. This deteriorating effect of calcium hydroxide can be reduced by inclusion of pozzolanic materials. The mineral admixtures such as fly ash, GGBS and silica fumes are mainly used to overcome these adverse effects of calcium hydroxide produced during the hydration of cement in concrete. These mineral admixtures react with calcium hydroxide to produce more calcium silicate hydrate thus enhancing micro structure and overall performance. The pozzolanic reaction of these mineral admixtures improves the durability of cement paste by making the paste denser and impervious. Hence, mineral admixtures which when used in optimum proportions improve the quality of concrete by:

- Lowering the heat of hydration and thermal shrinkage.
- Increasing the water tightness.
- Reducing the scope for alkali – aggregate reaction.
- Improving the chemical resistance.
- Improving the corrosion resistance.
- Improving the early strength, workability and extensibility.
- Improving the rate of strength development

## II. REACTION MECHANISM OF GROUND GRANULATED BLAST FURNACE SLAG

Ground Granulated Blast Furnace Slag is a by-product of iron manufacturing industry.

**Revised Manuscript Received on February 05, 2020.**

\* Correspondence Author


**Praveen Kumar Gahlot\***, structural department, MBM Engineering College or Jai Narain Vyas University, jodhpur, India. Email: [praveenkgahlot07@gmail.com](mailto:praveenkgahlot07@gmail.com)

**Dr Suresh Singh Sankhla**, department, structural department, MBM Engineering College or Jai Narain Vyas University, jodhpur, India. Email: [er.suresh.sankhla@gmail.com](mailto:er.suresh.sankhla@gmail.com).

**Krishan kumar saini**, structural department, MBM Engineering College or Jai Narain Vyas University, jodhpur, India. Email: [krishnacivilengineer@gmail.com](mailto:krishnacivilengineer@gmail.com).

Iron ore, coke and limestone are fed into the furnace, and the resulting molten slag floats over the molten iron at a temperature of about 1500°C to 1600°C. The molten slag has a composition of 30% to 40% Silicon Dioxide (SiO<sub>2</sub>) and approximately 40% Calcium Oxide (CaO), which is close to the chemical composition of Portland cement. In India, we produce about 7.8 million tons of GGBS. The disposal of such huge quantities of slag even as a waste fill is big problem and may cause serious environmental hazards with the projected economic growth and development in the steel industry. When used in concrete, GGBS being a cementations material can act as a partial substitution for Portland cement without significantly compromising on compressive strength. This replacement of Portland cement with GGBS will lead to a significant reduction of carbon dioxide gas emission which would also provide environmental and economic benefits with required workability, durability and strength necessary for the design of the structures.

GGBS is a hydraulically latent material, in the presence of lime contributed from cement, a secondary reaction involving glass (Calcium Alumina Silicates) components sets in. As a consequence of this, cementitious compounds are formed. They are categorized as secondary C-S-H gel. The interaction of GGBS and Cement in presence of water is described below:



The generation of secondary gel results in supply of additional C-S-H, a principal binding material. This is the main attribute of GGBS, which contributes to the strength and durability of the structure.

### III. AIM OF THE STUDY

The main purpose of the study is to provide practical guidance about the effects on compressive strength of two concrete mixes (M-30 and M-35) with varying percentage of supplementary cementations material of Ground-granulated blast-furnace slag (GGBS) and water reducing admixture called as plasticizer used for improving the workability at lower water-cement ratios without affecting the compressive strength.

### IV. EXPERIMENTAL PROGRAMME

#### A. Cement

Shree Cement OPC of Grade 53 was used in the work. The various physical & mechanical properties of cement were tested in accordance with test procedures prescribed in IS 4031:1968 and results so obtained are tabulated in Table I below.

**Table I: Properties of Cement**

S. No.	PROPERTY	VALUES
1	Specific Gravity	3.15
2	Standard Consistency	30%
3	Initial Setting Time	88 minutes
4	Final Setting Time	210 minutes
5	Compressive Strength	57.06 N/mm <sup>2</sup>

#### B. Granulated Blast Furnace Slag (GGBS)

Ground Granulated blast furnace slag is obtained during the manufacturing process of iron in blast furnace. The slag is a mixture of lime, silica, and alumina, the same oxides that make up Portland cement, but not in the same proportion.

**TABLE II: Properties of GGBS (JSW Cemented ltd. Maharashtra)**

S. No.	PROPERTY	VALUES
1	Colour	Off white
2	Specific Gravity	2.89
3	Bulk Weight (ton per m <sup>3</sup> )	1.0-1.3

#### C. Plasticizer

Water reducing admixture called as plasticizer are used for improving the workability at lower water-cement ratios without affecting the compressive strength. Plasticizers are essential components to provide necessary workability. The plasticizers used here is BASF MASTER REHO BUILD 823PQ based on second generation. Its properties are given in table below.

**Table III: Property of Plasticizer**

S. No.	PROPERTY	VALUES
1	Aspect	Dark brown free flowing liquid
2	Relative density	1.21 ± 0.02 at 25 <sup>0</sup>
3	pH	7 ± 1
4	Chloride ion content	<0.2%

#### D. Fine Aggregate

River sand was used as fine aggregate. IS 383:1970 lays down specifications for fine aggregates from natural sources for concrete. According to which, the aggregates should be chemically inert strong, hard, durable and of limited porosity. The Sieve analysis was performed on the fine aggregates the results are as follows

The fine aggregate thus conforms to be of ZONE II according to IS 393-1970.

The specific gravity and Void content of the fine aggregates were determined as per method prescribed in IS: 2386 (Part III) – 1963.

Specific Gravity = 2.45

Void Content = 29.29%

#### E. Coarse Aggregate

Locally available crushed coarse aggregates were used. The properties of 20mm and 10mm coarse aggregates are as follows. The specific gravity and Void content of 20 mm & 10 mm coarse aggregates were determined as per method prescribed in IS: 2386 (Part III) – 1963.

Specific Gravity, for 20mm = 2.74

Void Content, for 20mm = 41.48%

Specific Gravity, for 10mm = 2.74

Void Content, for 10mm = 46.97%

**F. Water**

Tapped municipal drinking water is used.

**V. MIX DESIGN**

The Mix Design Procedure As Prescribed In Is 10262:2009 And Using Is 456:2000 Was DEVELOPED For Grades M30 And M35 And The Weight Of Raw Materials (In Kg) Per M3 Of Concrete Mix For Different Grades Is Shown Below In Table IV.

**Table IV: Mix Design of Concrete M 30 Per Cubic Meter**

Grade	Total binding material (380kg)		FA	CA (55%) (20mm)	CA (45%) (10mm)	Water	Plasticizer (%)
	Cement	GGBS					
<b>M-30 (per m<sup>3</sup>)</b>	380	0	657	660	539	168	1.1
	342	38					
	304	76					
	266	114					
	247	133					

**Table V: Mix Design of Concrete M 30 Per Batch**

Grade	Total binding material (8.852kg)		FA	CA (20mm)	CA (10mm)	Water	Plasticizer (gm)
	Cement	GGBS					
<b>M-30 (per batch)</b>	8.85	0	15.3	15.375	12.55	3.91	100
	7.96	0.88					
	7.08	1.77					
	6.19	2.65					
	5.75	3.09					

**Table VI: Mix Design of Concrete M 35 Per Cubic Meter**

Grade	Total binding material (400kg)		FA	CA (55%) (20mm)	CA (45%) (10mm)	Water	Plasticizer (%)
	Cement	GGBS					
<b>M-35 (per m<sup>3</sup>)</b>	400	0	650	653	533	168	1.5
	360	40					
	320	80					
	280	120					
	260	140					

**Table VII: Mix Design of Concrete M 35 Per Batch**

Grade	Total binding material (9.318kg)		FA	CA (20mm)	CA (10mm)	Water	Plasticizer (gm)
	Cement	GGBS					
<b>M-35 (per batch)</b>	9.31	0	15.3	15.375	12.55	3.91	100
	8.38	0.93					
	7.45	1.86					
	6.52	2.79					
	6.05	3.26					

Mixing Procedure

First, the fine aggregates and cement in dry state were mixed for 3 to 5 minutes to have a uniform mixture. Thereafter the coarse aggregates were added and again mixed for 2 to 3 minutes. The water is added in two stages; firstly 3 kg water is added to the dry mix in the mixer and mixed thoroughly for 3 to 5 minutes and the remaining amount of water is mixed with the plasticizer and added to the mix while the mixing is still going on. The mixer is run for another 3 to 5 minutes as good quality mixes are formed with sufficient mixing time and energy.

The workability of the mix was such that the cone collapsed without segregation of concrete mix as observed in slump test.

VI. NOMENCLATURE OF CUBES

The nomenclature of the cubes for identification of the cubes is decided as per Table VIII below.

Table VIII: Nomenclature of Cubes

S. No	NOMENCLATURE	GRADE
1	0GB30M	0% GGBS M30 Grade
2	1GB30M	10% GGBS M30 Grade
3	2GB30M	20% GGBS M30 Grade

Table IX: - Compressive Strength of Cubes of M-30 Grade with % Variation of GGBS

S.No	NOMENCLATURE	Compressive strength in N/mm <sup>2</sup>					
		3 day	Variation	7 day	Variation	28 day	Variation
1	0GB30M	15.18		26.38		38.12	
2	1GB30M	15.60	2.76	28.22	6.97	39.80	4.40
3	2GB30M	16.42	8.16	31.25	18.46	40.42	6.03
4	3GB30M	14.9	-1.84	28.58	8.33	35.21	-7.86
5	3.5GB30M	13.18	-13.7	24.32	-7.80	32.12	-15.73

Table X: - Compressive Strength of Cubes of M-35 Grade with % Variation of GGBS

S.No	NOMENCLATURE	Compressive strength in MPa					
		3 day	% Variation	7 day	% Variation	28 day	% Variation
1	0GB35M	18.41		32.15		45.30	
2	1GB35M	19.25	4.56	33.22	3.33	46.10	1.76
3	2GB35M	20.40	10.8	35.29	9.76	49.20	8.61
4	3GB35M	20.10	9.17	33.58	4.44	44.20	-2.42
5	3.5GB35M	17.60	-4.39	31.65	-1.55	42.25	-6.73


4	3GB30M	30% GGBS M30 Grade
5	3.5GB30M	35% GGBS M30 Grade
6	0GB35M	00% GGBS M35 Grade
7	1GB35M	10% GGBS M35 Grade
8	2GB35M	20% GGBS M35 Grade
9	3GB35M	30% GGBS M35 Grade
10	3.5GB35M	35% GGBS M35 Grade

The cubes subjected to normally cured cube specimens were tested for their compressive strength at ages of 3-day, 7-days and 28-days.


VII. RESULTS AND DISCUSSIONS

Standard 150mm mold was used, each layer compacted is tampered using a certified compacting rod, 25 tamps per layer is done. Once the 3 layers have been tampered, the concrete is leveled off using hand vibrator for complete compaction of concrete and after that a float or trowel is used to give a smooth surface that is flush with top of the mold.


Procedure adopted is as prescribed by code IS 516:1959.

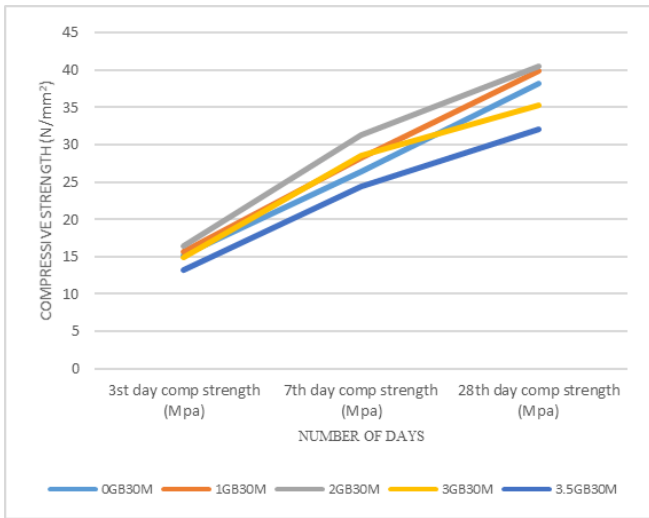


Graph 1: - Comparison of Compressive Strength of Cubes of M-30 Grade with % Variation of GGBS

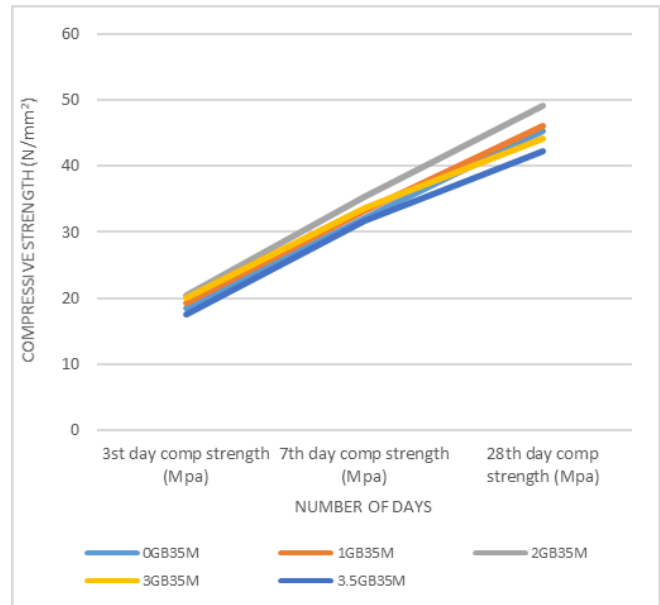

Graph 2: - Comparison of Compressive Strength of Cubes of M-35 Grade with % Variation of GGBS

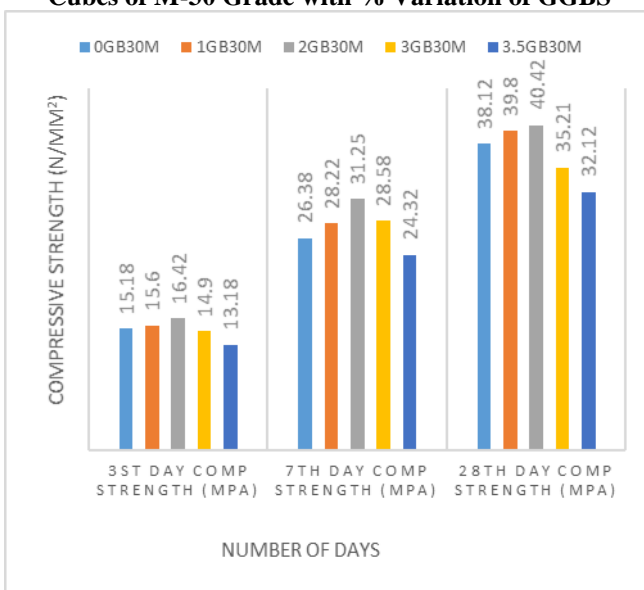


Bar Chart 1: - Comparison of Compressive Strength of Cubes of M-30 Grade with % Variation of GGBS

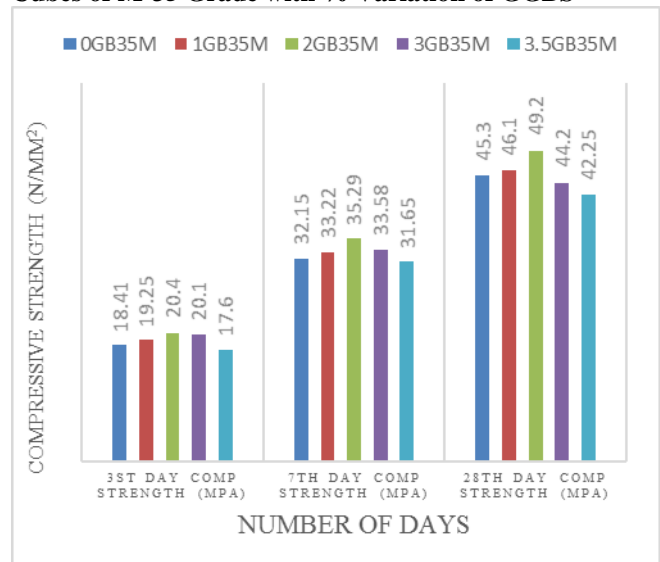


Bar Chart 2: - Comparison of Compressive Strength of Cubes of M-35 Grade with % Variation of GGBS

Table XI: - Compression of compressive Strength of Cubes of M-30 Grade and M-35 with % Variation of GGBS at 28<sup>th</sup> Days


S.No	NOMENCLATURE	28 day comp strength (N/mm <sup>2</sup> )	NOMENCLATURE	28 day comp strength (N/mm <sup>2</sup> )
1	0GB30M	38.12	0GB35M	45.30
2	1GB30M	39.80	1GB35M	46.10
3	2GB30M	40.42	2GB35M	49.20
4	3GB30M	35.21	3GB35M	44.20
5	3.5GB30M	32.12	3.5GB35M	42.25

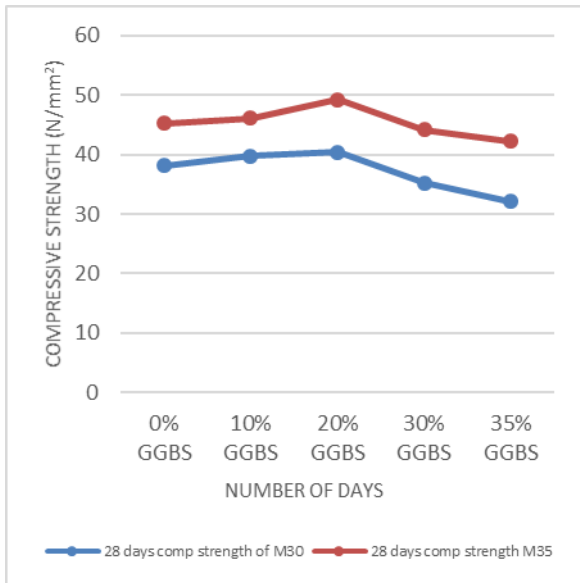


Graph 3: - Compressive Strength of Cubes of M-30 And M35 at 28 Days with % of GGBS Variation

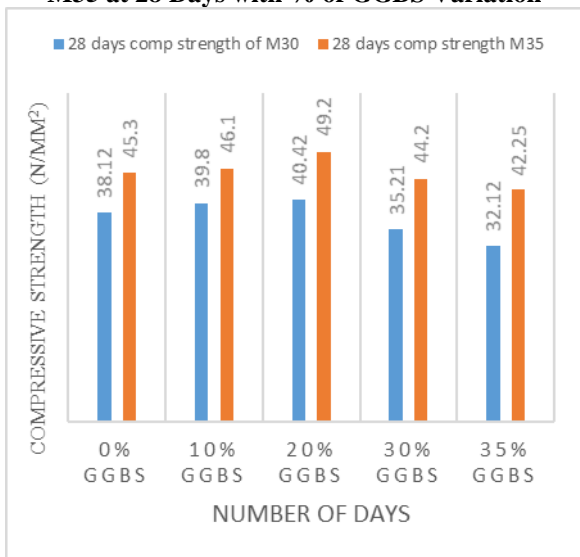

Bar Chart 3: - Compressive Strength of Cubes of M-30 and M35 at 28 Days with % of GGBS Variation

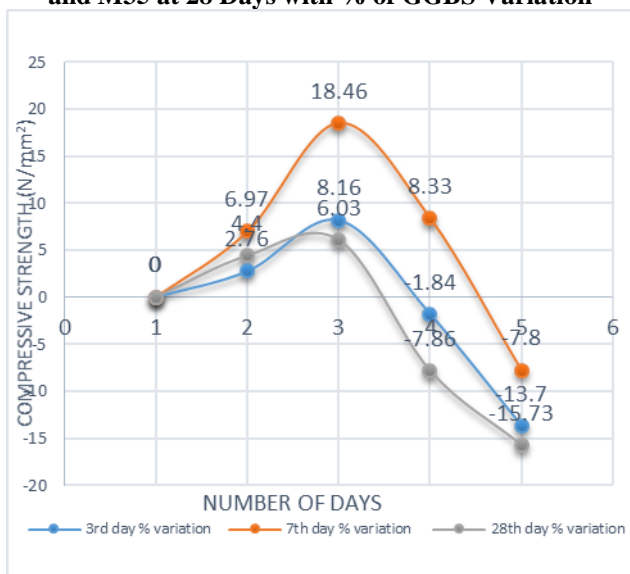

Graph 4: -The % Variation of Compressive Strength of M30

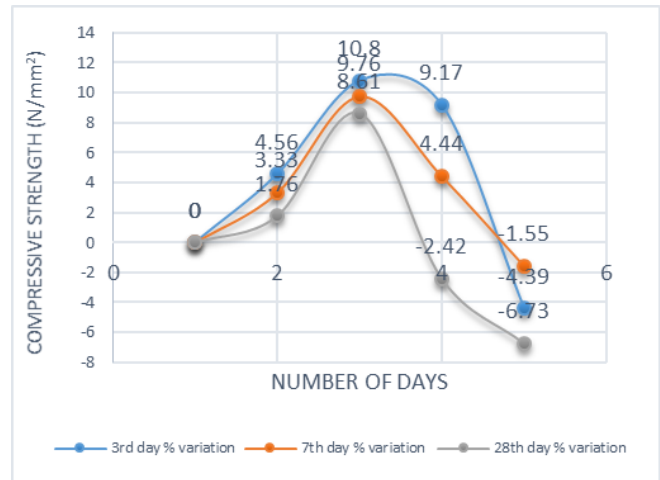

Graph 5: -The % Variation of Compressive Strength of M35

### VIII. CONCLUSIONS

From this experimental investigation, following conclusions are drawn:

With the addition of 20% of GGBS as partial replacement of Cement for M30 grade and M35 grade of concrete, there is an increase in compressive strength of concrete as compared to one where no replacement has been done.

The compressive strength of concrete cube after 28 days curing decreased at partial replacement percentage of 35 of ground granulated blast furnace slag (GGBS) with cement in both grade of concrete M30 and M35 as compared to cubes where no replacement was done.

It is also observed from the experimental work that the percentage increase in compressive strength of both grade of concrete mix (M 30 and M35) at initial days (7 days) is higher as compare to 28 days.

### ACKNOWLEDGMENT

We are thankful to MHRD for PhD Assistantship at MBM Engineering College, JNVU Jodhpur, Rajasthan under TEQIP 3 (TEQIP 3 The Technical Education Quality Improvement Project (TEQIP III) is implemented by the Ministry of HRD, Government of India with focus on improving the quality of technical education).

### REFERENCES

1. IS 10262:2009.
2. IS 456:2000.
3. IS 383:1970
4. IS 516:1959
5. European Journal of Scientific Research ISSN 1450-216X Vol.88 No-1 October, 2012, pp.155163@Euro journals Publishing, Inc. 2012 <http://www.europeanjournalofscientificresearch.com>.
6. Venu Malagavelliet.al./International Journal of Engineering Science and Technology Vol. 2(10), 2010, 5107-511.
7. ASTM C 989-940, Standard specification for ground granulated blast furnace slag for use in concrete and mortars
8. AvelineDarquennes, Stephanie Staquet, and Bernard Espion. (2011). "Behaviour of Slag Cement Concrete under Restraint Conditions". European Journal of Environmental and Civil Engineering, 15 (5), 787-798.

9. Santosh Kumar Karri, G. V. Rama Rao, P. MarkandeyaRaju "Strength and Durability Studies on GGBS Concrete", SSRG International Journal of Civil Engineering (SSRG - IJCE), V2 (10), 34-41 October 2015. ISSN: 2348 – 8352. www.internationaljournalssrg.org/IJCE/index.html. Published by: Seventh Sense Research Group.
10. MojtabaValinejadShoubi, AzinShakiba Borough, and OmidrezaAmirsoleimani. (2013). "Assessment of the Roles of Various Cement Replacements in Achieving Sustainable and High-Performance Concrete". International Journal of Advances in Engineering and Technology, 6 (1): 68-77.
11. Reginald B. Kogbara, and Abir Al-Tabbaa. (2011). "Mechanical and Leaching Behaviour of Slag-Cement and Limeactivated Slag Stabilized/Solidified Contaminated Soil". The science of the Total Environment, 409 (11), 2325-2335.

### AUTHORS PROFILE



**Praveen Kumar Gahlot<sup>1</sup>** PhD scholar, structural department, in MBM Engineering College, Jai Narain Vyas University Jodhpur.



**Dr Suresh Singh Sankhla**, Associate Professor, structural Department, MBM Engineering College, Jai Narain Vyas University Jodhpur, Rajasthan.



**Krishan Kumar Saini**, PhD scholar, structural department, in MBM Engineering College, Jai Narain Vyas University Jodhpur.