

AVEIRO - PORTUGAL



This paper must be cited as:

Martínez, E.D., García-Flores, A. F., Neto, A.N.C., Brites, C.D.S., Carlos, L. D., Urbano, R.R. Rettori, C., Nanoscale, 2021, 13, 16267-, <https://doi.org/10.1039/D1NR03223B>

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Controlling the Thermal Switching in Upconverting Nanoparticles Through Surface Chemistry

Eduardo D. Martínez^{a,*}, Alí F. García-Flores^b, Albano N. Carneiro Neto^c, Carlos D. S. Brites^c, Luís D. Carlos^c, Ricardo R. Urbano^b, Carlos Rettori^{b,d}

Photon upconversion taking place in small rare-earth-doped nanoparticles has been recently observed to be thermally modulated in an anomalous manner, showing thermal enhancement of the emission intensity. This effect was proved to be linked to the role of adsorbed water molecules as surface quenchers. Therefore, the surface capping of the particles has a direct influence on the thermal dynamics of water adsorption and desorption. Here, we show that the upconversion intensity of small-size (<25 nm) nanoparticles co-doped with Yb³⁺ and Er³⁺ ions, and functionalized with different capping molecules, present clear irreversibility patterns upon thermal cycling that strongly depend on the chemical nature of the nanoparticle surface. By performing temperature-controlled luminescence measurements we observed the formation of a thermal hysteresis loop, resembling an optical switching phenomenon, whose shape and trajectory depend on the hydrophilicity of the surface chemistry. Additionally, the formation of an intensity overshoot takes place immediately after turning off the heating source, affecting each radiative transition differently. We performed numerical modelling to understand this effect considering non-radiative energy transfer from surface defect states to the Er³⁺ ions. These findings are relevant for the comprehension of nanoparticle-based luminescence and the interplay between surface and volume effects, and more generally, for applications involving UCNPs such as nanothermometry, bioimaging, and the development of optical encoding systems.

^a Instituto de Nanociencia y Nanotecnología (INN), Centro Atómico Bariloche, Comisión Nacional de Energía Atómica (CNEA), Consejo Nacional de Investigaciones Científicas y Técnicas (CONICET), Av. E. Bustillo 9500, R8402AGP, S. C. de Bariloche, Río Negro, Argentina.

^b "Gleb Wataghin" Institute of Physics (IFGW), University of Campinas (UNICAMP), 13083-859, Campinas, SP, Brazil.

^c Phantom-g, CICECO-Aveiro Institute of Materials, Physics Department, University of Aveiro, 3810-193 Aveiro, Portugal.

^d CCNH, Federal University of ABC (UFABC), 09210-580, Santo André, SP, Brazil.

Electronic Supplementary Information (ESI) available: Details on materials, methods, experimental set-up, additional measurements and equations for optical thermometry and modelling of surface defects are available in the ESI. See DOI: 10.1039/x0xx00000x

1. Introduction

Recent reports on the upconversion luminescence (UCL) of small-size upconversion nanoparticles (UCNPs) demonstrated that temperature has an unexpected influence on its emission features.^{1–3} Rising temperatures lead to increased emissions intensity, contrary to what is observed for bulk upconverting materials and organic fluorophores. The conditions under which this effect occurs, and the mechanisms responsible for it, are still under discussion.^{4–8} The first work published on the subject by Shao and co-workers² reported thermal enhancement of UCL for small-size UCNPs (<27 nm) both for core-only and core-shell UCNPs, suggesting a non-direct correlation between the UCL enhancement and the nature of the surface. Therefore, the authors proposed that the phonon confinement effect, occurring exclusively in small-size particles, modifies the phonon density of states affecting the Yb³⁺-to-Er³⁺ energy transfer rates, and thus favouring the enhancement of the UCL.² Later, the same authors reconsidered their rationale by analysing the temperature-dependent emissions of UCNPs in different atmospheres.⁴ They concluded that the enhancement relies on the thermal desorption of water molecules, thus reducing the quenching produced by –OH groups located on the surface. Intriguingly, a core-shell system, with an inert shell (thicker than the one presented in their previous work), was shown to display the usual thermal quenching, supporting the importance of the nanoparticle's surface in the results. In 2018, Jin's group proposed that surface phonons, generated by the chelating ligands between Yb³⁺ and carboxylic moieties, favour the sensitizer-to-activators energy transfer.⁷ The authors showed that the thermal enhancement of the UCL could take place even in UCNPs as large as 57 nm, which ruled out the phonon confinement scenario. A few months later, Lei and co-workers⁹ strengthened the enhancement effect by deliberately generating surface defects through the doping of UCNPs with low-valence ions (Ca²⁺). The authors suggested that the electrons trapped in the surface defects with the appropriate energy may be thermally released, further populating the activator ions, and causing the thermal enhancement of the emission. More recently, the desorption and re-adsorption of water molecules upon thermal treatment was demonstrated by Meijerink's group who reported the occurrence of thermally enhanced UCL in doped NaY(WO₄)₂ UCNPs.¹⁰ Based on carefully designed experiments and structural characterization by thermogravimetry (TGA) and Fourier-transform infrared spectroscopy (FTIR) the authors demonstrated that the intensity variations could be ascribed to the desorption

of surface moisture at high temperatures (~470 K), finding a 0.5% weight loss or gain on heating and cooling, respectively. Nevertheless, despite the extensive work on the subject, reviewed in a series of recent papers,^{11–13} the real-time monitoring of the emissions during heating-cooling cycles has been disregarded. Only recently, Li and co-workers have briefly compared the thermally dependent UCL of oleic acid capped and uncapped UCNPs.⁶ This is a fundamental tool for studying the reversibility of the effect and to understand the physical mechanism underpinning the thermal enhancement of the UCL.

Therefore, in this work, we quantitatively exploited the role of the surface coating in the regulation of the thermo-optical properties in detail, given that the fundamental mechanism of the water desorption and re-adsorption has already been thoroughly studied by others. Our results show that the surface coating can be used to effectively control the quenching effect of water molecules, not only regarding its magnitude but also its dynamic behaviour. The more hydrophilic is the coating, the clearer will be the quenching action and more evident will be the emission intensity enhancement upon thermal desorption of water molecules. We investigate the correlation between the surface chemistry (including the surface defects) and the thermal UCL enhancement properties in detail by using a blended experimental and theoretical approach. As illustrative examples, small-size (<25 nm) UCNPs co-doped with Yb³⁺ and Er³⁺ were synthesized and their surface was further modified to incorporate capping molecules able to provide distinct chemical environments. The thermal behaviour of the UCL in all the prepared UCNPs was investigated using the luminescence of the Er³⁺ ion for accurate and intrinsic temperature control. We were able to explore the reversibility of the UCL and the formation of a hysteresis loop by following the optical emissions under near-infrared (NIR) laser excitation (976 nm) while cycling the temperature.

By controlling the hydrophilicity of the surface capping, UCNPs with specific opto-thermal behaviours can be designed. We believe that these experimental findings are key to reveal the physical mechanism behind the optical properties of UCNPs. Moreover, we rationalize the UCL response with temperature using numerical calculations on the transfer rates between the surface defects and the lanthanide ions, concluding that the energetic position of the surface defects depends on the nature of the UCNPs surface chemistry.

2. Results and discussion

2.1. Synthesis and morphological characterization of the nanoparticles

A batch of UCNPs with a nominal composition β - NaY_xF_4 doped with 5 %at. Yb^{3+} and 2 %at. Er^{3+} ($x=0.93$) was prepared.¹⁴ Transmission electron microscopy (TEM) images are presented in **Figure 1a-c**. The resulting UCNPs present a mean size of (21.5 ± 1.5) nm and narrow size distribution (**Figure 1g**). The as-prepared particles are capped with oleic acid (OA) and form stable dispersions in low-polarity solvents such as cyclohexane, toluene, and chloroform.

We then modified the capping ligand, first by removing the OA with HCl treatment and dispersing the UCNPs in water.^{15,16} Aliquots of the uncapped UCNPs colloid in water were subsequently treated to form different polymeric coatings on the UCNPs. We used polyacrylic acid (PAA) and polyvinylpyrrolidone (PVP) that allowed the formation of stable water colloids. In addition, we synthesized a core-shell structure by growing a shell layer of $\text{NaGd}_x\text{F}_4:\text{Yb}30\%:\text{Tm}0.5\%$ ($x=0.695$) using the $\text{Yb}^{3+}/\text{Er}^{3+}$ co-doped OA-UCNPs as seed particles. Tm^{3+} ions were used in the shell layer with the purpose to study the thermal behaviour of the emissions of the activator ions located in the core (Er^{3+}) and the shell (Tm^{3+}). For this reason, the core-UCNPs were prepared with a nominal 5%at. atomic fraction of Yb^{3+} instead of the commonly employed 20%at. concentration, to intentionally reduce the quantum yield of UCL and obtain similar emission intensities for the activator ions located in the core and the shell. However, the emission of Tm^{3+} in the UV spectral region was hardly detected, and only the more intense emission bands at 800 nm were observed, as shown in the Electronic Supplementary Information (ESI) (**Figure S2a,b**).

TEM analyses under different modes of operation are shown in **Figure 1d-f**. Detailed information on the chemical synthesis and surface modification is given in the Materials and Methods section. The shell was characterized by several transmission electron microscopy techniques including high-resolution TEM images (**Figure 1d**), high-angle annular dark-field scanning (HAADF-STEM) (**Figure 1e**), providing images highly sensitive to variations in the atomic number of atoms, and performing a composition map by energy dispersive spectroscopy (EDS) as shown in **Figure 1f**. Particle size analysis of TEM images shows a mean size of (40 ± 4) nm in diameter for the core-shell UCNPs, corresponding to a shell layer thickness of (9 ± 3) nm. The core-shell structure is evidenced by the distribution of the Gd atoms in the EDS profiles and the brighter shell observed in HAADF-STEM images (**Figure 1g**).

All prepared nanoparticles were characterized by FTIR at room temperature (**Figure 1h**). The C–H

stretching bands at $2850\text{--}2950\text{ cm}^{-1}$ are present in all the samples but barely detected for the uncapped ones. Normalizing the spectra to the bands of CO_2 at $\sim 2350\text{ cm}^{-1}$, the signal from C–H is considerably smaller for the uncapped sample. Although remnant OA could still be present, FTIR data confirms its successful removal after synthesis. On the other hand, it is observed a broad absorption band at $3200\text{--}3700\text{ cm}^{-1}$, assigned to the O–H stretching vibration of PAA and PVP capped particles that is, however, absent in the uncapped and OA capped ones. The characteristic stretching bands of the carboxylic group appear as multiple dips between 1350 and 1650 cm^{-1} in PAA, PVP, and OA capped samples. The bending vibrations of O–H can be assigned to the absorption bands at $1018\text{--}1025\text{ cm}^{-1}$. This fingerprint region also contains absorption dips from C–N and C–O bonds.

2.2. Luminescence and primary thermometry using the upconverting nanoparticles

The characterization of the luminescence spectra was performed by depositing the UCNPs directly from their cyclohexane-based colloids on silicon wafers and left to dry. We measured the UCL at different temperatures by performing heating and cooling cycles on a Peltier plate (see Materials and Methods and a scheme of the experimental set-up in **Figure S1**, ESI).

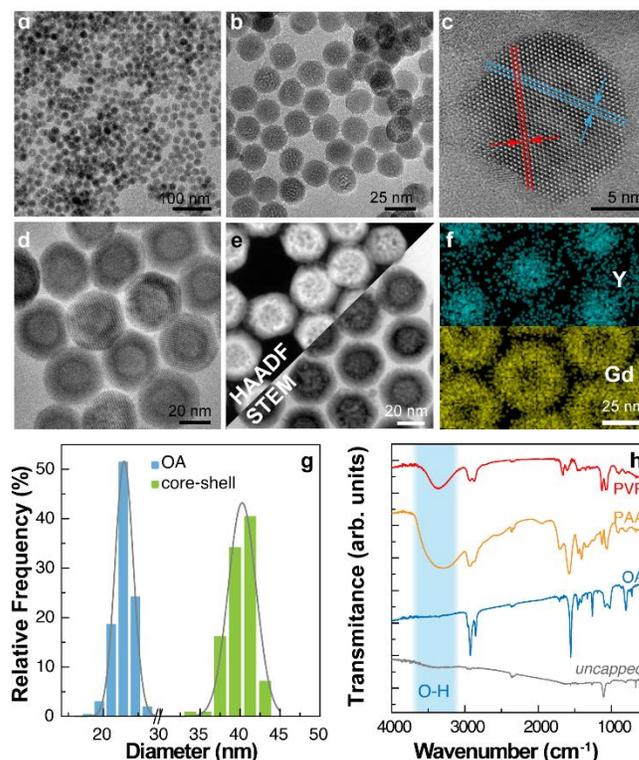


Figure 1. Structure and (a,b) transmission electron micrographs of as-synthesized UCNPs-OA. (c) High-resolution TEM of a single UCNP. The plane separation $d=0.504 \pm 0.004$ nm corresponds to the (100) plane of β -NaYF₄. (d) TEM and (e) combined STEM and HAADF micrographs of core-shell nanoparticles. (f) Compositional mapping by EDS showing the yttrium and gadolinium profiles corresponding to the core and shell materials, respectively. (g) Size distribution extracted from the TEM images. The solid line corresponds to the best fit to a Gaussian distribution of mean \pm SD 21.5 ± 1.5 nm (OA) and 40 ± 4 nm (core-shell) ($r^2 > 0.97$). (h) FTIR transmittance spectra of the uncapped UCNPs and the UCNPs with different capping ligands.

The intensity of the emission spectrum of the OA-capped UCNPs is enhanced upon increasing temperatures (Figure 2a). Also, the upconversion emissions produced by the Er³⁺ ions allow the optical determination of the local temperature by analysing the ratio between the integrated intensities of the $^2H_{11/2} \rightarrow ^4I_{15/2}$ (I_H) and $^4S_{3/2} \rightarrow ^4I_{15/2}$ (I_S) transitions in the green spectral region (Figure 2b-d). The temperature dependence of the thermometric parameter is well described by:¹⁷

$$\Delta = \frac{I_H}{I_S} = B \exp\left(-\frac{\Delta E}{k_B T}\right) \quad (1)$$

where k_B is the Boltzmann constant, and the pre-exponential factor B is dependent on the degeneracies, branching ratios, spontaneous absorption coefficients, and frequencies of the $^2H_{11/2} \rightarrow ^4I_{15/2}$ and $^4S_{3/2} \rightarrow ^4I_{15/2}$ transitions, if the intensities are measured as power densities, in $W \cdot m^{-2}$ (B is independent of the transition energies if the intensities are measured through single-photon counting detection, as is usual today).¹⁸ The temperature can be calculated from an emission spectrum using:

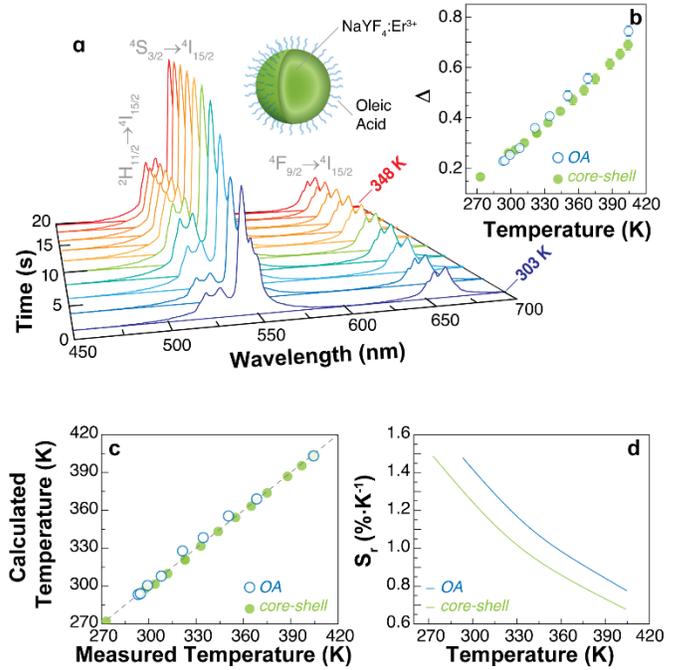


Figure 2. (a) Temperature dependence of the upconversion emission spectra of UCNPs-OA under 976 nm excitation (~ 30 $W \cdot cm^{-2}$). The Er³⁺ transitions are identified. (b) Calibration curve for the UCNPs-OA and core-shell NPs in the 293-405 K range. The calibration temperature is recorded using a Pt100 thermistor thermometer. (c) Comparison between the temperature values measured by the external thermometer (x -axis) and those calculated using Eq. 2 (y -axis) for the UCNPs-OA and core-shell NPs. The $x=y$ line corresponds to the perfect agreement between both employed methods. (d) Relative thermal sensitivity of the thermometers in the calibration range.

$$\frac{1}{T} = \frac{1}{T_0} - \frac{k_B}{\Delta E} \ln\left(\frac{\Delta}{\Delta_0}\right) \quad (2)$$

where T_0 is a known temperature corresponding to the intensity ratio Δ_0 . We demonstrated that thermally coupled energy levels can be used to define an intrinsically primary thermometer governed by an equation of state outcoming from Eq. 1. The temperature determination in primary thermometers using Eq. 2 depends only on the parameters of the material without demanding additional calibration.^{19,20} The calculation of Δ at different temperatures measured with regular thermometers is shown in Figure 2b,c for oleic-acid capped and core-shell UCNPs. A similar trend demonstrates that the thermometric capabilities of UCNPs are independent of surface conditions as they are a unique feature of the Er³⁺ ion energy level structure. The relative thermal sensitivity for oleic acid capped and

core/shell UCNPs (Eq. S1, ESI) are concordant with those reported for $\text{Yb}^{3+}/\text{Er}^{3+}$ doped UCNPs.¹⁷

2.3 Thermal cycling

We prepare a protocol for studying the heating-cooling trajectories of the emissions that consist of recording the emission of the samples (integration time of 10-15 s) upon continuous 976 nm excitation during heating and cooling cycles. The on/off cycles were automatically controlled on a Peltier heating element every 15 minutes. A scheme of the experimental set-up is presented in Figure S1 (ESI) The temperature was cycled from room temperature (298-303 K) to a maximum temperature of 373-393 K. We analysed the integrated intensities of each emission line and the overall integrated spectra separately. In each acquisition, the thermometric parameter Δ is calculated, providing information on the instantaneous temperature in real-time.

The intensity profiles during thermal cycling recorded for the UCNPs with different capping and core-shell UCNPs are presented in **Figure 3** for the first 2 heating-cooling cycles. The integrated intensities of the I_H and I_S emission lines, the intensity of the $^4F_{9/2} \rightarrow ^4I_{15/2}$ transition (I_F) and the total intensity ($I_{\text{Total}} = I_H + I_S + I_F$) are shown. Many important observations can be extracted from these figures. First, the apparent thermal enhancement effect is observed in all systems without a shell layer irrespectively of the molecular capping. Nevertheless, the thermal enhancement in all samples is notoriously different both in terms of magnitude and temperature dependence. Second, important differences occur when the heating source is powered off. In addition to the gradual decrease and recovery of the emission intensity at room temperature, a sudden enhancement (overshoot) at the beginning of the cooling branch was detected in some cases (e.g., PVP and PAA capped UCNPs). This unexpected effect will be discussed in detail in the following section. A comparison of the overall integrated intensity trends for the first two cycles of all samples is shown in **Figure 3d** for clarity.

For the as-synthesized OA capped UCNPs, the adsorption of water is limited. Ideally, the hydrophilic carboxylic groups of OA should be attached to the surface forming carboxylate-ligands with surface Y^{3+} or Yb^{3+} ions, only exposing hydrophobic aliphatic chains. In reality, dangling bonds remain available for interacting with water considering that carboxylate groups can be protonated and detached from the UCNPs surface.^{28,29} Hence, water can be adsorbed in the OA-UCNPs system. The increase in temperature favours the gradual desorption of water resulting in the apparent

enhancement of the emission intensity. Notice that this phenomenon is not properly an enhancement but the reduction of the quenching effect of water molecules. When the heating element is turned off, water re-adsorption begins.

On the other hand, the thermometric parameter Δ follows the expected profiles during the thermal cycles (**Figure 4a-e**). The effect of temperature on the emission intensity can be presented differently by plotting the total intensity vs the thermometric parameter as shown in **Figure 4f-j**. Here, the thermal effects are easily observed in the non-reversible

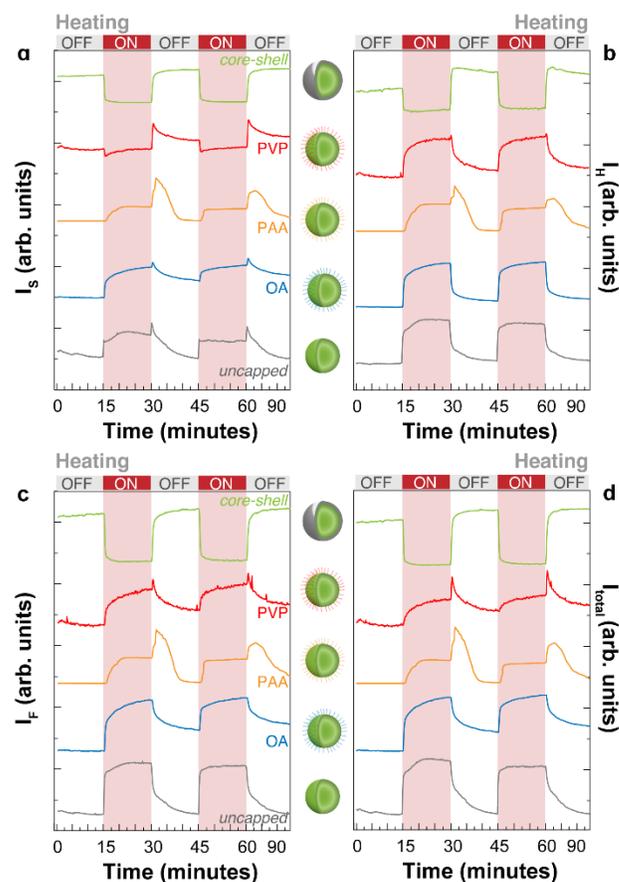


Figure 3. The integrated intensity in two thermal cycles corresponding to the (a) S transition (I_S , $^4S_{3/2} \rightarrow ^4I_{15/2}$), (b) H transition (I_H , $^2H_{11/2} \rightarrow ^4I_{15/2}$), (c) F transition (I_F , $^4F_{9/2} \rightarrow ^4I_{15/2}$), and (d) the sum of the areas of S, H, and F transitions (I_{total}) for all the samples studied in this work.

trajectories followed during the heating and cooling branches of the thermal cycles. Except for the core-shell sample, which will be discussed below, all other samples show hysteresis loops upon thermal cycling, resembling those of ferromagnetic materials. This highlights the

importance of the thermal history in the emission intensity of UCNPs.

In the uncapped UCNPs, the absence of coating molecules (**Figure 3** and **Figure 4j**) results in very fast adsorption and desorption kinetics. During the heating branch of the thermal cycle, a small increase in the temperature produces an abrupt increase in the emission intensity until a saturation level is observed and the emission intensity remains practically unchanged. When the heating source is turned off, a gradual diminishing of the emission intensity is observed, which is compatible with the adsorption of water molecules. Again, the kinetics involved in adsorption/desorption of water can explain the difference in the thermal behaviour of capped and uncapped UCNPs, as well as the hysteresis loop. Briefly, the trajectories shown in **Figure 4f-j** during heating and cooling cycles depend on the diffusion and adsorption of water molecules on the surface of the UCNPs; therefore, for a given temperature (or equivalently Δ) the content of water is not

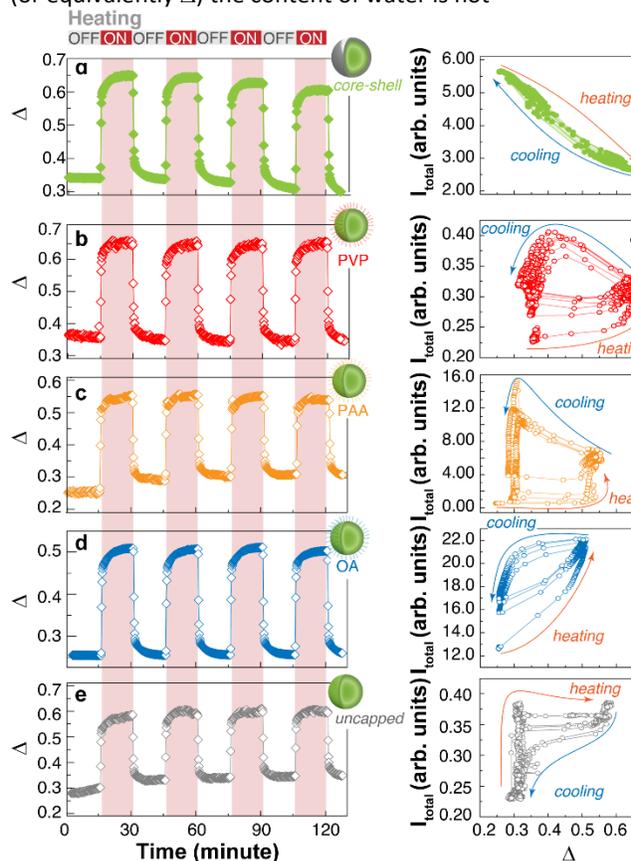


Figure 4. Evolution of the thermometric parameter (Δ) in four thermal cycles for (a) core-shell, (b) PVP-capped, (c) PAA-capped, (d) OA-capped nanoparticles, and (e) uncapped nanoparticles. The corresponding dependence of the total integrated intensities (I_{total}) with Δ are presented in f-j in consecutive heating-cooling cycles.

univocally defined but rather depends on the thermal history and the humidity of the atmosphere, as shown by Wang *et al.*¹⁰ and others.⁶ Because these measurements were done in non-equilibrium conditions, kinetic factors must be considered, also explaining the observed cycle-to-cycle differences.

When particles are capped with a water-soluble polymer, such as PVP, the thermal behaviour is modified. The water desorption becomes energetically costly because of the strong interaction of water with the carbonyl of the pyrrolidone groups, forming hydrogen bonds. To desorb water during the duty cycle, higher final temperatures must be applied. We augmented the electrical power delivered to the heating element to reach higher temperatures. First, the emission intensity remains roughly constant until higher temperatures are reached, followed by a gradual increase. When the heating source is turned off, the emission intensity continues to increase until the temperature is low enough to allow water re-adsorption.

A very interesting behaviour is observed for UCNPs capped with PAA (**Figure 3**, **Figure 4c,h**, and **Figure 5**). PAA is a strongly hydrophilic polymer due to the multiple carboxylic groups free for hydrogen bonding. For this reason, the activation energy for water desorption is higher and thus occurs at higher temperatures. The heating branch of the thermal cycle shows that the emission intensity remains nearly constant until a critical temperature of $(85 \pm 1)^\circ\text{C}$ is reached, corresponding to $\Delta = 0.52 \pm 0.02$, and water desorption is activated. A rapid increase in the emission intensity follows, once again due to the “unquenching” effect from water release. On the cooling branch of the cycle, the reversal effect (*i.e.*, quenching) takes place on water re-adsorption at a characteristic temperature between 35 and 45 $^\circ\text{C}$, corresponding to Δ values between 0.28 and 0.32, respectively. The additional and sudden enhancement observed after turning the heating source off is discussed in the following section.

The need for a physical separation of the emitting ions and the external environment has motivated the introduction of an insulating shell in UCNPs.^{21–23} Here, we prepared an additional sample with a shell layer containing Yb^{3+} and Tm^{3+} ions. Interestingly, we can follow the thermal behaviour of the emissions from the ions in the core (Er^{3+}) and the shell (Tm^{3+}). The emission from the core is completely different from the profiles observed for the previously discussed systems. Here, the increase in temperature produces a quenching of the emission intensity of Er^{3+} and the effect is completely reversible (**Figure 3** and **Figure 4a, f**). This is the typical behaviour for large-sized UCNPs or bulk upconverting materials.^{2,24} We can understand this behaviour by considering that the Yb^{3+} - Er^{3+} coupled ions are spatially

separated from the adsorbed water molecules, avoiding the water's quenching effect and thus exposing only the regular thermal quenching effect. This result has already been reported for thick (> 3 nm) inert shells, *i.e.* without Yb^{3+} ions;^{7,21,25} however, as recently reported,⁴ active shells (~ 3.5 nm thick) can also display the thermal enhancing effect because of energy migration among Yb^{3+} ions reaching the surface and being quenched by the -OH vibrations from the adsorbed water. In our case, an active shell layer was grown with 30%at. content of Yb^{3+} ions and thickness of ~ 9 nm, but the thermal adsorption/desorption mechanism seems to be effectively suppressed. The difference here could be addressed to the thickness of the shell layer, but further research needs to be done to accurately measure the length along which energy migration can effectively occur.

On the other hand, the emissions from Tm^{3+} in the shell layer were studied by following the ${}^3\text{H}_4 \rightarrow {}^3\text{H}_6$ transition observed between 750 and 850 nm. Figure S2 in ESI shows that the thermal enhancement effect is also observed for the Tm^{3+} ions present in the shell, highlighting the importance of the distance between the emitting ions and the surface of the UCNPs. These observations demonstrate that the UCL enhancement effect is most effective for activator ions located closer to the surface of the UCNP. Moreover, the overshoot phenomenon clearly noticed here points out the role of the surface defect states (SDS). Experimental evidence of the SDS can be found in the literature^{26–28} for similar lanthanide-doped UCNPs. Also, the defects were modelled based on the density functional theory calculations, as detailed by Qin et al.²⁹ and Huang et al.³⁰ Thus, the SDS in $\text{NaYF}_4:\text{Yb}^{3+},\text{Er}^{3+}$ nanocrystal are mainly attributed to the fluorine vacancies due to incomplete coordination of the cations Na^+ , Y^{3+} , Yb^{3+} , and Er^{3+} on the surface. These vacancies create electron-hole pairs, and its recombination may provide long-lived photon trapping.³¹ In this sense, we modelled the SDS as an energy reservoir that can relax after the heating source is turned off, triggering the energy transfer to the Ln^{3+} ion, similarly to the persistent luminescence phenomenon.³²

A possible explanation for the thermal behaviour of UCL in these systems can be lined up with previous models of thermal enhancement for small-sized UCNPs. The important role of water adsorption on the quenching of upconversion luminescence was demonstrated in many recent reports.^{10,11,25} The adsorbed moisture provides non-radiative relaxation pathways for the populated excited levels of the lanthanide ions by transferring their energy to the stretching vibration of water molecules (~ 3500 cm^{-1}).²⁷ Vibrational overtones of OH-stretching were also pointed out for non-radiative

relaxation.³³ Increasing the temperature produces the desorption of water molecules, therefore reducing the quenching effect. This is perceived as an emission intensity enhancement but should be properly interpreted as an “unquenching” mechanism, also termed by some authors as “thermally alleviated surface quenching”.³⁴ These adsorption-related phenomena depend on the surface-to-volume ratio and surface chemistry. Whereas the former explains the existence of a critical size separating the thermal enhancement and quenching behaviours, the functionalization or chemical nature of the surface of the particle regulates the adsorption or desorption dynamics by setting its hydrophilicity or hydrophobicity.

2.4 Enhancement overshoot

The enhancement overshoot that shows up when turning off the heating source (at the very beginning of the cooling branch of the thermal cycles) is another observation that, to the best of our knowledge, has never been reported before and should be considered in detail (**Figure 3**). Instead of reversing the emission enhancement, a sudden increase in the intensity of emissions is produced. The enhancement overshoot is significantly different for each UCNPs system, showing the fundamental role of surface chemistry. For example, the effect is augmented for the UCNPs capped with PVP and PAA, and even between these samples the effect is quite different. Most importantly, the effect is not equivalent for each emission line and it is clearer for the ${}^4\text{S}_{3/2} \rightarrow {}^4\text{I}_{15/2}$ transition. For example, the UCNPs-uncapped shows a remarkable overshoot in the I_5 transition that is absent in the I_H and I_F profiles. A similar observation is valid for the UCNPs-OA system. As shown in the ESI (Figure S3), we have observed the thermal enhancement and the overshoot phenomenon in UCNPs-OA with smaller sizes (~ 8 nm) with or without a thin shell, as well as for the emissions in the NIR of Tm^{3+} in the core-shell sample (Figure S2). This points out a direct influence of the surface chemistry on the energy transfer and non-radiative transitions between the $4f^n$ multilevel structure.

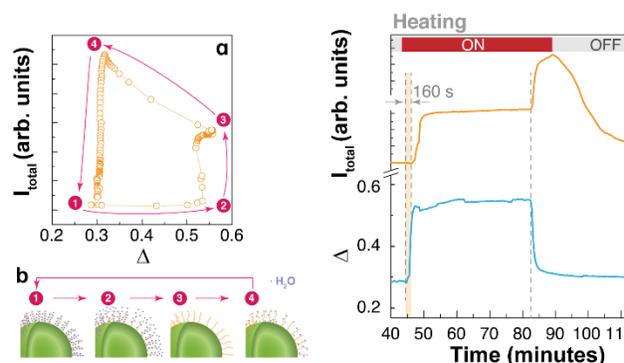


Figure 5. Water adsorption-desorption model exemplified for PAA-capped nanoparticles **(a)** Thermal hysteresis loop (second cycle) identifying four critical points. **(b)** Schematic representation of the water (blue dots) adsorption state in each of the critical points. In the initial state (1) the water content is maximum and the emission intensity is partially quenched. On state (2) water desorption from the PAA is thermally activated, producing the unquenching of the emissions. At state (3) the heating source is turned off; on cooling, the thermal quenching is reduced and the system reaches its maximum emission intensity on the state (4) when water re-adsorption occurs. **(c)** Time delay observed for the apparent enhancement during the initial heating cycle and the absence of such a delay when turning off the heating source.

The increasing emission intensities at the beginning of the cooling cycle can be interpreted considering two competing thermal effects. First, it is well known that temperature increase negatively affects the quantum efficiency of luminescence processes by increasing the non-radiative decay probabilities through multi-phonon relaxation.^{35,36} On thermal cooling the effect is the opposite and a higher emissivity is expected. On the other hand, considering the water adsorption/desorption mechanism, a temperature increase affects the emission intensity positively in these UCNPs by reducing the quenching effect of water molecules due to thermal desorption. On cooling, quenching occurs when water molecules are re-adsorbed. To illustrate a possible dynamics of water absorption/desorption in the heating-cooling cycle we use the PAA-coated UCNPs (**Figure 5a,b**). At the beginning (1), water molecules are already adsorbed at room temperature (T_1), partially quenching the UCL. Desorption takes place at elevated temperatures ($T_2 \sim 85^\circ\text{C}$) and the water quenching effect disappears (2); however, the opposite phononic thermal quenching effect becomes relevant. At point (3), one can assume that most water molecules were desorbed but the high temperature ($T_3 \sim 95^\circ\text{C}$) partially limits the upconversion quantum yield. When the heating source is turned off, as the sample cools down, the quantum yield is recovered,

and the emission intensity increases. At point (4), water adsorption rapidly occurs producing a notorious quenching of the upconversion, and the system returns to the initial condition.

Considering the overshoot phenomenon for the PAA-coated UCNPs system it is worth noting that there is a delay, of about 160 s, between the beginning of the heating cycle and the enhancement in the emission intensity. However, the overshoot enhancement after the thermal plate is turned off is immediate, without any delay. This is shown in **Figure 5c** in which the total emission intensity and the thermometric parameter are plotted as a function of time. This additional information is consistent with thermal desorption of water during heating, delayed by water diffusion, and a phononic thermal effect that is instantaneously reflected at the cooling stage. The distinctive characteristics of the overshoot peak for each sample and each transition line, point out an additional mechanism that must be related to surface states. We hypothesize that the presence and nature of surface defects play a significant role in this overshoot effect. To investigate this hypothesis, we performed numerical calculations considering surface defects involved in the energy transfer to activator ions.

2.5 Modelling the emission overshoot

We modelled the non-radiative energy transfer from SDS to the Ln^{3+} ions. This additional energy route is operative only when the population of these defects is operative only when the population of these defects decays to the valence band of the material when turning the heat source off. The energy released by this decay induces an abrupt population increase in the $^4\text{F}_{9/2}$, $^4\text{S}_{3/2}$, $^2\text{H}_{11/2}$ emitting levels of the Er^{3+} ion after non-radiative energy transfer (for light emission the SDS act as energy reservoirs). In other words, when the heating source is turned on, the SDS trap electrons from the valence band of the material, filling it up. From our theoretical model, we infer that this filling process is supported by the Ln^{3+} -to-SDS energy transfer. When the heating source is turned off, the SDS population starts to relax to the valence band transferring the equivalent amount of energy (E_D) to the Ln^{3+} ion.

This novel model introduced here is based on a well-established theory of Intramolecular Energy Transfer by Malta and collaborators.^{37–42} Further details can be found in the ESI.

For a semiconductor material, the temperature increasing should decrease the average energy of the creation of electron-hole pairs.⁴³ We expect this same trend in insulators such as the NaYF_4 nanoparticle. Thus, the SDS energy may be reduced and the SDS-to- Ln^{3+} energy transfer could be in out-of-resonance conditions. For this reason, we calculated the SDS-to- Ln^{3+} energy

transfer rates making a scan in the SDS energies from 0 to 30000 cm^{-1} , which is inside the bandgap interval of the NaYF_4 material (ca. 64500 cm^{-1})⁴⁴.

The SDS can occur in a low energetic condition (Situation 1, 4000 $\text{cm}^{-1} < E_D < 12000 \text{ cm}^{-1}$), close to the $^2\text{F}_{5/2}$ (Yb^{3+}) level.^{29,45,46} Here, we are also considering these states in a higher energy condition like a deep electron trap (Situation 2, 12000 $\text{cm}^{-1} < E_D < 30000 \text{ cm}^{-1}$), as considered by Rodrigues et al.⁴⁷ These two situations are depicted in **Figure 6c** and **Figure 6d**, respectively. Although some reports pointed out a possible existence of energy transfer from defects to Ln^{3+} ions,^{45,46,48} our data displayed in **Figure 6e** is the first quantitative analysis of the SDS-to- Ln^{3+} energy transfer rates (details in the ESI).

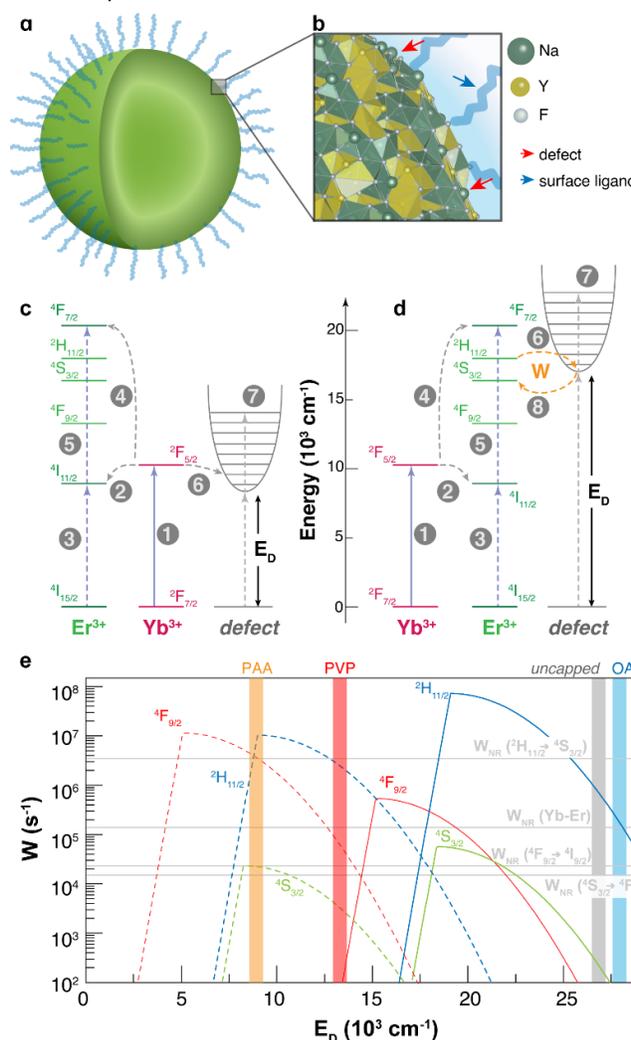


Figure 6. (a) Illustration of a NaYF_4 spherical nanoparticle and (b) its amplified image displaying surface defects and ligands. (c) and (d) are the two situations in which the defects would interact as energy donors. (1) is the Yb^{3+} absorption ($^2\text{F}_{7/2} \rightarrow ^2\text{F}_{5/2}$); (2) and (3) are the first step in the Yb-Er UC process where the Er^{3+} ground population is excited to an

intermediary level ($^4\text{I}_{15/2} \rightarrow ^4\text{I}_{11/2}$); (4) and (5) are the second step in the Yb-Er UC process, resulting in a population increase in the Er^{3+} emitting levels ($^2\text{H}_{11/2}$, $^4\text{S}_{3/2}$, and $^4\text{F}_{9/2}$) by a sequential multi-phonon relaxation; (6) is the energy transfer from the Ln^{3+} ($\text{Ln} = \text{Yb}$ and Er in (c) and (d), respectively) to the valence band promoting its population that will be trapped into the SDS with energy E_D ; (7) represents the vibrational states of the surface defects; (8) is the non-radiative energy transfer rate W from the SDS to the Er^{3+} levels, responsible for the luminescent overshoot phenomenon. (e) Semi-log scale of the energy transfer rates W between the SDS and the Er^{3+} ion. Dotted and full lines represent, respectively, the rates when the SDS state is resonant with the $^4\text{I}_{11/2}$ level (Situation 1, (c)) and with the $^2\text{H}_{11/2}$, $^4\text{S}_{3/2}$, and $^4\text{F}_{9/2}$ levels (Situation 2, (d)). The horizontal lines, from top to bottom, ordering the $^2\text{H}_{11/2} \rightarrow ^4\text{S}_{3/2}$ non-radiative decay rate, the average upconversion energy transfer rate Yb-Er,⁴⁹ and the $^4\text{F}_{9/2} \rightarrow ^4\text{I}_{9/2}$ and $^4\text{S}_{3/2} \rightarrow ^4\text{F}_{9/2}$ non-radiative decay rates.

Figure 6e and **Table 1** present the behaviour and the calculated SDS-to- Er^{3+} energy transfer rates using Eq. S5 (ESI) and the approximate energy position of the SDS that matches the luminescent overshoots (ratio $I_{\text{OFF}}/I_{\text{ON}} > 1$). Since the $^2\text{H}_{11/2}$ population decays very fast non-radiatively by multi-phonon relaxation (in the order of $W_{\text{NR}}(^2\text{H}_{11/2} \rightarrow ^4\text{S}_{3/2}) \sim 10^6 \text{ s}^{-1}$ at 120 °C, ESI), when the energy transfer rate is lower than the multi-phonon decay there is a population escape from the $^2\text{H}_{11/2}$ level, that effectively migrates to the $^4\text{S}_{3/2}$ one. As can be observed in **Figure 6e**, this condition affords W values between the $W_{\text{NR}}(^2\text{H}_{11/2} \rightarrow ^4\text{S}_{3/2})$ and the equilibrium rate $W_{\text{Yb-Er}}$. This can explain the luminescent overshoot behaviour for OA-capped and uncapped samples (both in Situation 2) that is present only in the transition $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{15/2}$. In the samples capped with PVP and PAA, the luminescent overshoot is observed in all transitions, some less pronounced than others (Table 1). In particular, the appearance of the luminescent overshoot in the $^2\text{H}_{11/2} \rightarrow ^4\text{I}_{15/2}$ transition indicates that the $^2\text{H}_{11/2}$ level receives a substantial energy rate W to compensate the $W_{\text{NR}}(^2\text{H}_{11/2} \rightarrow ^4\text{S}_{3/2})$ decay. Since the PAA has a higher luminescent overshoot among all samples, this leads to an SDS energetic position around 9400 cm^{-1} that favours a high transfer rate to all involved levels (Situation 1). The sample capped with PVP presents the same but less pronounced trend than the PAA ones, leading to an SDS around 12600 cm^{-1} , where the rates are decreasing moderately. The UCL overshoot does not affect the Boltzmann's thermal equilibrium between the $^2\text{H}_{11/2}$ and $^4\text{S}_{3/2}$ levels, with, thus, no impact in the thermometric parameter (**Figure 4**), because the energy transfer rate between SDS and the two Er^{3+} levels, and within these levels, (**Figure 6**) are much higher than the integration rate in two consecutive measurements.

Table 1 The ratio between the intensities when the heater is turned ON and OFF I_X^{OFF}/I_X^{ON} (X=F, S, and H). The SDS favourable energetic position E_D and its corresponding energy transfer from the SDS to each Er^{3+} level (F = $^4\text{F}_{9/2}$, S = $^4\text{S}_{3/2}$, and H = $^2\text{H}_{11/2}$).

Sample	OA	uncapped	PVP	PAA
I_F^{OFF}/I_F^{ON}	0.97	0.84	1.08	1.54
I_S^{OFF}/I_S^{ON}	1.08	1.18	1.52	2.21
I_H^{OFF}/I_H^{ON}	0.70	0.75	1.03	1.26
E_D (cm^{-1})	27000	25900	12600	9400
W_F (s^{-1})	12.5	83	$1.51 \times 10_5$	$2.73 \times 10_6$
W_S (s^{-1})	192	744	$5.49 \times 10_3$	$2.10 \times 10_4$
W_H (s^{-1})	$6.15 \times 10_5$	2.11×10^6	$3.81 \times 10_6$	$1.02 \times 10_7$

3. Conclusions

We have prepared a standard system consisting of UCNPs with a size of 21 nm co-doped with Yb^{3+} - Er^{3+} and capped with OA molecules. We performed a standard chemical procedure to modify the surface and obtain UCNPs without capping molecules or to replace the OA ligands with PVP or PAA, which are polymers with different hydrophilic characteristics. The successful modification of the surface chemistry was verified by FTIR. The intensity of the upconversion emissions under NIR excitation was recorded during heating and cooling cycles while the emissions from Er^{3+} ions were used to probe the temperature in real-time. Distinctive intensity-temperature trajectories were observed during the thermal cycling for UCNPs with different surface capping. The heating and cooling branches of the thermal cycles were markedly different showing that the emission intensity remains at a high-level state even when the heating source is turned off. In some cases, the intensity continues to increase upon cooling until the temperature is low enough. Based on the well-established mechanism of thermal adsorption and desorption of water molecules, here we showed that the hydrophilicity of the

particles' surface is of great importance in regulating the thermo-optical properties, as it determines the extent and kinetics of water adsorption/desorption. UCNPs with a highly hydrophilic surface, as in the case of UCNPs-PAA, show a remarkable bi-stable behaviour displaying an optical switching effect on thermal cycling. The fundamental role of the chemical coating is demonstrated when comparing the thermal performance of core-shell UCNPs, showing only the thermal quenching effect.

Depending on the surface capping of the UCNPs, and for specific radiative transitions, an overshoot peak in the emission intensity is observed immediately after shutting down the heat source. To explain this phenomenon, we proposed that surface defects act as thermally populated reservoirs that, upon cooling, transfer their stored energy to the emitting levels of activator ions. Ultimately, we performed numerical calculations on the transfer rates to address this mechanism quantitatively. We thus modelled the thermal behaviour observed for UCNPs with different surface capping by considering the presence of low- or high-energy surface defects. The energy position depends on the nature of the UCNPs surface: for PAA and PVP low energy defects states should be considered while for uncapped and OA capped UCNPs, high energy surface defects may be acting. We strikingly found that the proposed defects act as thermally populated reservoirs, providing a mechanism for the sudden increase in UCL observed immediately after turning the heat source off. All these findings shed new light on the thermal properties of UCNPs and will be useful for the development of novel nanophotonic-based technologies and photoresponsive materials⁵⁰.

4. Materials and methods

4.1 Synthesis of UCNPs. The UCNPs were synthesized by the co-precipitation method using rare-earth acetates and sodium fluoride following well-established protocols by Wang *et al.*¹⁴ After the synthesis, UCNPs were washed and extracted by multiple steps of dispersion in ethanol and centrifugation. Stable colloids in cyclohexane were prepared. For the synthesis of a shell layer, a layer-by-layer method was applied following procedures reported by Li and co-workers.²³ Briefly, Rare-earth (Gd, Yb, Tm) acetates dissolved in OA and $\text{Na}(\text{COOCF}_3)$ in OA were successively added by injection to a dispersion of the core-UCNPs in OA and ODE at 280 °C. Three cycles of injection of each reactant were performed in total. A detailed explanation of the synthesis procedures is provided in the ESI.

4.2 Surface modification. The surface modification of core UCNPs was performed following HCl acid treatment as detailed by Bogdan and co-workers¹⁵ and generalized

by Kong et al.¹⁶ Experimental details are described in the ESI.

4.3 Luminescence measurements. A solid-state NIR (976 nm) continuous wave (CW) FBG stabilized laser (BL976-PAG900 ThorLabs) was used for excitation. Emission spectra were acquired using a portable spectrometer (QEPro, Ocean Optics). A short-pass optical filter was added to avoid the spectrometer saturation by the 976 nm line of the laser. Several drops of the corresponding colloids of functionalized UCNPs were deposited on silicon wafers and left to dry. The wafers were placed in thermal contact on a Peltier plate using a high thermal conductivity paste. Temperatures were directly measured by positioning a thermocouple, or a resistance temperature detector (Pt100), on the Peltier plate. The thermal cycling was automated using an Arduino-controlled relay.

4.4 Electronic Microscopy. Transmission electron microscopy (TEM) images were obtained with an electronic microscope (JEM 2100, JEOL) equipped with a LaB₆ filament and operated at 200 kV. EDS maps were acquired by a coupled EDAX spectrometer.

Author Contributions

The manuscript was written through the contributions of all authors. All authors have approved the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgments

This work was supported and performed under the auspices of FAPESP through Grants #2011/19924-2, #2012/04870-7, #2012/05903-6, #2015/21290-2, #2015/21289-4, and #2017/10581-1. E. D. M was the beneficiary of a post-doctoral FAPESP fellowship #2015/23882-4 during part of the development of this work. R. R. U acknowledges CNPq Grant No 309483/2018-2. E. D. M. acknowledges funding from ANPCyT-FONCyT PICT 2017-0307. Research supported by LNNano-Brazilian Nanotechnology National Laboratory (CNPEM/MCTI) during the use of the electron microscopy open-access facility. This work was also developed within the scope of the project CICECO – Aveiro Institute of Materials, UIDB/50011/2020, financed by Portuguese funds through the FCT/MEC and when appropriate co-financed by FEDER under the PT2020 Partnership Agreement. Financial support from

the European Union's Horizon 2020 FET Open programme under grant agreement no. 801305 is also acknowledged. This work was initiated at IFGW-UNICAMP, Brazil, continued and finished at the current affiliation of the corresponding author.

Notes and references

- 1 D. D. Li, Q. Y. Shao, Y. Dong, F. Fang and J. Q. Jiang, *Part. Part. Syst. Charact.*, 2015, **32**, 728–733.
- 2 D. Li, Q. Shao, Y. Dong and J. Jiang, *J. Phys. Chem. C*, 2014, **118**, 22807–22813.
- 3 E. D. Martínez, R. R. Urbano and C. Rettori, *Nanoscale*, 2018, **10**, 14687–14696.
- 4 Y. Hu, Q. Shao, P. Zhang, Y. Dong, F. Fang and J. Jiang, *J. Phys. Chem. C*, 2018, **122**, 26142–26152.
- 5 H. Zou, X. Yang, B. Chen, Y. Du, B. Ren, X. Sun, X. Qiao, Q. Zhang and F. Wang, *Angew. Chemie - Int. Ed.*, 2019, **58**, 17255–17259.
- 6 D. Li, W. Wang, X. Liu, C. Jiang and J. Qiu, *J. Mater. Chem. C*, 2019, **7**, 4336–4343.
- 7 J. Zhou, S. Wen, J. Liao, C. Clarke, S. A. Tawfik, W. Ren, C. Mi, F. Wang and D. Jin, *Nat. Photonics*, 2018, **12**, 154–158.
- 8 C. Mi, J. Zhou, F. Wang and D. Jin, *Nanoscale*, 2019, **11**, 12547–12552.
- 9 L. Lei, J. Xia, Y. Cheng, Y. Wang, G. Bai, H. Xia and S. Xu, *J. Mater. Chem. C*, 2018, **6**, 11587–11592.
- 10 Z. Wang, J. Christiansen, D. Wezendonk, X. Xie, M. A. van Huis and A. Meijerink, *Nanoscale*, 2019, **11**, 12188–12197.
- 11 R. Shi, E. D. Martinez, C. D. S. Brites and L. D. Carlos, *Phys. Chem. Chem. Phys.*, 2021, **23**, 20–42.
- 12 Y. Zhou, Y. Cheng, Q. Huang, J. Xu, H. Lin and Y. Wang, *J. Mater. Chem. C*, 2021, **9**, 2220–2230.
- 13 Y. Wang, B. Chen and F. Wang, *Nanoscale*, 2021, **13**, 3454–3462.
- 14 F. Wang, R. Deng and X. Liu, *Nat. Protoc.*, 2014, **9**, 1634–1644.
- 15 N. Bogdan, F. Vetrone, G. A. Ozin and J. A. Capobianco, *Nano Lett.*, 2011, **11**, 835–840.
- 16 W. Kong, T. Sun, B. Chen, X. Chen, F. Ai, X. Zhu, M. Li, W. Zhang, G. Zhu and F. Wang, *Inorg. Chem.*, 2017, **56**, 872–877.
- 17 C. D. S. Brites, A. Millán and L. D. Carlos, in *Handbook on the Physics and Chemistry of Rare Earths, Vol. 49*, eds J.-C. G. Bünzli and V. K. Pecharsky, Elsevier, 2016, pp. 339–427.
- 18 M. Suta and A. Meijerink, *Adv. Theory Simulations*, , DOI:10.1002/adts.202000176.
- 19 S. Balabhadra, M. L. Debasu, C. D. S. Brites, R. A. S. S. Ferreira and L. D. Carlos, *J. Phys. Chem. C*, 2017, **121**, 13962–13968.

- 20 C. D. S. Brites, S. Balabhadra and L. D. Carlos, *Adv. Opt. Mater.*, 2019, **7**, 1801239.
- 21 Q. Su, S. Han, X. Xie, H. Zhu, H. Chen, C. K. Chen, R. S. Liu, X. Chen, F. Wang and X. Liu, *J. Am. Chem. Soc.*, 2012, **134**, 20849–20857.
- 22 G.-S. Yi and G.-M. Chow, *Chem. Mater.*, 2007, **19**, 341–343.
- 23 X. Li, D. Shen, J. Yang, C. Yao, R. Che, F. Zhang and D. Zhao, *Chem. Mater.*, 2013, **25**, 106–112.
- 24 E. D. Martínez, C. D. S. Brites, L. D. Carlos, A. F. García-Flores, R. R. Urbano and C. Rettori, *Adv. Funct. Mater.*, 2019, **29**, 1807758.
- 25 Q. Shao, G. Zhang, L. Ouyang, Y. Hu, Y. Dong and J. Jiang, *Nanoscale*, 2017, **9**, 12132–12141.
- 26 F. Wang, J. Wang and X. Liu, *Angew. Chemie Int. Ed.*, 2010, **49**, 7456–7460.
- 27 F. T. Rabouw, P. T. Prins, P. Villanueva-Delgado, M. Castelijns, R. G. Geitenbeek and A. Meijerink, *ACS Nano*, 2018, **12**, 4812–4823.
- 28 D. Yuan, M. C. Tan, R. E. Riman and G. M. Chow, *J. Phys. Chem. C*, 2013, **117**, 13297–13304.
- 29 X. Qin, L. Shen, L. Liang, S. Han, Z. Yi and X. Liu, *J. Phys. Chem. C*, 2019, **123**, 11151–11161.
- 30 B. Huang, H. Dong, K.-L. Wong, L.-D. Sun and C.-H. Yan, *J. Phys. Chem. C*, 2016, **120**, 18858–18870.
- 31 A. N. Carneiro Neto and O. L. Malta, *Nature*, 2021, **590**, 396–397.
- 32 X. Ou, X. Qin, B. Huang, J. Zan, Q. Wu, Z. Hong, L. Xie, H. Bian, Z. Yi, X. Chen, Y. Wu, X. Song, J. Li, Q. Chen, H. Yang and X. Liu, *Nature*, 2021, **590**, 410–415.
- 33 R. Arppe, I. Hyppänen, N. Perälä, R. Peltomaa, M. Kaiser, C. Würth, S. Christ, U. Resch-Genger, M. Schäferling and T. Soukka, *Nanoscale*, 2015, **7**, 11746–11757.
- 34 B. Chen and F. Wang, *Trends Chem.*, 2020, **2**, 427–439.
- 35 D. Yu, J. Ballato and R. E. Riman, *J. Phys. Chem. C*, 2016, **120**, 9958–9964.
- 36 X. Shen, Q. Nie, T. Xu, S. Dai and X. Wang, *J. Lumin.*, 2010, **130**, 1353–1356.
- 37 O. L. Malta, *J. Lumin.*, 1997, **71**, 229–236.
- 38 F. R. G. e Silva and O. L. Malta, *J. Alloys Compd.*, 1997, **250**, 427–430.
- 39 W. M. Faustino, O. L. Malta and G. F. de Sá, *J. Chem. Phys.*, 2005, **122**, 054109.
- 40 A. N. Carneiro Neto, E. E. S. Teotonio, G. F. de Sá, H. F. Brito, J. Legendziewicz, L. D. Carlos, M. C. F. C. Felinto, P. Gawryszewska, R. T. Moura Jr., R. L. Longo, W. M. Faustino and O. L. Malta, in *Handbook on the Physics and Chemistry of Rare Earths, volume 56*, eds. J.-C. G. Bünzli and V. K. Pecharsky, Elsevier, 2019, pp. 55–162.
- 41 E. Kasprzycka, A. N. Carneiro Neto, V. A. Trush, L. Jerzykiewicz, V. M. Amirkhanov, O. L. Malta, J. Legendziewicz and P. Gawryszewska, *J. Rare Earths*, 2020, **38**, 552–563.
- 42 P. P. Lima, S. S. Nobre, R. O. Freire, S. A. Júnior, R. A. Sá Ferreira, U. Pischel, O. L. Malta and L. D. Carlos, *J. Phys. Chem. C*, 2007, **111**, 17627–17634.
- 43 A. M. Barnett, J. E. Lees and D. J. Bassford, *Appl. Phys. Lett.*, 2013, **102**, 181119.
- 44 K. Chong, T. Hirai, T. Kawai, S. Hashimoto and N. Ohno, *J. Lumin.*, 2007, **122–123**, 149–151.
- 45 X. Dai, L. Lei, J. Xia, X. Han, Y. Hua and S. Xu, *J. Alloys Compd.*, 2018, **766**, 261–265.
- 46 L. Lei, D. Chen, C. Li, F. Huang, J. Zhang and S. Xu, *J. Mater. Chem. C*, 2018, **6**, 5427–5433.
- 47 L. C. V. Rodrigues, J. Hölsä, M. Lastusaari, M. C. F. C. Felinto and H. F. Brito, *J. Mater. Chem. C*, 2014, **2**, 1612.
- 48 J. Xia, L. Lei, H. Xia and S. Xu, *Opt. Commun.*, 2019, **444**, 131–136.
- 49 A. N. Carneiro Neto, R. T. Moura and O. L. Malta, *J. Lumin.*, 2019, **210**, 342–347.
- 50 L. Liang, Y. Tang, X. Hu, J. Wang, S. Xiao, D. Li, L. Fu, Z. Li and Q. Yuan, *CCS Chem.*, 2019, **1**, 490–501.