

Performance of Self Compacting Concrete Exposed to Marine Environment

Mehwish Asad¹, Muhammad Asad Bhatti², Muhammad Safdar³

¹ MA Engineering Consultant, Pakistan

² Mott MacDonald, Pakistan

³ MES, Pakistan

Abstract:- Enhanced durability of concrete plays a crucial role in the serviceability of structures in marine environments. In this study, performance of self compacting concrete (SCC) blended with Fly Ash (FA) and Silica Fume (SF) in the form of binary and ternary mixtures in the simulated marine environment is investigated. This study aimed at utilization of high volumes of FA, up to 60% replacement of Ordinary Portland Cement (OPC), for development of sustainable and durable SCC located in marine environment. SCC was examined for fresh as well as hardened state characteristics like flowability, compressive strength, split tensile strength and durability characteristics such as sorptivity and chloride ion penetration resistance. The results showed that SCC can be prepared with FA and SF up to 40% and 10% replacement of OPC respectively. There was a remarkable improvement in the durability performance of SCC in ternary mixtures containing 30% FA and 10% SF. At later ages, SCC in ternary mixtures showed improved strength in marine environment. The experimental investigation indicated improved performance of high-volume FA based SCC in marine environments.

I. INTRODUCTION

Self-compacting concrete (SCC) is a special type of innovative concrete which can be placed and compacted under its own weight, without any vibration effort and without segregation and bleeding due to cohesiveness. SCC completely fills the formwork even in the situation of heavy reinforcement. The concept of SCC was given by Okamura in 1986, and the prototype was at the University of Tokyo in 1988 [1,2]. SCC has many advantages in comparison to conventional concrete, including: (1) speedy construction; (2) reducing labor cost and noise pollution; (3) better placement due to improved workability (4) good filling ability of concrete in densely reinforced structural members; (5) good interfacial transitional zone between mortar and aggregate or reinforcement; (6) improved durability. SCC has key fresh properties like flowability, passing ability and segregation resistance. Fresh characteristics of SCC are mainly achieved by increasing fines, particle size less than 0.125mm as defined by The European Federation of Specialist Construction Chemicals and Concrete Systems (EFNARC) [3]. Because it requires more utilization of Ordinary Portland Cement (OPC) and chemical admixtures for attaining fresh characteristics, the SCC didn't become popular as conventional concrete in construction industry. High OPC content usually introduces problems like high heat of hydration and high shrinkage, which in turn leads the

severe cracking and damages the structural integrity by the attack of harmful substances into the concrete matrix [4]. Moreover, the consumption of natural resources and carbon dioxide emissions associated with OPC can cause serious environmental impacts [5]. In past few years, numerous efforts [5–12] have been done for producing sustainable SCC by replacing OPC with supplementary cementitious materials (SCMs) such as fly ash (FA), silica fume (SF), nano silica (NS), ground granulated blast-furnace slag (GGBS) and metakaolin (MK). Replacing OPC with these SCMs not only improves the performance of concrete but also lowers the cost of SCC. In addition, use of SCMs in construction industry minimizes the landfilling and undesirable depletion of natural resources.

Marine concrete is subjected to some of the harshest conditions in the engineering environment [13]. The actual life of marine concrete structures is usually much shorter than the designed service time due to various attacks from seawater [14],[15]. Chloride-induced reinforcement corrosion is regarded as the primary durability issues [16],[17]. The seawater chemically interacts with the cementitious materials and deteriorate the concrete exposed in the marine environment [18]. Chlorides, present in seawater, directly affect durability of concrete by instigating corrosion of the reinforcement steel. It is important to safeguard steel reinforcement from corrosion for long-term serviceability of concrete. Since all aggressive ions and chemicals penetrate through microcracks and porous structure of concrete, deformation and transport properties such as shrinkage, permeability, capillary absorption, porosity, and chloride diffusion are widely used to determine concrete durability. It is well-known that densification of concrete improves the microstructure and lowers the ingress of external aggressive ions. Blending OPC with SCMs is effective in densification of the microstructure and reducing the external attack on concrete.

FA from thermal power plants [19] and SF from silicon metal alloys or silicon metal production [20],[21] have been used as SCMs in construction industry for last few decades. It is evident from the previous research [22],[23],[24],[25],[26] that the addition of these SCMs improve the performance and microstructure of concrete due to their pozzolanic reactivity and ability to fill the micropores respectively. FA and SF, being pozzolanic in nature, designated type II additives following the EFNARC guidelines could significantly be used in improving the long-term performance of concrete.

Previously, researchers investigated properties of SCC in marine environments using blends of OPC and SCMs at lower replacement levels. Further detailed information on the optimum utilization of SCMs in SCC for durability indicators is limited. There is a knowledge gap in examining the performance of SCC modified with mineral admixture such as SF and FA, at higher replacement levels, in the marine environment. This study aims at performance-based investigation of SCC, designed using varying proportions of SF, FA and binary admixtures (SF+FA) as replacement of OPC up to 70%, in simulated marine environment. High volume FA based SCC was examined for durability indicators including the chloride migration and sorptivity besides fresh and other hardened characteristics. The significance of this research is utilization of high-volume FA, which otherwise be landfilled, in development of sustainable SCC in marine environment.

II. MATERIALS AND METHODS

A. Materials

ASTM type II OPC was used to produce various mixtures. In addition, SF and Class F FA were used as mineral admixtures. Table 1 summarizes physical properties and chemical composition of the OPC, FA and SF.

Natural crushed limestone aggregate (NCA) having maximum size of 12mm and specific gravity 2.67 was sourced from Margala Hill quarry. Natural siliceous sand from Lawrencepur Qibla Bandi was used as natural fine aggregates (NFA). Particle size distribution of NCA and NFA is shown in Figure 1. Characteristics of NCA and NFA are presented in table 2. The petrographic thin section analysis of NCA was carried out to check potential alkali aggregate reactivity. Petrographic description is shown in Figure 2. It was revealed that NCA has neither alkali carbonate (ACR) nor alkali silica (ASR) reaction potential. NCA therefore, be safely used as an aggregate with OPC.

A third generation polycarboxylate based superplasticizer, consisting of 48.15% maximum solid content, was used as water reducing admixture.

Available items	FA	SF	OPC
SiO ₂ (Silica)	54.12	93.48	20.77
Al ₂ O ₃ (Alumina)	15.42	0.39	5.2
Fe ₂ O ₃ (Iron Oxide)	2.16	0.16	3.5
CaO (Lime)	5.9	1.12	62.89
MgO (Magnesia)	0.8	0.22	2.2
SO ₃ (Sulphuric Anhydride)	1.6	0.34	2.56
LOI (Loss on Ignition)	4.8	3.32	2.04
IR (Insoluble Residue)	-	-	0.56
Physical Requirements:			
Standard Consistency	-	-	29.45
Initial setting time(minutes)	-	-	130
Final setting time (minutes)	-	-	185
Fineness (Blaine)(cm ² /gm)	-	-	3046
Le-Chatlier's expansion(mm)	-	-	1

Table 1: Temperature and wildlife count in the three areas covered by the study

	NCA	NFA
Los Angles Abrasion Value	18.96%	-
Crushing Value	23.81%	-
Impact Value	17.45%	-
Specific Gravity	2.67	2.72
Water Absorption	0.80%	1.20%
Fineness Modulus	-	1.84
Unit Weight (Rodded)	1557 kg/m ³	1540 kg/m ³
Unit Weight (Loose)	1446 kg/m ³	1443 kg/m ³
Flakiness Index	26.40%	-
Elongation Index	20.50%	-

Table 2: Characteristics of NCA and NFA

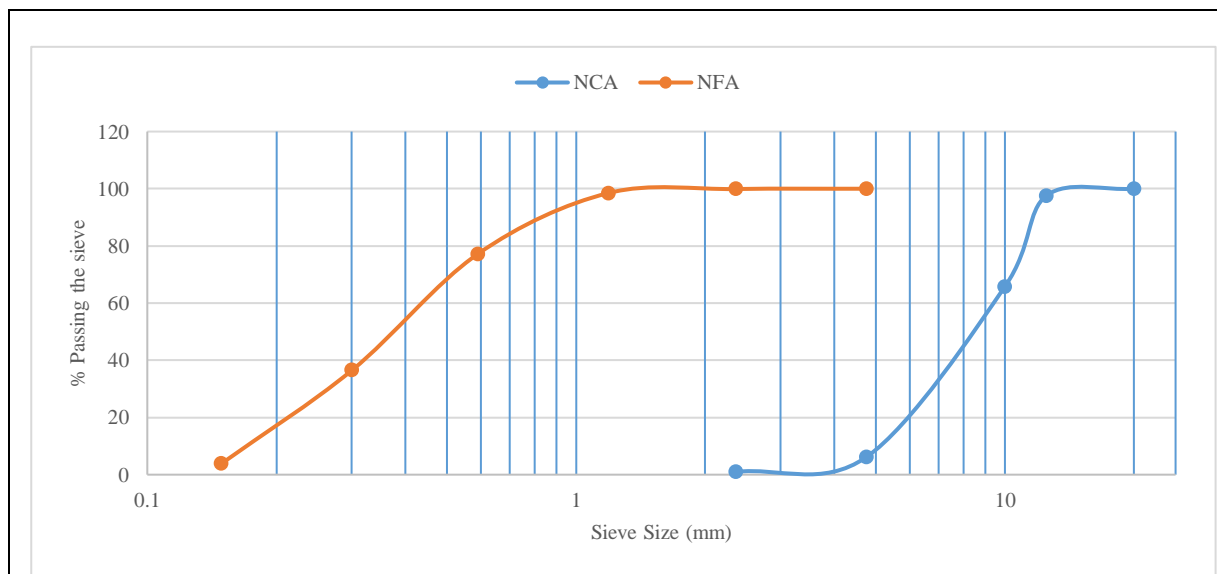


Fig. 1: Particle size distribution of aggregates

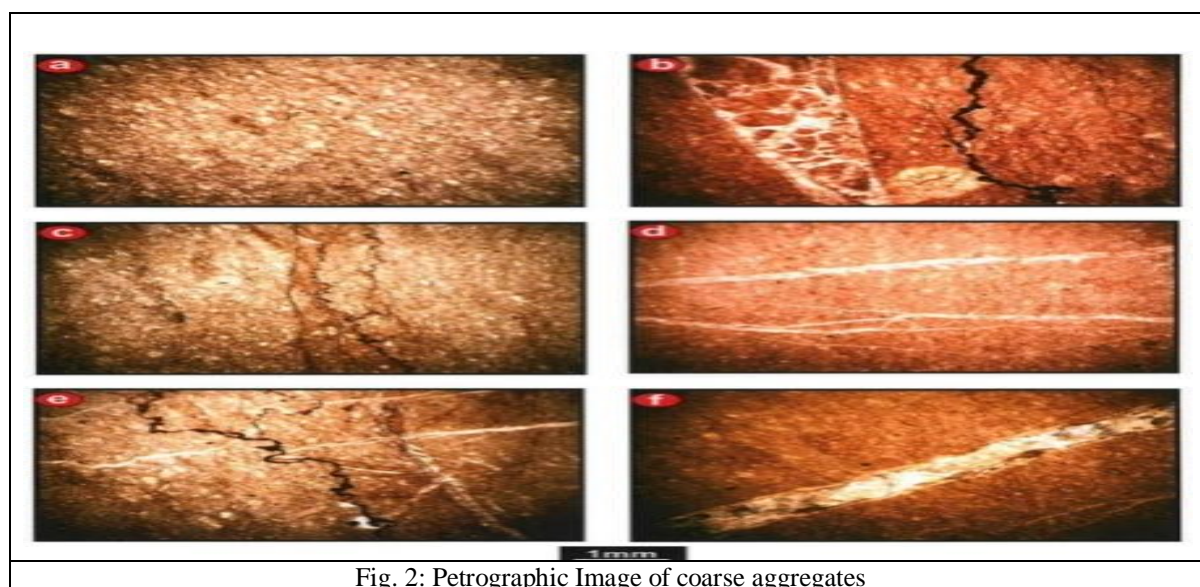


Fig. 2: Petrographic Image of coarse aggregates

B. Simulation of Marine Environment in laboratory

The exposure conditions of reinforced concrete structures in real marine environment can be classified into atmospheric (A), tidal (T), and submerged (S) zones [27]. A test chamber was designed to simulate marine environment considering submerged zones. Seawater was simulated in accordance with ASTM D1141 [28] that has the ion

concentration as mentioned in table 3. The temperature of simulated seawater was maintained at about 20°C. To achieve this temperature, the test chamber was installed with aquarium rods and a small electric pump was installed for continuous circulation of dissolved salts. A blower was arranged on top of the test chamber to balance the humidity and temperature distribution of the air.

Conc.[mg/l]	Cl ⁻	Na ⁺	Mg ²⁺	SO ₄ ²⁻	Ca ²⁺	K ⁺	CO ₃ ²⁻
Simulated Water	21870	11862	1080	2911	443	401	151
ASTM D1141-98 [28]	19845	11024	1314	2766	418	397	145

Table 3: Concentrations of the main ions in simulated marine water

C. Mix Proportions and sample preparation

Mix design was carried out with the trial-and-error method in accordance with EFNARC specifications [3]. A total of 57 concrete mixtures were designed with a constant water/binder ratio of 0.32 and a total binder content of 600kg/m³, 550kg/m³ and 500kg/m³. Concrete mixtures

contain SF and FA at various replacement levels by weight of concrete. Table 4 represents each variation as a weight of constituents for 1m³ of concrete. The abbreviations for labeling the mixtures were adopted in such a way that each designation clearly defines the main parameters and their replacement levels.

Concrete Mix ID	w/b	Water	Binder (kg/m ³)			Aggregates (kg/m ³)		SP (%)
			OPC	SF	FA	NFA	NCA	
Mix Type-I (Binder content 600kg/m ³)								
C600	0.32	192	600	0	0	840	960	1.2
600M10FA	0.32	192	540	0	60	840	960	1.2
600M20FA	0.32	192	480	0	120	840	960	1.1
600M30FA	0.32	192	420	0	180	840	960	1.08
600M40FA	0.32	192	360	0	240	840	960	1
600M50FA	0.32	192	300	0	300	840	960	0.99
600M60FA	0.32	192	240	0	360	840	960	0.98
600M5SF10FA	0.32	192	510	30	60	840	960	1.1
600M10SF10FA	0.32	192	480	60	60	840	960	1.2
600M5SF20FA	0.32	192	450	30	120	840	960	1.01
600M10SF20FA	0.32	192	420	60	120	840	960	1.08
600M5SF30FA	0.32	192	390	30	180	840	960	1
600M10SF30FA	0.32	192	360	60	180	840	960	1.02
600M5SF40FA	0.32	192	330	30	240	840	960	0.95
600M10SF40FA	0.32	192	300	60	240	840	960	0.98
600M5SF50FA	0.32	192	270	30	300	840	960	0.85
600M10SF50FA	0.32	192	240	60	300	840	960	0.88
600M5SF60FA	0.32	192	210	30	360	840	960	0.87
600M10SF60FA	0.32	192	180	60	360	840	960	0.92
Mix Type-II (Binder content 550kg/m ³)								
C550	0.32	176	550	0	0	881	969	1.4
550M10FA	0.32	176	495	0	55	881	969	1.4
550M20FA	0.32	176	440	0	110	881	969	1.31
550M30FA	0.32	176	385	0	165	881	969	1.3
550M40FA	0.32	176	330	0	220	881	969	1.27
550M50FA	0.32	176	275	0	275	881	969	1.2
550M60FA	0.32	176	220	0	330	881	969	1.17
550M5SF10FA	0.32	176	467.5	27.5	55	881	969	1.36
550M10SF10FA	0.32	176	440	55	55	881	969	1.39
550M5SF20FA	0.32	176	412.5	27.5	110	881	969	1.32
550M10SF20FA	0.32	176	385	55	110	881	969	1.4
550M5SF30FA	0.32	176	357.5	27.5	165	881	969	1.2
550M10SF30FA	0.32	176	330	55	165	881	969	1.3
550M5SF40FA	0.32	176	302.5	27.5	220	881	969	1.1
550M10SF40FA	0.32	176	275	55	220	881	969	1.15
550M5SF50FA	0.32	176	247.5	27.5	275	881	969	1.01
550M10SF50FA	0.32	176	220	55	275	881	969	1.09
550M5SF60FA	0.32	176	192.5	27.5	330	881	969	1
550M10SF60FA	0.32	176	165	55	330	881	969	1.05
Mix Type-III (Binder content 500kg/m ³)								
C500	0.32	160	500	0	0	900	1000	1.51
500M10FA	0.32	160	450	0	50	900	1000	1.5
500M20FA	0.32	160	400	0	100	900	1000	1.5
500M30FA	0.32	160	350	0	150	900	1000	1.45
500M40FA	0.32	160	300	0	200	900	1000	1.41
500M50FA	0.32	160	250	0	250	900	1000	1.3
500M60FA	0.32	160	200	0	300	900	1000	1.29
500M5SF10FA	0.32	160	425	25	50	900	1000	1.3
500M10SF10FA	0.32	160	400	50	50	900	1000	1.38
500M5SF20FA	0.32	160	375	25	100	900	1000	1.32
500M10SF20FA	0.32	160	350	50	100	900	1000	1.4
500M5SF30FA	0.32	160	325	25	150	900	1000	1.23
500M10SF30FA	0.32	160	300	50	150	900	1000	1.3
500M5SF40FA	0.32	160	275	25	200	900	1000	1.28
500M10SF40FA	0.32	160	250	50	200	900	1000	1.34
500M5SF50FA	0.32	160	225	25	250	900	1000	1.17
500M10SF50FA	0.32	160	200	50	250	900	1000	1.22
500M5SF60FA	0.32	160	175	25	300	900	1000	1.11

500M10SF60FA	0.32	160	150	50	300	900	1000	1.08
--------------	------	-----	-----	----	-----	-----	------	------

Table 4: Mix proportions of SCC for 1m3 of concrete


Sample preparation was carried out in accordance with the EFNARC specifications [3]. The fresh properties for certain workability parameters including slump flow, T₅₀₀, L-Box and J-ring were determined according to EFNARC [3] guidelines. Mechanical properties, i.e., axial compression test, ultrasonic pulse velocity and splitting tensile strength test were determined according to the American Standards ASTM C39 [29], ASTM C597 [30] and ASTM C496 [31] respectively. Water absorption and chloride ion penetration in all specimens were determined according to ASTM C1585 [32] and NT Build 492 [33] respectively.


III. RESULTS AND DISCUSSION

A. Fresh Properties


Figure 3 indicates the results of workability parameters i.e., slump flow with and without J-Ring, T₅₀₀ and Visual stability index (VSI). All mixes were classified as SF2/VS2 type SCC as per EFNARC guidelines [3]. It was noticeable that slump flow continues to increase with the increase in amount of FA. The increase in flow is most probably because of ball bearing effect due to spherical nature of FA [3]. Similar results are reported by different researchers [34], [35], [36], [37] & [38]. With the addition of SF, the slump flow decreases with increasing levels of replacement. The decrease in slump is attributed to larger specific surface area of SF, the same is reported previously by several researchers [35], [39] & [40].

The passing ability (PA) of SCC is assessed using L-Box with three bars. All samples showed PA>0.8. PA significantly reduces with increasing FA, this is attributed to the cohesiveness of mixtures [3]&[41].

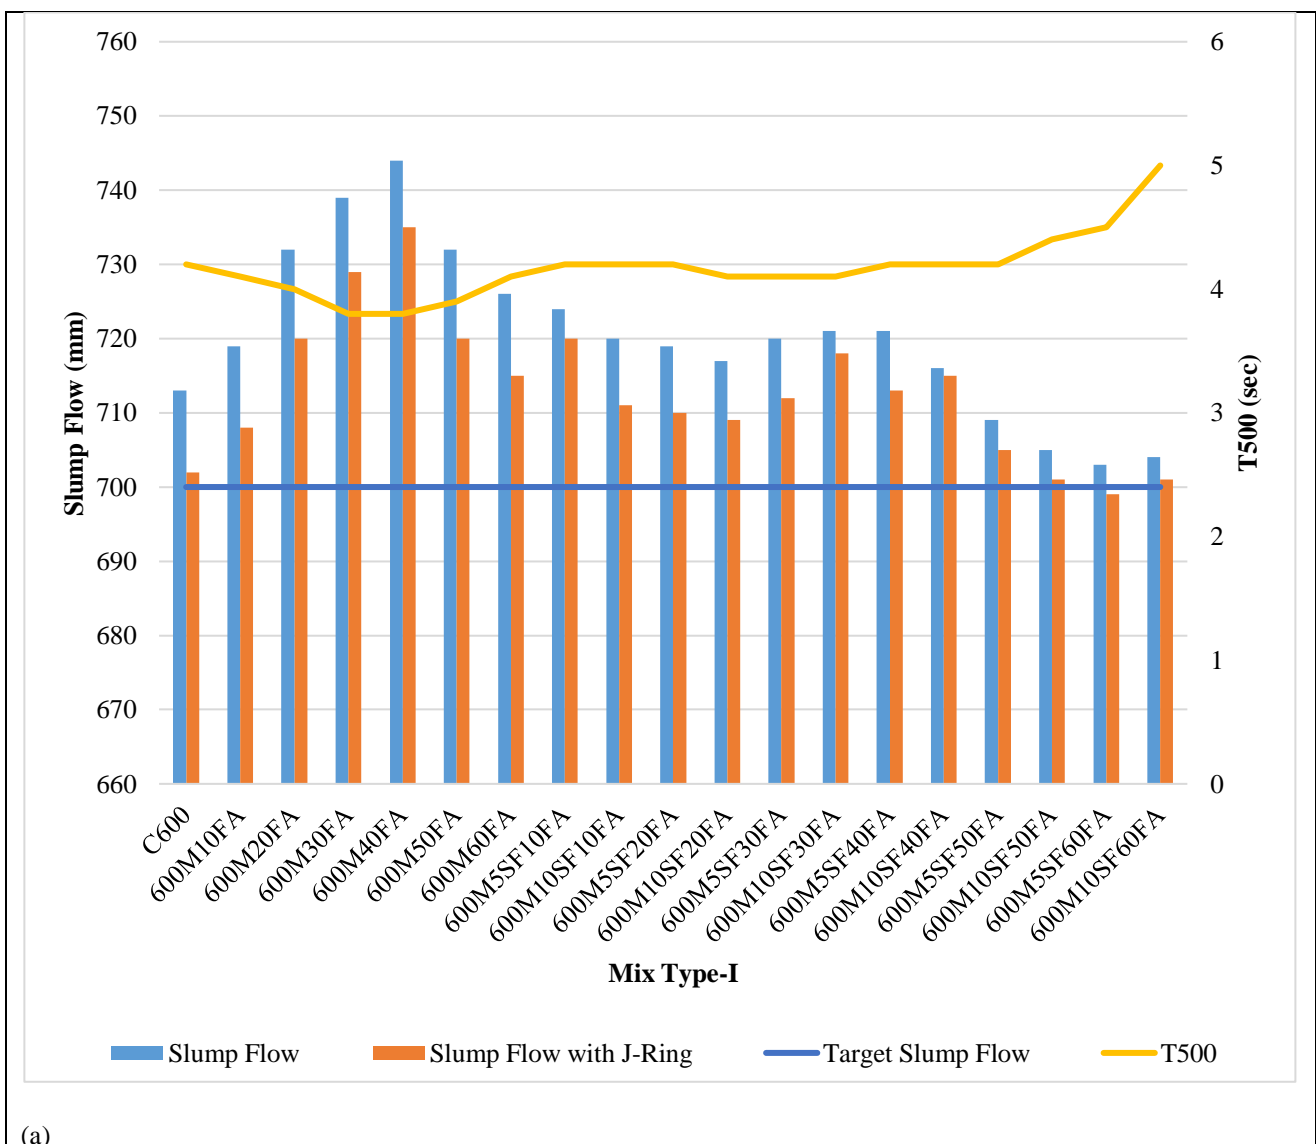

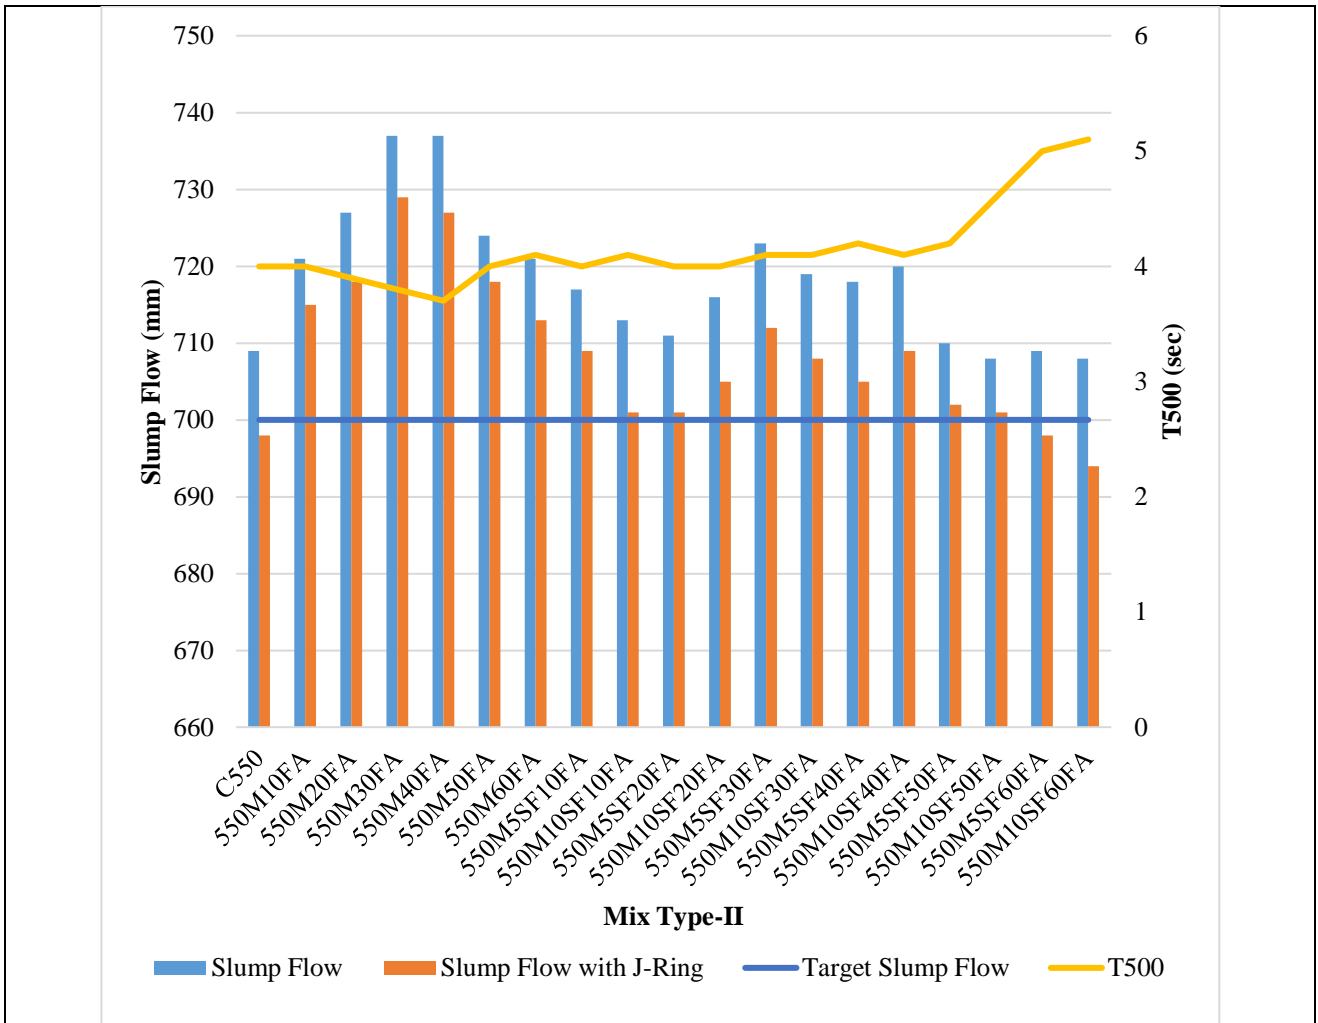

(b)

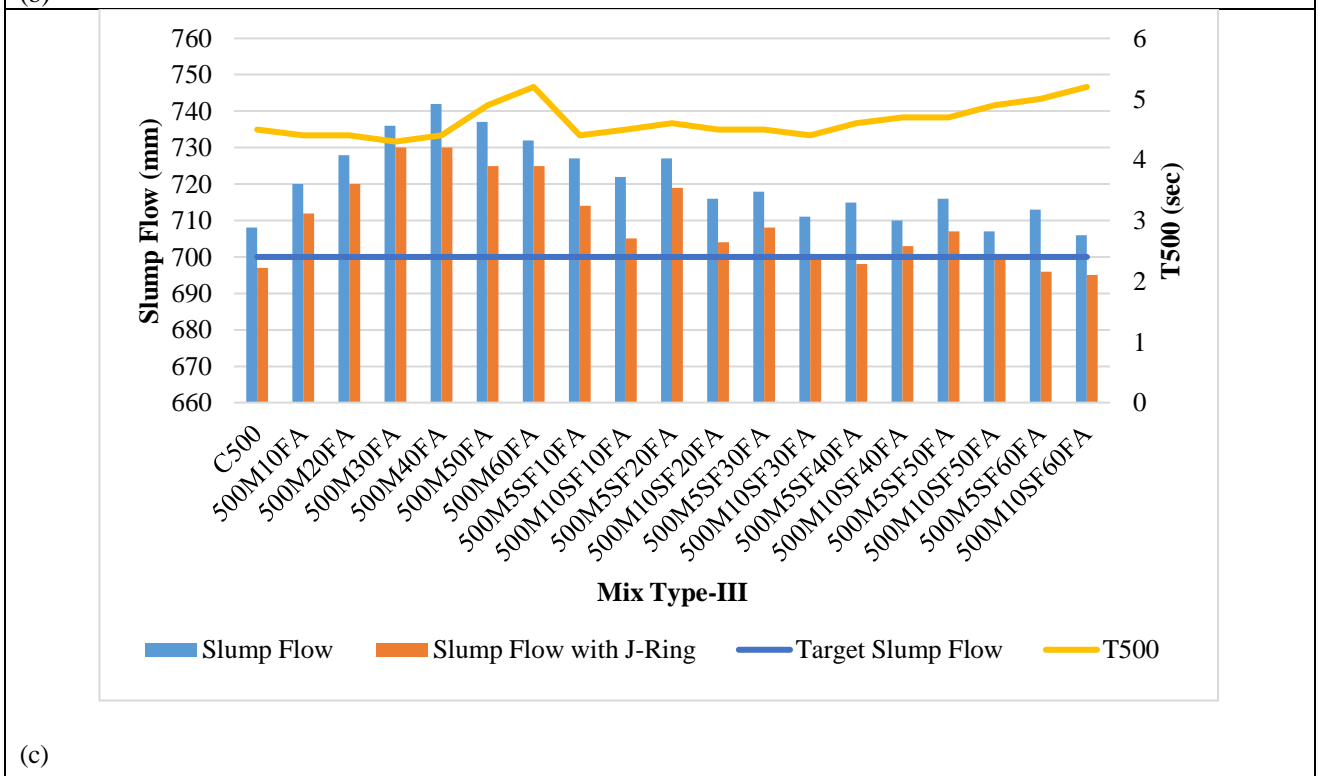

(c)



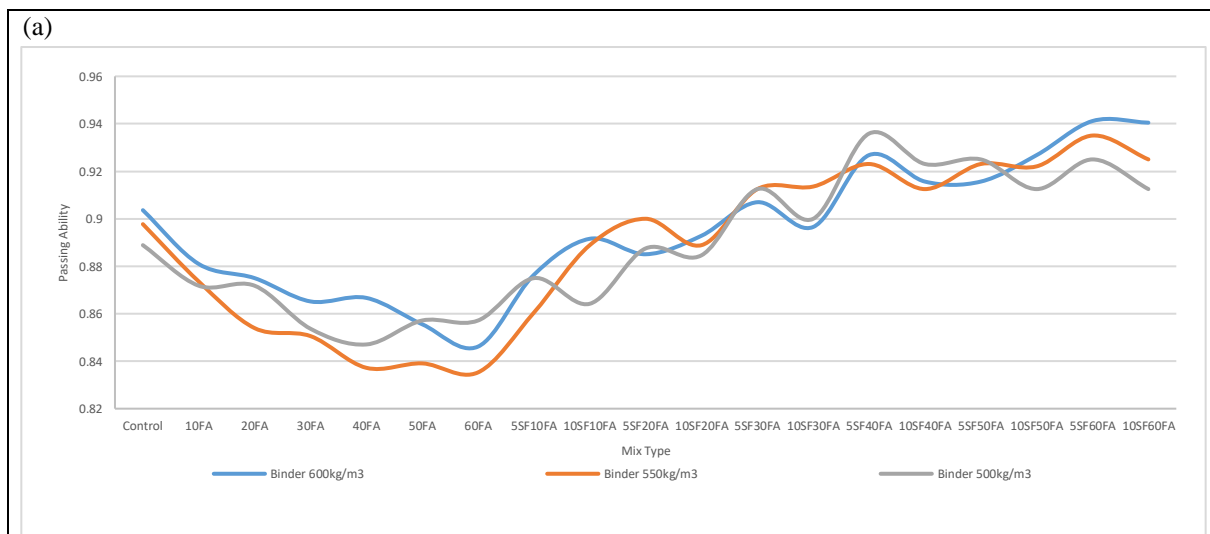



Fig. 4: a) L-Box Ratio, b) L-Box experiment

B. Compressive Strength

Figure 5 indicates the experimental results of compressive strength at 7, 14, 28 and 91 days period of maturity. It has been observed that the initial rate of strength gain for mixes containing FA was low that increases with age and gains maximum strength at 91 days in this study. The possible reason of delay in strength is the slow pozzolanic reactions in concrete due to low calcium content in Class F FA that might resulted in the development of calcium silicate hydrate (C-S-H) gel which causes densification of SCC thus, results in increasing compressive strength with the age, as reported earlier by a few researchers [43],[44]. This effect was more significant with higher replacement levels [42]. In all design types, the optimum value of FA was observed to be at 40% replacement of OPC that gives the maximum 28 days compressive strength. The strength development was 87%, 84%, 82%, 76%, 72% and 65% for 10%, 20%, 30%, 40%, 50% and 60% replacement of OPC with FA, respectively for

Mix Type-I. Strength development for Mix Type-II and III was 95%, 93%, 91%, 87%, 81%, 76% and 97%, 94%, 93%, 89%, 85%, 80% for same replacement levels. Strength development was rapid in mixes containing lesser amounts of FA. It was observed that there was an enhancement in strength by adding binary admixtures (SF+FA). Strength of control mixes decreased when cured in simulated sea water. Strength of mixes containing FA, when cured in sea water, showed decrease in strength at early age as compared to the strength of similar mixes cured in normal water. Similar findings are discussed in previous research [51]. The strength of mixes containing binary admixtures (SF+FA) showed similar strength at early age in both types of curing. However, at later ages, binary admixtures (SF+FA) showed improved strength when cured in sea water as compared to normal water cured specimens. The improvement in strength at later ages, is due to pozzolanic reactivity of FA that made the concrete resilient to sea water.

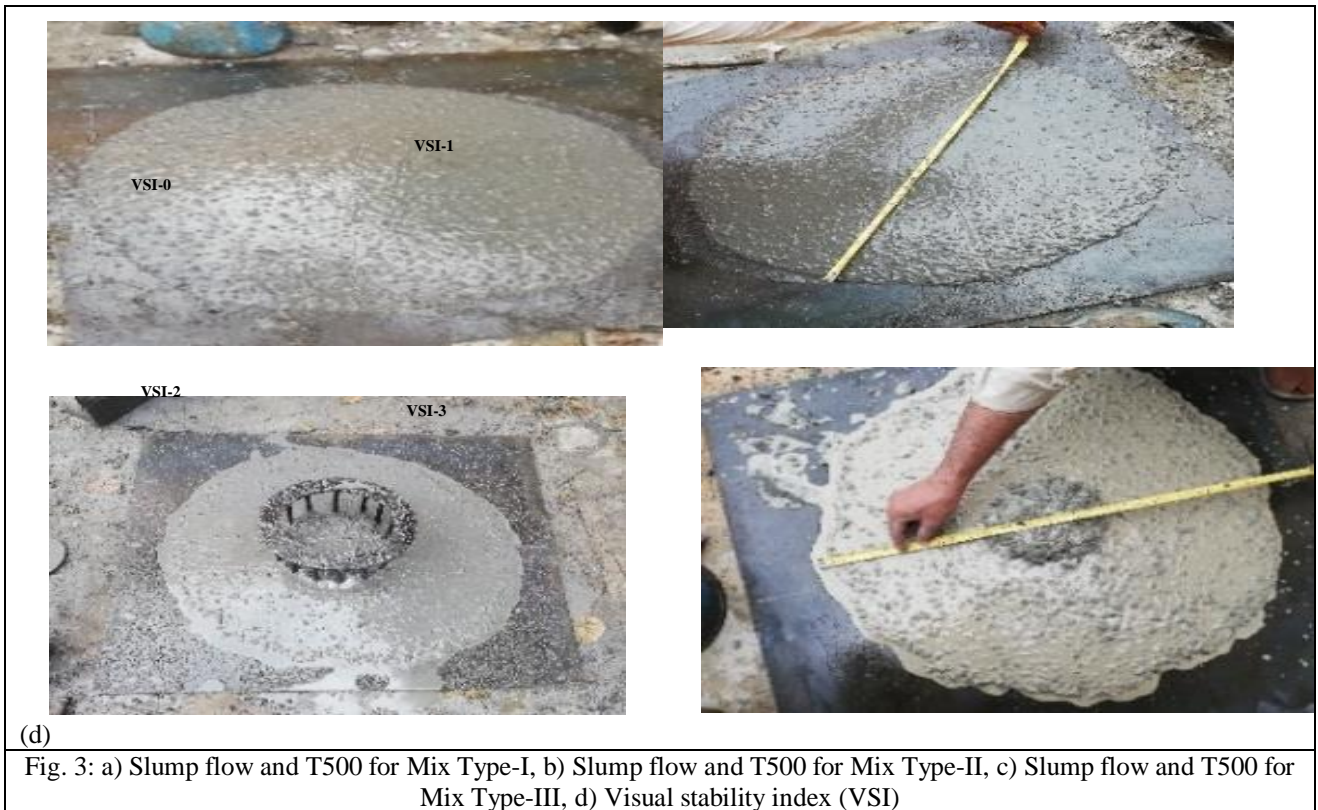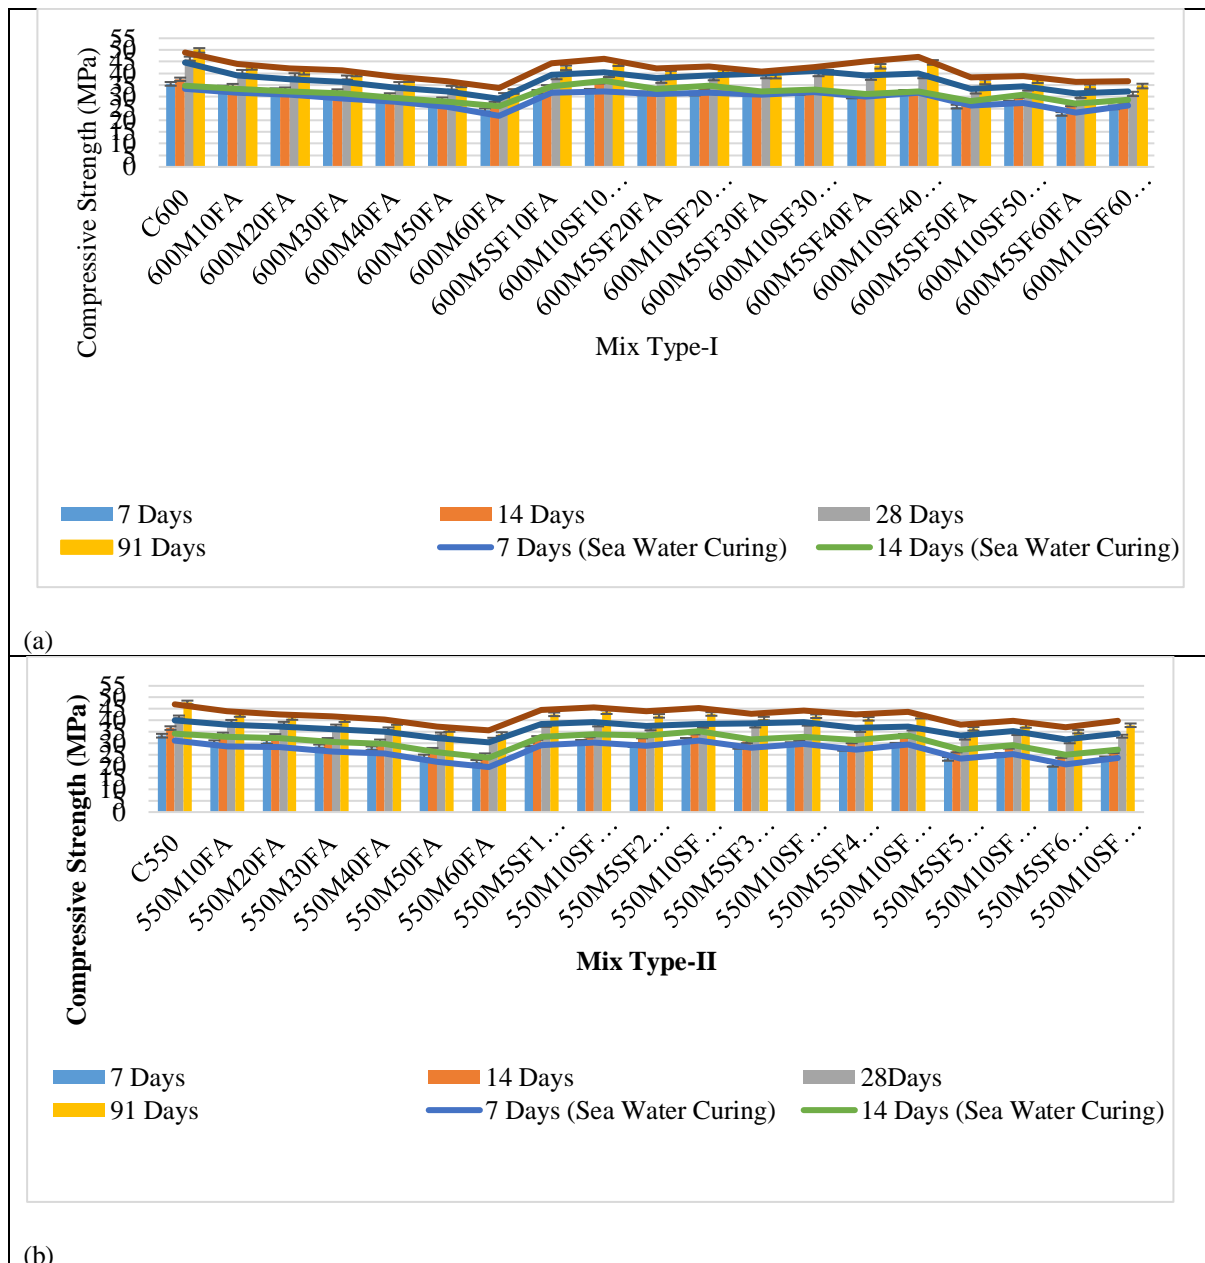

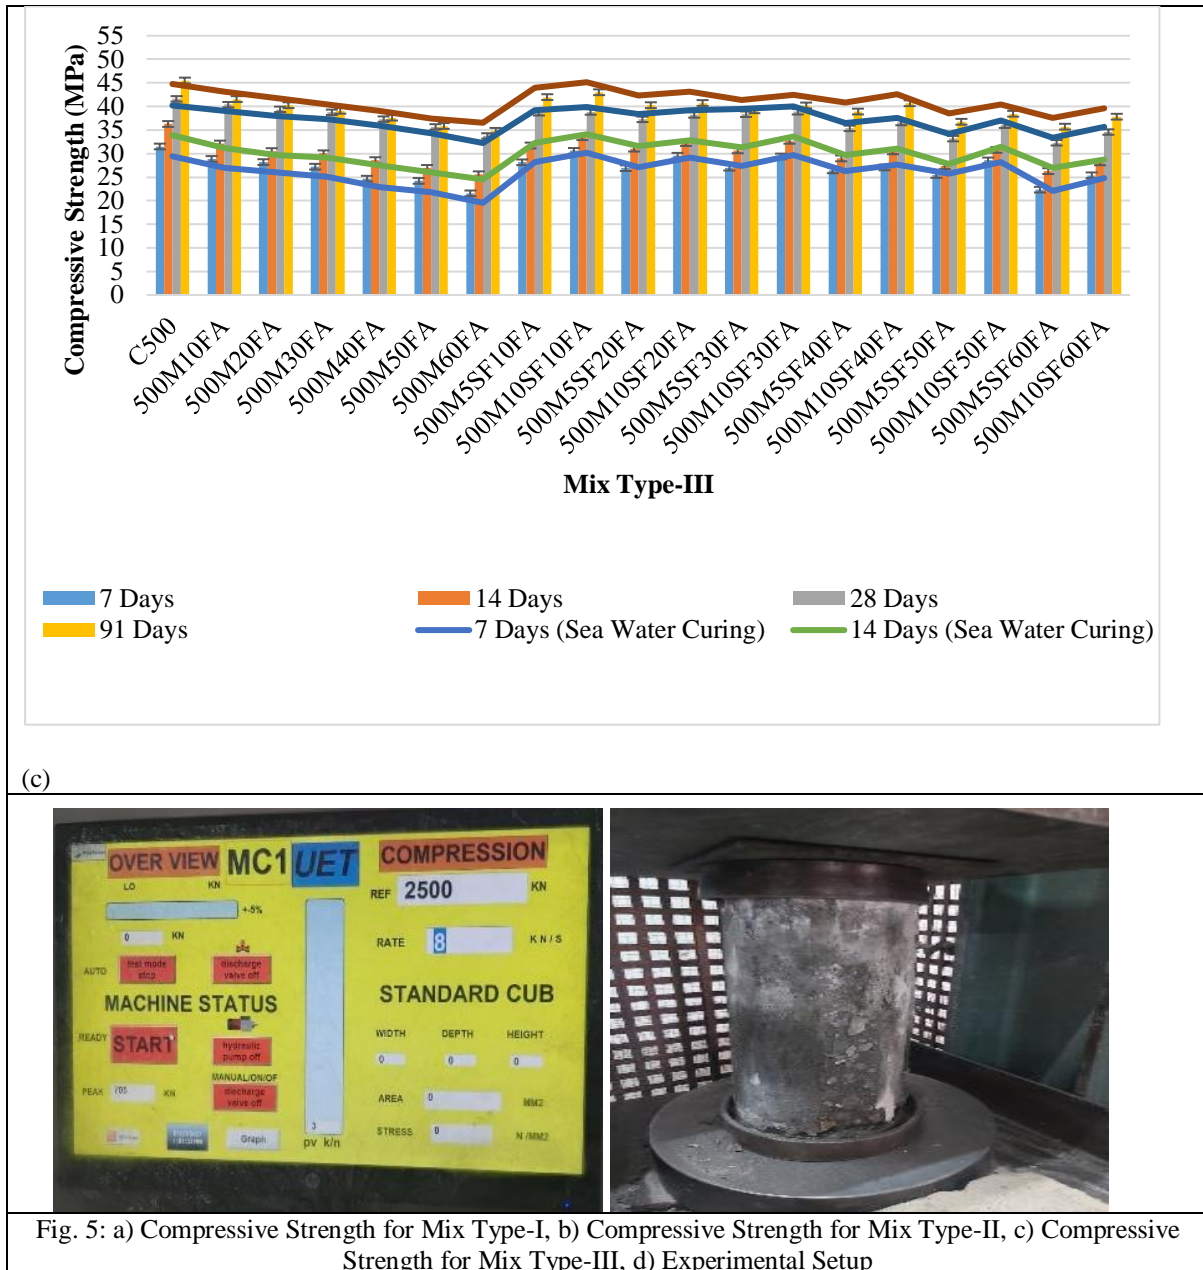

(c)

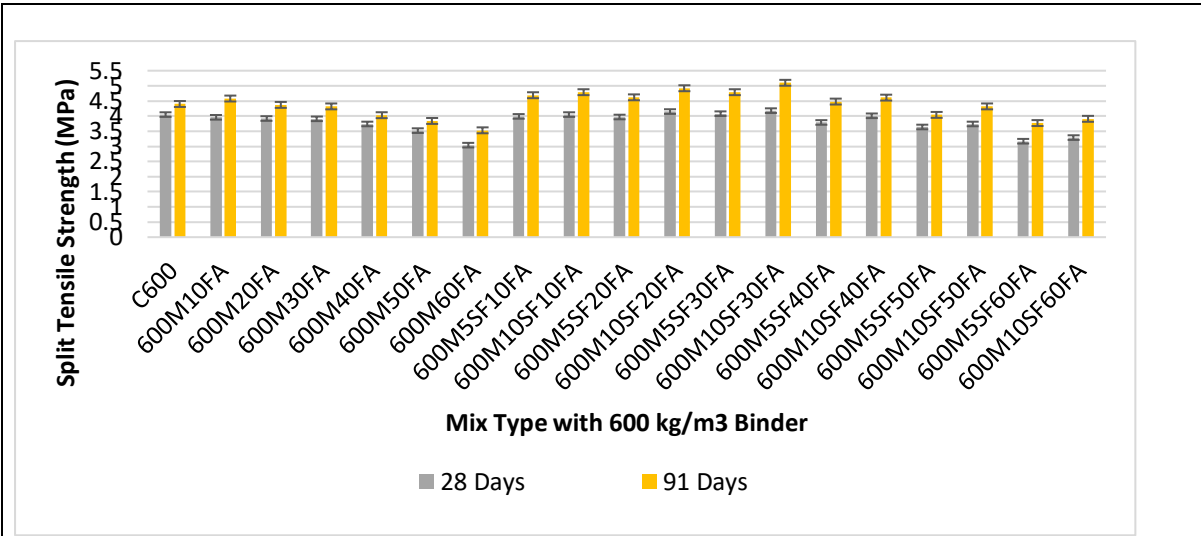


Fig. 5: a) Compressive Strength for Mix Type-I, b) Compressive Strength for Mix Type-II, c) Compressive Strength for Mix Type-III, d) Experimental Setup


C. Splitting Tensile Strength

The split tensile test method does not give true tensile strength but the failure pattern of specimens under splitting action of loads gives a fair idea about the tensile strength of the material [45]. Split tensile strength at 28 and 91 days are shown in Figure6. It was observed that the replacement of OPC with FA and SF affected the spilt tensile strength at 28 days and 91 days in similar way as it affected the compressive strength. The results are in line with that of compressive strength. 28 days tensile strength continues to


decrease in mixes containing FA only and with the addition of SF 28 days tensile strength becomes comparable with control mix. On contrary, tensile strength increases significantly with age for all mixes and the maximum tensile strength was noticed in mixes containing 30%FA+10%SF. The increase in split tensile strength was ascribed to the filling effects of fine particles of binary admixtures. Split tensile strength was recorded max 11% and 12 % of compressive strength at 28 days and 91 days respectively for mix containing 30%FA+10%SF.



(a)

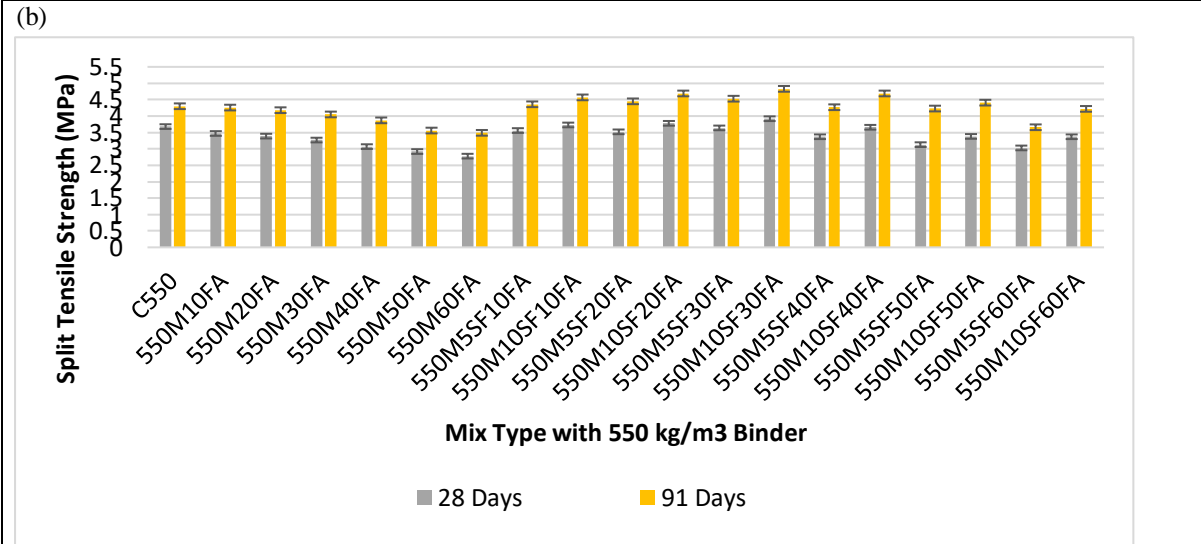

(b)

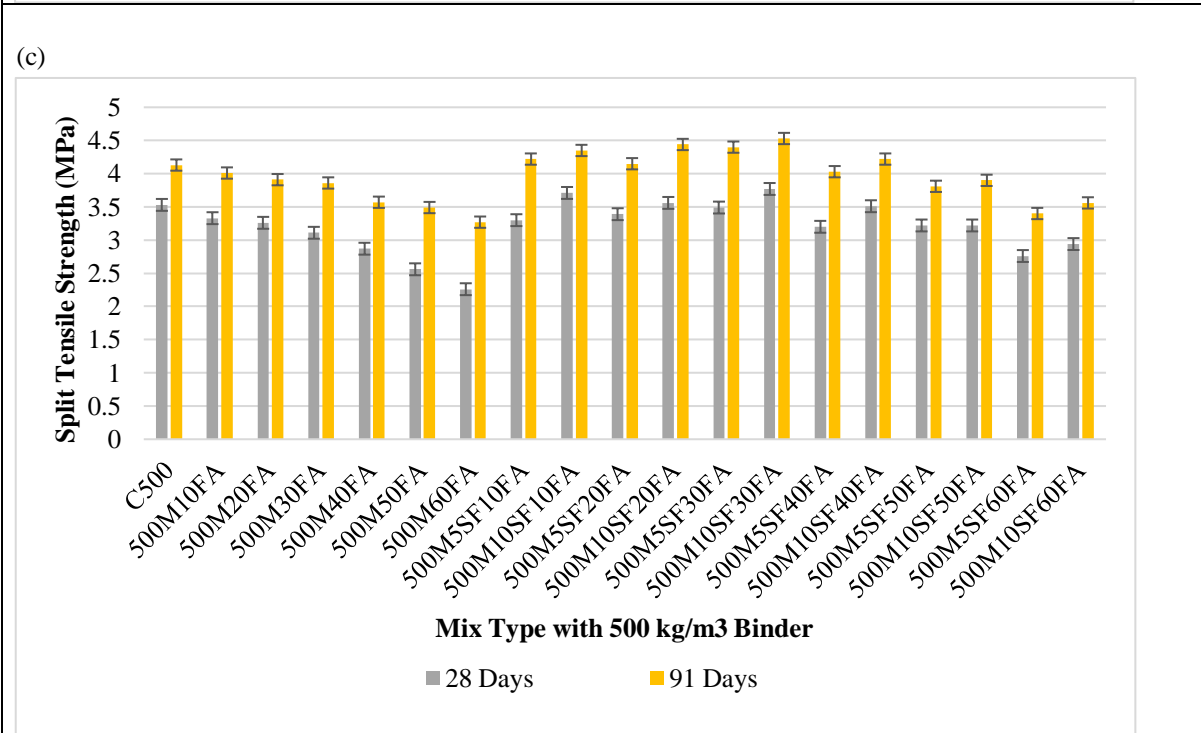

(c)



(d)

Fig. 6: a) Split tensile strength for C600, b) Split tensile strength for C550, c) Split tensile strength for C500, d) Experimental Setup

The variation of ultrasonic pulse velocity in design mixes at 91 days is presented in Figure 7. The UPV has also been compared with compressive strength at the same age. It was revealed that the UPV variation was in close relation that of the compressive strength. The UPV was lower for mixes with higher FA content that was improved by the addition of SF. All the mixes had UPV in the range of 3.59km/s to 4.62km/s. The maximum UPV value of 4.62km/s was obtained in mix containing 10%SF+40%FA. UPV value was observed to decrease with increase in the content of FA in SCC mixes and theminimum value

3.59km/s was recorded in mix with 60% FA. Generally, the UPV is a function of porosity, and it decreases with the increasing of porosity [46]. The presence of pores, non-homogeneity, feeble particle packing, and miscellaneous imperfections are the probable causes for the observed drops in UPV values [47]. The concrete is categorized as “excellent,” “good,” “doubtful,” “poor,” and “very poor” for UPV values of 4500 m/s and above, 3500–4500; 3000–3500; 2000–3000; and 2000 m/s, respectively, in line with previous research [48].

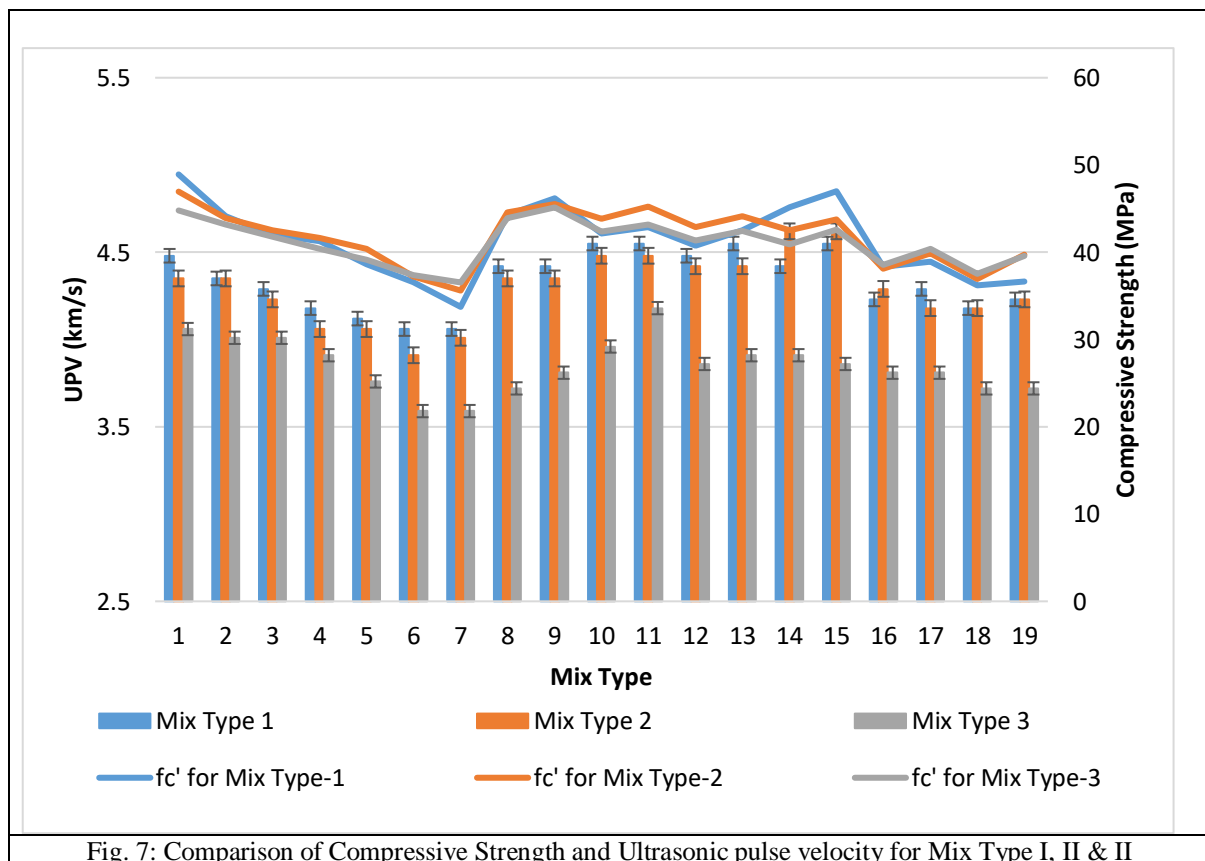


Fig. 7: Comparison of Compressive Strength and Ultrasonic pulse velocity for Mix Type I, II & II

D. Sorptivity

The sorptivity coefficient was measured at 28 and 91 days. The results are shown in Figure 8. It was revealed that the sorptivity was gradually reduced with binary admixtures and with age in all type of mixes. The concrete with 60%FA exhibited about 90% of control mix sorptivity. The concrete with binary admixtures further reduced the sorptivity. On average, concrete with binary admixtures 10%SF+60%FA exhibited about 81% of sorptivity as measured for control mix. The FA particles are finer comparing to OPC as the FA had a higher specific surface

area of $430 \text{ m}^2\text{kg}^{-1}$ whereas OPC had a specific surface area of $360 \text{ m}^2\text{kg}^{-1}$ [44]. It is an established fact through literature [49][50] that FA as a binder reduce the interconnecting voids and reduce the thickness of transition zone between the binder and aggregates. Therefore, the concrete composed of FA has lower capillary pores. The use of FA and SF blends together in the ternary system seemed to be the most effective in the reduction of sorptivity index [48]. For example, the least sorptivity $0.0028 \text{ mm/sec}^{1/2}$ was recorded for 10%SF+60%FA concrete in all mix types. This is also in line with the results of previous research [48].


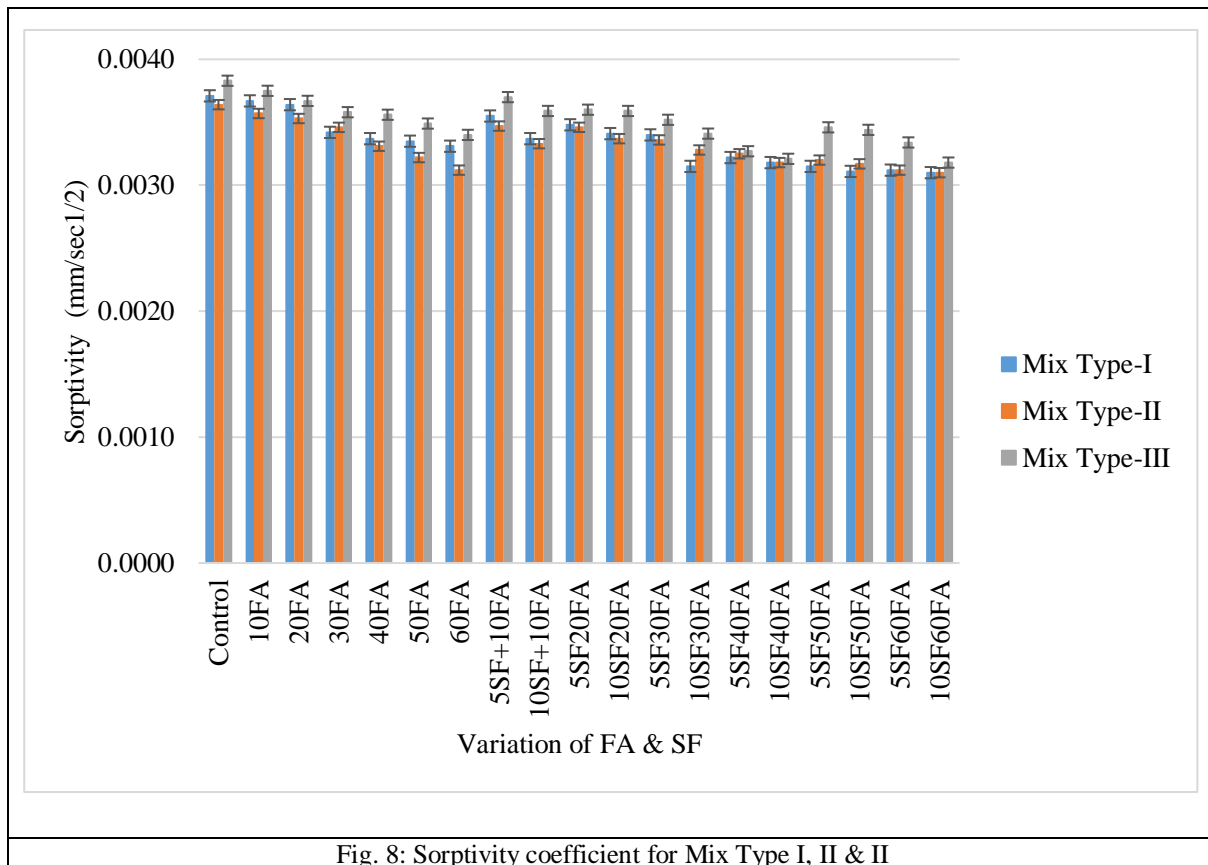


Fig. 8: Sorptivity coefficient for Mix Type I, II & III

E. Non steady state chloride migration coefficient

The durability of concrete in marine environment is mainly dependent on its resistance towards Cl⁻ ion penetration. Non steady state chloride migration coefficient (D_{nssm}) was determined according to NT build 492 [33]. Through published literature, it was summarized that D_{nssm} is inversely related to the quality of concrete [52],[53],[54],[55],[56]. D_{nssm} was measured at 91 days of concrete maturity and reported in Figure 9. It was revealed that with the addition of FA, concrete showed more resistance towards chloride ion penetration. And concrete with binary admixtures (SF+FA) showed even better resistance towards chlorides till 10%SF+30%FA that gives the maximum value of D_{nssm} $1.746 \times 10^{-12} \text{ m}^2/\text{s}$. After this level of replacement, the resistance of concrete towards

chlorides becomes almost steady. According to Chinese standard JGJ/T 193–2009 [55], the chloride penetration resistance is evaluated as five levels (poor, relatively poor, relatively good, good and very good) based on the value of D_{nssm} , and the chloride penetration resistance being very good for D_{nssm} less than $1.5 \times 10^{-12} \text{ m}^2/\text{s}$ [52][54]. Whereas [53] concluded, using the coulomb and surface resistivity limits, that D_{nssm} value between $12 \times 10^{-12} \text{ m}^2/\text{s}$ and $17 \times 10^{-12} \text{ m}^2/\text{s}$ represent the cut off between the moderate to high chloride penetration resistance, and $20 \times 10^{-12} \text{ m}^2/\text{s}$ to $25 \times 10^{-12} \text{ m}^2/\text{s}$ may represent the limit between the low to moderate chloride penetration resistance of concrete. All the mixes, in this study, showed good chloride penetration resistance as the maximum recorded value of D_{nssm} was $6.323 \times 10^{-12} \text{ m}^2/\text{s}$.

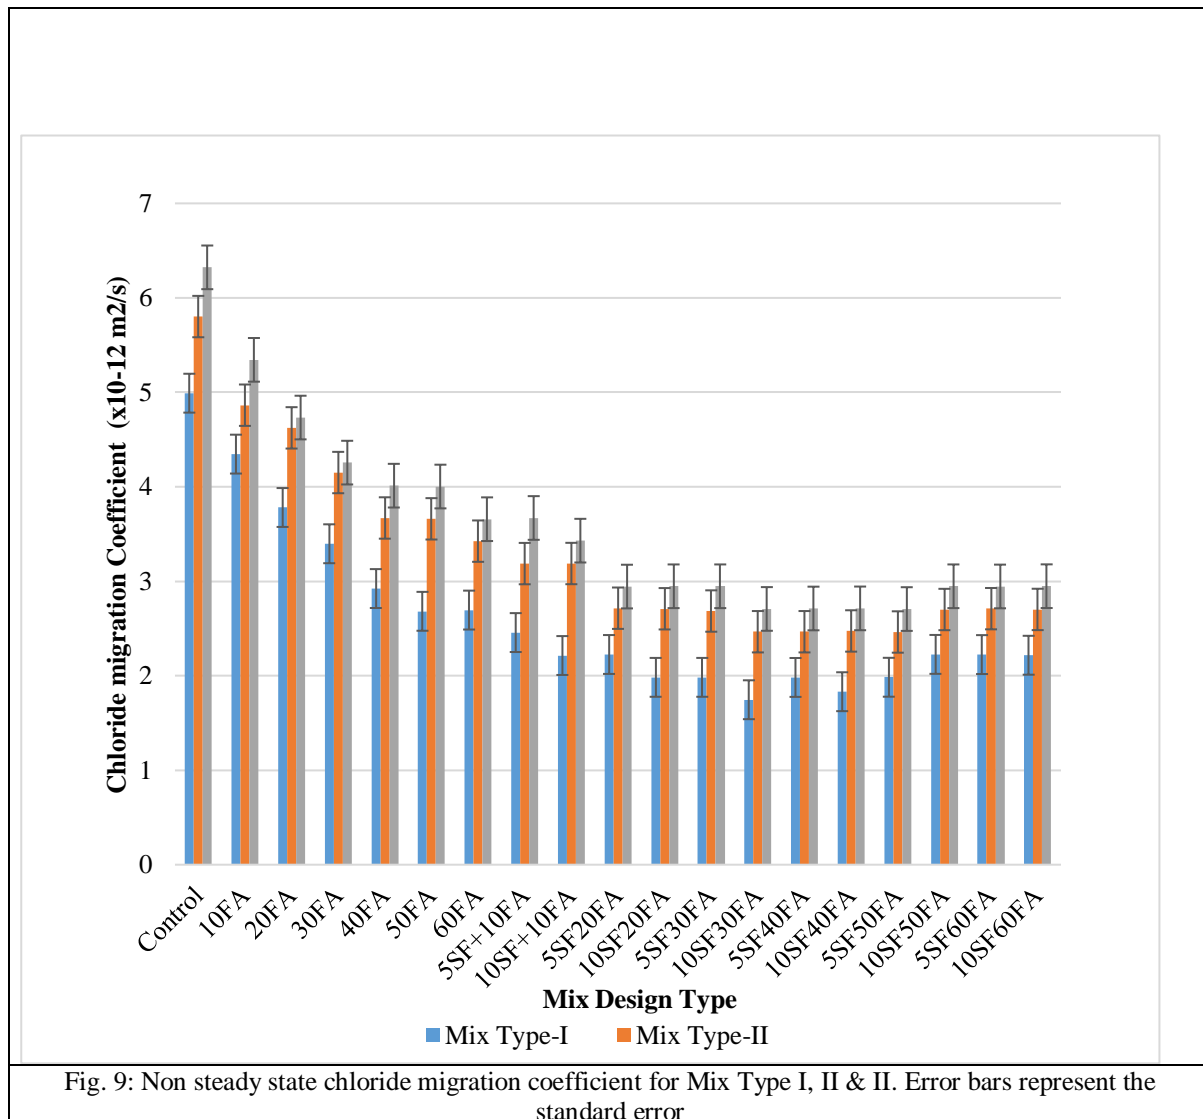

IV. CONCLUSIONS

Class F FA and SF was used as a partial replacement of OPC in developing SCC, in line with EFNARC [3] guidelines, with improved characteristics for marine environment. Compressive strength was evaluated for normal water curing and simulated sea water curing in controlled environment. The experimental work evaluated the effectiveness of partial replacement of OPC on the mechanical and durability characteristics of SCC. Following conclusions are drawn:

- SCC can be prepared in binary and ternary mixes using FA up to 40% and SF up to 10% replacement level of OPC. Further increase in FA affected the flowability and early age compressive strength of SCC. Increase in SF drastically affected the flowability of concrete.
- With the addition of FA, SCC showed a decrease in compressive strength at early age. However, compressive strength was improved at later ages in normal water as well as in sea water. The maximum strength was achieved in SCC with binary admixture 10%SF+40%FA.
- The tensile strength increases significantly with age for all mixes and the maximum tensile strength was noticed in SCC containing 30%FA+10%SF. Split tensile strength

was recorded max 11% and 12 % of compressive strength at 28 days and 91 days respectively.

- The UPV was lower for mixes with higher percentage FA that was improved with the addition of SF. All the mixes had UPV in the range of 3.59 km/s to 4.62 km/s. The maximum UPV value of 4.62 km/s was obtained in SCC containing 10%SF+40%FA.
- It was revealed that the sorptivity was gradually reduced with binary admixtures and with age in all type of mixes. The concrete with 60%FA exhibited about 90% of control mix sorptivity. The concrete with binary admixtures further reduced the sorptivity. On average, concrete with binary admixtures 10%SF+60%FA exhibited about 81% of control mix sorptivity.
- With the addition of FA, concrete showed more resistance towards chloride ion penetration. And concrete with binary admixtures 10%SF+30%FA showed maximum resistance towards chlorides.
- **Data Availability:** The data used to support the findings of this study are available from the corresponding author upon request.
- **Conflicts of Interest:** The authors declare that they have no conflicts of interest.

ACKNOWLEDGMENTS

The authors gratefully acknowledge the Chief executive officer, S K Hydro (Pvt)ltd, for the supply of materials and technical support.

REFERENCES

- [1.] Okamura H, Self-compacting high-performance concrete,"*Concr Int Design Constr* 1997;19(7):50–4.
- [2.] Ozawa K. Development of high performance concrete based on the durability design of concrete structures. *EASEC-2* 1989;1:445–50.
- [3.] EFNARC, "The European Guidelines for Self-Compacting Concrete: Specification, Production and Use," *Eur. Guidel. Self Compact. Concr.* 68 (2005)
- [4.] A. Boukhelkhal, L. Azzouz, S. Kenaiet al., "Combined effects of mineral additions and curing conditions on strength and durability of self-compacting mortars exposed to aggressive solutions in the natural hot-dry climate in North African desert region," *Construction and Building Materials* 197 (2019) 307–318.
- [5.] Mostafa Jalal, Alireza Pouladkhan, Omid FasihiHarandiet al. "Comparative study on effects of Class F fly ash, nano silica and silica fume on properties of high performance self compacting concrete," *Construction and Building Materials* 94 (2015) 90–104
- [6.] S. Dadsetan, J. Bai, "Mechanical and microstructural properties of self-compacting concrete blended with metakaolin, ground granulated blast-furnace slag and fly ash," *Construction and Building Materials* 146 (2017) 658–667.
- [7.] P. Dinakar, M. Kartik Reddy, M. Sharma, "Behaviour of self compacting concrete using Portland pozzolana cement with different levels of fly ash," *Materials & Design* 46 (2013) 609–616.
- [8.] H. Zhao, W. Sun, X. Wu, B.o. Gao, "The properties of the self-compacting concrete with fly ash and ground granulated blast furnace slag mineral admixtures," *Journal of Cleaner Production* 95 (2015) 66–74.
- [9.] R. Kurda, J. de Brito, J.D. Silvestre, "Water absorption and electrical resistivity of concrete with recycled concrete aggregates and fly ash," *Cement and Concrete Composites* 95 (2019) 169–182.
- [10.] B.H. Nagaratnam, M.A. Mannan, M.E. Rahmanet al, "Strength and microstructural characteristics of palm oil fuel ash and fly ash as binary and ternary blends in Self-Compacting concrete," *Construction and Building Materials* 202 (2019) 103–120.
- [11.] N. Pathak, R. Siddique, "Effects of elevated temperatures on properties of self-compacting-concrete containing fly ash and spent foundry sand," *Construction and Building Materials* 34 (2012) 512–521.
- [12.] B. Rai, S. Kumar, K. Satish, "Effect of quarry waste on self-compacting concrete containing binary cementitious blends of fly ash and cement," *Advances in Materials Science and Engineering* 2016 (2016) 1–11.
- [13.] A. Nazanin, M. Sajjad, S.J Ali Akbar, "Durability of self-consolidating concrete and mortar mixtures containing ternary and quaternary cement blends exposed to simulated marine environment," *Construction and Building Materials* 259 (2020) 119767
- [14.] D.V. Val, M.G. Stewart, "Life-cycle cost analysis of reinforced concrete structures in marine environments," *Struct. Saf.* 25 (4) (2003) 343–362.
- [15.] H. Zhao, X. Yu, C. Xiaodong, et al., "Mechanical properties and volumetric deformation of early-age concrete containing CaO-MgO blended expansive agent and temperature rising inhibitor," *Construction and Building Materials* 299 (2021) 123977
- [16.] A. Costa, J. Appleton, "Case studies of concrete deterioration in a marine environment in Portugal," *Cement Concr. Compos.* 24 (1) (2002) 169–179.
- [17.] S.D. Cramer, B.S. Covino, S.J. Bullard, et al., "Corrosion prevention and remediation strategies for reinforced concrete coastal bridges," *Cement Concr. Compos.* 24 (1) (2002) 101–117.
- [18.] Y. Yong, Z. Deju, G. Shuaicheng, Z. Zuhua, et al., "A review on the deterioration and approaches to enhance the durability of concrete in the marine environment," *Cement and Concrete Composites* 113 (2020) 103695
- [19.] I. Navarrete, F. Vargas, P. Martinez, et al., "Flue gas desulfurization (FGD) fly ash as a sustainable, safe alternative for cement-based materials," *J. Clean. Prod.*, 283 (2021), Article 124646
- [20.] S. Pranav, S. Aggarwal, E. Yang, et al., "Alternative materials for wearing course of concrete pavements: a critical review," *Construct. Build. Mater.*, 236 (2020), Article 117609
- [21.] J. Seelapureddy, J. Bommisetty, M.V.S. Rao, "Effect of metakaolin and micro silica on strength characteristics of standard grades of self-compacting concrete," *Mater. Today Proc.*, 45 (2) (2020), pp. 884-890
- [22.] T. Hemalatha, A. Ramaswamy, "A review on fly ash characteristics towards promoting high volume utilization in developing sustainable concrete," *J. Clean. Prod.*, 147 (2017), pp. 546-559
- [23.] V. Vishwakarma, D. Ramachandran, "Green Concrete mix using solid waste and nanoparticles as alternatives-A review," *Construct. Build. Mater.*, 162 (2018), pp. 96-103
- [24.] M. Gruszczyński, M. Lenart, "Durability of mortars modified with the addition of amorphous aluminum silicate and silica fume," *Theor. Appl. Fract. Mech.*, 107 (2020), Article 102526
- [25.] B.V. Kavyateja, J.G. Jawahar, C. Sashidhar Effectiveness of alccofine and fly ash on mechanical properties of ternary blended self

- compacting concrete Mater. Today Proc., 33 (1) (2020), pp. 73-79
- [26.] G. Tyagi, A. Singhal, S. Routroy, et al., "Radiation Shielding Concrete with alternate constituents: an approach to address multiple hazards," J. Hazard Mater., 404 (B) (2021), Article 124201
- [27.] Nanqiao You, Jinjie Shi, Yamei Zhang, "Corrosion behaviour of low-carbon steel reinforcement in alkali-activated slag-steel slag and Portland cement-based mortars under simulated marine environment," Corrosion Science 175 (2020) 108874
- [28.] ASTM D1141 – 98, "Standard Practice for the Preparation of Substitute Ocean Water," Am. Soc. Test. Mater., West Conshohocken, USA, 2020
- [29.] ASTM C39/C39M-17B, "Standard test method for compressive strength of cylindrical concrete specimens," Am. Soc. Test. Mater., West Conshohocken, USA, 2018
- [30.] ASTM C597/C597M-16, "Standard Test Method for Pulse Velocity Through Concrete," Am. Soc. Test. Mater., West Conshohocken, USA, 2020
- [31.] ASTM C496/C496M-17, "Standard Test Method for Splitting Tensile Strength of Cylindrical Concrete Specimens," Am. Soc. Test. Mater., West Conshohocken, USA, 2021
- [32.] ASTM C1585-20, "Standard Test Method for Measurement of Rate of Absorption of Water by Hydraulic Cement Concretes," Am. Soc. Test. Mater., West Conshohocken, USA, 2021
- [33.] NT Build 492: "Concrete, mortar and cement-based repair materials: chloride migration coefficient from non-steady-state migration experiments," 1999.
- [34.] C. Jithendra1, S. Elavenil, "Effects of Silica Fume on Workability and Compressive Strength Properties of Aluminosilicate Based Flowable Geopolymer Mortar under Ambient Curing," Silicon. 12, (2020) 1965–1974
- [35.] Antoni, L. Chandra, D. Hardjito," The impact of using fly ash, silica fume and calcium carbonate on the workability and compressive strength of mortar," Procedia Engineering 125 (2015) 773–779
- [36.] A. Jain, R. Gupta, S. Chaudhary,"Sustainable development of self-compacting concrete by using granite waste and fly ash," Construct. Build. Mater., 262 (2020), p. 120516
- [37.] P. Promsawat, B. Chatveera, G. Sua-iam, et al., "Properties of self-compacting concrete prepared with ternary Portland cement-high volume fly ash-calcium carbonate blends," Case Stud. Constr. Mater., 13 (2020), Article e00426
- [38.] G. Sua-iam, B. Chatveera,"A study on workability and mechanical properties of eco-sustainable self-compacting concrete incorporating PCB waste and fly ash," Journal of Cleaner Production 329 (2021) 129523
- [39.] S. Anjali, P.K. Mehta, K. Rakesh,"Performance of binary admixtures (Fly Ash and Silica Fume) on Self Compacting concrete," Materials Today: Proceedings 58 (2022) 970–977
- [40.] C. Jithendra1, S. Elavenil,"Effects of Silica Fume on Workability and Compressive Strength Properties of Aluminosilicate Based Flowable Geopolymer Mortar under Ambient Curing," Silicon. 12, (2020) 1965–1974
- [41.] B. Naraindas, A. Paul, T. Tafsirojjaman, et al., "Synergic effect of metakaolin and groundnut shell ash on the behavior of fly ash-based self-compacting geopolymer concrete," Construction and Building Materials 311 (2021) 125327
- [42.] H.T. Timothy Zhi, E.R. Muhammad, H.L. Hieng, "Sustainable lightweight self-compacting concrete using oil palm shell and fly ash," Construction and Building Materials 264 (2020) 120590
- [43.] J. Abhishek Jain, C. Sandeep, G. Rajesh, "Mechanical and microstructural characterization of fly ash blended self-compacting concrete containing granite waste," Construction and Building Materials 314 (2022) 125480
- [44.] K.S. Ashish, "Effect of class F fly ash on the durability properties of concrete," Sustainable Environment Research 28 (2018) 25e31
- [45.] M. Bilal, E. Ayub, B. Salim, A. Babar,"Mechanical and durability performance of recycled aggregate concrete incorporating low calcium bentonite," Construction and Building Materials 237 (2020) 117760
- [46.] S. Hossein, A. Farhad, "Effect of specimen shape, silica fume, and curing age on durability properties of self-compacting concrete incorporating coarse recycled concrete aggregates," Construction and Building Materials 228 (2019) 117054
- [47.] S. Navdeep, K. Pawan Kumar, G. Paresh, "Reviewing the behavior of high volume fly ash based self-compacting concrete" Journal of Building Engineering 26 (2019) 100882
- [48.] G. Erhan, G. Mehmet, B. Emad, et al., "Strength and permeability properties of self-compacting concrete with cold bonded fly ash lightweight aggregate" Construction and Building Materials 74 (2015) 17-24
- [49.] Kuroda M, Watanabe T, Terashi N, "Increase of bond strength at interfacial transition zone by the use of fly ash." Cement Concr Res 2000;30:253e8.
- [50.] Saha AK, Sarker PK, "Compressive strength of mortar containing ferronickel slag as replacement of natural sand," Procedia Eng 2017;171:689e94.
- [51.] D. Ramachandran, R. P. George, V. Vinita, et al., "Strength and Durability Studies of Fly Ash Concrete in Sea Water Environments Compared with Normal and Superplasticizer Concrete," KSCE Journal of Civil Engineering (2017) 21(4):1282-1290
- [52.] M Xinqi, Q. Wenjun, Z. Peng, et al., "Influence of recycled powder on chloride penetration resistance of green reactive powder concrete," Construction and Building Materials 251 (2020) 119049
- [53.] N. Clay, F. John, B. Paolo, et al., "Chloride migration characteristics and reliability of reinforced concrete highway structures in

- Pennsylvania,” *Construction and Building Materials* 231 (2020) 117045
- [54.] Y. Jin, Z. Linghao, H. Xingyang, et al., “Improving durability of heat-cured high volume fly ash cement mortar by wet-grinding activation,” *Construction and Building Materials* 289 (2021) 123157
- [55.] “Ministry of Housing and Urban-Rural Construction of the People’s Republic of China. Standard for Inspection and Assessment of Concrete Durability,” JGJ/T 193-2009; China Building Industry Press: Beijing, China, 2009.
- [56.] L. Shiming, Z. Miaomiao, D. Xinxin, et al., “High-Durability Concrete with Supplementary Cementitious Admixtures Used in Corrosive Environments,” *Crystals* 2021, 11, 196.